

Multi-Spin-Axis Structure for CoO[†]

B. VAN LAAR

Reactor Centrum Nederland, Petten, The Netherlands

(Received 20 November 1964)

New intensity data from CoO in the antiferromagnetic state have been obtained with a high-resolution neutron diffractometer. These improved data can be interpreted by a collinear spin structure with an angle of 27.4° between the spin axis and the *c* axis, as compared with the older data of Roth which gave this angle as 11.5°. Alternatively a multi-spin-axis model is proposed which explains the intensity data equally well. This model is related to the collinear model B proposed by Li and has a tetragonal spin superstructure in conformity with the tetragonal crystallographic deformation below the Néel temperature.

INTRODUCTION

THE arrangement of atomic spins in the antiferromagnetic state of MnO, FeO, CoO, and NiO was described by Shull, Strauser, and Wollan¹ in 1951 and by Roth² in 1958. In the antiferromagnetic state these oxides are approximately cubic (NaCl type). Their neutron diffraction patterns in the antiferromagnetic (af) state can be indexed with a doubled unit cell edge. The reflection conditions *h, k, l*, all even for the nuclear intensities and *h, k, l*, all odd for the magnetic intensities, are those for a fcc magnetic unit cell in which each spin has an antiparallel partner at $+\left(\frac{1}{2}, \frac{1}{2}, \frac{1}{2}\right)$. Since in this arrangement next-nearest neighbors have antiparallel spins, the existence of a superexchange interaction is directly evident.

It has been shown by Li³ that for a single-spin-axis arrangement the four face-centered sublattices can be correlated in two different ways in order to fulfill this condition. These two possibilities are model A and model B, as designated by Li in his paper. The principal difference between the two possibilities is that model A is compatible with a rhombohedral deformation while model B is compatible with a tetragonal deformation.

In the antiferromagnetic state the oxides are not cubic; there is a small crystallographic distortion (Rooksby,⁴ Tombs and Rooksby⁵). MnO and NiO become rhombohedral with $\alpha > 60^\circ$, FeO becomes rhombohedral with $\alpha < 60^\circ$ and CoO becomes tetragonal with $c/a < 1$.

From neutron diffraction data both Shull *et al.* and Roth rejected model B and accepted model A, based on ferromagnetic sheets of moments, parallel to (111) planes with signs alternating in adjacent sheets. Roth, who had the most accurate data, derived for the spin directions: (a) in MnO and NiO the spin axis is in the (111) plane; (b) in FeO the spin axis is along the [111] axis; (c) in CoO the spin axis is parallel to [11 $\bar{7}$], thus making an angle of 11°30' with the *c* axis. Evidently

the arrangement of moments is consistent with the crystallographic distortion, except in the case of CoO.

Nagamiya and Motizuki,⁶ who modified a theory of Kanamori,⁷ tried to explain the tetragonal deformation of CoO by assuming a balancing between cubic anisotropy and trigonal dipolar anisotropy, characterized respectively by the constants *K* and *T*. To explain an angle of 10° between the tetragonal *c* axis and the spin axis a ratio of *T/K* as large as 0.3 had to be assumed, which they did not consider impossible.

The interpretation of Roth's diffraction data was complicated by the lack of reliable values for the Co⁺⁺ form factor on which the calculated angle of deviation is strongly dependent. Due to the limited resolving power of his neutron diffractometer, Roth was able to measure only the intensity of the peaks of the cubic forms {*hkl*} but he recognized that additional information might be obtained from the separate intensities {*hkl*} and {*hkk*}. As the resolving power of the diffractometer at the High Flux Reactor in Petten is high enough to separate these intensities, CoO has been reinvestigated to obtain more reliable information about the spin arrangement.

EXPERIMENTAL

The sample of CoO was prepared from Merck CoO by heating to 950°C in a nitrogen atmosphere. Chemical analysis showed the composition to be CoO_{0.97}. Neutron diffraction data were collected at liquid-nitrogen temperature from a sample contained in a cylindrical aluminium sample holder with a diameter of 20 mm and a wall thickness of 0.05 mm. The neutron wavelength was 1.273 Å. Soller slits of 5½' angular divergence were mounted between the reactor and the copper monochromator. The slits in front of the BF₃ detector had an angular divergence of 5'.

RESULTS AND DISCUSSION

Single-Spin-Axis Structure

Although the separation of the peaks {113} and {311}, and also {331} and {313} is not complete (the

⁶ T. Nagamiya and K. Motizuki, *Rev. Mod. Phys.* **30**, 89 (1958).

⁷ J. Kanamori, *Progr. Theoret. Phys. (Kyoto)* **17**, 1777, 197 (1956).

[†] Work sponsored jointly by Reactor Centrum Nederland, the Netherlands and Institutt for Atomenergi, Norway.

¹ C. G. Shull, W. A. Strauser, and E. O. Wollan, *Phys. Rev.* **83**, 333 (1951).

² W. L. Roth, *Phys. Rev.* **110**, 1333 (1958).

³ Y. Y. Li, *Phys. Rev.* **100**, 627 (1955).

⁴ H. P. Rooksby, *Acta Cryst.* **1**, 226 (1948).

⁵ N. C. Tombs and H. P. Rooksby, *Nature* **165**, 442 (1950).

angular distances are $14'$ and $15'$ in 2θ), it is quite simple, by means of a computer program, to obtain the relative intensities, which are given in Table I. The peaks are shown in Figs. 1 and 2.

TABLE I. Comparison of the observed ratios of the intensities from $\{hkl\}$ and $\{h'k'l'\}$ with those calculated from different models. The second part of the table refers to the collinear model with two different values for the angle of deviation; the third part refers to the multispin models, proposed by Roth.

	$\frac{\Sigma F_m^2\{311\}}{\Sigma F_m^2\{113\}}$	$\frac{\Sigma F_m^2\{331\}}{\Sigma F_m^2\{313\}}$
Observed	>50	0.367 ± 0.008
$A[11.5^\circ]$	32	0.64
$A[27.4^\circ]$	158	0.366
I	0.55	0.86
J	1.99	0.03
K	1.20	0.36
R	1.20	0.36
T	1.20	0.36
U	2.06	0.88
V	2.15	0.82
Multi-spin-axis structure proposed in this paper	158	0.366

From the almost complete absence of the $\{113\}$ peak a rough indication of the direction of the antiferromagnetic axis is obtained if the existence of a single-spin-axis model is assumed. A much more sensitive determination is possible from the ratio of the intensities $\{331\}$ and $\{313\}$. Combining these criteria shows unambiguously that the spin axis is situated in the $(1\bar{1}0)$ plane and that the angle of deviation from the c axis is $(27.4 \pm 0.5)^\circ$.

This model would imply that there is hardly any difference between the CoO and the MnO structures; in MnO the spins are in the (111) planes; in CoO they are tipped out of these planes by an angle of 8° . Two important objections can be made; however, (1) the distortion from cubic symmetry below the Néel tem-

FIG. 1. Neutron diffraction peaks $\{311\}$ and $\{113\}$.


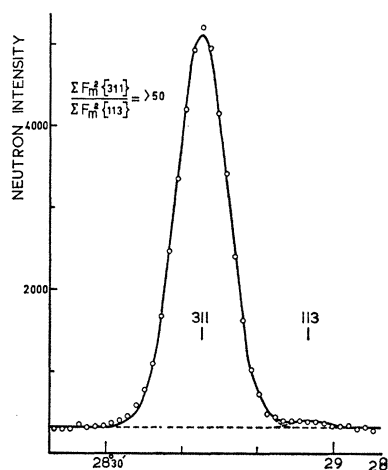


FIG. 2. Neutron diffraction peaks $\{331\}$ and $\{313\}$.

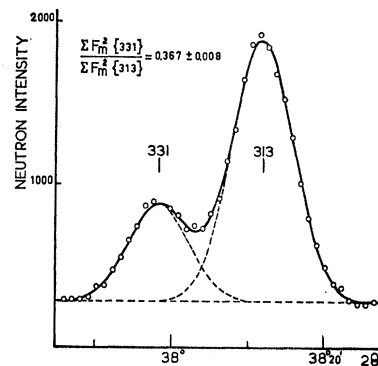

perature is tetragonal for CoO and rhombohedral for MnO, although according to this model their spin structures would be nearly equal; (2) to explain the angle of deviation of 27.4° by means of the theory of Nagamiya and Motizuki a ratio of T/K of 0.55 has to be assumed, which is very improbable.

Rejecting the collinear model for CoO for these reasons, the only other possibility for the CoO structure is a noncollinear model.

Multi-Spin-Axis Structure

In a multi-spin-axis structure the four antiferromagnetic fc sublattices are independent. Therefore the direction of the spins of four atoms has to be determined, the spin of each of these atoms generating eight other spin directions [four parallel spins due to the face-centering and then again four antiparallel spins at $(\frac{1}{2}, \frac{1}{2}, \frac{1}{2})$]. These four independent atoms are taken at $(0, 0, 0)$; $(\frac{1}{4}, 0, \frac{1}{4})$; $(\frac{1}{4}, \frac{3}{4}, \frac{1}{2})$; $(0, \frac{3}{4}, \frac{3}{4})$. The magnetic structure factor is then given by:

$$\mathbf{F}_m = 8\mu_{\text{Co}^{++}} f_{\text{Co}^{++}} \left[\frac{e\gamma}{2mc^2} \right] \times \left\{ \mathbf{q}_1 + \mathbf{q}_2 \exp \left[2\pi i \frac{h+l}{4} \right] + \mathbf{q}_3 \exp \left[2\pi i \frac{h+3k+2l}{4} \right] + \mathbf{q}_4 \exp \left[2\pi i \frac{3k+3l}{4} \right] \right\}.$$

$$\mathbf{q}_i = \boldsymbol{\varepsilon}(\boldsymbol{\varepsilon} \cdot \mathbf{k}_i) - \mathbf{k}_i.$$

In this expression e and m are the electron charge and mass, γ is the magnetic moment of the neutron expressed in nuclear magnetons, $\mu_{\text{Co}^{++}}$ is the magnetic moment of the Co^{++} ion expressed in Bohr magnetons, $f_{\text{Co}^{++}}$ is form factor for the magnetic scattering by the Co^{++} ion, $\boldsymbol{\varepsilon}$ is the scattering vector and \mathbf{k}_i is a unit vector in the direction of the magnetic moment of the Co^{++} ion.

Roth⁸ proposed seven multispin models for CoO (designated I, J, K, R, T, U , and V). From the present data it is found that all of these can be rejected since

⁸ W. L. Roth, Phys. Rev. **111**, 772 (1958).

TABLE II. Multi-spin-axis structure of CoO.

Atom	Direction cosines of spins		
	α	β	γ
1. 0, 0, 0	-0.325	-0.325	+0.888
2. $\frac{1}{2}, 0, \frac{1}{2}$	+0.325	-0.325	-0.888
3. $\frac{1}{2}, \frac{3}{4}, \frac{3}{4}$	+0.325	+0.325	+0.888
4. 0, $\frac{3}{4}, \frac{3}{4}$	-0.325	+0.325	-0.888

they give too low a value for the ratio of the {311} and the {113} intensity (Table I).

A model, fitting the intensities perfectly well, is given in Table II. This model leads to exactly the same powder intensities as the collinear model A with an angle of deviation of 27.4° ($\alpha = -0.325$, $\beta = -0.325$, $\gamma = +0.888$), but while the multispin model gives exactly the same intensity for all members of a form { hkl }, in model A only one quarter of the possible reflections accounts for the full intensity.

A survey of calculated and observed structure factors is given in Table III. In the calculation of $\Sigma(F_m^2/64p^2)$ from the observed intensities, the Co^{++} form factor given by Scatturin⁹ was used. The magnetic moment of the Co^{++} ion at 77°K was deduced to be $3.52 \mu_B$, which is about 10% less than the value reported by Roth, who

TABLE III. Comparison of calculated and observed intensities. $\text{CoO}_{0.966}$; $b_{\text{Co}} = 0.245 \times 10^{-12}$ cm; $b_{\text{O}} = 0.577 \times 10^{-12}$ cm; $\mu_{\text{Co}} = 3.52 \mu_B$; $2B = 0.74 \times 10^{-16}$ cm². The good fit between the calculated and observed nuclear scattering confirms the reliability of the above-mentioned value of the nuclear scattering amplitude of Co, first reported by Roth in his paper on CoO, then by the same author in Co_3O_4 .⁹ This value is considerably smaller than the usually tabulated value of 0.28×10^{-12} cm, given by Shull and Wollan.^b

{ hkl }	Nuclear scattering $\Sigma F_n^2 (\times 10^{24})$	
	Calculated	Observed
222	796.8	810 ± 20
400	2633.6	2600 ± 30
004	1316.8	1320 ± 20
440	2633.6	2650 ± 40
404	5267.2	5280 ± 50
444	5267.2	5200 ± 50

{ hkl }	Magnetic scattering $\Sigma (F_m^2/64p^2)$	
	Calculated	Observed
111	31.4	32.1 ± 0.7
311	50.7	50.1 ± 1.0
113	0.3	
331	18.3	18.5 ± 0.4
313	50.1	
511	61.4	50.4 ± 1.0
333	31.4	
115	14.9	68.9 ± 1.4
531	63.9	
513	24.6	107.6
315	16.3	
	104.8	106.0 ± 2.0
		109.0 ± 4.0

^a W. L. Roth, J. Phys. Chem. Solids 25, 1 (1964).

^b C. G. Shull and E. O. Wollan, Phys. Rev. 81, 527 (1951).

⁹ V. Scatturin, L. Corliss, N. Elliot, and J. Hastings, Acta Cryst. 14, 19 (1961).

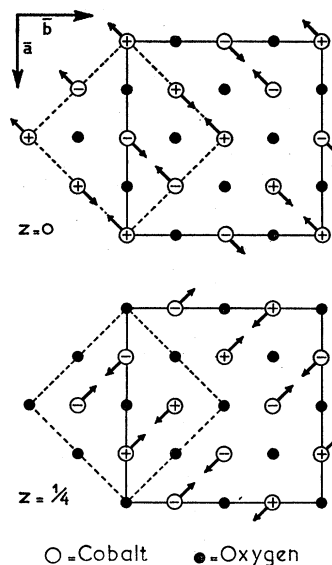


FIG. 3. Multi-spin-axis structure of CoO as proposed in this paper. The plus or minus signs designate the z components of the spins pointing up and down into the paper. The arrows represent the projection of the spins on the a - b plane. The layers $z = \frac{1}{2}$ and $z = \frac{3}{4}$ are constructed by reversing the spin directions in the layers $z = 0$ and $z = \frac{1}{4}$, respectively. The drawn lines represent the pseudocubic F cell, the dotted lines the tetragonal I cell as discussed in the text.

obtained this result from averaged data of runs at 77 and 4.2°K.

Although it is not possible to make a choice between the two models from powder data, the multispin model is attractive in that the spin structure is strictly tetragonal in conformity with the observed deformation (which amounts to $c/a = 0.988$ in the sample used in this investigation).

As there are no conclusive arguments against a multi-spin axis model, this model seems to be more probable than the collinear model, proposed by Roth.

The multispin axis structure that is obtained (Fig. 3) is related to Li's model B in the sense that the z components of the spins are arranged according to this model.

Symmetry in the Antiferromagnetic State

As the symmetry in the antiferromagnetic (af) state is no longer cubic but tetragonal, it should be possible to find the proper spacegroup in the tetragonal system. The tetragonal unit cell is body-centered with an a axis equal to one-half the face diagonal of the pseudocubic cell. The cell volume is one-half that of the pseudocubic cell and the cell contains 16 CoO units.

There are no I groups with two sixteenfold positions in which all coordinates are fixed by symmetry; the group $I4_1/acd (D_{4h}^{20})$ is the only one with one sixteenfold fixed position. Selecting this group we have available for Co the position $16c$ on the centers of symmetry and for O the position $16e$ (with $x=0$) on the twofold axes. The Co atoms cannot be sited on the twofold axes as

this would restrict the direction of the Co spins along the c axis, or perpendicular to this axis.

It should be noted that in the tetragonal state the oxygen atoms are no longer required by symmetry to be exactly halfway between the Co atoms. In the nuclear intensities, however, no evidence was found for a deviation.

ACKNOWLEDGMENTS

The author is grateful to Professor Dr. J. A. Goedkoop and Dr. B. O. Loopstra for numerous discussions, to Dr. E. H. P. Cordfunke for the preparation and analysis of the sample and to Dr. W. L. Roth for the suggestion of the problem.

Master Equation for Ising Model*

S. P. HEIMS

Department of Physics, Brandeis University, Waltham, Massachusetts

(Received 29 October 1964)

A spin system with unperturbed Hamiltonian $\mathcal{H}_0 = \frac{1}{2} \sum \sum B_{jk} \sigma_x^j \sigma_x^k - \gamma H \sum \sigma_x^j$ relaxing via the spin-lattice coupling $G = \frac{1}{2} \sum \sum C_{jk} \sigma_x^j (\sigma_y^k + \sigma_z^k)$ is studied by means of the general density-matrix theory of magnetic relaxation. By making some assumptions about the magnitude and time constants of the lattice correlation functions $\langle C_{ij}(t) C_{kl}(0) \rangle$, a master equation is obtained. It agrees at high temperatures with a master equation previously suggested by Glauber for the one-dimensional nearest-neighbor case. At high temperatures the magnetic moment relaxes with a single relaxation time, and the spin pair-correlation functions satisfy a closed set of equations. At low temperatures, however, the equations for the magnetization and the correlation functions are coupled to higher-order moments.

INTRODUCTION

A MASTER equation to describe the time-dependent behavior for a one-dimensional Ising model has been proposed by Glauber.¹ The master equation of Glauber is based on a simple stochastic model. The equation leads to explicit solutions for the magnetization and for correlation functions; it is constructed to yield also the correct equilibrium distribution.

Another, perhaps more fundamental, approach to obtaining a master equation begins with the quantum-mechanical Liouville equation for an explicit Hamiltonian. This approach has several advantages: (1) The physical assumptions and approximations going into the master equation can be clearly stated, and therefore also the physical circumstances to which it corresponds are more evident. (2) Generalizations of the master equation, which include off-diagonal elements of the density matrix, can be obtained. (3) The equation is equally valid for the one-, two-, or three-dimensional Ising model, and is not restricted to nearest-neighbor coupling. The two- and three-dimensional Ising models are of particular interest because for those cases the system can undergo a phase transition.

There is already in existence a general theory of the time-dependent behavior for a spin system, which interacts with a heat reservoir, presumably consisting of the lattice vibrations and other coordinates of the solid. In the theory first developed by Bloch,² and

extended and refined by others,³ the Liouville equation for the combined system of spins and "lattice" is the starting point. Mostly the theory has been applied to single or weakly coupled spins, but it can equally well be applied to a many-particle system if that system can be solved exactly. In this note the general theory will be applied to the special case of the Ising model spin system (with arbitrary range and sign of interaction), with an additional interaction causing transitions. The master equation obtained will be shown to agree in the one-dimensional case with Glauber's at high temperatures (relative to J/k) and zero magnetic field, but not at low temperatures or finite field strengths.

DERIVATION OF MASTER EQUATION

The total Hamiltonian to be considered is

$$\mathcal{H} = \mathcal{H}_s + \mathcal{H}_L + G, \quad (1)$$

where \mathcal{H}_s and \mathcal{H}_L depend only on spin and lattice coordinates, respectively, and G depends on both. The "lattice" (i.e., all degrees of freedom other than the spins of interest) will be regarded as a thermal reservoir. Consequently the detailed form of \mathcal{H}_L is not needed. For \mathcal{H}_s the following explicit form is taken:

$$\mathcal{H}_s = \frac{1}{2} \sum_j \sum_k B_{jk} \sigma_x^j \sigma_x^k - \gamma H \sum_j \sigma_x^j, \quad (2)$$

* Supported by the U. S. Office of Naval Research.

¹ R. Glauber, *J. Math. Phys.* **4**, 294 (1963).

² F. Bloch, *Phys. Rev.* **105**, 1206 (1957).

³ A. Redfield, *IBM J. Res. Develop.* **1**, 17 (1957); P. Hubbard, *Rev. Mod. Phys.* **33**, 249 (1961); P. N. Argyres and P. L. Kelley, *Phys. Rev.* **134**, A98 (1964).