

Current-Induced Nucleation and Dynamics of Skyrmions in a Co-based Heusler Alloy

W. Akhtar,¹ A. Hrabec,^{1,2} S. Chouaieb,¹ A. Haykal,¹ I. Gross,¹ M. Belmeguenai,³ M.S. Gabor,⁴ B. Shields,⁵ P. Maletinsky,⁵ A. Thiaville,² S. Rohart,² and V. Jacques^{1,*}

¹*Laboratoire Charles Coulomb, Université de Montpellier and CNRS, 34095 Montpellier, France*

²*Laboratoire de Physique des Solides, CNRS UMR 8502, Universités Paris-sud and Université Paris Saclay, 91405 Orsay Cedex, France*

³*LSPM, CNRS-Université Paris 13, Sorbonne Paris Cité, 99 avenue Jean-Baptiste Clément, 93430 Villejuif, France*

⁴*Center for Superconductivity, Spintronics and Surface Science, Technical University of Cluj-Napoca, Str. Memorandumului 28, 400114 Cluj-Napoca, Romania*

⁵*Department of Physics, University of Basel, Klingelbergstrasse 82, Basel 4056, Switzerland*



(Received 14 December 2018; revised manuscript received 12 February 2019; published 27 March 2019)

We demonstrate room-temperature stabilization of dipolar magnetic skyrmions with diameters in the range of 100 nm in a single ultrathin layer of the Heusler alloy Co₂FeAl (CFA) under moderate magnetic fields. Current-induced skyrmion dynamics in microwires is studied with a scanning nitrogen-vacancy magnetometer operating in the photoluminescence quenching mode. We first demonstrate skyrmion nucleation by spin-orbit torque and show that its efficiency can be significantly improved using tilted magnetic fields, an effect that is not specific to Heusler alloys and could be advantageous for future skyrmion-based devices. We then show that current-induced skyrmion motion remains limited by strong pinning effects, even though CFA is a magnetic material with a low magnetic damping parameter.

DOI: 10.1103/PhysRevApplied.11.034066

I. INTRODUCTION

Since the first proposition to use magnetic skyrmions for spintronic devices [1], a concerted research effort has led to the experimental demonstration of several key aspects required to achieve this ambitious goal [2,3]. Skyrmions have now been successfully observed at room temperature in numerous types of technologically relevant magnetic materials [4–10]. Most of these results were obtained in magnetic multilayer stacks lacking inversion symmetry, in which the interfacial Dzyalosinskii-Moriya interaction (IDMI) promotes chiral spin textures that can be efficiently driven by spin-orbit torques [11,12]. In recent years, skyrmion diameters ranging from the micrometer scale down to a few tens of nanometers have been observed depending on the balance between the strength of IDMI, magnetic anisotropy, and dipolar fields [13,14]. Current-induced skyrmion motion has also been reported [6,8,9], but with velocities remaining much smaller than those expected from seminal theoretical predictions [12,15], which points out the key role of sample defects in skyrmion dynamics [8,16–18]. The last key requirement of skyrmion nucleation has been demonstrated by Joule heating in

nanotrails [16], current concentrations in constrictions [4] or point contact [8], and spin-orbit-torque action at sample defects [19,20].

A large variety of host materials are currently being explored with the aim of optimizing the properties of skyrmions for spintronic applications. Here, we investigate the possibility of improving current-induced skyrmion dynamics by using an Heusler alloy, a class of ferromagnetic materials with an intrinsically low magnetic damping coefficient [21]. Although a skyrmion phase was recently identified at low temperature in some Heusler alloys, such as Mn₂CoAl and Mn₂RhSn, by detecting a topological Hall effect [22–24], the stabilization of magnetic skyrmions under ambient conditions has remained elusive to date and the promise of Heusler alloys for efficient skyrmion motion still needs to be explored.

In this paper, we employ a nitrogen-vacancy (N-V) magnetometer [25] to demonstrate room-temperature stabilization of dipolar magnetic skyrmions with diameters in the range of 100 nm in a single ultrathin layer of the Heusler alloy Co₂FeAl (CFA) under moderate magnetic fields. We then investigate skyrmion nucleation by spin-orbit torque and show that its efficiency can be significantly improved using tilted magnetic fields, an effect which is not specific to Heusler alloys and that could be

*vincent.jacques@umontpellier.fr

used in other systems. Finally current-induced skyrmion motion is addressed, showing that pinning effects still limit skyrmion velocity, even in a host material with low magnetic damping.

II. EXPERIMENTAL METHODS

The sample used in this study is a multilayer stack deposited by magnetron sputtering on a thermally oxidized silicon wafer [26]. As shown in Fig. 1(a), it consists of a CFA layer with thickness $t = 1.6$ nm sandwiched between 3 nm of Pt and 1.8 nm of MgO. Prior to the growth of this Pt(3 nm)\CFA(1.6 nm)\MgO(1.8 nm) heterostructure, a 2-nm-thick Ta buffer layer is deposited on the silicon substrate. A capping layer of Ta is also added to prevent oxidation of the stack. X-ray diffraction experiments indicate that the CFA film exhibits a (022) out-of-plane texture, which is the typical crystal structure of CFA films grown on (111) textured underlayers such as Pt or Ir [27]. Hysteresis loops recorded with a vibrating sample magnetometer (VSM) indicate a uniaxial perpendicular magnetic

anisotropy of the CFA layer $K_u = 8.9 \times 10^5$ J/m³ and a saturation magnetization $M_s = 1.14 \times 10^6$ A/m. In this sample, the effective anisotropy is therefore low, $K_{\text{eff}} = 74$ kJ/m³, which induces a low domain-wall energy and therefore favors skyrmion stabilization through demagnetizing effects [13,14]. The strength of IDMI, which is another key parameter for stabilizing skyrmions, is determined by monitoring the nonreciprocal propagation of spin waves with Brillouin light spectroscopy (BLS) in the Damon-Eshbach geometry [28,29], leading to an effective IDMI constant $D = -0.70 \pm 0.06$ mJ/m², i.e., with the same sign as the Pt\Co\AlO_x structure. Finally, a damping parameter $\alpha \sim 0.02$ is inferred from BLS measurements. The multilayer stack is patterned into 1-μm-wide magnetic wires by using a combination of e-beam lithography and ion milling. Ti\Au electrical contact pads are then deposited to apply current pulses into the magnetic wires.

Magnetic imaging is performed with a scanning-N-V magnetometer operating in the photoluminescence(PL) quenching mode under ambient conditions [25]. As sketched in Fig. 1(a), a single N-V defect located at the apex of a diamond tip [30,31] is integrated into an atomic force microscope (AFM) and scanned above the magnetic sample. The AFM system is combined with a confocal optical microscope that collects the N-V defect PL signal at each point of the scan. When a magnetic field larger than approximately 5 mT is applied perpendicular to the N-V defect quantization axis, an efficient mixing of its electron spin sublevels leads to an overall reduction of the PL intensity [32,33]. Here, this magnetic-field-induced PL quenching is exploited to map regions of the sample producing large stray fields with a spatial resolution fixed by the N-V-to-sample distance $d_{\text{N-V}}$ [34,35]. This parameter is measured through the calibration procedure described in Ref. [36], leading to $d_{\text{N-V}} \sim 80$ nm.

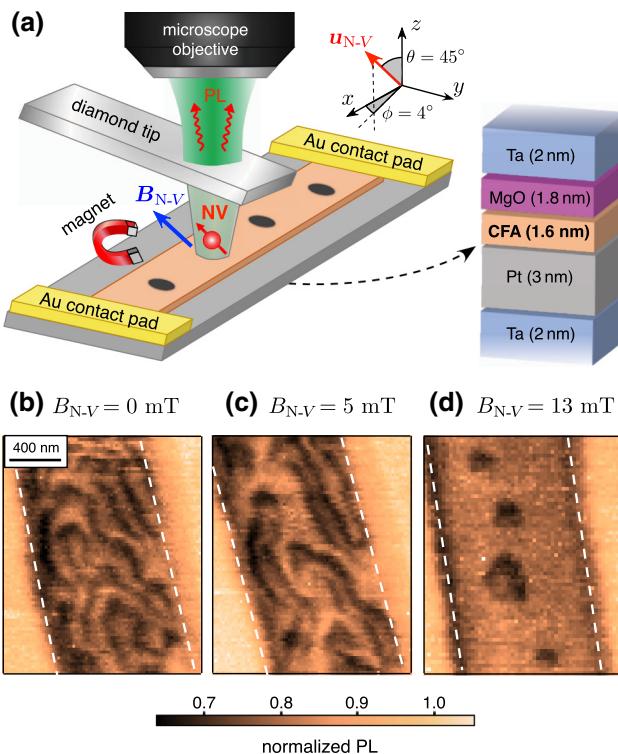


FIG. 1. (a) Principle of the experiment. A scanning-N-V magnetometer operating in the PL-quenching mode is employed to map the stray field produced above a 1-μm-wide magnetic wire made of Ta(2)\Pt(3)\CFA(1.6)\MgO(1.8)\Ta(2) (units in nm). A static magnetic field $B_{\text{N-V}}$ is applied along the N-V axis $\mathbf{u}_{\text{N-V}}$ with a permanent magnet. The Au contact pads are used for current injection. (b)–(d) PL-quenching images recorded for different external magnetic fields $B_{\text{N-V}}$ above the same area of the sample.

III. RESULTS AND DISCUSSION

Figure 1(b) shows a typical PL-quenching image recorded at zero field above a 1-μm-wide wire of the Pt\CFA\MgO stack. Dark PL contours indicate high stray field areas, which correspond to a network of domain walls organized in a wormlike structure. Compared to magnetic force microscopy, here the main advantage of scanning-N-V magnetometry is the absence of magnetic back-action on the sample. This is particularly important for the study of spin textures in ultrathin films, which are often highly sensitive to magnetic perturbations.

Nucleation of isolated dipolar skyrmions was first achieved by applying a static magnetic field. In order to avoid parasitic PL-quenching effects, the external field must be applied along the N-V defect quantization axis $\mathbf{u}_{\text{N-V}}$, which is characterized by the independently measured polar angles ($\theta \approx 45^\circ, \phi \approx 4^\circ$) in the (x, y, z) sample reference frame [see Fig. 1(a)]. For a magnetic field

$B_{N-V} = 5$ mT applied along the N-V axis, the magnetic domains start to shrink [Fig. 1(c)], and for $B_{N-V} = 13$ mT the wormlike domain structure fully collapses into isolated skyrmions, with a minimum diameter in the range of 100 nm [Fig. 1(d)]. The variation in shape and size of the resulting skyrmions is linked to pinning effects arising from structural disorder in the sample [18,37,38].

We now investigate skyrmion nucleation induced by short current pulses injected into the magnetic wire. As shown in Fig. 2(a), the experiments start with a fully saturated wire and a magnetic field $B_{N-V} = 13$ mT applied along the N-V quantization axis. We stress that this corresponds to an in-plane field component $B_x \approx 9$ mT along the $+e_x$ direction. A bunch of three 30-ns pulses with a current density $J = 6 \times 10^{11}$ A/m² is first applied along the $-e_x$ direction. In these conditions, skyrmions are not nucleated in the magnetic wire [Fig. 2(b)]. By simply reversing the current direction to $+e_x$, nucleation becomes highly efficient [Fig. 2(c)]. Such an asymmetric nucleation process with the current polarity cannot be explained solely by a thermal activation through Joule heating [16]. The main driving force of the nucleation process is attributed here to the spin-orbit torque resulting from the spin Hall effect (SHE) in the Pt layer, as explained below.

The SHE leads to a spin accumulation at the Pt\|CFA interface, which results in a damping like torque associated with an effective magnetic field [39]

$$\mathbf{H}_{\text{SHE}} = \frac{\hbar\theta_H}{2e\mu_0 M_s t} (\mathbf{e}_z \times \mathbf{J}) \times \mathbf{m},$$

where θ_H denotes the spin Hall angle, which is positive for Pt. The perpendicular magnetization component m_z leads to a SHE field along $\pm e_x$, with a sign fixed by the current direction. This effective field induces a slight tilt of the magnetization but does not favor magnetization reversal for a particular current polarity [40]. However, in our experiments the external magnetic field B_x breaks the symmetry by producing an in-plane magnetization component m_x , which modifies the effect of the SHE-induced torque and promotes a switching directionality, as previously invoked in the context of magnetization reversal in thin magnetic nanodots [40]. More precisely, the m_x component leads to an effective SHE field perpendicular to the sample surface, which can switch the magnetization and assist skyrmion nucleation. In our case, as the in-plane component of the external field is along $+e_x$, m_x is positive, and H_{SHE} has a component along $-e_z$ (respectively $+e_z$) when the current is applied along $+e_x$ (respectively $-e_x$). Starting from a saturated state with $m_z > 0$, skyrmion nucleation is therefore expected to be more efficient for a current applied along $+e_x$, in agreement with the experimental observation.

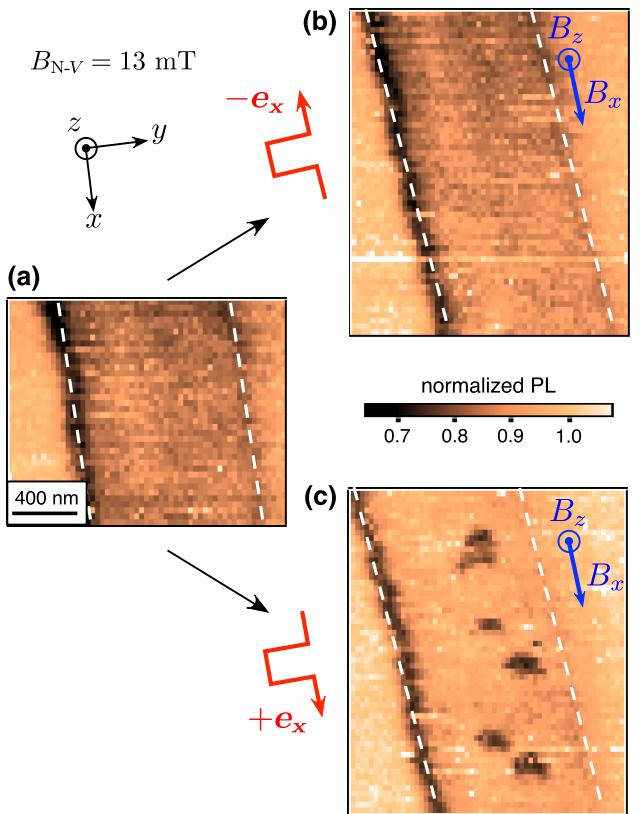


FIG. 2. Current-induced skyrmion nucleation. (a) PL-quenching image recorded over a saturated magnetic wire. The same wire is imaged after applying a bunch of three 30-ns current pulses with $J = 6 \times 10^{11}$ A/m² (b) along the $-e_x$ direction and (c) along the $+e_x$ direction. These experiments are performed with an external magnetic field $B_{N-V} = 13$ mT, which correspond to an in-plane field component $B_x \approx 9$ mT (see blue arrows).

This qualitative interpretation is confirmed by micromagnetic simulations of the nucleation process using the MUMAX3 code [41] with magnetic parameters extracted from independent measurements. Thickness fluctuations of the magnetic layer with a relative amplitude of 2% are included in the simulation following the procedure described in Ref. [18]. Such a structural disorder provides a network of nucleation centers in the sample. A magnetic field $B_z = 9$ mT is always applied perpendicular to the sample surface and the nucleation process is simulated by applying a single 2-ns-long current pulse. The initial state is chosen to be uniform along the perpendicular field direction, so that nucleated skyrmion cores are opposite to this field. The skyrmion density is extracted from the simulated magnetization maps, while varying (i) the current density and (ii) the in-plane magnetic field component B_x . We note that these simulations do not intend to quantitatively reproduce the experimental observations because we lack an accurate description of several key parameters of the experiment, such as the pinning landscape induced by structural disorder or thermal activation.

Simulations of the nucleated skyrmion density as a function of the current density are shown in Fig. 3(a). Without an in-plane magnetic field, skyrmion nucleation is obtained above a current threshold $J_{\text{th}} \approx 1.6 \times 10^{11} \text{ A/m}^2$, independently of the current polarity. This nucleation threshold is found to be tuned by an in-plane magnetic field. More precisely, J_{th} decreases when the current is applied along the in-plane field direction ($+e_x$), and increases when the current direction is reversed. As discussed earlier, this effect is expected from the symmetry of the SHE-induced torque. This is further illustrated by Fig. 3(b) showing the evolution of J_{th} as a function of the in-plane magnetic field. For $B_x = 10 \text{ mT}$, the nucleation threshold decreases (respectively increases) by $\approx 20\%$ when the current is applied along $+e_x$ (respectively $-e_x$). This effect leads to an asymmetric nucleation efficiency with the current polarity, as observed in our experiments. Although recent reports in the literature have also invoked SHE-induced torque as

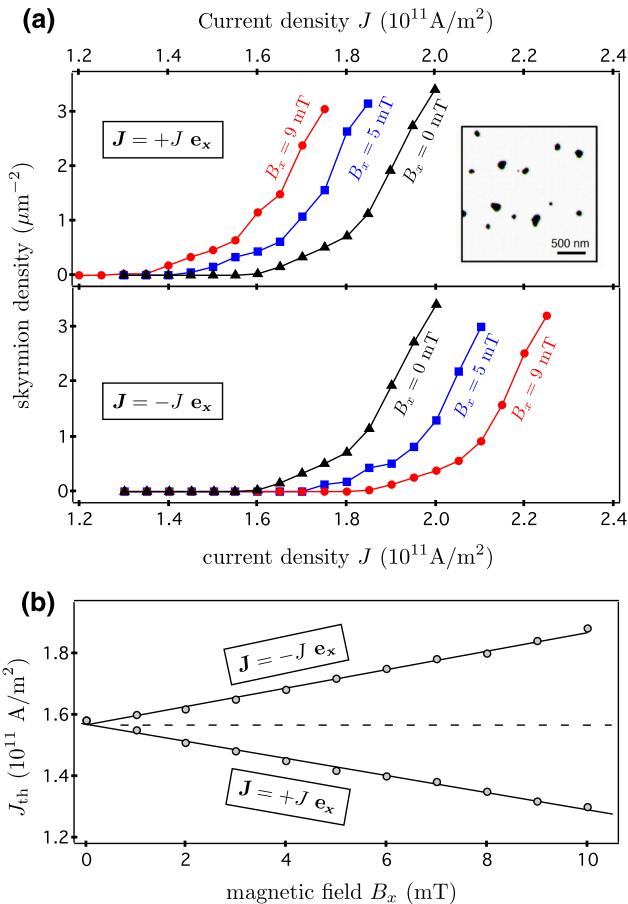


FIG. 3. Simulations of the skyrmion nucleation process. (a) Variation of the nucleated skyrmion density as a function of the current density and polarity, for three values of the in-plane magnetic field B_x . The inset shows a typical simulated magnetization map obtained for $B_x = 9 \text{ mT}$ and $J = 1.65 \times 10^{11} \text{ A/m}^2$ applied along $+e_x$. (b) Current threshold for skyrmion nucleation, J_{th} , as a function of B_x for the two different current polarities.

a driving force to explain deterministic skyrmion nucleation [19,20], our work demonstrates that its efficiency can be significantly improved by applying an additional in-plane magnetic field.

Once the microwires are filled with isolated skyrmions, we then investigate their current-induced motion. To this end, PL-quenching images are recorded after applying subsequent single current pulses with a magnetic field $B_{N-V} = 13 \text{ mT}$ applied along the N-V axis. In order to avoid nucleation or annihilation of skyrmions by Joule heating and SHE-induced torque, the current density is decreased to study their dynamics. Figures 4(a)–4(c) show the initial magnetic configuration of a wire and those observed after applying single 30-ns current pulses along the $+e_x$ direction with a current density $J = 3 \times 10^{11} \text{ A/m}^2$. Although most of the magnetic textures remain pinned in the wire, current-induced motion can be observed for some skyrmions. Importantly, the motion is found against the electron flow. This observation is confirmed in another wire in which the current polarity is reversed, as shown in Figs. 4(d)–4(f). This suggests that the SHE is the principal source of motion and that the skyrmions are of Néel type with a left-handed chirality [12,42], in agreement with the negative value of the IDMI constant measured by Brillouin light spectroscopy. We note that skyrmion displacements are not equal for successive current pulses owing to pinning effects. The motion is thus in the hopping regime, which prevents a clear observation of the skyrmion Hall

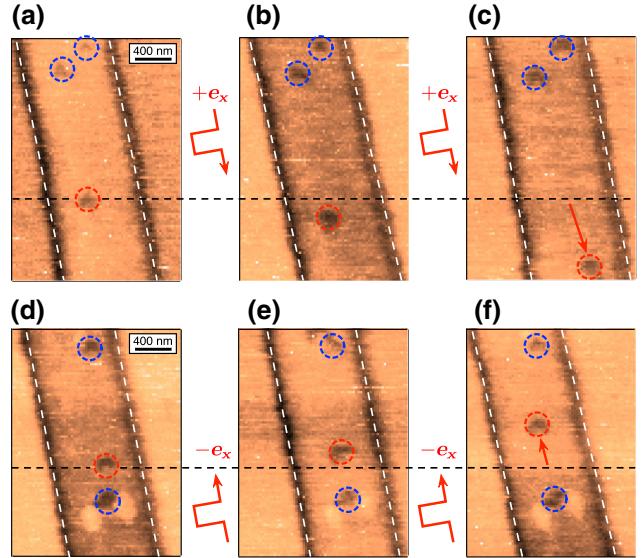


FIG. 4. Current-induced skyrmion motion. (a)–(c) Series of PL-quenching images recorded above a magnetic wire after applying subsequent 30-ns pulses with a current density $J = 3 \times 10^{11} \text{ A/m}^2$ along the $+e_x$ direction. (d)–(f) The same experiments performed on another wire while reversing the current polarity and using 15-ns pulses with $J = 4.5 \times 10^{11} \text{ A/m}^2$. All images are recorded with a magnetic field $B_{N-V} = 13 \text{ mT}$ applied along the N-V axis.

effect [43]. Nevertheless, based on the data shown in Fig. 4, we can estimate a velocity in the range of ≈ 10 m/s. It is worth mentioning that motion at higher current density could not be studied owing to parasitic skyrmion nucleation or annihilation effects. Although thin layers of CFA exhibit a low damping parameter, our observations indicate that skyrmion dynamics remain limited by strong pinning effects in this material.

IV. CONCLUSION

In conclusion, we have used scanning-N-V magnetometry in photoluminescence quenching mode to image current-induced nucleation and dynamics of dipolar skyrmions in a Co-based Heusler alloy at room temperature. Skyrmion nucleation is found to be asymmetric with the current polarity. This asymmetry is attributed to the SHE-induced spin-orbit torque in the presence of an in-plane magnetic field, which is further corroborated by micromagnetic simulations. This effect suggests a path towards efficient, deterministic generation of skyrmions via spin-orbit torques, which will be advantageous for future skyrmion-based devices. Current-induced skyrmion motion in our experiments remains limited by strong pinning effects, pointing out the key role of sample defects in skyrmion dynamics even in materials with intrinsically low magnetic damping.

ACKNOWLEDGMENTS

This research was supported by the European Research Council (Grant no. ERC-StG-2014, IMAGINE), the French Agence Nationale de la Recherche (Grant no. ANR-17-CE24-0025, TOPSKY) and the DARPA TEE program, through Grant no. MIPR#HR0011831554. B.M. acknowledges financial support from the Conseil régional Ile-de-France through the DIM NanoK (BIDUL project). M.S.G. acknowledges financial support from MRI-UEFI-SCDI through Grant no. PN-III-P1-1.1-TE-2016-2131-SOTMEM Grant no. 24/02.05.2018. P.M. acknowledges financial support from the Swiss National Science Foundation Grant No. 169321.

-
- [1] Albert Fert, Vincent Cros, and João Sampaio, Skyrmions on the track, *Nat. Nanotech.* **8**, 152 (2013).
 - [2] Giovanni Finocchio, Felix Büttner, Riccardo Tomasello, Mario Carpentieri, and Mathias Kläui, Magnetic skyrmions: From fundamental to applications, *J. Phys. D: Appl. Phys.* **49**, 423001 (2016).
 - [3] Albert Fert, Nicolas Reyren, and Vincent Cros, Magnetic skyrmions: Advances in physics and potential applications, *Nat. Rev. Mater.* **2**, 17031 (2017).
 - [4] W. Jiang, P. Upadhyaya, W. Zhang, G. Yu, M. B. Jungfleisch, F. Y. Fradin, J. E. Pearson, Y. Tserkovnyak, K. L. Wang, O. Heinonen, S. G. E. te Velthuis, and A.

- Hoffmann, Blowing magnetic skyrmion bubbles, *Science* **349**, 283 (2015).
- [5] Olivier Boulle *et al.*, Room-temperature chiral magnetic skyrmions in ultrathin magnetic nanostructures, *Nat. Nanotech.* **11**, 449 (2016).
- [6] Seonghoon Woo, Kai Litzius, Benjamin Krüger, Mi-Young Im, Lucas Caretta, Kornel Richter, Maxwell Mann, Andrea Krone, Robert M. Reeve, Markus Weigand, Parnika Agrawal, Ivan Lemesh, Mohamad-Assaad Mawass, Peter Fischer, Mathias Kläui, and Geoffrey S. D. Beach, Observation of room-temperature magnetic skyrmions and their current-driven dynamics in ultrathin metallic ferromagnets, *Nat. Mater.* **15**, 501 (2016).
- [7] C. Moreau-Luchaire, C. Moutafis, N. Reyren, J. Sampaio, C. A. F. Vaz, N. Van Horne, K. Bouzehouane, K. Garcia, C. Deranlot, P. Warnicke, P. Wohlhüter, J.-M. George, M. Weigand, J. Raabe, V. Cros, and A. Fert, Additive interfacial chiral interaction in multilayers for stabilization of small individual skyrmions at room temperature, *Nat. Nanotech.* **11**, 444 (2016).
- [8] A. Hrabec, J. Sampaio, M. Belmeguenai, I. Gross, R. Weil, S. M. Chérif, A. Stashkevich, V. Jacques, A. Thiaville, and S. Rohart, Current-induced skyrmion generation and dynamics in symmetric bilayers, *Nat. Commun.* **8**, 15765 (2017).
- [9] Seonghoon Woo, Kyung Mee Song, Xichao Zhang, Yan Zhou, Motohiko Ezawa, Xiaoxi Liu, Nyun Jong Lee, Sang-Il Kim, Seung-Young Park, Younghak Kim, Jae-Young Kim, Dongjoon Lee, Ouk Jae Lee, Jun Woo Choi, Byoung-Chul Min, Hyun Cheol Koo, and Joonyeon Chang, Current-driven dynamics and inhibition of the skyrmion Hall effect of ferrimagnetic skyrmions in GdFeCo films, *Nat. Commun.* **9**, 959 (2018).
- [10] Lucas Caretta, Maxwell Mann, Felix Büttner, Kohei Ueda, Bastian Pfau, Christian M. Günther, Piet Hessing, Alexandra Churikova, Christopher Klose, Michael Schneider, Dieter Engel, Colin Marcus, David Bono, Kai Babschik, Stefan Eisebitt, and Geoffrey S. D. Beach, Fast current-driven domain walls and small skyrmions in a compensated ferrimagnet, *Nat. Nanotech.* **13**, 1154 (2018).
- [11] A. Thiaville, S. Rohart, É. Jué, V. Cros, and A. Fert, Dynamics of Dzyaloshinskii domain walls in ultrathin magnetic films, *Europhys. Lett.* **100**, 57002 (2012).
- [12] J. Sampaio, V. Cros, S. Rohart, A. Thiaville, and A. Fert, Nucleation, stability and current-induced motion of isolated magnetic skyrmions in nanostructures, *Nat. Nanotech.* **8**, 839 (2013).
- [13] F. Büttner, I. Lemesh, and G. S. D. Beach, Theory of isolated magnetic skyrmions: From fundamentals to room temperature applications, *Sci. Rep.* **8**, 4464 (2018).
- [14] A. Bernand-Mantel, L. Camosi, A. Wartelle, N. Rouge-maille, M. Darques, and L. Ranno, The skyrmion-bubble transition in a ferromagnetic thin film, *SciPost Phys.* **4**, 27 (2018).
- [15] Junichi Iwasaki, Masahito Mochizuki, and Naoto Nagaosa, Universal current-velocity relation of skyrmion motion in chiral magnets, *Nat. Commun.* **4**, 1463 (2013).
- [16] William Legrand, Davide Maccariello, Nicolas Reyren, Karin Garcia, Christoforos Moutafis, Constance Moreau-Luchaire, Sophie Collin, Karim Bouzehouane, Vincent Cros, and Albert Fert, Room-temperature current-induced

- generation and motion of sub-100 nm skyrmions, [Nano Lett. 17, 2703 \(2017\)](#).
- [17] Wanjun Jiang, Xichao Zhang, Guoqiang Yu, Wei Zhang, Xiao Wang, M. Benjamin Jungfleisch, John E. Pearson, Xuemei Cheng, Olle Heinonen, Kang L. Wang, Axel Zhou, Yan Hoffmann, and Suzanne G. E. te Velthuis, Direct observation of the skyrmion Hall effect, [Nat. Phys. 13, 162 \(2017\)](#).
- [18] I. Gross, W. Akhtar, A. Hrabec, J. Sampaio, L. J. Martínez, S. Chouaieb, B. J. Shields, P. Maletinsky, A. Thiaville, S. Rohart, and V. Jacques, Skyrmion morphology in ultrathin magnetic films, [Phys. Rev. Mater. 2, 024406 \(2018\)](#).
- [19] F. Büttner, I. Lemesh, M. Schneider, B. Pfau, C. M. Günther, P. Hessing, J. Geilhufe, L. Caretta, D. Engel, B. Krüger, B. J. Viehaus, S. Eisebitt, and G. S. D. Beach, Field-free deterministic ultrafast creation of magnetic skyrmions by spin-orbit torques, [Nat. Nanotech. 12, 1040 \(2017\)](#).
- [20] Seonghoon Woo, Kyung Mee Song, Xichao Zhang, Motohiko Ezawa, Yan Zhou, Xiaoxi Liu, Markus Weigand, Simone Finizio, Jörg Raabe, Min-Chul Park, Ki-Young Lee, Jun Woo Choi, Byoung-Chul Min, Hyun Cheol Koo, and Joonyeon Chang, Deterministic creation and deletion of a single magnetic skyrmion observed by direct time-resolved x-ray microscopy, [Nat. Electron. 1, 288 \(2018\)](#).
- [21] S. Mizukami, D. Watanabe, M. Oogane, Y. Ando, Y. Miura, M. Shirai, and T. Miyazaki, Low damping constant for Co₂FeAl Heusler alloy films and its correlation with density of states, [J. Appl. Phys. 105, 07D306 \(2009\)](#).
- [22] B. M. Ludbrook, G. Dubuis, A.-H. Puichaud, B. J. Ruck, and S. Granville, Nucleation and annihilation of skyrmions in Mn₂CoAl observed through the topological Hall effect, [Sci. Rep. 7, 13620 \(2017\)](#).
- [23] C. Phatak, O. Heinonen, M. De Graef, and A. Petford-Long, Nanoscale skyrmions in a nonchiral metallic multiferroic: Ni₂MnGa, [Nano Lett. 16, 4141 \(2016\)](#).
- [24] K. G. Rana, O. Meshcheriakova, J. Kübler, B. Ernst, J. Karel, R. Hillebrand, E. Pippel, P. Werner, A. K. Nayak, and C. Felser, Observation of topological Hall effect in Mn₂RhSn films, [New J. Phys. 18, 085007 \(2016\)](#).
- [25] L. Rondin, J.-P. Tetienne, T. Hingant, J.-F. Roch, P. Maletinsky, and V. Jacques, Magnetometry with nitrogen-vacancy defects in diamond, [Rep. Prog. Phys. 77, 056503 \(2014\)](#).
- [26] M. Belmeguenai, Y. Roussigné, H. Bouloussa, S. M. Chérif, A. Stashkevich, M. Nasui, M. S. Gabor, A. Mora-Hernández, B. Nicholson, O.-O. Inyang, A. T. Hindmarch, and L. Bouchenoire, Thickness Dependence of the Dzyaloshinskii-Moriya Interaction in Co₂FeAl Ultrathin Films: Effects of Annealing Temperature and Heavy-Metal Material, [Phys. Rev. Appl. 9, 044044 \(2018\)](#).
- [27] M. Belmeguenai, M. S. Gabor, Y. Roussigné, T. Petrisor, R. B. Mos, A. Stashkevich, S. M. Chérif, and C. Tiisan, Interfacial Dzyaloshinskii-Moriya interaction sign in Ir/Co₂FeAl systems investigated by Brillouin light scattering, [Phys. Rev. B 97, 054425 \(2018\)](#).
- [28] Kai Di, Vanessa Li Zhang, Hock Siah Lim, Ser Choon Ng, Meng Hau Kuok, Jiawei Yu, Jungbum Yoon, Xuepeng Qiu, and Hyunsoo Yang, Direct Observation of the Dzyaloshinskii-Moriya Interaction in a Pt/Co/Ni Film, [Phys. Rev. Lett. 114, 047201 \(2015\)](#).
- [29] Mohamed Belmeguenai, Jean-Paul Adam, Yves Roussigné, Sylvain Eimer, Thibaut Devolder, Joo-Von Kim, Salim Mourad Cherif, Andrey Stashkevich, and André Thiaville, Interfacial Dzyaloshinskii-Moriya interaction in perpendicularly magnetized Pt/Co/AlO_x ultrathin films measured by brillouin light spectroscopy, [Phys. Rev. B 91, 180405 \(2015\)](#).
- [30] P. Maletinsky, S. Hong, M. S. Grinolds, B. Hausmann, M. D. Lukin, R. L. Walsworth, M. Lončar, and A. Yacoby, A robust scanning diamond sensor for nanoscale imaging with single nitrogen-vacancy centres, [Nat. Nanotech. 7, 320 \(2012\)](#).
- [31] Patrick Appel, Elke Neu, Marc Ganzhorn, Arne Barfuss, Marietta Batzer, Micha Gratz, Andreas Tschope, and Patrick Maletinsky, Fabrication of all diamond scanning probes for nanoscale magnetometry, [Rev. Sci. Instrum. 87, 063703 \(2016\)](#).
- [32] R. J. Epstein, F. M. Mendoza, Y. K. Kato, and D. D. Awschalom, Anisotropic interactions of a single spin and dark-spin spectroscopy in diamond, [Nat. Phys. 1, 94 \(2005\)](#).
- [33] N. D. Lai, D. Zheng, F. Jelezko, F. Treussart, and J.-F. Roch, Influence of a static magnetic field on the photoluminescence of an ensemble of nitrogen-vacancy color centers in a diamond single-crystal, [Appl. Phys. Lett. 95, 133101 \(2009\)](#).
- [34] L. Rondin, J.-P. Tetienne, P. Spinicelli, C. Dal Savio, K. Karrai, G. Dantelle, A. Thiaville, S. Rohart, J.-F. Roch, and V. Jacques, Nanoscale magnetic field mapping with a single spin scanning probe magnetometer, [Appl. Phys. Lett. 100, 153118 \(2012\)](#).
- [35] J.-P. Tetienne, L. Rondin, P. Spinicelli, M. Chipaux, T. Debuisschert, J.-F. Roch, and V. Jacques, Magnetic-field-dependent photodynamics of single NV defects in diamond: An application to qualitative all-optical magnetic imaging, [New J. Phys. 14, 103033 \(2012\)](#).
- [36] T. Hingant, J.-P. Tetienne, L. J. Martínez, K. Garcia, D. Ravelosona, J.-F. Roch, and V. Jacques, Measuring the Magnetic Moment Density in Patterned Ultrathin Ferromagnets with Submicrometer Resolution, [Phys. Rev. Appl. 4, 014003 \(2015\)](#).
- [37] K. Zeissler, M. Mruczkiewicz, S. Finizio, J. Raabe, P. M. Shepley, A. V. Sadovnikov, S. A. Nikitov, K. Fallon, S. McFadzean, S. McVitie, T. A. Moore, G. Burnell, and C. H. Marrows, Pinning and hysteresis in the field dependent diameter evolution of skyrmions in Pt/Co/Ir superlattice stacks, [Sci. Rep. 7, 15125 \(2017\)](#).
- [38] R. Juge, S.-G. Je, D. de Souza Chaves, S. Pizzini, L. D. Buda-Prejbeanu, L. Aballe, M. Foerster, A. Locatelli, T. Onur Mentes, A. Sala, F. Maccherozzi, S. S. Dhesi, S. Auffret, E. Gautier, G. Gaudin, J. Vogel, and O. Boulle, Magnetic skyrmions in confined geometries: Effect of the magnetic field and the disorder, [J. Magn. Magn. Mater. 455, 3 \(2018\)](#).
- [39] R. Lo Conte, A. Hrabec, A. P. Mihai, T. Schulz, S.-J. Noh, C. H. Marrows, T. A. Moore, and M. Kläui, Spin-orbit torque-driven magnetization switching and thermal effects studied in Ta/CoFeB/MgO nanowires, [Appl. Phys. Lett. 105, 122404 \(2014\)](#).

- [40] Luqiao Liu, O. J. Lee, T. J. Gudmundsen, D. C. Ralph, and R. A. Buhrman, Current-Induced Switching of Perpendicularly Magnetized Magnetic Layers using Spin Torque from the Spin Hall Effect, *Phys. Rev. Lett.* **109**, 096602 (2012).
- [41] Arne Vansteenkiste, Jonathan Leliaert, Mykola Dvornik, Mathias Helsen, Felipe Garcia-Sanchez, and Bartel Van Waeyenberge, The design and verification of MUMAX3, *AIP Adv.* **4**, 107133 (2014).
- [42] Satoru Emori, Uwe Bauer, Sung-Min Ahn, Eduardo Martinez, and Geoffrey S. D. Beach, Current-driven dynamics of chiral ferromagnetic domain walls, *Nat. Mater.* **12**, 611 (2013).
- [43] W. Jiang, X. Zhang, G. Yu, W. Zhang, X. Wang, M. B. Jungfleisch, J. E. Pearson, X. Cheng, O. Heinonen, K. L. Wang, Y. Zhou, A. Hoffmann, S. G. E. te Velthuis, Direct observation of the skyrmion Hall effect, *Nat. Phys.* **13**, 162 (2016).