

High-pressure study of the low- Z rich superconductor Be_{22}Re

J. Lim ^{1,*}, A. C. Hire ^{2,3,*}, Y. Quan,^{1,2,3} J. Kim ¹, L. Fanfarillo ^{1,4}, S. R. Xie,^{2,3} R. S. Kumar,⁵ C. Park,⁶ R. J. Hemley ^{5,7},
Y. K. Vohra,⁸ R. G. Hennig ^{2,3}, P. J. Hirschfeld,¹ G. R. Stewart,¹ and J. J. Hamlin ^{1,†}

¹Department of Physics, University of Florida, Gainesville, Florida 32611, USA

²Department of Materials Science and Engineering, University of Florida, Gainesville, Florida 32611, USA

³Quantum Theory Project, University of Florida, Gainesville, Florida 32611, USA

⁴Scuola Internazionale Superiore di Studi Avanzati (SISSA), Via Bonomea 265, 34136 Trieste, Italy

⁵Department of Physics, University of Illinois at Chicago, Chicago, Illinois 60607, USA

⁶HPCAT, X-ray Science Division, Argonne National Laboratory, Argonne, Illinois 60439, USA

⁷Department of Chemistry, University of Illinois at Chicago, Chicago, Illinois 60607, USA

⁸Department of Physics, University of Alabama at Birmingham, Birmingham, Alabama 35294, USA



(Received 2 April 2021; revised 22 June 2021; accepted 19 July 2021; published 13 August 2021)

With $T_c \sim 9.6$ K, Be_{22}Re exhibits one of the highest critical temperatures among Be-rich compounds. We have carried out a series of high-pressure electrical resistivity measurements on this compound to 30 GPa. The data show that the critical temperature T_c is suppressed gradually at a rate of $dT_c/dP = -0.05$ K/GPa. Using density functional theory (DFT) calculations of the electronic and phonon density of states (DOS) and the measured critical temperature, we estimate that the rapid increase in lattice stiffening in Be_{22}Re overwhelms a moderate increase in the electron-ion interaction with pressure, resulting in the decrease in T_c . High-pressure x-ray diffraction measurements show that the ambient pressure crystal structure of Be_{22}Re persists to at least 154 GPa.

DOI: [10.1103/PhysRevB.104.064505](https://doi.org/10.1103/PhysRevB.104.064505)

I. INTRODUCTION

The recent discovery of several hydrogen-rich compounds that become superconducting at record-breaking temperatures [1–4] has highlighted the potential of low- Z conventional superconductors to exhibit high temperatures superconductivity. Among systems at ambient pressure, MgB_2 ($T_c = 39$ K) provides the best known example of a low- Z superconductor with a high critical temperature [5]. The lightest elemental metal Li ($Z = 3$) exhibits a critical temperature of only 0.4 mK at ambient pressure [6], but this increases to a relatively high 15–20 K under pressures of ~ 30 GPa [7–9]. A number of studies have focused on the potential for high- T_c superconductivity in novel lithium based compounds at high pressure (e.g., Ref. [10]).

Substantially less work has been done on compounds of the second lightest elemental metal Be ($Z = 4$). This may be due, in part, to the dangers associated with the inhalation of Be, though alloys and compounds of Be such as Be-Cu are safe to handle and find widespread use. Elemental Be is a poor superconductor with $T_c = 26$ mK [11], but the potential for high T_c values in Be compounds has been appreciated for some time [12]. Beryllium tends to form compounds that are very Be rich (e.g., Be_{22}Re), but unlike the case of the superhydrides [2,3,13,14], these low- Z rich compounds can often be synthesized at ambient pressure. Several Be-rich compounds are found to be superconductors at ambient pressure (Be_{13}U [15],

Be_{13}Th [16], Be_{13}Lu [16], and Be_{22}Re), while several others have yet to be reported to be superconducting (e.g., Be_{13}La , Be_{13}Y , Be_{13}Re). It is interesting to consider whether higher T_c values can be induced in Be-rich compounds through the application of high pressure.

Among Be-rich compounds, Be_{22}Re displays one of the highest critical temperatures, with $T_c = 9.6$ K (nearly 400 times higher than the T_c of elemental Be [11]). Superconductivity was reported in the Be_{22}X ($X = \text{Mo}, \text{W}, \text{Tc}, \text{or Re}$) family of compounds by Bucher and Palmy in 1967 [17]. The crystal structure is a cubic, ZrZn_{22} type, with space group $Fd\bar{3}m$ (No. 227) and $Z = 8$ formula units per conventional unit cell. The structure is reminiscent of the clathratelike structures found in certain superhydrides at high pressure [18]. Recent measurements on Be_{22}Re indicate isotropic s -wave superconductivity [19].

In this work we report the pressure dependence of the superconducting transition temperature in Be_{22}Re revealed by high-pressure electrical resistivity measurements to 30 GPa. The superconducting transition temperature T_c decreases monotonically with increasing pressure at a rate of $-0.055(3)$ K/GPa. Density functional theory (DFT) calculations indicate that pressure decreases the electronic density of states at the Fermi level $N(0)$, and we present arguments why the effect of pressure on the electron-phonon matrix element and the electronic density of states is weak, such that lattice stiffening dominates the reduction of T_c with pressure.

II. METHODS

Polycrystalline Be_{22}Re was synthesized by arc-melting. Be and Re in stoichiometric amounts (with 3% excess Be added

*These authors contributed equally to the work.

†Corresponding author: jhamlin@ufl.edu

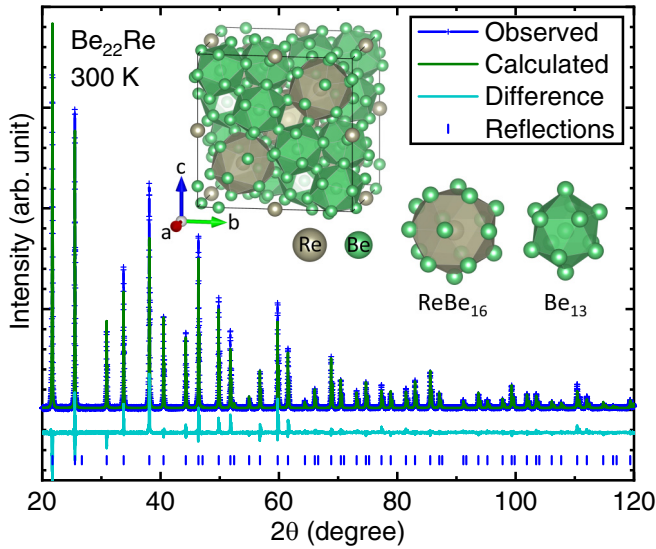


FIG. 1. X-ray diffraction pattern of Be_{22}Re at ambient pressure. The blue tick marks indicate the expected locations of the peaks. No additional peaks, indicative of impurity phases, were detected. Inset shows the crystal structure of cubic Be_{22}Re (8 formula units) with $a_0 = 11.568 \text{ \AA}$, $V_0 = 1547.86 \text{ \AA}^3$, and $\rho_0 = 3.299 \text{ g/cm}^3$ in good agreement with the previous study [21].

to account for mass loss during melting) were arc-melted together three times using 99.5% pure Be from Brush Wellman and 99.97% pure Re from Alfa Aesar.

Powder x-ray diffraction measurements were performed using a Panalytical X'Pert Pro diffractometer. Analysis of the diffraction pattern was performed using the software GSAS-II [20] and indicates single phase material after melting (see Fig. 1). Magnetic susceptibility measurements performed using a Quantum Design MPMS gave a T_c onset of 8.6 K and indicate full shielding (see Fig. 2).

For the high-pressure resistivity measurements, a micron-sized Be_{22}Re polycrystal sample ($\sim 30 \times 30 \times 5 \text{ \mu m}^3$) was

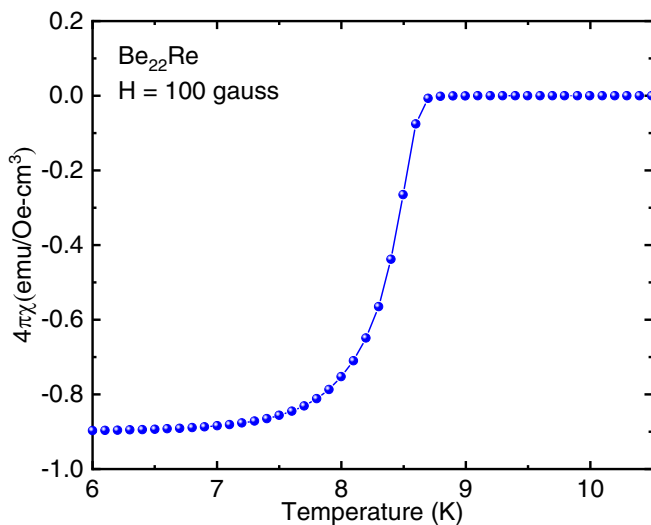


FIG. 2. Magnetic susceptibility of Be_{22}Re versus temperature at ambient pressure. The data are consistent with full shielding.

cut from a larger piece of bulk sample and placed in a gas-membrane-driven diamond anvil cell (OmniDAC from Almax-EasyLab) along with a ruby ($\sim 10 \text{ \mu m}$ in diameter) for pressure calibration [22]. Two opposing diamond anvils (0.15 and 0.5 mm central flats) were used, one of which was a designer-diamond anvil (0.15 mm central flat) with six symmetrically deposited tungsten microprobes in the encapsulated high-quality-homoepitaxial diamond [23]. A 316 stainless steel metal gasket was pre-indented from ~ 150 to 25 \mu m in thickness with a hole ($\sim 80 \text{ \mu m}$ in diameter), which was filled with soapstone (steatite) for electrically insulating the sample from the gasket and also serving as the pressure-transmitting medium. The diamond cell was placed inside a customized continuous-flow cryostat (Oxford Instruments). A home-built optical system attached to the bottom of the cryostat was used for the visual observation of the sample and for the measurement of the ruby manometer. Pressure was applied at $\sim 8 \text{ K}$ to the desired pressure, and then the sample was cooled down to 5 K and warmed up to 15 K at a rate of $\sim 0.5 \text{ K/min}$ at each pressure for the temperature-dependent resistivity measurement. During compression around 8 GPa, pressure was accidentally unloaded to $\sim 3 \text{ GPa}$ and then increased again to 15 GPa.

To estimate the electrical resistivity from the resistance, we used the van der Pauw method (assuming an isotropic sample in the measurement plane) $\rho = \pi t R / \ln 2$, where t is the sample thickness ($\sim 5 \text{ \mu m}$) with currents of 0.1–2 mA. The accuracy of the estimated resistivity is roughly a factor of 2 considering uncertainties in the initial thickness of the sample. No attempt was made to take into account the changes in the sample thickness under high pressures.

The high-pressure angle-dispersive x-ray diffraction (ADXRD) experiments on Be_{22}Re powder sample were carried out at beamline 16-BM-D, Advanced Photon Source (APS), Argonne National Laboratory. The x-ray beam with a wavelength of 0.4133 \AA (30.00 keV) was focused to $\sim 5 \text{ \mu m}$ (vertical) $\times 5 \text{ \mu m}$ (horizontal) (FWHMs) at the sample position. X-ray diffraction intensities were recorded using a MAR345 image plate detector. The typical exposure time was ~ 60 to 120 s/image depending on the sample position. The sample to detector distance was calibrated using a CeO_2 standard. The pressure inside the DAC was determined using an online ruby spectrometer and the Au grains loaded inside the sample chamber. Ne was used as the pressure transmitting medium. The 2D diffraction images were converted to 1D XRD patterns using the DIOPTAS software [24], which were then further analyzed by LHPM-Rietica software and Le Bail methods [25].

For evaluating the density of states (DOS) at the Fermi level as a function of pressure, we used density functional theory (DFT) as implemented in VASP [26,27]. The cutoff energy for the plane-wave basis set was set to 520 eV and a k -point density of 60 points per \AA^{-3} was used to relax the structures at various pressures. We used the Perdew-Burke-Ernzerhof (PBE) generalized gradient approximation (GGA) [28] for the exchange-correlation energy along the projector augmented wave (PAW) pseudopotentials [29]. To obtain accurate electronic DOS values, the tetrahedron method with Blöchl correction was used [30].

As the primitive cell contains 46 atoms, a complete calculation of the full phonon dispersion at multiple pressures is computationally prohibitive. Therefore, we attempt here to develop a qualitative understanding of trends in T_c with pressure based on estimates using phonon frequencies only at the Γ point. The phonon frequencies are calculated using the finite-difference method [31]. To estimate the phonon density of states (PDOS), $F(\omega)$ from the Γ point phonon frequencies, we apply a Gaussian smearing with a width of $\sigma = 1$ THz (4.135 meV),

$$F(\omega) = \sum_{i=1}^N \frac{D(\omega_i)}{\sqrt{2\pi}\sigma} \exp\left(-\frac{(\omega - \omega_i)^2}{2\sigma^2}\right), \quad (1)$$

where the summation is over all the Γ point phonons, and $D(\omega_i)$ is the degeneracy of the phonon with frequency ω_i .

Allen *et al.* [32] noted that for simple materials (e.g., elements) α^2F is proportional to F . For example, the α^2F and F for Pb have almost identical shapes and only differ in magnitude by a constant factor (see Appendix I of Ref. [32]). Assuming that the same holds also for Be_{22}Re , we approximate α^2F as

$$\alpha^2F = kN(0)F(\omega), \quad (2)$$

where k is a proportionality factor and $N(0)$ is the density of states at the Fermi level, accounting for possible changes in the number of states that can couple to the phonons. With this approximation, we obtain the Allen-Dynes parameters λ , ω_{\log} , and $\langle\omega^2\rangle$ [32] from the phonon density of states as

$$\lambda = 2 \int_0^\infty d\omega \frac{\alpha^2F(\omega)}{\omega} = 2kN(0) \int_0^\infty d\omega \frac{F(\omega)}{\omega}, \quad (3)$$

$$\begin{aligned} \omega_{\log} &= \exp\left[\frac{2}{\lambda} \int_0^\infty d\omega \frac{\alpha^2F(\omega)}{\omega} \ln \omega\right] \\ &= \exp\left[\frac{2kN(0)}{\lambda} \int_0^\infty d\omega \frac{F(\omega)}{\omega} \ln \omega\right], \end{aligned} \quad (4)$$

$$\begin{aligned} \langle\omega^n\rangle &= \frac{2}{\lambda} \int_0^\infty d\omega \alpha^2F(\omega) \omega^{n-1} \\ &= \frac{2kN(0)}{\lambda} \int_0^\infty d\omega F(\omega) \omega^{n-1}. \end{aligned} \quad (5)$$

If k were a function of ω , it would quantify the interaction/coupling strength between electrons at E_f and the phonons at frequency ω . In this study we first assume that k is independent of ω and pressure. We then fix the value of the constant k such that the simplified Allen-Dynes equation (i.e., $f_1 = f_2 = 1$) [32],

$$T_c = \frac{\omega_{\log}}{1.20} \exp\left[-\frac{1.04(1 + \lambda)}{\lambda - \mu^*(1 + 0.62\lambda)}\right] \quad (6)$$

reproduces the experimental value of T_c at ambient pressure. In order to obtain trends in T_c that are relevant to the high-pressure data, we have used the extrapolated zero pressure T_c value from our high-pressure data $T_c(P=0) \sim 8$ K, which is somewhat lower than the ambient pressure $T_c \sim 8.6$ K from susceptibility data on a different piece of the sample. This may be due to strain induced disorder in the sample due to the non-hydrostatic conditions present in the pressure chamber. The

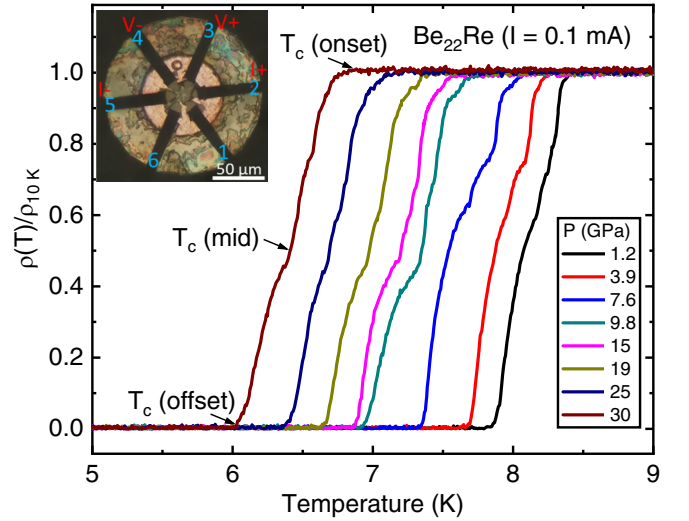


FIG. 3. Relative resistivity versus temperature measured while warming at several pressures to 30 GPa. Three arrows represent T_c (onset), T_c (mid), and T_c ($\rho = 0$), respectively, as defined in the text. All the data were taken during compression except for those at 9.8 GPa which were measured during decompression. The inset shows the photograph of the Be_{22}Re sample along with a ruby for pressure calibration, steatite insulation (bright area surrounding the sample at center), a 316 stainless steel metal gasket, and six tungsten leads configuration. Leads 2, 3, 4, and 5 were used for the measurement.

Coulomb pseudopotential μ^* is approximated as $\mu^* = 0.1$. If we instead allow k to vary with pressure such that the experimentally observed T_c values are reproduced, we find that the value of k varies by only about 4% between ambient pressure and 30 GPa. This suggests that a pressure independent k is a reasonably good approximation.

III. RESULTS

Figure 3 shows the relative resistivity $\rho(T)/\rho_{10K}$ versus temperature for Be_{22}Re to pressures of 30 GPa, focusing on the low temperature region near the superconducting transition. All the resistivity curves are based on compression except for 9.8 GPa, which was measured during decompression. We define T_c (onset), T_c (mid), and T_c ($\rho = 0$) as the temperatures where the resistivity just begins to drop below the normal state trend, drops to 50% of the normal state value, and drops to 0, respectively. The critical temperature T_c monotonically decreases with increasing pressure from 8.07 K at 1.2 GPa to 6.41 K at 30 GPa. Ambient pressure resistivity measurements found a transition width of 0.23 K [19]. Under pressure, the width of the superconducting transition ΔT_c , defined as the difference between T_c (onset) and T_c ($\rho = 0$), increases from 0.6 K at 1.2 GPa to 0.8 K at 30 GPa. The relatively small increase in transition width under pressure indicates that the tiny sample is subject to only small pressure gradients.

Figure 4 presents T_c versus pressure for Be_{22}Re to 30 GPa. The points are taken from the midpoint of the transition while the vertical error bars indicate T_c (onset) and T_c ($\rho = 0$) as defined in Fig. 3. The red line represents a linear fit

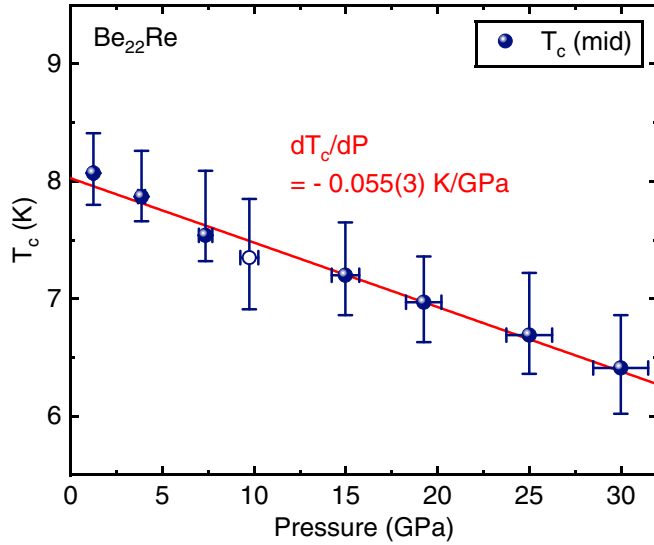


FIG. 4. Superconducting transition temperature (T_c) of Be_{22}Re versus pressure. Blue sphere (or open) symbols indicate the midpoint of the transition taken from compression (or decompression). The red solid line refers to the linear fit of T_c .

to the midpoint of the transition, which produces a slope $-0.055(3)$ K/GPa. The trend is reversible as the data at 9.8 GPa, which was measured during decompression, fits well within the trend. An estimate of T_c at ambient pressure from the linear fit yields ~ 8 K. This is somewhat lower than the ambient pressure resistivity onset reported by Shang *et al.* [19], but is consistent with the midpoint of the susceptibility transition that we measured (see Fig. 2).

High-pressure x-ray diffraction patterns measured at room temperature to pressures as high as 154 GPa are shown in Fig. 5. Clearly no structural transition is observed throughout the pressure range underscoring the significant stability of the initial cubic structure of Be_{22}Re . Some XRD patterns, for example at 18 and 97 GPa, show the presence of preferred orientation depending on the sample position, which is introduced by the nonhydrostatic pressure condition. The resulting pressure-volume (PV) curve is shown in Fig. 6, which is fitted with Vinet equation of state (EOS) [33]. The fit produces the enhanced value of bulk modulus (K_0), 155 GPa for Be_{22}Re , compared to that of Be metal, 114 GPa [34]. It is clear that despite the low concentration, the dilute Re plays an important role for the hardness of Be_{22}Re given that the bulk modulus of Re metal is 353 GPa [35]. The inset of Fig. 6 shows the refined diffraction pattern at 125 GPa in terms of the initial cubic structure using the Le Bail method [25], which confirms the absence of any structural transition.

Figures 7(a) and 7(b) show the VASP calculated Γ point phonons along with their degeneracies and the calculated phonon density of states using Gaussian smearing as described in Sec. II. Increasing the smearing σ leads to the smoothing of the phonon density of states. The resulting values of the integrated $F(\omega)$ are not strongly dependent on the smearing for reasonable values of σ . Figure 8 shows the pressure dependence of the density of states at the Fermi level $N(0)$ (red curve) and the electron-phonon coupling parameter λ (blue curve). λ is determined using Eq. (3), with the

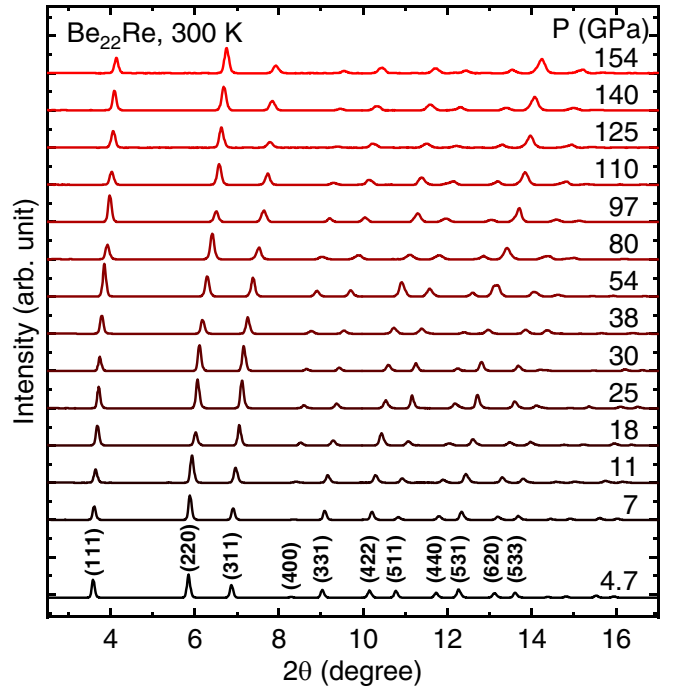


FIG. 5. Representative high-pressure XRD patterns of Be_{22}Re at pressures to 154 GPa. No structural transition was observed throughout the pressure range studied.

value of the constant k determined using the extrapolated zero pressure $T_c = 8$ K from the high-pressure data. $N(0)$ slightly monotonically decreases with pressure by about 20%, while λ decreases monotonically by nearly a factor of 2 between ambient pressure and 150 GPa.

The electron-phonon coupling parameter λ can also be represented by

$$\lambda = \frac{N(0)\langle I^2 \rangle}{M\langle \omega^2 \rangle} = \frac{\eta}{M\langle \omega^2 \rangle}, \quad (7)$$

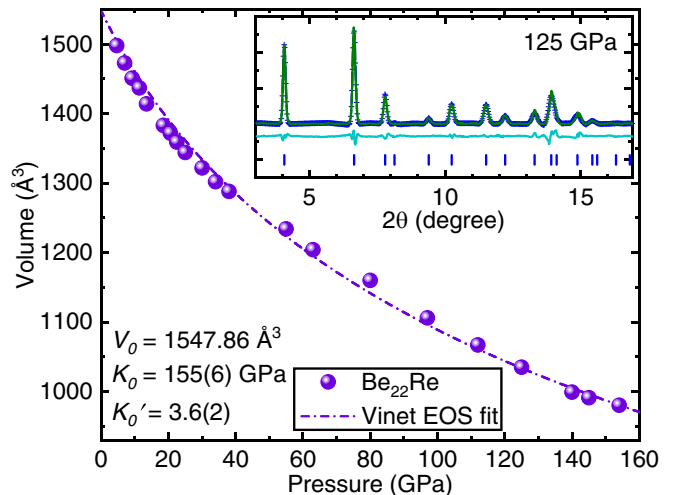


FIG. 6. PV isotherm of Be_{22}Re at room temperature. Inset shows the Le Bail fit at 125 GPa with the initial cubic structure. Numbers in the parentheses are the uncertainties on the last digit for K_0 and K_0' .

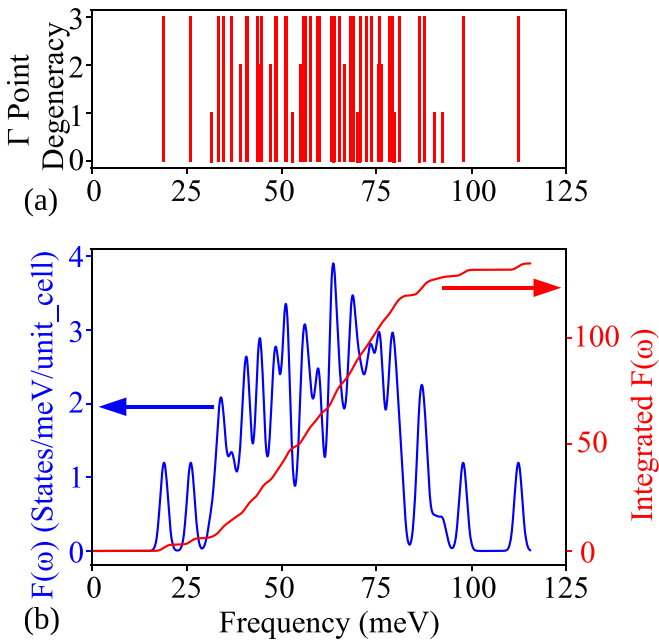


FIG. 7. (a) Γ point phonon frequencies and their respective degeneracies at 0 GPa. (b) Calculated phonon DOS given a smearing factor $\sigma = 4.135$ meV (1 THz).

where $\langle I^2 \rangle$ is the Fermi surface averaged electron-phonon matrix element, M represents an average atomic mass, and η is the McMillan-Hopfield parameter [36–38]. From Eq. (7) we can extract the value of $\langle I^2 \rangle/M$ as a function of pressure and this is plotted as the black data points in Fig. 8. Allen and Dynes [32] have highlighted that η is one of the key parameters controlling the superconducting critical temperature. We

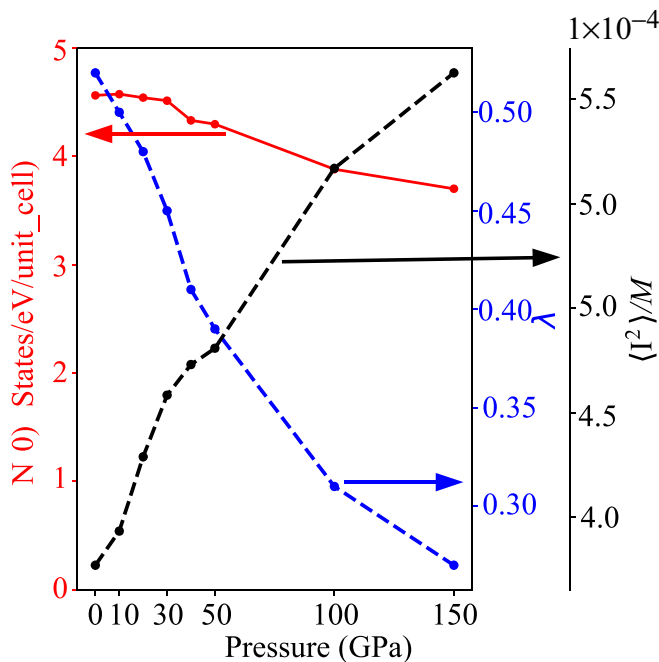


FIG. 8. Calculated density of states at the Fermi level $N(0)$ (red curve: both spins are included), electron-phonon coupling parameter λ (blue curve), and $\langle I^2 \rangle/M$ (black curve) as a function of pressures.

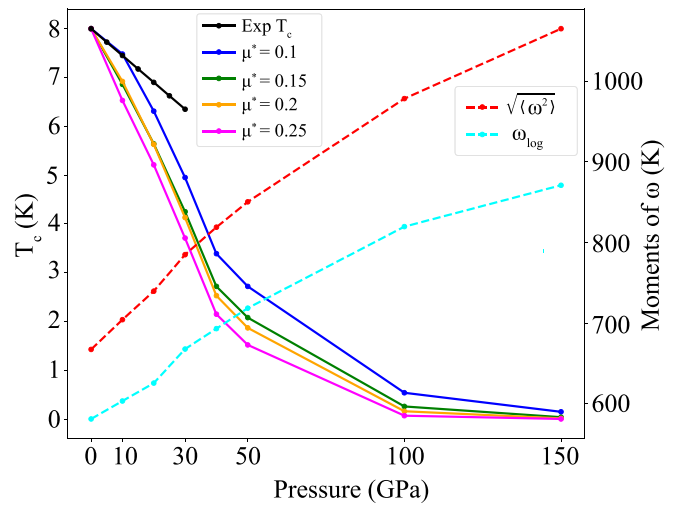


FIG. 9. Experimental and calculated T_c , and calculated $\sqrt{\langle \omega^2 \rangle}$ and ω_{\log} as a function of pressure. The T_c was calculated using Allen-Dynes equation at four values of μ^* .

find that η increases by more than 50% from ambient pressure to 30 GPa.

By combining the information obtained on the density of states at the Fermi level, electron-phonon coupling parameter, and phonon frequencies, we can estimate the expected pressure dependence of T_c . Figure 9 illustrates the pressure dependence of the phonon frequencies (dashed curves), experimental T_c (black curve), and the computationally estimated trend in T_c based on the approximation represented by Eq. (2) together with the Allen-Dynes equation [Eq. (6)]. Estimates are provided for different values of the Coulomb pseudopotential μ^* and, as expected, the values of T_c depend rather weakly on this parameter. In the region up to 30 GPa, where experimental data exist, the agreement is reasonably good, with T_c underestimated by only 25% at 30 GPa for $\mu^* = 0.1$. Since we know from the high-pressure x-ray diffraction data that the crystal structure remains unchanged to at least 150 GPa, we can use this method to estimate T_c to pressures beyond the range of the resistivity experiments. Based on the calculations we find that T_c continues to decrease, reaching a value below 1 K at 150 GPa.

Changes in λ (and consequently T_c) are controlled by the relative changes in η and $\langle \omega^2 \rangle$. The observed decrease in λ with pressure can be understood as deriving from the fact that lattice stiffening (increase in $\langle \omega^2 \rangle$) dominates over electronic effects (increase in η). At low pressures we find that the logarithmic volume derivative of η takes on a value of $d \ln \eta / d \ln V \approx -1.2$. This value is similar to that found for many simple metal (s , p) superconductors (including, e.g., MgB_2) and is significantly smaller than the value of ~ -3.5 found in many transition metals [39]. The comparatively small magnitude of $d \ln \eta / d \ln V$ in elemental simple metals causes T_c to decrease with pressure initially [40]. The fact that Be_{22}Re behaves as a simple metal in regards to superconductivity under pressure is consistent with the fact that the $N(0)$ is dominated by Be $2p$ electrons [19].

Adjacent to Be in the periodic table, Li is a prototypical simple metal at ambient pressure, but exhibits a remarkable

divergence from simple metal behavior at high pressure. Under pressure, Li becomes superconducting at temperatures approaching 20 K, exhibits complex crystal structures, and even becomes semiconducting above 75 GPa [7–9,41–44]. The anomalous behavior of Li has been attributed to the influence of the ion cores, which approach each other at high pressure, increasingly restrict the valence electrons to low symmetry interstitial regions, and eventually localize them enough to produce semiconducting behavior [41,43,44]. Similar physics is thought to influence the behavior of certain Li-rich compounds which have either been found [45] to exhibit superconductivity ($T_c = 13$ K) under pressure or have been predicted to exhibit higher temperature superconductivity or complex crystal structures under pressure [41,46,47]. However, the same evolution of complex crystal structures does not appear likely to occur in Be-rich compounds because the ion cores of Be are 25%–40% smaller than those of Li [48,49]. The size difference is significant enough that even at 300 GPa [34], the degree of core overlap for Be is much less than for Li at 75 GPa (the pressure where Li becomes semiconducting [43,50]). Thus, Be and Be-rich compounds may tend towards simple metal behavior even at multimegabar pressures.

IV. CONCLUSIONS

In summary, experiments show that the superconducting critical temperature of Be_{22}Re is suppressed by pressure to at least 30 GPa. Computational estimates based on electronic density of states and phonon calculations suggest that T_c will continue to be monotonically suppressed at higher pressures. Furthermore, the calculations and measurements indicate that lattice stiffening overcomes electronic effects, leading to the observed decrease in λ and T_c with pressure. High-pressure

x-ray diffraction shows that the ambient pressure crystal structure is remarkably stable and remains unchanged to at least 150 GPa. This stability is similar to that observed in elemental Be, which remains in the ambient pressure hcp structure to at least 170 GPa [51].

ACKNOWLEDGMENTS

We acknowledge enlightening discussion with L. Boeri and E. Zurek. We thank S. Tkachev (GSECARS, University of Chicago) for sample gas loading for the x-ray diffraction measurements. Work at the University of Florida performed under the auspices of U.S. Department of Energy Basic Energy Sciences under Contract No. DE-SC-0020385. High pressure, low temperature equipment development at the University of Florida was supported by U.S. National Science Foundation CAREER award DMR-1453752. A.H. acknowledges the support from the Center for Bright Beams, U.S. National Science Foundation award PHY-1549132. R.K. and R.H. acknowledge support from the U.S. National Science Foundation (DMR-1933622). X-ray diffraction measurements were performed at HPCAT (Sector 16), Advanced Photon Source (APS), Argonne National Laboratory. HPCAT operations are supported by the DOE-National Nuclear Security Administration (NNSA) Office of Experimental Sciences. The beamtime was made possible by the Chicago/DOE Alliance Center (CDAC), which is supported by DOE-NNSA (DE-NA0003975). Use of the gas loading system was supported by COMPRES under NSF Cooperative Agreement EAR-1606856 and by GSECARS through NSF grant EAR-1634415 and DOE grant DE-FG02-94ER14466. The Advanced Photon Source is a DOE Office of Science User Facility operated for the DOE Office of Science by Argonne National Laboratory under Contract No. DE-AC02-06CH11357.

-
- [1] A. P. Drozdov, M. I. Erements, I. A. Troyan, V. Ksenofontov, and S. I. Shylin, Conventional superconductivity at 203 kelvin at high pressures in the sulfur hydride system, *Nature (London)* **525**, 73 (2015).
 - [2] M. Somayazulu, M. Ahart, A. K. Mishra, Z. M. Geballe, M. Baldini, Y. Meng, V. V. Struzhkin, and R. J. Hemley, Evidence for Superconductivity Above 260 K in Lanthanum Superhydride at Megabar Pressures, *Phys. Rev. Lett.* **122**, 027001 (2019).
 - [3] A. P. Drozdov, P. P. Kong, V. S. Minkov, S. P. Besedin, M. A. Kuzovnikov, S. Mozaffari, L. Balicas, F. F. Balakirev, D. E. Graf, V. B. Prakapenka, E. Greenberg, D. A. Knyazev, M. Tkacz, and M. I. Erements, Superconductivity at 250 K in lanthanum hydride under high pressures, *Nature (London)* **569**, 528 (2019).
 - [4] E. Snider, N. Dasenbrock-Gammon, R. McBride, M. Debessai, H. Vindana, K. Vencatasamy, K. V. Lawler, A. Salamat, and R. P. Dias, Room-temperature superconductivity in a carbonaceous sulfur hydride, *Nature (London)* **586**, 373 (2020).
 - [5] J. Nagamatsu, N. Nakagawa, T. Muranaka, Y. Zenitani, and J. Akimitsu, Superconductivity at 39 K in magnesium diboride, *Nature (London)* **410**, 63 (2001).
 - [6] J. Tuoriniemi, K. Juntunen-Nurmilaukas, J. Uusvuori, E. Pentti, A. Salmela, and A. Sebedash, Superconductivity in lithium below 0.4 millikelvin at ambient pressure, *Nature (London)* **447**, 187 (2007).
 - [7] K. Shimizu, H. Ishikawa, D. Takao, T. Yagi, and K. Amaya, Superconductivity in compressed lithium at 20 K, *Nature (London)* **419**, 597 (2002).
 - [8] V. V. Struzhkin, M. I. Erements, W. Gan, H.-k. Mao, and R. J. Hemley, Superconductivity in dense lithium, *Science* **298**, 1213 (2002).
 - [9] S. Deemyad and J. S. Schilling, Superconducting Phase Diagram of Li Metal in Nearly Hydrostatic Pressures up to 67 GPa, *Phys. Rev. Lett.* **91**, 167001 (2003).
 - [10] H. Rosner, A. Kitaigorodsky, and W. E. Pickett, Prediction of High T_c Superconductivity in Hole-Doped LiBC, *Phys. Rev. Lett.* **88**, 127001 (2002).
 - [11] R. Falge, Superconductivity of hexagonal beryllium, *Phys. Lett. A* **24**, 579 (1967).
 - [12] J. Klein, A. Léger, S. d. Cheveigné, D. MacBride, C. Guinet, M. Belin, and D. Defourneau, Superconductivity in high Debye temperature material, *Solid State Commun.* **33**, 1091 (1980).
 - [13] Z. M. Geballe, H. Liu, A. K. Mishra, M. Ahart, M. Somayazulu, Y. Meng, M. Baldini, and R. J. Hemley, Synthesis and stability

- of lanthanum superhydrides, *Angew. Chem., Int. Ed.* **57**, 688 (2018).
- [14] P. P. Kong, V. S. Minkov, M. A. Kuzovnikov, S. P. Besedin, A. P. Drozdov, S. Mozaffari, L. Balicas, F. F. Balakirev, V. B. Prakapenka, E. Greenberg, D. A. Knyazev, and M. I. Erements, Superconductivity up to 243 K in yttrium hydrides under high pressure, [arXiv:1909.10482](https://arxiv.org/abs/1909.10482).
- [15] H. R. Ott, H. Rudigier, Z. Fisk, and J. L. Smith, UBe₁₃: An Unconventional Actinide Superconductor, *Phys. Rev. Lett.* **50**, 1595 (1983).
- [16] K. Uhlířová, N. Miura, V. Tkáč, J. Prokleška, M. Chrobak, Z. Tarnawski, H. Hidaka, T. Yanagisawa, V. Sechovský, and H. Amitsuka, Superconductivity in single crystalline ThBe₁₃ and LuBe₁₃, *Phys. B: Condens. Matter* **536**, 516 (2018).
- [17] E. Bucher and C. Palmy, Superconductivity and isotope effect in Be₂₂X compounds and molybdenum, *Phys. Lett. A* **24**, 340 (1967).
- [18] N. P. Salke, M. M. D. Esfahani, Y. Zhang, I. A. Kruglov, J. Zhou, Y. Wang, E. Greenberg, V. B. Prakapenka, J. Liu, A. R. Oganov, and J.-F. Lin, Synthesis of clathrate cerium superhydride CeH₉ at 80-100 GPa with atomic hydrogen sublattice, *Nat. Commun.* **10**, 4453 (2019).
- [19] T. Shang, A. Amon, D. Kasinathan, W. Xie, M. Bobnar, Y. Chen, A. Wang, M. Shi, M. Medarde, H. Q. Yuan, and T. Shiroka, Enhanced T_c and multiband superconductivity in the fully-gapped ReBe₂₂ superconductor, *New J. Phys.* **21**, 073034 (2019).
- [20] B. H. Toby and R. B. Von Dreele, GSAS-II: the genesis of a modern open-source all purpose crystallography software package, *J. Appl. Crystallogr.* **46**, 544 (2013).
- [21] D. E. Sands, Q. C. Johnson, A. Zalkin, O. H. Krikorian, and K. L. Kromholtz, The crystal structure of ReBe₂₂, *Acta Crystallogr.* **15**, 832 (1962).
- [22] A. D. Chijioke, W. J. Nellis, A. Soldatov, and I. F. Silvera, The ruby pressure standard to 150 GPa, *J. Appl. Phys.* **98**, 114905 (2005).
- [23] S. T. Weir, J. Akella, C. Aracne-Ruddle, Y. K. Vohra, and S. A. Catledge, Epitaxial diamond encapsulation of metal microprobes for high pressure experiments, *Appl. Phys. Lett.* **77**, 3400 (2000).
- [24] C. Prescher and V. B. Prakapenka, Dioptas: A program for reduction of two-dimensional x-ray diffraction data and data exploration, *High Press. Res.* **35**, 223 (2015).
- [25] A. Le Bail, H. Duroy, and J. Fourquet, Ab-initio structure determination of LiSbWO₆ by X-ray powder diffraction, *Mater. Res. Bull.* **23**, 447 (1988).
- [26] G. Kresse and J. Furthmüller, Efficiency of ab-initio total energy calculations for metals and semiconductors using a plane-wave basis set, *Comput. Mater. Sci.* **6**, 15 (1996).
- [27] G. Kresse and J. Furthmüller, Efficient iterative schemes for *ab initio* total-energy calculations using a plane-wave basis set, *Phys. Rev. B* **54**, 11169 (1996).
- [28] J. P. Perdew, K. Burke, and M. Ernzerhof, Generalized Gradient Approximation Made Simple, *Phys. Rev. Lett.* **77**, 3865 (1996).
- [29] P. E. Blöchl, Projector augmented-wave method, *Phys. Rev. B* **50**, 17953 (1994).
- [30] P. E. Blöchl, O. Jepsen, and O. K. Andersen, Improved tetrahedron method for Brillouin-zone integrations, *Phys. Rev. B* **49**, 16223 (1994).
- [31] G. Kresse, J. Furthmüller, and J. Hafner, *Ab initio* force constant approach to phonon dispersion relations of diamond and graphite, *Europhys. Lett.* **32**, 729 (1995).
- [32] P. B. Allen and R. C. Dynes, Transition temperature of strongly coupled superconductors reanalyzed, *Phys. Rev. B* **12**, 905 (1975).
- [33] P. Vinet, J. Ferrante, J. H. Rose, and J. R. Smith, Compressibility of solids, *J. Geophys. Res.: Solid Earth* **92**, 9319 (1987).
- [34] A. Lazicki, A. Dewaele, P. Loubeyre, and M. Mezouar, High-pressure-temperature phase diagram and the equation of state of beryllium, *Phys. Rev. B* **86**, 174118 (2012).
- [35] S. Anzellini, A. Dewaele, F. Occelli, P. Loubeyre, and M. Mezouar, Equation of state of rhenium and application for ultra high pressure calibration, *J. Appl. Phys.* **115**, 043511 (2014).
- [36] W. L. McMillan, Transition temperature of strong-coupled superconductors, *Phys. Rev.* **167**, 331 (1968).
- [37] J. J. Hopfield, Angular momentum and transition-metal superconductivity, *Phys. Rev.* **186**, 443 (1969).
- [38] J. J. Hopfield, On the systematics of high T_c in transition metal materials, *Physica* **55**, 41 (1971).
- [39] T. Tomita, J. J. Hamlin, J. S. Schilling, D. G. Hinks, and J. D. Jorgensen, Dependence of T_c on hydrostatic pressure in superconducting MgB₂, *Phys. Rev. B* **64**, 092505 (2001).
- [40] J. Hamlin, Superconductivity in the metallic elements at high pressures, *Physica C: Superconductivity and its Applications* **514**, 59 (2015).
- [41] J. B. Neaton and N. W. Ashcroft, Pairing in dense lithium, *Nature (London)* **400**, 141 (1999).
- [42] M. Hanfland, K. Syassen, N. E. Christensen, and D. L. Novikov, New high-pressure phases of lithium, *Nature (London)* **408**, 174 (2000).
- [43] T. Matsuoka and K. Shimizu, Direct observation of a pressure-induced metal-to-semiconductor transition in lithium, *Nature (London)* **458**, 186 (2009).
- [44] J. Lv, Y. Wang, L. Zhu, and Y. Ma, Predicted Novel High-Pressure Phases of Lithium, *Phys. Rev. Lett.* **106**, 015503 (2011).
- [45] T. Matsuoka, M. Debessai, J. J. Hamlin, A. K. Gangopadhyay, J. S. Schilling, and K. Shimizu, Pressure-Induced Superconductivity in CaLi₂, *Phys. Rev. Lett.* **100**, 197003 (2008).
- [46] J. Feng, N. W. Ashcroft, and R. Hoffmann, Theoretical Indications of Singular Structural and Electronic Features of Laves-Phase CaLi₂ under Pressure, *Phys. Rev. Lett.* **98**, 247002 (2007).
- [47] J. Feng, R. G. Hennig, N. W. Ashcroft, and R. Hoffmann, Emergent reduction of electronic state dimensionality in dense ordered Li-Be alloys, *Nature (London)* **451**, 445 (2008).
- [48] J. T. Waber and D. T. Cromer, Orbital radii of atoms and ions, *J. Chem. Phys.* **42**, 4116 (1965).
- [49] W. Martienssen and H. Warlimont, Eds., *Springer Handbook of Condensed Matter and Materials Data* (Springer, Berlin, 2005).
- [50] T. Matsuoka, M. Sakata, Y. Nakamoto, K. Takahama, K. Ichimaru, K. Mukai, K. Ohta, N. Hirao, Y. Ohishi, and K. Shimizu, Pressure-induced reentrant metallic phase in lithium, *Phys. Rev. B* **89**, 144103 (2014).
- [51] M. I. McMahon and R. J. Nelmes, High-pressure structures and phase transformations in elemental metals, *Chem. Soc. Rev.* **35**, 943 (2006).