

<sup>1</sup> V. B. Sandomirskii, Zh. Eksperim. i Teor. Fiz. **43**, 2309 (1962) [Soviet Phys. JETP **16**, 1631 (1963)].

<sup>2</sup> P. G. Harper and J. A. Hilder, Phys. Status Solidi **26**, 69 (1968).

<sup>3</sup> R. F. Frindt, J. Appl. Phys. **37**, 1928 (1966).

<sup>4</sup> R. F. Frindt, Phys. Rev. **140**, A536 (1965).

<sup>5</sup> J. A. Wilson and A. D. Yoffe, Advan. Phys. **18**, 193 (1969).

<sup>6</sup> L. H. Brixner, J. Inorg. Nucl. Chem. **24**, 257 (1962).

<sup>7</sup> M. Born and E. Wolf, *Principles of Optics*, 2nd revised ed. (Pergamon, New York, 1964), Chap. 13, p. 627.

<sup>8</sup> O. S. Heavens, *Optical Properties of Thin Solid Films* (Dover, New York, 1965), Chap. 4, p. 82.

<sup>9</sup> B. L. Evans and P. A. Young, Proc. Roy. Soc. (London) **A298**, 74 (1967).

<sup>10</sup> V. B. Sandomirskii, Zh. Eksperim. i Teor. Fiz. **52**, 158 (1967) [Soviet Phys. JETP **25**, 101 (1967)].

<sup>11</sup> If it were assumed that there exists a  $1/l^2$  variation of the exciton binding energy in addition to the  $1/l^2$  variation of the band gap, this value of  $m$  would be modified accordingly.

<sup>12</sup> H. I. Ralph, Solid State Commun. **3**, 303 (1965).

## Absolute Signs of Second-Harmonic Generation Coefficients of Piezoelectric Crystals

ROBERT C. MILLER AND WILLIAM A. NORDLAND

*Bell Telephone Laboratories, Murray Hill, New Jersey 07974*

(Received 3 August 1970)

This paper describes the measurement of the absolute signs of the nonlinear optical coefficients  $d_{ij}$  that give rise to second-harmonic generation in piezoelectric crystals. The measurements were made with a repetitively  $Q$ -switched Nd-yttrium aluminum garnet (Nd-YAG) laser ( $1.064 \mu$ ) and involve relative sign determinations between two crystals followed by a comparison of at least one of them with  $d_{14}$  of GaP, which has been shown previously to be positive with respect to the  $+[111]$ . To determine the unique directions in the crystals studied, several different methods were used, including: the piezoelectric effect, the pyroelectric effect, the etching behavior, and the electric field aligned spontaneous polarization. The crystals investigated included the following: zinc-blende crystals (ZnSe, ZnTe, and CdTe), wurtzite crystals (ZnO, BeO, CdS, and CdSe), ferroelectric crystals [LiTaO<sub>3</sub>, LiNbO<sub>3</sub>, BaTiO<sub>3</sub>, Ba<sub>2</sub>NaNb<sub>5</sub>O<sub>15</sub>, Gd<sub>2</sub>(MoO<sub>4</sub>)<sub>3</sub>, and Tb<sub>2</sub>(MoO<sub>4</sub>)<sub>3</sub>], and several other crystals (LiIO<sub>3</sub>, LiGaO<sub>2</sub>, LiCHO<sub>2</sub>·H<sub>2</sub>O, and quartz). Strong absorption of the second harmonic complicates the interpretation of the experimental results for ZnTe, CdTe, and CdSe. The present results and those of several recent theoretical predictions are in good agreement.

### I. INTRODUCTION

Recently, there have been a number of useful calculations of the signs and/or the magnitudes of the nonlinear optical coefficients  $d_{ij}$  that describe second-harmonic generation (SHG) and optical parametric interactions in piezoelectric crystals. One of the more important earlier predictions,<sup>1,2</sup> which was for crystals with wurtzite ( $w$ ) and zinc-blende ( $z$ ) structures, was that

$$d_{33}(w) = -2d_{31}(w) = (2/\sqrt{3})d_{14}(z).$$

Of the several papers that have considered SHG with III-V compounds,<sup>2-5</sup> the most successful utilized the electro-dynamical bond-charge model,<sup>2</sup> which led to predictions of signs and magnitudes in good agreement with experiment. In the case of the II-VI compounds, the bond-charge model, modified to take into account unequal atomic radii,<sup>6</sup> was even able to account for the observed<sup>7</sup> sign reversal of the  $d$ 's in going from CdS to ZnO. Other publications have included predictions for several of the niobates,<sup>8</sup> HfO<sub>3</sub> and LiIO<sub>3</sub>,<sup>9</sup> quartz,<sup>6</sup> and the general class of polar crystals.<sup>10</sup>

The early work having to do with sign predictions, notably that of Levine,<sup>2</sup> and Jeggo and Boyd,<sup>8</sup> stimulated the present rather extensive experimental investigation aimed at determining the absolute signs of the  $d$ 's for a variety of different crystals. Prior to the present measurements, the only published determinations of the absolute signs of  $d$ 's were for several crystals with the zinc-blende structure, namely, GaP,<sup>11</sup> and GaAs, InAs, and GaSb.<sup>12</sup> Some of the present results have been described previously in abbreviated letter form<sup>7</sup>; however, this paper presents a detailed description of the experimental measurements and many heretofore unpublished results.

The magnitudes of the  $d$ 's were not, in general, determined during the course of this study since they had been measured previously for most of the crystals investigated, and the results are included in an excellent recent summary of experimental data.<sup>13</sup>

### II. DETERMINATION OF UNIQUE CRYSTALLINE DIRECTIONS

The absolute signs of  $d$  only have meaning when they are related to an absolute direction in the piezoelectric

crystal. In general, these directions can be determined by x-ray analyses,<sup>14</sup> etching,<sup>15</sup> or piezoelectric tests.<sup>16</sup> For crystals belonging to polar crystal classes (crystals with a spontaneous polarization), one can also use the pyroelectric effect,<sup>17</sup> and for ferroelectric crystals (reversible pyroelectrics) the direction of the spontaneous polarization  $P_s$ . Of the above-mentioned techniques, only the x-ray method allows one to relate to the absolute crystal structure, that is, to the arrangement of atoms in the crystal. The theoretical predictions of the absolute signs of  $d$  are of course relative to the absolute crystal structure.

For the III-V and II-VI crystals, the outward normal from the metal  $A$  face (element II or III face) is defined as  $+[111]$  and  $+z$  for the zinc-blende and wurtzite forms, respectively. With most of the III-V and II-VI crystals investigated, the  $A$  faces were identified via etching procedures and/or piezoelectric measurements which had been previously related to the absolute crystal structures through x-ray analyses.<sup>15</sup>

For the general class of polar crystals, the  $+z$  direction is taken as the outward normal from the  $z$ -cut face that develops a negative charge on compression along  $z$ .<sup>16</sup> This definition is consistent with that given above for the wurtzite crystals (polar) which were studied. For the ferroelectric crystals investigated,  $+z$  is also the direction of  $\vec{P}_s$ . In addition, these definitions for polar crystals are consistent with  $+z$  defined as the outward normal from the  $z$ -cut face that develops a positive charge on cooling the crystal when  $dP_s/dT$  is negative (usually the case<sup>18</sup>), and a negative charge on cooling when  $dP_s/dT$  is positive.

The actual methods used to determine the unique directions of the crystals investigated belonging to the classes mentioned above, and other classes as well, are given in Table I. In many cases several different techniques were employed for a given crystal.

The first determination of an absolute sign for a  $d_{ij}$  was by Nelson and Turner,<sup>11</sup> who made use of the Faust-Henry experiment<sup>19</sup> to show that  $d_{14}$  is positive for GaP with respect to the  $+[111]$  as defined above. Subsequently, Wynne and Bloembergen<sup>12</sup> used an interference technique to compare GaAs, InAs, and GaSb with GaP and also found their  $d_{14}$ 's to be positive. These signs are in agreement with Refs. 2, 4, and 6, but in disagreement with Ref. 3.

### III. EXPERIMENTAL TECHNIQUE

The measurement involves relative sign determinations between two crystals for one or more of their  $d$ 's followed by a comparison of at least one of them with GaP and/or GaAs, both of which are reported to have a positive  $d_{14}$ . The technique used is in effect a modification of experimental methods developed earlier by Bloembergen and collaborators.<sup>12,20</sup>

TABLE I. Determination of unique directions.

Material	Piezo-electric test	Pyro-electric test	Etch test	Spontaneous polarization
GaP( $z$ )	a, b		c, d	
GaAs( $z$ )	a, e		d, f	
ZnTe( $z$ )			g, h, i	
CdTe( $z$ )			g	
ZnSe( $z$ )	j, k			
ZnO( $w$ )	l, e	m, n	n	
CdS( $w$ )	l, e		g	
BeO( $w$ )	l, o	m, o	o	
CdSe( $w$ )			g, p	
LiTaO <sub>3</sub>	q, r	s		t
LiNbO <sub>3</sub>	q, r	s		t
Ba <sub>2</sub> NaNb <sub>5</sub> O <sub>15</sub>	q, r	s		
Gd <sub>2</sub> (MoO <sub>4</sub> ) <sub>3</sub>	q, r	s		
Tb <sub>2</sub> (MoO <sub>4</sub> ) <sub>3</sub>	q, r	s		
BaTiO <sub>3</sub>				t
LiIO <sub>3</sub>	q, r			
LiGaO <sub>2</sub>	q, r	s		
LiCHO <sub>2</sub> ·H <sub>2</sub> O	q, r			
Quartz( $l$ )	u, r			

<sup>a</sup> A negative charge develops on the metal face on extension along  $+[111]$ .

<sup>b</sup> See Ref. 11.

<sup>c</sup> 10% Cl<sub>2</sub> in CH<sub>3</sub>OH.

<sup>d</sup> C. S. Fuller and H. W. Allison, J. Electrochem. Soc. **109**, 880 (1962).

<sup>e</sup> See Ref. 33 and references contained therein.

<sup>f</sup> 10% Br<sub>2</sub> in CH<sub>3</sub>OH.

<sup>g</sup> E. P. Warekois, M. C. Lavine, A. N. Mariano, and A. G. Gatos, J. Appl. Phys. **33**, 690 (1962); **37**, 2203(E) (1966).

<sup>h</sup> L. R. Shiozawa, J. M. Jost, and G. A. Sullivan, Aerospace Research Laboratories Technical Report No. ARL 68-0153, 1968 (unpublished).

<sup>i</sup> Concentrated HCl for 2 min. The Zn face becomes shiny and the Te face becomes dull. L. R. Shiozawa (private communication).

<sup>j</sup> A positive charge develops on the metal face on extension along  $+[111]$ .

<sup>k</sup> The piezoelectric coefficient is assumed to have a positive sign as other II-VI compounds; see Ref. 33.

<sup>l</sup> A positive charge develops on the metal face on extension along  $+[001]$ .

<sup>m</sup> A positive charge develops on the metal face on cooling.

<sup>n</sup> R. L. Barns, E. T. Keve, and S. C. Abrahams, J. Appl. Cryst. **3**, 27 (1970).

<sup>o</sup> S. B. Austerman, D. A. Berlincourt, and H. H. A. Krueger, J. Appl. Phys. **34**, 339 (1963).

<sup>p</sup> Concentrated HCl for 2 min. The Cd surface becomes shiny and the Se surface dull. L. R. Shiozawa (private communication).

<sup>q</sup> A positive charge develops on extension along the polar axis on the face from which the outward normal is taken as positive.

<sup>r</sup> See Ref. 16.

<sup>s</sup> A positive charge develops on the (001) face, on cooling, from which the outward normal is the positive  $[001]$ ;  $dP_s/dT$  is negative.

<sup>t</sup> An electric field was used to align the spontaneous polarization.

<sup>u</sup> For left-handed quartz, a positive charge develops on extension along the  $x$  axis on the face from which the outward normal is the positive  $x$  direction.

The second-order nonlinear polarization is defined by

$$P^{NL} = d(\mathcal{E}_1')^2, \quad (1)$$

where  $E_1' = \mathcal{E}_1' \exp i(k_1x - \omega t)$  represents the fundamental wave propagating in the  $x$  direction in the

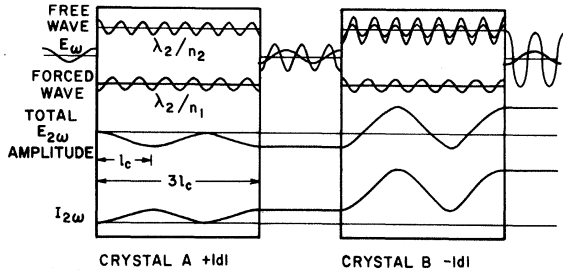


FIG. 1. Schematic drawing of SHG due to two identical crystals in series with their unique directions antiparallel. Reflections have been ignored and it is assumed that there is no dispersion between the two crystals. Each crystal contains three coherence lengths ( $l_c$ ) and therefore exhibits a Maker SHG maximum. The fundamental wave  $E_\omega$  enters crystal  $A$  from the left and generates free and forced second-harmonic waves which initially differ in phase by  $\pm\pi$  as shown. The free waves from both crystals add in crystal  $B$  giving rise to constructive interference. The figure also shows the variation of the second-harmonic amplitude ( $E_{2\omega}$ ) and intensity ( $I_{2\omega}$ ) as the waves propagate through the crystals. If the two unique directions are parallel (not shown), destructive interference occurs in crystal  $B$  and no second-harmonic emerges from the pair of crystals.

piezoelectric medium with a refractive index  $n_1$  at frequency  $\omega$  and a propagation constant  $k_1 = \omega n_1/c = 2\pi n_1/\lambda$ . It is convenient to express  $d$  by

$$d = d^0 \exp(i\varphi), \quad (2)$$

with respect to the positive directions defined earlier where  $d^0$  is real and positive. A negative  $d$  will therefore have  $\varphi = \pm\pi$ . The  $d$ 's are expected to be real for lossless media,<sup>12</sup> which are discussed first. For the present purpose, the tensor nature of the nonlinear interaction can be ignored.

### A. Transparent Crystals

Consider SHG in the first of two transparent crystals mounted in series. It can be shown that for plane waves, the second-harmonic field in vacuum at the end of a crystal platelet of thickness  $x_0$  can be represented by<sup>21,22</sup>

$$E_2 = -4\pi d \mathcal{E}_1^2 / (n_2 - n_1)(n_1 + 1)^2(n_2 + 1) \times \{ \exp[2i(k_1 x_0 - \omega t)] - \beta \exp[i(k_2 x_0 - 2\omega t)] \}, \quad (3)$$

with

$$\beta = 2n_2(n_1 + 1) / (n_2 + 1)(n_2 + n_1) \approx 1, \quad (4)$$

where  $n_2$  is the refractive index of the nonlinear medium at frequency  $2\omega$ ,  $\mathcal{E}_1$  the fundamental field amplitude incident on the crystal, and  $k_2 = 2\omega n_2/c = 4\pi n_2/\lambda$ . If the crystal is fabricated into a flat and parallel platelet suitable for the observation of Maker SHG fringes<sup>23</sup> and the path length  $l \geq x_0$  in the crystal is adjusted such that  $|E_2|$  is a maximum near normal incidence, i.e.,  $\Delta k l = (k_2 - 2k_1)l = N_{\text{odd}}\pi$ , where  $N_{\text{odd}}$  is an odd integer,

Eq. (3) becomes

$$E_2 = -\frac{4\pi d \mathcal{E}_1^2 \exp[2i(k_1 l - \omega t)]}{(n_2 - n_1)(n_1 + 1)^2(n_2 + 1)} [1 + \beta]. \quad (5)$$

Under these conditions it can be seen that the phase angle between the harmonic "forced wave"<sup>21</sup> [the inhomogeneous solution<sup>22</sup> or first term of Eq. (3)] and the fundamental squared at the front surface of the crystal, namely,  $\varphi \pm \pi$  for  $n_2 > n_1$ , is equal to the phase angle between the second-harmonic wave and the fundamental squared at the exit of the crystal except for a multiple of  $2\pi$ . If  $n_2 < n_1$ , i.e., the coherence length  $l_c = \pi/\Delta k = \lambda/4(n_2 - n_1)$  is negative, and the relative phase angle becomes  $\varphi$ .

If a second nonlinear crystal ( $B$ ) is now positioned in the path of the fundamental and harmonic beams coming from the first crystal ( $A$ ), interference effects can be observed which enable one to determine the relative phases and hence the relative signs of the two  $d$ 's being compared. Assume  $n_2 > n_1$  for both crystals and that the medium between the two crystals is not dispersive. Then, the phase angle between the second-harmonic wave from crystal  $A$  and the fundamental squared at the front surface of crystal  $B$ , in general, defined by  $\varphi_A' \pm \pi$ , is in this case equal to  $\varphi_A \pm \pi$ . The second-harmonic wave from crystal  $A$  contributes to the "free wave"<sup>21</sup> [homogeneous solution<sup>22</sup> or second term in Eq. (3)] in crystal  $B$ . Since the phase angle between the free wave generated in crystal  $B$  and the fundamental squared just within the second crystal is  $\varphi_B$ , the phase difference between the two components of the free wave in crystal  $B$  will be  $\varphi_A - \varphi_B \pm \pi$ . Thus for  $\varphi_A - \varphi_B = \pm\pi$ , one has constructive interference and for  $\varphi_A - \varphi_B = 0$ , destructive interference. This is evident in the expression below which describes the second-harmonic field within crystal  $B$ :

$$E_2'(B) \propto \{ \exp[2i(k_1 x - \omega t)] + [(n_1 + 1)/(n_2 + 1)] \times (\gamma \exp[i(\varphi_A - \varphi_B)] - 1) \exp[i(k_2 x - 2\omega t)] \}. \quad (6)$$

In Eq. (6), all quantities refer to crystal  $B$  except  $\varphi_A$  and  $\gamma$ , which is the ratio of the second-harmonic field amplitude in crystal  $B$  due to crystal  $A$  to that of the free wave due to crystal  $B$  alone. With crystal  $B$  also in the form of a flat and parallel platelet, and set (in the absence of crystal  $A$ ) at a Maker-fringe maximum near normal incidence, the second-harmonic power  $P_2$  emergent from the two crystals in series can be approximated by

$$P_2 \propto \{ 4 + \gamma[\gamma - 4 \cos(\varphi_A - \varphi_B)] \}, \quad (7)$$

where it has been assumed that for crystal  $B$ ,

$$\beta = 2n_2(n_1 + 1) / (n_1 + n_2)(n_2 + 1) = 1.$$

Figure 1 illustrates the two-crystal situation described above for the case where both crystals are set at

Maker SHG maxima and the crystals identical except that their unique directions are antiparallel so that  $\varphi_A - \varphi_B = \pm\pi$ . Reflections have been ignored. For the corresponding case (not shown in Fig. 1) with  $\varphi_A = \varphi_B$ , the two free waves would interfere destructively in crystal *B* with the result that no second-harmonic light would emerge from the pair of crystals.

As a result of uncertainties in  $\gamma$  due to beam divergence and other factors, it is usually not possible to deduce  $\varphi_A - \varphi_B$  from Eq. (7) alone. To circumvent this difficulty, dispersion is introduced between the two crystals. Initially, the phase difference between the second-harmonic wave and the fundamental squared is adjusted to change by exactly  $4\pi$  over the distance *s* between the two crystals, i.e.,  $\varphi_A' \pm \pi - (\varphi_A \pm \pi) = 4\pi$ . By means of two identical crystals and Eq. (7), where now  $\varphi_A$  should be replaced by  $\varphi_A'$ , it was found that when the enclosure housing the crystals, photomultiplier, etc., was nominally filled with dry  $\text{CO}_2$ , a distance *s* equal to 13.3 cm provided the desired  $4\pi$  phase difference. This value for *s* is in agreement with estimates from published refractive index data on  $\text{CO}_2$ .<sup>24</sup> The  $\text{CO}_2$  is then replaced slowly with He, which has a much smaller dispersion than  $\text{CO}_2$ ,<sup>24</sup> thereby changing  $\varphi_A'$  by more than  $2\pi$  so that over one cycle of Eq. (7) is scanned. Figure 2 shows typical data for  $d_{33}$  for two identical  $\text{LiNbO}_3$  crystals mounted with their *z* axes parallel, i.e.,  $\varphi_A = \varphi_B$ . As expected from Eq. (7), one observes a minimum in  $P_2$  with a  $\text{CO}_2$  atmosphere, which then goes through a maximum as the  $\text{CO}_2$  is partially replaced by He. Thus, it is clear that when  $P_2(\text{CO}_2)$  is a minimum,  $\varphi_A = \varphi_B$  and the *d*'s have the same signs. Likewise the two *d*'s have opposite signs if  $P_2(\text{CO}_2)$  is a maximum, i.e.,  $\varphi_A - \varphi_B = \pm\pi$ .

For these experiments the fundamental frequency was

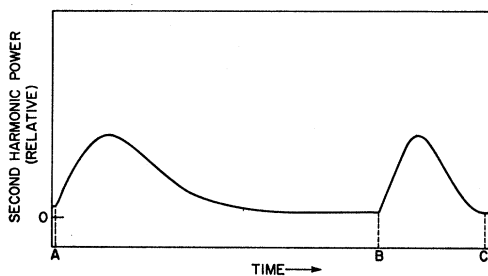


FIG. 2. Second-harmonic power  $P_2$  due to  $d_{33}$  emergent from two identical  $\text{LiNbO}_3$  platelets mounted in series with their  $+z$  directions parallel. Each crystal is separately adjusted to a Maker fringe maximum near normal incidence to the Nd-YAG laser beam. The atmosphere between the two crystals is slowly changed from air to essentially pure  $\text{CO}_2$  by introducing  $\text{CO}_2$  at a constant flow rate beginning at time *A*. A steady state is reached at time *B*, at which point the  $\text{CO}_2$  flow is stopped and He is introduced at a constant rate.  $P_2$  traces out a complete cycle between *B* and *C*. Since the values of  $P_2$  at times *B* and *C* are both minima with the same value, the two  $d_{33}$ 's have the same phase shift, as expected.

TABLE II. Absolute signs and phases of SHG coefficients.

Transparent crystals						
	$d_{14}$	$d_{33}$	$d_{31}$	$d_{32}$	$d_{22}$	$d_{11}$
ZnSe( <i>z</i> )	+					
ZnO( <i>w</i> )		-	+			
BeO( <i>w</i> ) <sup>a</sup>		-	-			
CdS( <i>w</i> ) <sup>b</sup>		+	-			
LiTaO <sub>3</sub>		-	-		+	
LiNbO <sub>3</sub> <sup>c</sup>		-	-		+	
BaTiO <sub>3</sub>		-	-			
Ba <sub>2</sub> NaNb <sub>5</sub> O <sub>15</sub> <sup>b</sup>		-	-	-		
Gd <sub>2</sub> (MoO <sub>4</sub> ) <sub>3</sub>		-	-	+		
Tb <sub>2</sub> (MoO <sub>4</sub> ) <sub>3</sub>		-	-	+		
LiIO <sub>3</sub> <sup>d</sup>		-	-			
LiGaO <sub>2</sub>		-	-	+		
LiCHO <sub>2</sub> ·H <sub>2</sub> O		+	e	-		
Quartz( <i>l</i> )						+
Absorbing crystals						
	$(\varphi_{14})_{\text{expt}}$	$(\varphi_{33})_{\text{expt}}$	$(\varphi_{31})_{\text{expt}}$			
ZnTe( <i>z</i> )		0°				
CdTe( <i>z</i> )		$\pm\pi$				
CdSe( <i>w</i> )			$\pi - 44^\circ \pm \pi$	$-49^\circ \pm \pi$		

<sup>a</sup> See Ref. 37 for the relative signs.

<sup>b</sup> See Ref. 10 for the relative signs.

<sup>c</sup> The relative signs of  $d_{22}$  and  $d_{31}$  were determined by J. E. Bjorkholm, Appl. Phys. Letters 13, 36 (1968).

<sup>d</sup> Relative signs determined by J. Jerphagnon, Appl. Phys. Letters 16, 298 (1970).

<sup>e</sup> SHG due to  $d_{31}$  could not be observed with the sample orientation used.

provided by a Nd-yttrium aluminum garnet (Nd-YAG) laser (1.064  $\mu$ ) acoustically *Q*-switched at a 1-kHz rate. The unapertured multimode output beam was several mm in diam and had a peak power of about 400 W. For samples with a small cross section, an adjustable iris was utilized to limit the beam diameter to as small as about 1 mm. When comparing two crystals, the beam was never focused. However, for the determination of the relative signs of coefficients for a given crystal,<sup>25</sup> moderately focused beams were sometimes used.

The samples were fabricated into optically flat platelets, typically several mm thick, with the opposite sides parallel to about one minute of arc or less. In the case of ferroelectric crystals, only single domain regions were investigated.<sup>26</sup> The two crystals to be compared were mounted in series, each on a rotatable head with the unique direction known. State of the art detection methods were used.

## B. Absorbing Crystals

The appropriate equations for absorbing crystals are obtained from Eq. (3) by allowing the refractive indices and hence  $k_1$  and  $k_2$  to be complex quantities, in par-

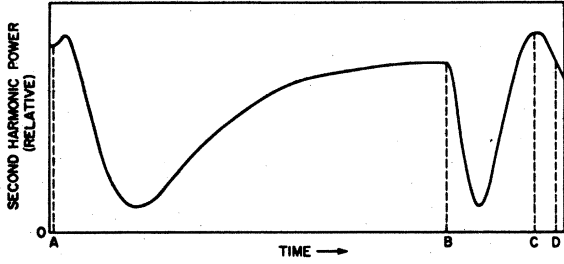


FIG. 3. Second-harmonic power  $P_2$  due to  $d_{33}$  from CdSe and ZnO platelets using the same controlled dispersion technique described in the caption for Fig. 2.  $P_2$  traces a complete cycle between times  $B$  and  $D$ . Since  $P_2$  at point  $B$  does not correspond to an extremum of the He cycle between  $B$  and  $D$ , the relative phase of the two  $d_{33}$ 's is not simply 0 or  $\pm\pi$ . Analysis of these data shows that the relative phase between the two  $d_{33}$ 's is  $\pi - 44^\circ \pm \pi$ .

ticular

$$k_j = k_j' + \frac{1}{2}i\alpha_j, \quad n_j = n_j' + i\lambda\alpha_j/4\pi j. \quad (8)$$

The  $a_j$  are the power absorption coefficients. In the most general case, Eq. (3) becomes

$$E_2 = - \frac{8\pi\omega\epsilon_1^2 d \exp[2i(k_1'x_0 - \omega t) - \alpha_1 x_0]}{c(\Delta k' + i\alpha)(n_1 + 1)^2(n_2 + 1)} \times \{1 - \beta \exp[i(\Delta k' + i\alpha)x_0]\}. \quad (9)$$

In Eq. (9),  $\alpha = \frac{1}{2}\alpha_2 - \alpha_1$  and  $\beta$ , defined earlier by Eq. (4), will also be complex via Eqs. (8).

Next consider two specific cases; first, SHG in GaP with a 1.06- $\mu$  laser. The present data show that  $\alpha_1 \approx 0$ ,  $\alpha_2 \approx 120 \text{ cm}^{-1}$ , and  $\Delta k' \approx 5 \times 10^4 \text{ cm}^{-1}$ . For this case, Eq. (9) can be approximated by

$$E_2 = - \frac{4\pi\epsilon_1^2 d \exp[2i(k_1x_0 - \omega t)]}{(n_2' - n_1)(n_1 + 1)^2(n_2' + 1)} \times \{1 - \beta \exp[i(\Delta k' - \frac{1}{2}\alpha_2)x_0]\}, \quad (10)$$

where  $\beta$  is real. Thus, the main effects of this level of absorption of the second harmonic are to reduce the contrast ratio of the Maker fringes and their amplitudes. For the intensity maxima, which will occur for  $\Delta k'l = N_{\text{odd}}\pi$ , the phase difference between the second harmonic and the fundamental squared emergent from the crystal will be the same as that in the absence of absorption, namely,  $\varphi \pm \pi$ . Therefore, it is seen that with a 1.06- $\mu$  laser, absorption in GaP at the second-harmonic frequency should not introduce any difficulties.

Consider next the case of GaAs, where  $\alpha_1 \approx 0$ ,  $\alpha_2 \approx 4.8 \times 10^4 \text{ cm}^{-1}$ , and  $\Delta k' \approx 6.4 \times 10^4 \text{ cm}^{-1}$ .<sup>27</sup> The free wave, represented by the second term in Eq. (9), is now absorbed so that Maker SHG fringes are not observed and one has to a good approximation,

$$E_2 = - \frac{8\pi\omega\epsilon_1^2 d \exp[2i(k_1'x_0 - \omega t)]}{c(\Delta k' + \frac{1}{2}i\alpha_2)(n_1 + 1)^2(n_2' + 1)}. \quad (11)$$

Therefore, it is expected that the absorption coefficient

of the second harmonic in GaAs will result in a phase shift  $\varphi^a$  in  $E_2$  due to its effect on the index mismatch, where

$$\varphi^a = \tan^{-1}(-\alpha_2/2\Delta k'), \quad (12)$$

or  $\varphi^a \approx -20^\circ$ . In addition to this phase shift, it may be anticipated that  $d$  will be complex for GaAs in this wavelength region.<sup>20</sup>

It should be noted that a crystal with  $\alpha_2 x_0 \gg 0$ , as in the case of GaAs, must be in position  $A$  when comparing two crystals since the harmonic wave from crystal  $A$  has to be transmitted at least in part through crystal  $B$  for the required interference effects to take place.

#### IV. EXPERIMENTAL RESULTS

Table II gives the absolute signs of the  $d$ 's determined in these experiments for the transparent crystals, and the experimental values of the  $\varphi$ 's for the absorbing crystals. The experimental value of  $\varphi$ , namely,  $(\varphi_{ij})_{\text{expt}}$ , is defined by

$$(\varphi_{ij})_{\text{expt}} = \varphi_{ij} + \varphi^a, \quad (13)$$

where the phase shift due to the complex indices of refraction in Eq. (9) is included in  $\varphi^a$  and  $\varphi_{ij}$  is the phase of  $d$ . In preparing Table II, it was assumed that the combined effects of absorption were less than  $2\pi$ .

With every pair of transparent crystals investigated,  $P_2(\text{CO}_2)$  was at an extremum within the experimental uncertainties of the measurement, namely,  $\pm 15^\circ$ , thereby indicating that for these crystals  $\varphi_A - \varphi_B = 0$  or  $\pm\pi$ . Since the  $d$ 's are expected to be real for lossless media, these data show that for the transparent crystals  $\varphi = 0$  or  $\pm\pi$ .

The several crystals investigated which absorbed at the second-harmonic frequency were ZnTe, CdSe, CdTe, GaAs, and GaP. In order to convert the relative sign measurements to an absolute basis, platelets of GaP and/or GaAs, with known  $+[111]$  directions, were used as crystal  $A$ . Comparisons between thin GaP platelets which exhibited Maker fringes and any of the transparent crystals always gave  $\varphi_A - \varphi_B = 0$ , or  $\pi$ , thereby showing that  $d_{14}$  for GaP is also real in this wavelength region. This is not surprising since it was found in these experiments that  $\alpha_2 \approx 120 \text{ cm}^{-1}$  for GaP.

Maker fringes were not observed with GaAs due to absorption at 0.53  $\mu$  as discussed earlier. The present data with GaAs platelets give a phase  $(\varphi_{14})_{\text{expt}} = +15^\circ \pm 15^\circ$  when compared to transparent crystals whose  $d$ 's were positive. A phase of  $+15^\circ \pm 15^\circ \pm \pi$  is ruled out by additional comparisons between GaP and GaAs taking into account that the  $d$ 's are positive for both GaAs and GaP at 10.6  $\mu$ , where they are transparent.<sup>12</sup> Since absorption in GaAs at 0.53  $\mu$  is expected to give a phase shift of  $\varphi^a = -20^\circ$  due to its effect on the complex index mismatch as shown in Eq. (12), it is concluded that for a 1.06- $\mu$  fundamental,  $\varphi_{14} = +35^\circ \pm$

$20^\circ$ , or  $d_{14}(\text{GaAs}) = d_{14}^0(\text{GaAs}) \exp i(35^\circ \pm 20^\circ)$  with respect to the  $+[111]$  direction.

In the case of  $\text{ZnTe}(z)$ , the limited refractive index data<sup>28,29</sup> show that  $\varphi^a$  is of the order of  $0^\circ$  to  $-10^\circ$ , so that  $d_{\text{ZnTe}}$  is most likely positive with a small positive phase shift due to dispersion, namely,  $\varphi_{14}(\text{ZnTe}) \approx 0^\circ$  to  $+10^\circ$ .

Refractive index data for  $\text{CdTe}(z)$  indicate that  $\alpha_2 \sim 6 \times 10^4 \text{ cm}^{-1}$ ,<sup>30</sup> which should in turn produce a phase shift  $\varphi^a$  of about  $-30^\circ$ . Therefore the present data suggest that  $\varphi_{14}$  for  $\text{CdTe}$  can be either  $-\pi+30$ , or  $\pi+30$ .

The data most difficult to analyze for the absorbing crystals are those for  $\text{CdSe}(w)$ . Figure 3 shows a plot of  $P_2$  during the controlled dispersion cycle (described earlier) in a comparison between the  $d_{33}$ 's of  $\text{CdSe}$  and  $\text{ZnO}$ . The two  $+z$  directions were parallel. Since  $P_2(\text{CO}_2)$ , point  $B$  in the figure, is not at an extremum, the relative phase shift is not simply 0 or  $\pm\pi$ . Analysis of these data in the light of Eq. (7), where  $\varphi_{33}$  for  $\text{ZnO}$  is  $\pm\pi$ , shows that  $(\varphi_{ij})_{\text{expt}} = \pi - 44^\circ \pm \pi$  for  $d_{33}$  in  $\text{CdSe}$ . The two publications<sup>31,32</sup> which include relevant refractive index data for  $\text{CdSe}$  are for the present purposes in poor agreement. Furthermore, the present experiments show that  $\alpha_1$  is sufficiently small so that it can be ignored in these experiments, which is in contrast to the published index data.<sup>30</sup> As a result, the present authors are not able to estimate reliably the effects of the complex refractive indices on  $(\varphi_{ij})_{\text{expt}}$ . On the other hand, it seems reasonable to assume that the effects of absorption will be approximately the same for  $d_{33}$  as for  $d_{31}$ , in which case one can conclude that  $d_{31}$  and  $d_{33}$  have opposite signs for  $\text{CdSe}$ , i.e., their phases differ by  $\pm\pi$ .

## V. COMPARISON WITH THEORY

### A. Zinc-Blende Crystals

The electro-dynamical bond-charge model developed by Levine<sup>2</sup> predicts that  $d_{14}$  is positive for the zinc-blende crystals investigated here, and for those measured earlier as well.<sup>11,12</sup> This theory applies to crystals that are essentially nondispersive, that is, transparent at the laser fundamental and harmonic frequencies. The one transparent zinc-blende crystal measured in this study,  $\text{ZnSe}$ , is believed to have a positive  $d_{14}$ ; however, as indicated in Table II, there is no x-ray analysis to relate the absolute structure of the material to its piezoelectric or etching properties. Therefore, it was assumed in preparing Table II that  $\text{ZnSe}$  has a positive piezoelectric coefficient as do other similar II-VI crystals.<sup>33</sup> In addition, the theory of Phillips and Van Vechten predicts a positive piezoelectric coefficient for  $\text{ZnSe}$ .<sup>34</sup> Thus, it is concluded that  $d_{14}$  is positive for  $\text{ZnSe}$  and hence in agreement with the theory of Levine

as are the earlier sign determinations for  $\text{GaP}$ ,<sup>11</sup>  $\text{GaAs}$ ,  $\text{InAs}$ , and  $\text{GaSb}$ .<sup>12</sup>

The two absorbing zinc-blende crystals measured,  $\text{ZnTe}$  and  $\text{CdTe}$ , appear to have positive and negative  $d$ 's, respectively; however, the effects of dispersion on  $\varphi_{14}$  are not known so that a comparison with extant theories is not now possible.

### B. Wurtzite Crystals

Geometrical considerations based on the assumption that the II-VI tetrahedra of the wurtzite structures are undistorted lead to the prediction that for this class of crystals  $\pm 2d_{31} = \mp d_{33}$ ,<sup>1,2</sup> which agrees with the relative signs given in Table II except for  $\text{BeO}$  where  $d_{31}$  and  $d_{33}$  have the same signs. The sign and magnitude of the ratio  $d_{33}/d_{31}$  for  $\text{BeO}$  remain unexplained within the framework of Levine's theories.<sup>2,6</sup> The difficulty is that the calculation of  $d_{31}$  becomes unreliable when there is a near cancellation of the two terms<sup>6</sup> that contribute to the bond nonlinear susceptibility as is the case for  $\text{BeO}$ . Except for  $d_{31}$  for  $\text{BeO}$ , Levine<sup>6</sup> predicts the observed signs for all the transparent wurtzite crystals measured including the reversal in sign of  $d_{33}$  going from  $\text{CdS}$  to  $\text{ZnO}$  and  $\text{BeO}$ . This sign reversal occurs for crystals that contain a first row element, like  $\text{ZnO}$ , in which case the bond charge is off center.

### C. Polar Crystals

The recent theory of Jerphagnon<sup>10</sup> is subjected to a rather stringent test by the present data on polar crystals. Jerphagnon has shown that the vector part of the  $\delta$  form of the nonlinear tensor that describes SHG, namely,  $\delta_{31} + \delta_{32} + \delta_{33}$ , is proportional to the spontaneous polarization  $P_s$ , where  $\delta$  (using the full notation) is defined by<sup>35</sup>

$$d_{ijk} = \delta_{ijk} \chi_{ii}^{2\omega} \chi_{jj}^{\omega} \chi_{kk}^{\omega}. \quad (14)$$

The quantities  $\chi_{ll}$  are the optical susceptibilities  $(n_l^2 - 1)/4\pi$  along the principal index directions  $l$  at frequency  $\omega$  or  $2\omega$  as indicated by the superscript. Jerphagnon finds that<sup>10</sup>

$$\delta_{31} + \delta_{32} + \delta_{33} = -(1.0 \pm 0.3) \times 10^{-7} P_s \text{ esu}, \quad (15)$$

where  $P_s$  is in  $\mu\text{C}$  per  $\text{cm}^2$ . The sign<sup>7</sup> and magnitude<sup>13</sup> of the coefficient of  $P_s$  are determined from experimental data. The crystals  $\text{LiTaO}_3$ ,  $\text{LiNbO}_3$ ,  $\text{BaTiO}_3$ , and  $\text{Ba}_2\text{NaNb}_5\text{O}_{15}$  have been discussed by Jerphagnon<sup>10,36</sup> and are found to substantiate Eq. (15). The wurtzite crystals  $\text{ZnO}$ ,  $\text{BeO}$ , and  $\text{CdS}$  have also been discussed<sup>10,37</sup> by Jerphagnon and are again found to be consistent with Eq. (15) provided that one assumes the direction for  $P_s$  in these materials is that which would result from covalent II-VI bonds. It is of interest to note that Eq. (15) requires  $d_{31}$  and  $d_{33}$  in  $\text{BeO}$  both be negative as is observed. The above assumption may be questioned

in view of the work of Van Vechten<sup>38</sup> who finds the II-VI bonds for the wurtzite crystals in question to be more ionic than covalent.

The two ferroelastic-ferroelectric molybdates,<sup>39</sup>  $Gd_2(MoO_4)_3$  and  $Tb_2(MoO_4)_3$  are of special interest since in each case  $|d_{31}| \approx |d_{32}|$  and  $d_{31}/d_{33} \gg 1$ . In particular,  $|\delta_{32}/\delta_{33}| \approx |\delta_{31}/\delta_{33}|$  is equal to 69 and 56 for  $Gd_2(MoO_4)_3$  and  $Tb_2(MoO_4)_3$ , respectively.<sup>40</sup> Thus the difference between  $\delta_{31}$  and  $\delta_{32}$  must be determined to a precision of about 1% or better to test Eq. (15). The best data on  $Gd_2(MoO_4)_3$  show that  $\delta_{31}/\delta_{32} = -1.006 \pm 0.014$ , and the corresponding quantity for  $Tb_2(MoO_4)_3$  is  $-1.011 \pm 0.014$ . Therefore since  $\delta_{33}$  is -, these data give a negative sign for the sum  $\delta_{31} + \delta_{32} + \delta_{33}$  as required by Eq. (15). The magnitudes of these sums are  $(-0.23 \pm 0.16) \times 10^{-7}$  and  $(-0.26 \pm 0.14) \times 10^{-7}$  esu for  $Gd_2(MoO_4)_3$  and  $Tb_2(MoO_4)_3$ , respectively.<sup>40,41</sup> The value of  $P_s$  for both materials is  $\sim 0.19 \mu C/cm^2$ ,<sup>39</sup> and therefore in agreement with Eq. (15); however, more precise data are clearly desirable.

The directions and magnitudes of  $P_s$  for  $LiIO_3$ ,<sup>9</sup>

$LiGaO_2$ ,<sup>42</sup> and  $LiCHO_2 \cdot H_2O$ <sup>43</sup> are unknown so that comparisons with Eq. (15) are not possible.

#### D. Other Crystals

The sign of + for  $d_{11}$  for left-handed quartz is in agreement with the prediction of Levine when account is taken of the two different ionic radii.<sup>6</sup>

#### ACKNOWLEDGMENTS

The authors would like to express their appreciation to those who so generously supplied high-quality crystals for this research; in particular, A. A. Ballman ( $LiTaO_3$  and  $Ba_2NaNb_5O_{15}$ ), K. Nassau [ $Tb_2(MoO_4)_3$ ], L. G. Van Uitert ( $LiCHO_2 \cdot H_2O$ ), and the Isomet Corp. [ $LiGaO_2$  and  $Gd_2(MoO_4)_3$ ]. The important role of S. Bortas in putting optical finishes on many of the crystals used in these experiments is also gratefully acknowledged. Lastly, it is a pleasure to acknowledge many stimulating and informative discussions with G. D. Boyd, J. Jerphagnon, D. A. Kleinman, B. F. Levine, J. C. Phillips, and S. Singh.

- <sup>1</sup> F. N. H. Robinson, Phys. Letters **26A**, 435 (1968).
- <sup>2</sup> B. F. Levine, Phys. Rev. Letters **22**, 787 (1969).
- <sup>3</sup> S. S. Jha and N. Bloembergen, Phys. Rev. **171**, 891 (1968); IEEE J. Quantum Electron. **4**, 670 (1968).
- <sup>4</sup> C. Flytzanis and J. Ducuing, Phys. Rev. **178**, 1218 (1969).
- <sup>5</sup> J. C. Phillips and J. A. Van Vechten, Phys. Rev. **183**, 709 (1969).
- <sup>6</sup> B. F. Levine, Phys. Rev. Letters **25**, 440 (1970).
- <sup>7</sup> R. C. Miller and W. A. Nordland, Optics Commun. **1**, 400 (1970).
- <sup>8</sup> C. R. Jeggo and G. D. Boyd, J. Appl. Phys. **41**, 2741 (1970).
- <sup>9</sup> C. R. Jeggo, Optics Commun. **1**, 375 (1970).
- <sup>10</sup> J. Jerphagnon, Phys. Rev. B **1**, 1739 (1970).
- <sup>11</sup> D. F. Nelson and E. H. Turner, J. Appl. Phys. **39**, 3337 (1968).
- <sup>12</sup> J. J. Wynne and N. Bloembergen, Bull. Am. Phys. Soc. **14**, 26 (1969); Phys. Rev. **188**, 1211 (1970).
- <sup>13</sup> R. Bechmann and S. K. Kurtz, in *Landolt-Börnstein Numerical Data and Functional Relationships*, edited by K.-H. Hellwege (Springer-Verlag, Berlin, 1969), Vol. 1.
- <sup>14</sup> For example, see D. Coster, K. S. Knol, and J. A. Prins, Z. Physik **63**, 345 (1930).
- <sup>15</sup> For example, see H. C. Gatos and M. C. Lavine, in *Chemical Behavior of Semiconductors*, edited by A. F. Gibson and R. E. Burgess (Spottiswoode, Ballantyne and Co., London, 1965), Vol. 9.
- <sup>16</sup> IRE Committee Report, J. G. Brainerd, Chairman, Proc. IRE **37**, 1378 (1949).
- <sup>17</sup> W. G. Cady, *Piezoelectricity* (Dover, New York, 1964), revised ed., Vol. II, Chap. XXIX.
- <sup>18</sup> For example, see F. Jona and G. Shirane, *Ferroelectric Crystals* (Macmillan, New York, 1962).
- <sup>19</sup> W. L. Faust and C. H. Henry, Phys. Rev. Letters **17**, 1265 (1966).
- <sup>20</sup> R. K. Chang, J. Ducuing, and N. Bloembergen, Phys. Rev. Letters **15**, 6 (1965).
- <sup>21</sup> D. A. Kleinman, Phys. Rev. **128**, 1761 (1962).
- <sup>22</sup> J. A. Armstrong, N. Bloembergen, J. Ducuing, and P. S. Pershan, Phys. Rev. **127**, 1918 (1962).
- <sup>23</sup> P. D. Maker, R. W. Terhune, M. Nisenoff, and C. M. Savage, Phys. Rev. Letters **8**, 21 (1962).
- <sup>24</sup> *International Critical Tables of Numerical Data, Physics, Chemistry and Technology*, edited by E. W. Washburn (McGraw-Hill, New York, 1930), Vol. VII, p. 11.
- <sup>25</sup> R. C. Miller and W. A. Nordland, Appl. Phys. Letters **16**, 174 (1970); **16**, 372(E) (1970).
- <sup>26</sup> R. C. Miller, Phys. Rev. **134**, A1313 (1964).
- <sup>27</sup> H. R. Philipp and H. Ehrenreich, Phys. Rev. **129**, 1550 (1963).
- <sup>28</sup> A. C. Aten, C. Z. van Doorn, and A. T. Vink, in *Proceedings of the International Conference of the Physics of Semiconductors* (The Institute of Physics and the Physical Society, London, 1962), pp. 696-702.
- <sup>29</sup> R. K. Chang, J. Ducuing, and N. Bloembergen, Phys. Rev. Letters **15**, 415 (1965).
- <sup>30</sup> F. H. Pollak, in *II-VI Semiconducting Compounds, 1967 International Conference*, edited by D. G. Thomas (Benjamin, New York, 1967), p. 565.
- <sup>31</sup> M. Cardona and G. Harbeke, Phys. Rev. **137**, A1467 (1965).
- <sup>32</sup> W. L. Bond, J. Appl. Phys. **36**, 1674 (1965).
- <sup>33</sup> G. Arlt and P. Quadflieg, Phys. Status Solidi **25**, 323 (1968).
- <sup>34</sup> J. C. Phillips and J. A. Van Vechten, Phys. Rev. Letters **23**, 1115 (1969).
- <sup>35</sup> R. C. Miller, Appl. Phys. Letters **5**, 17 (1964).
- <sup>36</sup> J. Jerphagnon, Abstracts of the Sixth International Conference on Quantum Electronics, Kyoto, Japan (unpublished).
- <sup>37</sup> J. Jerphagnon and H. W. Newkirk, Appl. Phys. Letters (to be published).
- <sup>38</sup> J. A. Van Vechten, Phys. Rev. **182**, 891 (1969).
- <sup>39</sup> E. T. Keve, S. C. Abrahams, K. Nassau, and A. M. Glass, Solid State Commun. **8**, 1517 (1970).
- <sup>40</sup> R. C. Miller and W. A. Nordland (unpublished).
- <sup>41</sup> The magnitude of  $d_{31} \approx d_{32}$  has been determined by S. Singh and L. G. Van Uitert (private communication).
- <sup>42</sup> R. C. Miller and W. A. Nordland, J. Appl. Phys. **41**, 3008 (1970).
- <sup>43</sup> S. Singh, W. A. Bonner, J. R. Potopowicz, and L. G. van Uitert, Appl. Phys. Letters (to be published).