

Shock launching in silicon studied with use of pulsed x-ray diffraction

J. S. Wark

Laboratory for Laser Energetics, University of Rochester, Rochester, New York 14623

R. R. Whitlock

U.S. Naval Research Laboratory, Washington, D.C. 20375-5000

A. Hauer

Los Alamos National Laboratory, Los Alamos, New Mexico 87545

J. E. Swain and P. J. Solone

Lawrence Livermore National Laboratory, Livermore, California 94550

(Received 16 December 1986)

Multikilobar shocks were launched into a single crystal of (111) silicon coated with 1000 Å of aluminum and a 25- μm transparent plastic layer by irradiation with a 1-nsec pulse of 1.06- μm laser light at 0.8–8 J cm^{-2} . Peak lattice compressions were directly measured and shocked-lattice stresses inferred as a function of irradiance and time by Bragg-diffracting a short (< 100 psec) burst of probing x rays through the shock-launching region. Compressions of up to ~4% were measured, corresponding to stresses of the order of 70 kbar, at irradiances of $\sim 4 \times 10^9 \text{ W cm}^{-2}$.

The laser generation of shocks encompasses a wide range of physical processes and effects,^{1–3} since virtually every property of condensed matter can be altered with pressure. For the more conventional shock-driving mechanisms, the shock-launching region, i.e., the initial layer of compressed material, is obscured by the driving mechanism. While laser-driven shocks do not present this limitation, so far *direct* measurements of the lattice spacing of the impact surface have been intractable. Such measurements are of importance because many physical phenomena not in agreement with classical dislocation theory, such as elastic-plastic interactions, originate at this surface.

In this Rapid Communication we report results of an experiment in which, for the first time, we have probed the initial^{4,5} micrometers of the shock-launching region in a crystal lattice with pulsed x rays, and directly observed the spatial and temporal evolution of lattice compression and subsequent relaxation in one dimension of Bragg x-ray diffractometry. We observe the existence of a range of compressions (lattice spacings) in the launch phase, and have also examined the experimentally determined peak compression as a function of laser irradiance.

The use of x rays to measure the compression of shocked materials was first performed by Johnson, Mitchell, Keeler, and Evans in the early 1970s.⁴ They shocked LiF to several hundred kilobars using conventional explosive techniques,^{5,6} and diffracted a 40–50-nsec pulse of x rays⁷ off the shocked material. However, to our knowledge, the work presented here is the first of a similar nature to be presented since then, with a 500-fold improvement in temporal resolution, and it is the first time that either the spatial or temporal development of the compression within the launch region has been studied directly.

The experiment was performed on the JANUS research laser system at the Lawrence Livermore National Labora-

tory, California. The experimental setup is shown in schematic form in Fig. 1. The shocked targets consisted of 250- μm -thick (111) silicon wafers 5 cm in diameter, the surface of which had been coated first with 1000 Å of aluminum and then with 25 μm of plastic (CH). The motivation for such a target design is explained below. Half of the target was irradiated to a vacuum by a (1 ± 0.05) -nsec pulse of 1.06- μm laser light at an irradiance varying from 0.8 to 8 J cm^{-2} with a beam diameter on target of 3.9 cm. A beam block prevented irradiation of the other half of the target; diffraction from this unshocked region gave us a reference point from which to measure the changes in Bragg angle. After the shock had been launched in the silicon crystal, a second laser beam containing $\sim 10 \text{ J}$ of 0.53- μm light in 100 psec, which was synchronous with known and variable delay with respect to the shock-launching beam, was focused to a ~ 40 - μm -diam spot on a second, calcium-containing target. The

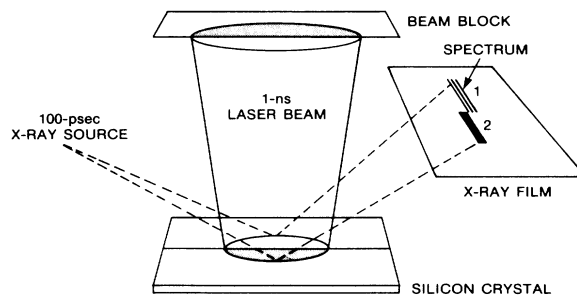


FIG. 1. The experimental setup showing schematically the x-ray diffraction from the (1) unshocked and (2) shocked crystal.

ionized heliumlike calcium x-ray lines thus produced⁸ were Bragg diffracted off the silicon (111) planes and recorded on Kodak SB5 x-ray film. The reduction in x-ray intensity due to passage through the 25- μm plastic overcoat is estimated to be $\sim 35\%$, with a further $\sim 4\%$ reduction due to passage through the aluminum. A single laser shot provided recordable x-ray levels; a series of shots was taken to obtain data at different irradiances and delay times.

Previous experiments at irradiances similar to those used here have shown that uncoated silicon is simply heated by the laser light rather than shocked,⁹ due to the several-millimeter absorption length of 1.06- μm light in silicon at room temperature. The aluminum coating was therefore applied to act as an abrupt absorber to the incident radiation. This effectively prevented the penetration of the laser light into the silicon, and instead produced an aluminum plasma which in turn generates a pressure pulse for driving the shock into the material. Overcoating the aluminum with plastic transparent to 1.06- μm light causes the expanding aluminum plasma to be inertially confined between silicon and plastic, which in turn increases the strength of the shock launched into the silicon. Such overcoating techniques have previously been used to enhance shock pressures in the tens of kilobar range.¹⁰

A set of typical diffraction patterns is shown in Fig. 2. The three lines in the unshocked region are the resonance line (3.177 \AA), the intercombination line (3.193 \AA), and the unresolved j, k dielectronic satellites (3.21 \AA) of heliumlike calcium.⁸ In the shocked region of the crystal, the

lattice spacing d is reduced, increasing the diffraction angle θ in accordance with a differentiation of Bragg's law:

$$\Delta(2d)/2d = -\Delta\theta \cot\theta.$$

This effect can clearly be seen in Fig. 2. Thus a simple measurement of the maximum angular shift gives us a direct measurement of the peak compression of the (111) planes, and knowledge of the distribution of angular shifts yields information on the distribution of (111) lattice spacings within the probed region.

The probe depth of the x rays in such highly strained crystals is determined by the photoelectric absorption coefficient rather than by the extinction length. This is because x rays incident at a particular angle only diffract off that particular region of the crystal at which the lattice spacing is such that the Bragg condition is satisfied; the rest of the crystal up until the point (with slightly different lattice spacings) simply acts as an x-ray filter. A Beer's-law attenuation factor of $1/e$ for the heliumlike calcium lines in silicon corresponds to an x-ray path length of 8.5 μm , or a depth of 4.3 μm below the surface at the Bragg angle. Taking further account of the signal dynamic range we estimate a probe depth of 4–5 μm below the surface.

Diffraction measurements such as those shown in Fig. 2 were made for a variety of levels of irradiance and delay times. We define the laser-beam delay as the interval between the arrival, at chamber center, of the peak of the long (shock-producing) laser pulse followed by the peak of the short (x-ray-producing) laser pulse. The x-ray probe delay was 0.09 nsec greater than the delay between laser beams, due to the setup geometry and time-of-flight considerations. It can be seen from Fig. 2 that at 0.0-nsec delay we still observe diffraction at the original Bragg angle as well as diffraction over a range of angles, corresponding to a range of lattice spacings up to a peak compression of 3.35%. The obvious physical explanation for this is that, at this early time, the shock has not yet penetrated past the maximum probe depth, and we are probing the shock front as well as the as yet unshocked region. The range of lattice spacings represents a spatial strain gradient. For all data collected after this delay time, when the shock was proceeded further into the material, we no longer observe diffraction from the unperturbed crystal.

In Fig. 3 we show the peak change in interatomic spacing of the (111) planes as a function of time for those shots where the average energy density of the shock-producing laser pulse was 4 J cm^{-2} on target (i.e., an average irradiance of $4 \times 10^9 \text{ W cm}^{-2}$). The accuracy of the laser timing may include a constant systematic error estimated to be no more than ± 200 psec; random timing fluctuations were evidently of lesser magnitude. The error bar on the compression measurement primarily results from a consideration of observed effects of laser nonuniformities on the maximum Bragg diffraction angle. [These effects can be seen in Fig. 2(a) as a variation in angular shift in the diffracted radiation.] Other effects, such as intrinsic x-ray linewidth, crystal rocking-curve breadth, and x-ray source broadening, are of considerably lesser importance. A maximum change of the lattice spacing of 3.85% was observed at this energy density, and the data

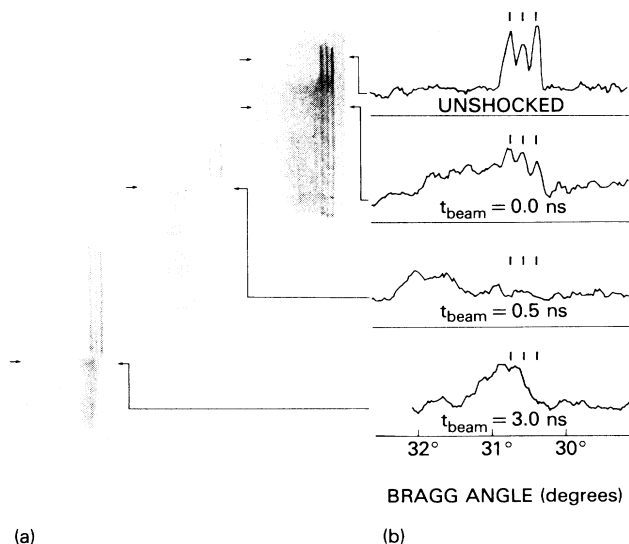


FIG. 2. Diffraction results. (a) X-ray line spectra diffracted from silicon shocked at an incident energy density of $4 \pm 0.3 \text{ J cm}^{-2}$ (an irradiance of $4 \times 10^9 \text{ W cm}^{-2}$) are shown adjacent to reference lines simultaneously diffracted by the unstrained silicon lattice, from a series of beam delays. Each photograph represents a separate shot and beam delay. (b) Densitometer scans, taken at indicated locations through the spectra in (a), are shown for a typical unshocked spectrum, and shocked spectra at 0.0-, 0.5-, and 3.0-nsec beam delays.

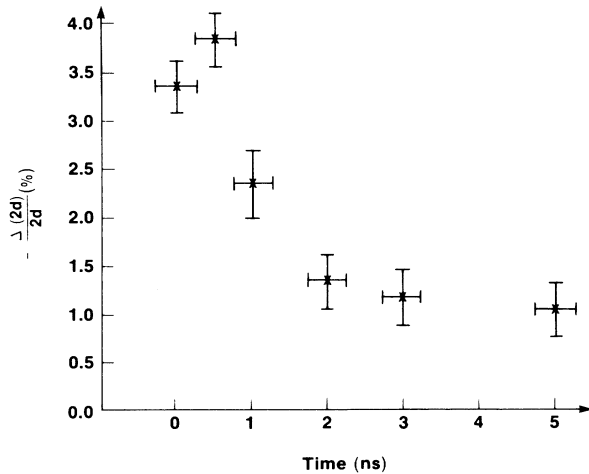


FIG. 3. The measured peak change in interatomic spacing as a function of time for those laser shots with an energy density of $4 \pm 0.3 \text{ J cm}^{-2}$.

are consistent with a pressure pulse with a full width at half maximum (FWHM) of 1 nsec. It can be seen that the rise time of the shock compression is similar to that of the laser pulse. However, after peak compression has been reached, the compression falls off with a far longer decay time than that of the laser. Indeed, even 5 nsec after the peak of the shock-producing pulse, the crystal is still compressed by $\sim 1\%$. At no time did we observe the front-surface density to fall below that of solid. Such inhibition of the rarefaction wave has previously been observed by other diagnostic methods¹¹ (using similar layered targets), and is due to the tamping effect of the plastic.

The Hugoniot elastic limit (HEL) has been reported to occur in (111) silicon at a compression of 2.6%,^{12,13} corresponding to a pressure of about 54 kbar. Following the stress-volume curve of Gust and Royce¹² to the observed 3.85% compression we estimate a peak stress of 67 kbar at an energy density of 4 J cm^{-2} . However, in comparing these results to Hugoniot measurements, it should be borne in mind that we are probing the shock-launching phase, rather than merely observing the arrival of an already steepened shock front. Furthermore, elastic response may extend above the HEL on a transient basis.^{14,15}

Figure 4 shows the experimentally measured peak compressions as a function of irradiance for various probe delay times. The rapid falloff in compression at low irradiances is due to the increased importance of thermal conduction into the silicon at lower irradiances,¹¹ as well as an increase in the fraction of laser energy expended in the latent heat of vaporization of the aluminum.

The technique of pulsed x-ray diffraction from laser-shocked materials opens up several new avenues for the

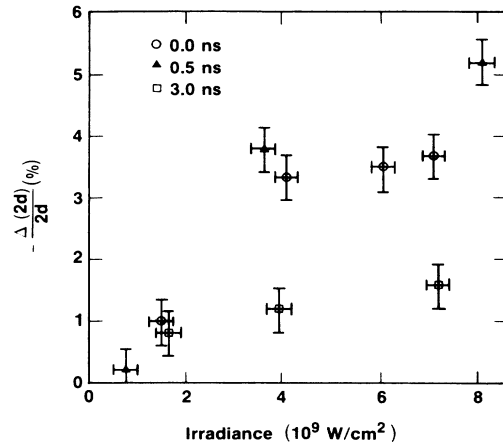


FIG. 4. The peak change in interatomic spacing as a function of irradiance for delay times indicated. The HEL is at 2.6% compression.

study of the transient response of crystal lattices. We have shown here that it is possible to measure one vector component of the strain on the front surface of a shocked crystal. The temporal resolution afforded by this technique, coupled with its ability to probe crystal structure, may allow us to time resolve pressure-induced phase transitions, as well as study possible transient elastic-plastic effects in crystals compressed beyond the HEL.^{14,15} Furthermore, a detailed study of the x-ray reflectivity as a function of angle may yield compression-depth information using methods similar to those developed for studying laser-annealed crystals.^{16,17}

In conclusion, we have directly observed the temporal history of lattice compression within the front surface of a laser-shocked crystal by short-pulse x-ray diffraction. We have observed diffraction from material both in front of and behind the developing shock front at early stages during the laser drive pulse. We have followed the lattice compression to values above the HEL, and further observed the onset of rarefaction as the pressure pulse decayed. Crystallinity was preserved throughout this process.

We acknowledge the encouragement of R. W. Lee and J. D. Kilkenny at Lawrence Livermore National Laboratory (LLNL) and the helpful discussions with P. D. Goldstone at Los Alamos National Laboratory (LANL), D. J. Nagel at Naval Research Laboratory (NRL), and J. W. Forbes at Naval Surface Weapons Center (NSWC). We are grateful for the capable efforts of L. Foreman and P. Gobby and their colleagues at the LANL target fabrication facility. This work was supported by the Sponsors of the Laser Fusion Feasibility Project at the Laboratory for Laser Energetics, and by the Defense Sciences Office of the Defense Advanced Research Projects Agency.

- ¹L. C. Yang, *J. Appl. Phys.* **45**, 2601 (1974).
- ²A. N. Pirri, *Phys. Fluids* **20**, 221 (1977).
- ³B. P. Fairand, B. A. Wilcox, W. J. Gallagher, and D. N. Williams, *J. Appl. Phys.* **43**, 3893 (1972).
- ⁴Quintin Johnson, A. Mitchell, R. Norris Keeler, and L. Evans, *Phys. Rev. Lett.* **25**, 1099 (1970).
- ⁵Quintin Johnson, Arthur Mitchell, and L. Evans, *Nature (London)* **231**, 310 (1971).
- ⁶Quintin Johnson, Arthur C. Mitchell, and L. Evans, *Appl. Phys. Lett.* **21**, 29 (1972).
- ⁷Quintin Johnson and A. C. Mitchell, *Phys. Rev. Lett.* **29**, 1369 (1972).
- ⁸U. Feldman, G. A. Doschek, D. J. Nagel, R. D. Cowan, and R. R. Whitlock, *Astrophys. J.* **192**, 213 (1974).
- ⁹J. G. Lunney, P. J. Dobson, J. D. Hares, S. D. Tabatabaei, and R. W. Eason, *Opt. Commun.* **58**, 269 (1986).
- ¹⁰N. C. Anderholm, *Appl. Phys. Lett.* **16**, 113 (1970).
- ¹¹B. P. Fairand and A. H. Clauer, *J. Appl. Phys.* **50**, 1497 (1979).
- ¹²W. H. Gust and E. B. Royce, *J. Appl. Phys.* **42**, 1897 (1971).
- ¹³Tsuneaki Goto, Toshiyuki Sato, and Yasuhiko Syono, *Jpn. J. Appl. Phys.* **21**, L369 (1982).
- ¹⁴J. R. Asay, G. R. Fowles, G. E. Duvall, M. H. Miles, and R. F. Tender, *J. Appl. Phys.* **43**, 2132 (1972).
- ¹⁵Y. M. Gupta, G. E. Duvall, and G. R. Fowles, *J. Appl. Phys.* **46**, 532 (1975).
- ¹⁶B. C. Larson, C. W. White, T. S. Noggle, J. F. Barhorst, and D. M. Mills, *Appl. Phys. Lett.* **42**, 282 (1983).
- ¹⁷B. C. Larson and J. F. Barhorst, *J. Appl. Phys.* **51**, 3181 (1980).

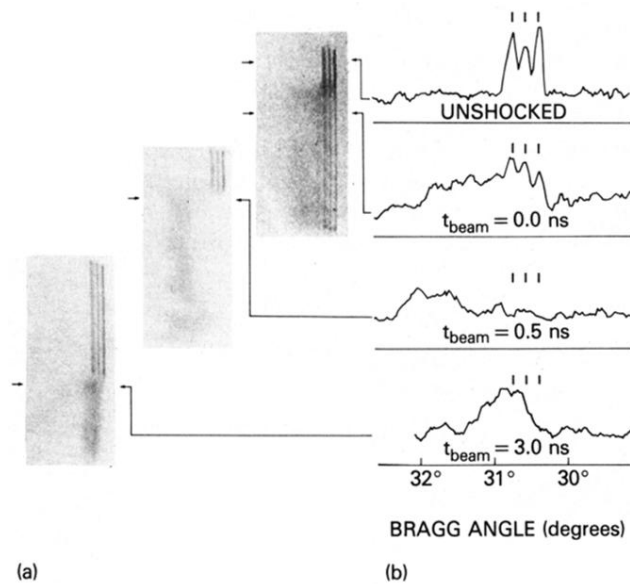


FIG. 2. Diffraction results. (a) X-ray line spectra diffracted from silicon shocked at an incident energy density of $4 \pm 0.3 \text{ J cm}^{-2}$ (an irradiance of $4 \times 10^9 \text{ W cm}^{-2}$) are shown adjacent to reference lines simultaneously diffracted by the unstrained silicon lattice, from a series of beam delays. Each photograph represents a separate shot and beam delay. (b) Densitometer scans, taken at indicated locations through the spectra in (a), are shown for a typical unshocked spectrum, and shocked spectra at 0.0-, 0.5-, and 3.0-nsec beam delays.