

Electronic structure, cohesive, and magnetic properties of the actinide-iridium Laves phases

O. Eriksson

Condensed Matter Theory Group, Department of Physics, University of Uppsala, Box 530, S-75121 Uppsala, Sweden

B. Johansson*

Center for Materials Science, Los Alamos National Laboratory, Los Alamos, New Mexico 87545

M. S. S. Brooks

Commission of the European Communities, Joint Research Centre, European Institute for Transuranium Elements, Postfach 2340, D-7500 Karlsruhe, Federal Republic of Germany

H. L. Skriver

Laboratory of Applied Physics, Technical University of Denmark, DK-2800 Lyngby, Denmark

(Received 3 October 1988)

The electronic structure of the isostructural $A\text{Ir}_2$ systems ($A = \text{Th}, \text{Pa}, \text{U}, \text{Np}, \text{Pu}, \text{and Am}$) has been obtained by means of the scalar relativistic and fully relativistic linear muffin-tin orbital techniques. Ground-state properties such as lattice constants and onset of magnetic order have been calculated and compared with measured data. The hybridization between the actinide $5f$ and the ligand $5d$ states and the direct $5f$ wave-function overlap are found to be of comparable importance for the bandwidth of the itinerant $5f$ states. The anomalous paramagnetism of PuIr_2 can be explained only by a fully relativistic treatment.

I. INTRODUCTION

The $A\text{Ir}_2$ ($A = \text{Th}, \text{Pa}, \text{U}, \text{Np}, \text{Pu}, \text{Am}, \text{and Cm}$) series of intermetallic compounds exhibits many interesting physical properties. It is found that ThIr_2 becomes superconducting below 6.5 K.¹ UIr_2 is a nearly temperature-independent paramagnet, with a small maximum in the magnetic susceptibility at 60 K.² The coefficient of the linear contribution to the specific heat γ is high (62 mJ/mol K²) (Ref. 3) and the resistivity shows a T^2 dependence at low temperatures.² These two facts have been taken to be an indication of spin-fluctuation effects in UIr_2 .² NpIr_2 is the first compound in the $A\text{Ir}_2$ series to order magnetically. Mössbauer experiments indicate that it is an antiferromagnet with an ordering temperature of 5.8 K (Ref. 4) or 7.5 K (Ref. 5) and the measured hyperfine field corresponds to a magnetic moment of $0.6\mu_B$.^{4,5} A maximum in the susceptibility was found at 7.5 K,⁵ but the specific heat showed a maximum at a somewhat lower temperature, indicating that the Néel temperature is 6.6 K.⁶ The small moment together with a low magnetic entropy of $0.38R \ln 2$ suggest that NpIr_2 is an itinerant antiferromagnet.^{5,6} The measured coefficient of the linear contribution to the specific heat γ is very high in the antiferromagnetic phase (400 mJ/mol K²) and an extrapolation for the paramagnetic phase gives a γ value of 234 mJ/mol K². The next compound PuIr_2 is a temperature-independent paramagnet^{7,8} and the resistivity shows a temperature dependence of the form $\rho = \rho_0 + BT^3$. The T^3 dependence was argued to be characteristic of s - f interband scattering.⁷ Finally, to the authors knowledge, only the lattice constants are known for AmIr_2 and CmIr_2 .

Since the $A\text{Ir}_2$ systems are isostructural and crystallize

in the relatively simple, cubic Laves phase ($C15$), they are attractive for theoretical studies. Here as in many other intermetallic compounds involving $5f$ states, there is strong evidence that the $5f$ electrons play a crucial role both for the chemical bonding⁹ and the magnetic properties.¹⁰ The paramagnetic behavior of PuIr_2 appears particularly anomalous since the preceding system NpIr_2 is an antiferromagnet and UIr_2 shows spin-fluctuation effects. Conventional ideas about $5f$ band narrowing as one proceeds along the actinide series would suggest even more pronounced magnetism for PuIr_2 than for NpIr_2 .

In the present work we report on *ab initio* energy-band calculations for the $A\text{Ir}_2$ series. We have performed both paramagnetic and spin-polarized equation of state calculations in order to elucidate the nature of the chemical bonding and the magnetism in the $A\text{Ir}_2$ systems. Special attention was paid to the anomalous nonmagnetic state of PuIr_2 . To understand its properties we have performed fully relativistic calculations and have found it illustrative to compare these calculations with similar calculations for UIr_2 and NpIr_2 . The role of the $5f$ bonding in these systems has also been studied in more detail using a simplified model of the densities of states and this model can also serve as a basis for the understanding of the role of hybridization of the actinide $5f$ states with the Ir $5d$ states in these systems.

The problem of localized versus itinerant $5f$ electrons in actinide metals and compounds is an old and fascinating one, and we will here consider this problem for the $A\text{Ir}_2$ systems drawing special attention to the bonding nature of itinerant $5f$ electrons. In the formation of $5f$ bonds in actinide compounds hybridization has been shown to be of crucial importance¹¹⁻¹⁵ as has the influence of the direct overlap between the $5f$ wave func-

tions.¹⁶ The latter effect forms the basis for the interpretation of the so-called Hill plots.¹⁷ For all $A\text{Ir}_2$ systems up to AmIr_2 the A - A spacing is lower than, or at the border of, the Hill limit for $5f$ localization indicating that the $5f$ electrons are itinerant for all the $A\text{Ir}_2$ compounds with the exception of AmIr_2 and CmIr_2 (and the compounds beyond these two), in which they are localized.

In the computation of the electronic structure of the $A\text{Ir}_2$ compounds, scalar and fully relativistic linear muffin-tin orbital energy-band calculations in the atomic-sphere approximation with the combined correction terms¹⁸ were performed. The frozen core approximation was used and the valence charge density was iterated until it was self-consistent with a maximum error in the valence charge density being of the order of one part into 10^3 at each point of the radial mesh ($\Delta\rho < 10^{-3}\rho$, ρ denotes density). The local spin-density approximation, with the von Barth-Hedin exchange and correlation potential¹⁹ was adopted. The energy bands were first calculated at 20 k points in the irreducible wedge of the Brillouin zone (BZ) and then for the final convergence at 89 k points. The energy bands and the ground-state properties (pressure, occupation number, and magnetic moment) were almost the same for these two calculations. Lattice parameters were obtained from the zero-temperature equation of state calculation.²⁰

In Sec. II we present our results of the cohesive properties and in Sec. III we report on spin-polarized calculations. Section IV contains results of relativistic calculations and in Sec. V we present a model calculation for UIr_2 . Conclusions are given in Sec. VI.

II. COHESIVE PROPERTIES

According to Vegard's law the volume of the unit cell of the compound is obtained by an appropriate sum of the metal atom volumes.²¹ We have plotted these expected compound volumes together with the measured ones in Fig. 1. Although Vegard's law is often obeyed, here the disagreement is apparent. The reason for this is two-fold.

(a) It is for the compounds where we expect no or little $5f$ bonding, i.e., ThIr_2 , AmIr_2 , and CmIr_2 , that the mea-

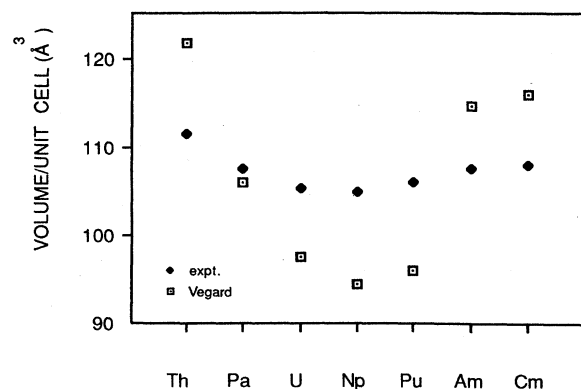


FIG. 1. Experimental volumes and volumes calculated from Vegard's law for the $A\text{Ir}_2$ systems.

asured volume is lower than predicted by Vegard's law. This reflects the large-energy gain due to the formation of the compound. This compound bonding contracts the lattice and the effect is largest for the formation of compounds between late and early transition metals, where the bonding orbitals can be filled and the antibonding orbitals left empty. For ThIr_2 this volume contraction is 9.9 \AA^3 and for AmIr_2 and CmIr_2 it is about 8.0 \AA^3 . The number of d electrons for Ir is 7.4 and Th, being tetravalent, has 1.9 d electrons whereas Am and Cm have 1.2 d electrons each. Hence, upon formation of the compound, ThIr_2 can with $2 \times 7.4 + 1.9 = 16.7$ d electrons nearly fill its bonding d band (which has the capacity to contain 20 electrons) and in AmIr_2 and CmIr_2 , with 16.0 d electrons, the bonding d band is also nearly full. The volume contraction effect should, however, be a little less here, as compared to ThIr_2 , and this is indeed so.

(b) In sharp contrast to this, for the systems with a strong indication of having bonding $5f$ electrons, the experimental volumes exceed Vegard's law volumes. We explain this apparent paradox by the difference between the $5f$ bonding in the pure actinide metal and the corresponding $5f$ bonding in the intermetallic compound. The electronic pressure the $5f$ electrons contribute, can, in the simplest approximation, be divided into two components.^{20,22,12,9} One is called the band center term and is in the actinide metals and in the $A\text{Ir}_2$ systems repulsive. The other term which is called the bandwidth term is negative (bonding) and dominates in these systems. It can, in its simplest form, be written

$$(3pV)_f = -n_f(14-n_f) \frac{W}{28} \left[-\frac{\partial \ln W}{\partial \ln S} \right], \quad (1)$$

where W is the bandwidth, S is the Wigner-Seitz radius, and n_f is the partial $5f$ occupation number. As has been noted elsewhere²³ the number of $5f$ electrons is about the same in the metal as in an intermetallic compound (Table I), and an estimate of $-\delta \ln W / \delta \ln S$ is $2l+1=7$ for f states.¹² Therefore the $5f$ pressure will change, when going from a metal to a compound, only if the bandwidth W changes. For example, we calculate the $5f$ bandwidth in UIr_2 to be 0.2 Ry whereas it is 0.3 Ry in uranium metal.

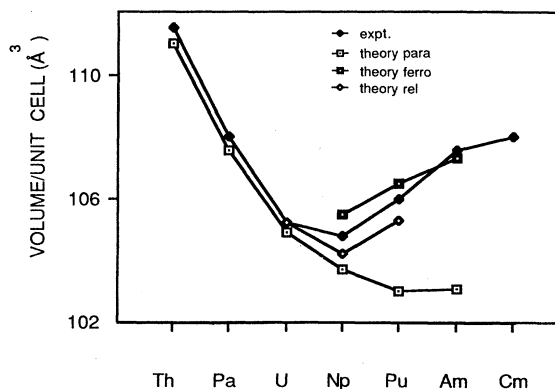


FIG. 2. Experimental and theoretical (scalar relativistic, spin-polarized scalar relativistic, and fully relativistic) volumes for the $A\text{Ir}_2$ systems.

TABLE I. Self-consistently calculated actinide $5f$ occupation numbers, n_f ; magnetic moments, m_{tot} ; multiband Stoner products, ID ; relativistic Stoner product, $ID(\text{relativistic})$; and band masses, μ_f , for the $A\text{Ir}_2$ systems. Also given are the band center term, $(pV)_C$, and the bandwidth term, $(pV)_W$, from Eq. (2).

	ThIr ₂	PaIr ₂	UIr ₂	NpIr ₂	PuIr ₂	AmIr ₂
n_f	0.8	1.7	2.9	4.0	5.2	6.3
$(3pV)_C$ (Ry)	0.21	0.10	0.07	0.06	0.05	0.04
$(3pV)_W$ (Ry)	-1.06	-1.08	-1.15	-1.10	-0.96	-0.87
ID	0.15	0.22	0.89	2.80	1.97	3.06
$ID(\text{relativistic})$					0.6	
m_{tot} (μ_B)				2.70	4.50	5.80
μ_f	8.71	13.68	17.03	19.95	23.08	26.16

Thus, there is a significant reduction of the $5f$ bonding in the compound as compared to the actinide metal, which is due to this band narrowing effect. This volume expansion due to the relative loss of $5f$ bonding is greater than the volume contraction due to $6d-5d$ bonding in the compound. Therefore for systems with itinerant $5f$ electrons both in the metal and in the intermetallic compound, Vegard's law underestimates the volumes.

Of course, for a quantitative theoretical description of the lattice constants, we require *ab initio* equation of state calculations and the result of our calculations are shown in Fig. 2 together with the experimental data. Here we have plotted the volumes obtained from a paramagnetic calculation together with the volumes from a spin-polarized and a fully relativistic (but nonpolarized) calculation. The general agreement between experiments and the calculated paramagnetic volumes is good up to PuIr₂ where there is a clear difference between the measured and calculated volume. In the next compound, AmIr₂, the disagreement is even larger. Neglecting for the moment these two discrepancies we notice that the experimental parabolic trend in volume for the early $A\text{Ir}_2$ systems is well reproduced.

To understand this trend, and especially the role the $5f$ electrons play, we have plotted the self-consistently obtained $5f$ partial pressure for the $A\text{Ir}_2$ systems from a paramagnetic calculation in Fig. 3. These pressures were all taken from a fixed volume (chosen to be 106 \AA^3) in the calculations, to consistently observe the trends in the $5f$

bonding. As can be seen from Fig. 3 the paramagnetic $5f$ pressure indeed shows a parabolic behavior with a maximum contribution for UIr₂. This is the result of essentially three effects, namely, (a) the filling of the $5f$ band, (b) the variation of the $5f$ bandwidth, and (c) the hybridization with the ligand states. The first effect causes the product $n_f(14-n_f)$, in Eq. (1), to have its maximum for $n_f=7$ and it is the reason for the parabolic trend in the volumes of the transition metals^{20,24} and the actinide metals.²⁵ However, for a fixed volume of the $A\text{Ir}_2$ series, incomplete screening of the extra added $5f$ electron, when the atomic number of the actinide is increased (in going, for example, from UIr₂ to NpIr₂), contracts the $5f$ wave function and the $5f$ band becomes more narrow (in Table I this is reflected in the increasing value of the band mass μ_f). Therefore the maximum in bonding $5f$ pressure is moved from $n_f=7$ (Cm) to somewhere between uranium and neptunium. This is in fact similar to the trend the $5f$ pressures show in the A metals calculated for a fixed common volume. This second effect is, however, often completely compensated by the band broadening due to the contraction of the lattice when we occupy bonding orbitals. The third effect originates from the hybridization between actinide $5f$ and ligand d (or p) states and it has earlier been explained to account for the minimum of the lattice constant at UN in the AN series.¹²

Sometimes it can be useful to calculate the equation of state by means of a more transparent but less accurate expression than Pettifor's full pressure formula.²⁰ This is the first-order pressure expression^{20,22,12,9} and we will use it here to ease the interpretation of the different contributions to the chemical bonding. Using this expression the partial pressure divides into a band center term and a bandwidth term and it can be written

$$(3pV)_1 = n_1 \left[\frac{-\partial C_1}{\partial \ln S} \right] + n_1 (E_1 - C_1) \left[-\frac{\partial \ln W_1}{\partial \ln S} \right]. \quad (2)$$

Here E_1 is the center of gravity of the occupied part of the 1 band and C_1 is the center of this band. The $5f$ partial pressure from Eq. (2) has been calculated and is plotted in Fig. 3. In Eq. (2) the first term (called the band center term) is found to be 0.2 Ry for ThIr₂ and to decrease continuously to a value of 0.04 Ry in AmIr₂ (Table I). Hence we find that it is the second term (called the bandwidth term) that dominates in these systems and

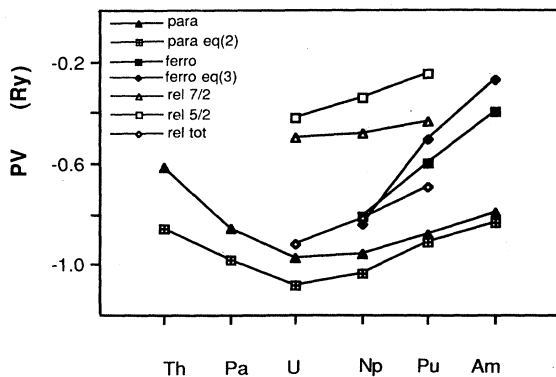


FIG. 3. Actinide $5f$ partial pressure (scalar relativistic, spin-polarized scalar relativistic, and fully relativistic) for the $A\text{Ir}_2$ systems at the constant volume 106 \AA^3 .

that it causes the $5f$ partial pressure and consequently the volumes to have a parabolic trend (Table I). Also the agreement using Eq. (2) as compared to the full pressure formula²⁰ is good.

In order to get a general picture of the band structure for a whole series of compounds it can be illustrative to estimate the bandwidth and band positions using the bottom, center, and top band parameters.^{18,20} These have been plotted in Fig. 4 and give a rough picture of the energy band structure (at the constant volume 106 \AA^3). According to this model the electronic structure of ThIr_2 consists of a broad d band cut by the Fermi energy (E_F) at the upper part of this band. Above E_F there is a fairly broad $5f$ band (bandwidth 0.35 Ry), but this band is unoccupied and thorium behaves as a normal tetravalent element like Ti, Zr, or Hf. In the other compounds of the $A\text{Ir}_2$ series both the d -band width and the position are more or less invariant. The major changes occur in the $5f$ band which becomes more narrow and whose energy is lowered relative to E_F . Hence PaIr_2 is the first compound with $5f$ bands below E_F (this is found in the actinide metals as well and also in compounds^{12,9}) and the $5f$ bandwidth is 0.2 Ry. For the systems UIr_2 up to AmIr_2 the $5f$ band is pinned to E_F lowering its energy just enough to add approximately one electron per A atom with increasing atomic number. Here the effect of incomplete screening can also be seen since the bandwidth gradually becomes narrower and in AmIr_2 its width is reduced to 0.1 Ry.

We conclude this section by remarking that the above presented simplified model of the density of states (DOS) is close to those shown in Fig. 5. These latter DOS's are computed from the eigenvalues in the BZ self-consistently and consequently contain the detailed band-structure information, especially hybridization effects. These hybridization effects are the reason for the long tail of the $5f$ DOS which extends quite far into the $5d$ band, and it is these tails of the DOS that causes the $5f$ count

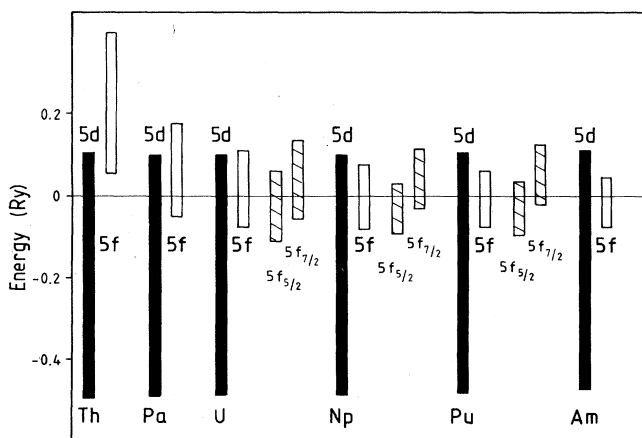


FIG. 4. Schematic picture of the electronic structure of the $A\text{Ir}_2$ systems (for details see text). Solid rectangles are the Ir d states, open rectangles are the A f states, and dashed rectangles are the A $5f_{5/2}$ and the A $5f_{7/2}$ states.

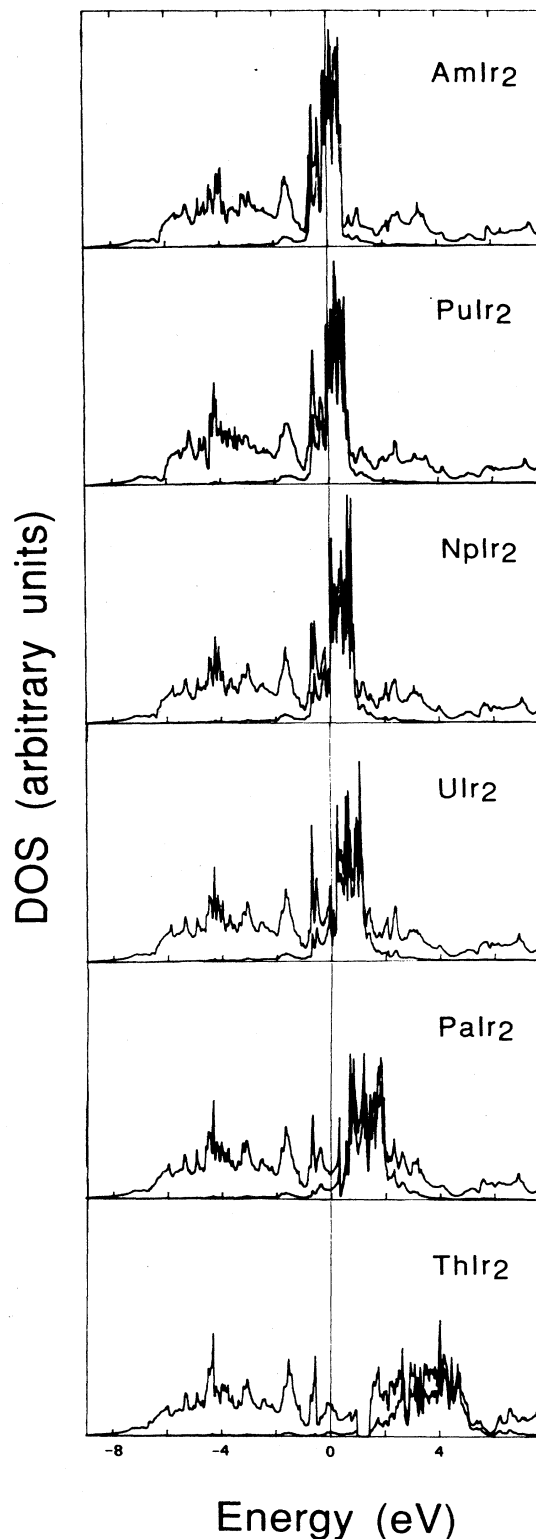


FIG. 5. Calculated densities of states (DOS) for the $A\text{Ir}_2$ systems. In each panel the upper curve is the total DOS and the lower is the A $5f$ partial DOS.

to be about 0.8 in ThIr_2 instead of zero as in the schematic model above. Otherwise the width of the $5d$ and $5f$ bands, as well as their positions, are more or less the same as in Fig. 4.

III. SPIN-POLARIZED CALCULATIONS

The Stoner product $ID(E_F)$ for all compounds [calculated as explained in detail in Ref. 26; I is the Stoner exchange parameter and $D(E_F)$ is the total DOS at the Fermi energy] was calculated for the paramagnetic state. From Table I we notice that for ThIr_2 and PaIr_2 the Stoner product is low (as is normal for Th and Pa and their compounds^{12,9}) but for UIr_2 the Stoner product is 0.89 at the experimental volume. This high value is in full agreement with the suggestion² of spin fluctuations being present in this system.

However, for NpIr_2 the Stoner product is larger than one and for a ferromagnetic spin ordering the self-consistently calculated spin moment in NpIr_2 is $2.7\mu_B$ per formula unit. This large moment gives rise to large magnetovolume effects and brings the theoretical lattice constant into rather good agreement with experiment. The absolute value of the magnetic moment is, however, in bad agreement with the experimental value. The reason for this is most likely the large orbital contributions to the total magnetic moment one encounters when dealing with $5f$ band magnetism.¹⁰ In the light actinides the orbital moment is coupled antiparallel to the spin moment and therefore it reduces the magnitude of the total moment. Still the large intrinsic spin magnetism reduces the $5f$ pressure and in order to quantify this reduction we have used Eq. (2) but allowed for spin polarization. The bandwidth term then becomes^{20,22,12,9}

$$(3pV)_f^{\text{pol}} = (3pV)_f^{\text{para}} \{1 - m_f^2 / [14n_f(1 - n_f/14)]\}, \quad (3)$$

where m_f is the spin polarization of the $5f$ electrons. Thus a $5f$ spin moment will reduce the $5f$ contribution to the bonding as compared to the paramagnetic state. For NpIr_2 this reduces the $5f$ contribution to the chemical bonding by about 40% and the theoretical lattice constant from this calculation is actually somewhat larger than the experimental one (Fig. 2). In PuIr_2 a substantial $5f$ spin moment also developed when we allowed for spin polarization (Table I). Finally in AmIr_2 the $5f$ spin moment almost saturates, filling the spin-up band and strongly reducing the $5f$ bonding pressure. This causes a dramatic change in the chemical bonding of the $5f$ electrons. It has previously been suggested that a completely spin-polarized situation for a half-filled band system can account for the localization of the $5f$ electrons^{27,22,12,9} and we make the same interpretation here. Therefore the good agreement between the calculated spin-polarized and the experimental volume in Fig. 2 is consistent with a localized $5f^6$ configuration in AmIr_2 .

In Fig. 3 we have plotted the partial $5f$ pressure from the spin-polarized calculations of NpIr_2 , PuIr_2 , and AmIr_2 both as obtained from the full pressure formula²⁰ and from Eq. (3). Here the large effect the magnetic moment has on the bonding pressure in Eq. (3) becomes clear and when, for a half-filled band, the spin polarization is complete, Eq. (3) gives a zero contribution. The

reason we get a nonzero although small pressure from Eq. (3) for AmIr_2 can be traced back to the 0.2 $5f$ electrons being present in the spin-down band. For the spin-polarized calculations, as well as the paramagnetic calculations, the simple model in Eqs. (2) and (3) gives a good understanding of the chemical bonding. We conclude this section by noting that the spin-polarized calculations account very well for the volumes of NpIr_2 and AmIr_2 but that the moment of the Np site in NpIr_2 is overestimated, although this is most likely mainly due to our neglect of the spin-orbit coupling. The nonmagnetic state of PuIr_2 could, however, not be explained in the calculations and this problem will be addressed below.

IV. RELATIVISTIC EFFECTS

Although the calculations described above contain the important relativistic mass velocity term and the Darwin shift, they do not include the spin-orbit term which is less important for other than magnetic properties. This can however, as we have shown elsewhere, sometimes be too crude an approximation.^{10,28,29} Therefore we shall now describe the results of fully relativistic calculations for UIr_2 , NpIr_2 , and PuIr_2 . By "fully relativistic" we mean that we solve the Dirac equation and the relativistic band-structure problem self-consistently.^{30,28} The difference between these calculations and the scalar-relativistic calculations is essentially the inclusion of the spin-orbit coupling although that is not explicit in the formalism. The equilibrium volumes obtained from these calculations are plotted in Fig. 2, whereas the partial $5f$ pressures divided into the $5f_{5/2}$ and $5f_{7/2}$ parts are plotted in Fig. 3. It is clear from Fig. 2 that the change in volume due to spin-orbit coupling is small for UIr_2 and NpIr_2 . In PuIr_2 , however, the effect is already quite substantial and the calculated volume is actually brought into good agreement with experiment. The reason for this is that in PuIr_2 the $5f_{5/2}$ and the $5f_{7/2}$ bands are split apart by spin-orbit coupling so much that the $5f_{5/2}$ occupation number by far exceeds that of the $5f_{7/2}$ band. Consequently the $5f_{5/2}$ band is almost filled whereas the $5f_{7/2}$ band is almost empty, strongly reducing the partial $5f$ electronic pressure. In order to demonstrate the spin-orbit effect more clearly we have in Fig. 4 plotted the estimated bandwidths and band positions from the bottom, center, and top band parameters obtained from the fully relativistic calculations. A convenient measure of the importance of spin-orbit coupling is the ratio $R_2 = n_{j=1-1/2} / n_{j=1+1/2}$.^{28,9} We show the values of this ratio^{28,9} for the pure elements U, Np, and Pu together with our present values for UIr_2 , NpIr_2 , and PuIr_2 in Fig. 6. Here it can be seen that the effect of spin-orbit coupling is much larger in the AIr_2 compounds than for the pure actinide metals, which is due to narrower $5f$ bands in the compounds. It can also be seen that for the PuIr_2 system this ratio becomes very large, demonstrating strong effects of spin-orbit coupling for this compound.

We now turn to the interesting nonmagnetic state of PuIr_2 which we could not account for by using the scalar relativistic calculations. In this case the computed Stoner product was 1.9 and consequently the system will become spin polarized. In the same manner as described else-

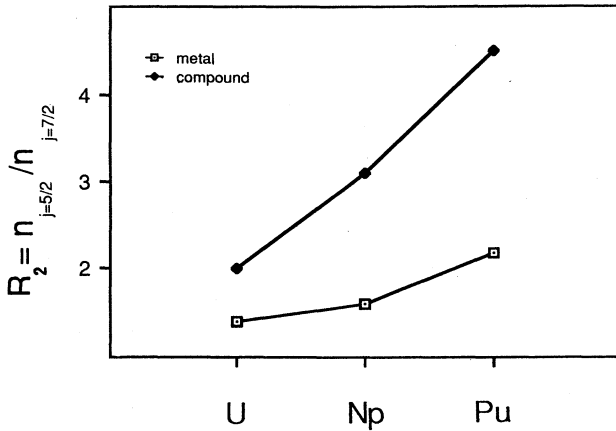


FIG. 6. Calculated ratio between the $A 5f_{5/2}$ and the $A 5f_{7/2}$ occupation numbers for the AIr_2 systems and the A metals (Ref. 28).

where³¹ we obtained the value of the relativistic Stoner product from the fully relativistic calculation. This value is 0.6, which is a dramatic reduction as compared to normal multiband Stoner theory.²⁶ Hence the strong spin-orbit coupling in $PuIr_2$ suppresses magnetism and ex-

plains the observed temperature-independent paramagnetism. This effect was earlier argued to account for the nonmagnetic state of δ -Pu (Ref. 32) and also here it accounts for the nonmagnetic state of $PuIr_2$. In earlier calculations of this type³¹ we have found that it is for systems where the spin-orbit coupling creates a dramatic reduction of the DOS at the Fermi level that a large reduction of the Stoner product takes place. In the most extreme cases, the spin-orbit splitting of the $5f$ band can even give rise to an energy gap and be accompanied by semiconducting properties, whereas a scalar relativistic treatment would predict spin ordering.²⁹ Examining the DOS at the Fermi level for the AIr_2 systems we find that it is only for $PuIr_2$ that a substantial reduction takes place and therefore we have only performed the cumbersome calculation of the relativistic Stoner product for this compound. Finally, in Fig. 7, we have plotted the DOS from our fully relativistic calculation for UIr_2 , $NpIr_2$, and $PuIr_2$. Here as well as in Fig. 4 and Fig. 6 the effect of the spin-orbit coupling is clear and the $5f_{5/2}$ and the $5f_{7/2}$ states are rather well separated. The spin-orbit splitting in UIr_2 is 0.9 eV, in $NpIr_2$ it is 1.0 eV, and finally it is 1.2 eV in $PuIr_2$. This is comparable to the actinide $5f$ bandwidths in these systems. Apart from these spin-orbit splittings the similarity with the scalar-relativistic calculations is striking (Fig. 5).

V. MODEL CALCULATION FOR THE AIr_2 SYSTEMS

We will now describe a more detailed semianalytic investigation of the different contributions to the band structure in the present compounds. Such an exercise is especially interesting in these systems since the direct overlap between the $5f$ wave functions is quite large and at the same time hybridization effects are substantial.

The bandwidth can, neglecting hybridization, be written as^{22,11,12,9}

$$W_{tl} = [(12/N_{tl})S_{tl}^{t/2}]^{1/2}\Delta_{tl} \quad (4)$$

Here Δ_{tl} is

$$\Delta_{tl} = 1/[\mu_{tl}s_t^2(s/s_t)^{2l+1}] \quad (5)$$

and $N_{tl} = (2l+1)n_t$, where n_t is the number of type t atoms per primitive cell and l is the angular momentum. Furthermore $S_{tl}^{t/2}$ is the second moment of the canonical tl band, s_t is the atomic radius of atom t , and s is a characteristic radius for the lattice.^{22,11,12,9,33} Using these expressions and evaluating moments for the cubic Laves phase, an estimate of the canonical bandwidths of, for example, the UIr_2 compound yields a 0.5 Ry broad Ir d band and a U f band of width 0.1 Ry. This Ir d bandwidth is in excellent agreement with the ones calculated including hybridization (Fig. 5). For the U $5f$ states, however, only 50% of the total bandwidth can be accounted for, when hybridization is neglected. Hence hybridization with the Ir d states is of equal importance for the width of the $5f$ states as the direct overlap between the $5f$ wave functions. A good measure of the hybridization is the number of tl electrons that reside in what unhybridized is a pure $t'l'$ band, i.e., $N_{tl}^{t'l'}$. This can be calculated using

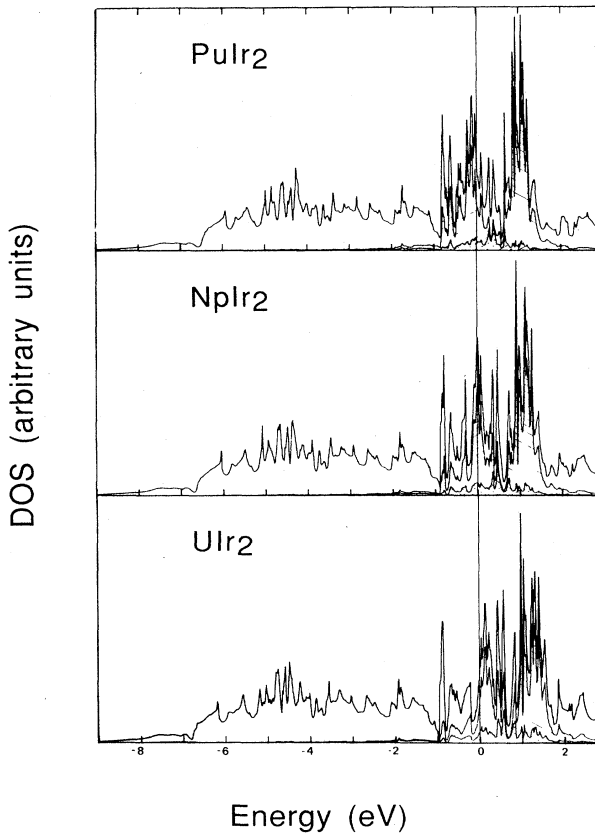


FIG. 7. Calculated total, $A 5f_{5/2}$ and $A 5f_{7/2}$ DOS for the AIr_2 systems. The $5f_{5/2}$ and $5f_{7/2}$ bands are hatched by differently tilted lines, with the $5f_{7/2}$ band being highest in energy.

TABLE II. Second moments of the structure constants for the Laves phase structure. Also given is the Ir d band mass and the number of actinide $5f$ electrons residing in the iridium $5d$ band, calculated from Eq. (6).

$S_{Ir d}^{Ir d^2}$	1180
$S_U^U f^2$	80
$S_{Ir d}^U f^2$	264
$\mu_{Ir d}$	4.6
$N_{Ir d}^{Th f}$	0.91
$N_{Ir d}^{Pa f}$	0.74
$N_{Ir d}^U f$	1.1
$N_{Ir d}^{Np f}$	1.2
$N_{Ir d}^{Pu f}$	1.2

$$N_{tl}^{t'l} = 2S_{tl}^{t'l^2} \Delta_{tl} \Delta_{t'l'} (C_{tl} - C_{t'l'})^{-2}. \quad (6)$$

Here C_{tl} and $C_{t'l'}$ are the center of bands for the tl and $t'l'$ band, respectively. Armed with Eq. (6) we can now easily calculate the strength of the hybridization, i.e., the number of actinide $5f$ electrons that are hybridized into an originally pure iridium $5d$ band, for the different compounds in the AIr_2 systems. These values are given in Table II, and we notice that the 0.8 $5f$ electrons found in $ThIr_2$ are entirely located in what was originally a pure Ir $5d$ band. When the actinide atomic number increases the difference between C_f and C_d decreases and consequently $N_{Ir d}^A f$ is expected to increase. However Δ_f is decreasing along the series and this decreases $N_{Ir d}^A f$. Since these two effects to a large extent cancel this value is almost constant from UIr_2 to $PuIr_2$ (Table II). Also hybridization pushes the two pure tl and $t'l'$ bands apart by an amount

$$\delta E_{tl} = \frac{1}{N_{tl}} S_{tl}^{t'l^2} \Delta_{tl} \Delta_{t'l'} (C_{tl} - C_{t'l'})^{-1}. \quad (7)$$

Inserting appropriate numbers, for instance, for UIr_2 we find that the iridium $5d$ band is pushed down by 6 mRy and the uranium $5f$ band is pushed up by 8 mRy.

VI. CONCLUSION

By using *ab initio* energy band calculations we have obtained a detailed picture of the electronic structure, magnetic properties, and equilibrium volumes for the AIr_2 systems. Good agreement was found both for the occurrence of magnetism and the equilibrium volumes. In accordance with experiment we find that $NpIr_2$ is the only compound that orders magnetically. The paramagnetism of $PuIr_2$ can only be understood from a fully relativistic treatment. Special attention to hybridization effects have also been given and it is shown that the $5f$ bandwidth originates almost equally from the $5f$ wave function overlap as from hybridization between the $5f$ and the ligand $5d$ states.

Also the problem of localization has been addressed by means of spin-polarized calculations, where an almost completely spin-polarized and close to half-filled band situation was found in $AmIr_2$. We ascribe this to a localized $5f^6$ ground state in $AmIr_2$ and this compound is consequently the first localized AIr_2 system. It is interesting to note that the calculations reproduce the experimentally observed volume jump between $PuIr_2$ and $AmIr_2$. This is also the case for the pure actinides with a dramatic volume change between Pu and Am.^{25,27} This success of the local-density approximation (LDA) seems to be in contrast to the rather poor results for conventional mixed valence systems like SmS.³⁴ The main difference is that for the present actinide systems the change is from a bonding to a nonbonding situation for the $5f$ electrons, while the mixed valence in SmS involves two different nonbonding configurations $4f^6$ and $4f^5$. The difficulty to simultaneously deal with two localized configurations is probably the reason why LDA calculations so far have met with rather limited success for conventional mixed valence systems.

ACKNOWLEDGMENTS

O. Eriksson is grateful to The Bank of Sweden Tercentenary Foundation and B. Johansson is grateful to the Swedish Natural Science Research Council for financial support. Valuable discussions with Dr. V. Sechovsky and Dr. L. Havela are acknowledged.

*Permanent address: Condensed Matter Theory Group, Department of Physics, University of Uppsala, Box 530, S-75121 Uppsala, Sweden.

¹B. I. Matthias, V. B. Compton, and E. Corenzwit, *J. Phys. Chem. Solids* **19**, 130 (1961).

²V. Sechovsky and L. Havela, in *Intermetallic Compounds of Actinides*, Vol. 4 of *The Handbook of Ferromagnetic Materials*, edited by E. P. Wohlfarth and K. H. J. Buschow (North-Holland, Amsterdam, 1988).

³M. B. Brodsky and R. J. Trainor, *Bull. Am. Phys. Soc.* **21**, 442 (1976).

⁴J. Gal, Z. Hadari, U. Atzmony, E. R. Bauminger, I. Nowik, and S. Ofer, *Phys. Rev. B* **8**, 1901 (1973).

⁵A. I. Aldred, B. D. Dunlap, D. J. Lam, and I. Nowik, *Phys. Rev. B* **10**, 1011 (1974).

⁶M. B. Brodsky and R. J. Trainor, *J. Phys. (Paris) Colloq.* **8**, C6-777 (1978).

⁷W. J. Nellis and M. B. Brodsky, in *Magnetism and Magnetic Materials (Chicago, 1971)*, Proceedings of the 17th Annual Conference on Magnetism and Magnetic Materials, AIP Conf. Proc. No. 5, edited by C. D. Graham, Jr. and J. J. Rhyne (AIP, New York, 1972).

⁸A. R. Harvey, M. B. Brodsky, and W. J. Nellis, *Phys. Rev. B* **7**, 4137 (1973).

⁹M. S. S. Brooks, B. Johansson, and H. L. Skriver, in *Handbook on the Physics and Chemistry of the Actinides*, edited by A. J. Freeman and G. H. Lander (North-Holland, Amsterdam, 1984), Vol. 1, p. 153.

¹⁰M. S. S. Brooks and P. J. Kelly, *Phys. Rev. Lett.* **51**, 1708 (1983); M. S. S. Brooks, O. Eriksson, B. Johansson, J. J. M.

- Fransé, and P. H. Frings, *J. Phys. F* **18**, 133 (1988); M. R. Norman and D. D. Koelling, *Phys. Rev. B* **33**, 3803 (1986).
- ¹¹M. S. S. Brooks and D. Glötzel, *Physica B+C* **102B**, 51 (1980); *J. Magn. Mater.* **15-18**, 873 (1980).
- ¹²M. S. S. Brooks, *J. Phys. F* **14**, 639 (1984); **14**, 653 (1984); **14**, 657 (1984).
- ¹³D. D. Koelling, B. D. Dunlap, and G. W. Crabtree, *Phys. Rev. B* **31**, 4966 (1984).
- ¹⁴R. C. Albers, *Phys. Rev. B* **32**, 7646 (1985).
- ¹⁵B. Johansson, O. Eriksson, M. S. S. Brooks, and H. L. Skriver, *Phys. Scr.* **T13**, 65 (1986); *Inorgan. Chim. Acta* **140**, 59 (1987); O. Eriksson, B. Johansson, M. S. S. Brooks, and H. L. Skriver, *Phys. Rev. B* **38**, 12 858 (1988).
- ¹⁶A. J. Freeman and D. D. Koelling, in *The Actinides: Electronic Structure and Related Properties*, edited by A. J. Freeman and J. B. Darby (Academic, New York, 1974), Vol. I, p. 51.
- ¹⁷H. H. Hill, *Plutonium 1970 and Other Actinides*, edited by W. N. Miner (The Metallurgical Society of the AIME, New York, 1970), p. 2.
- ¹⁸O. K. Andersen, *Phys. Rev. B* **12**, 3060 (1975); H. L. Skriver, *The LMTO Method* (Springer-Verlag, Berlin, 1984).
- ¹⁹U. von Barth and L. Hedin, *J. Phys. C* **5**, 1629 (1972).
- ²⁰D. G. Pettifor, *Commun. Phys.* **1**, 1 (1976); A. R. Mackintosh and O. K. Andersen, in *Electrons at the Fermi Surface*, edited by M. Spingford (Cambridge University Press, Cambridge, England, 1979); O. K. Andersen, O. Jepsen, and D. Glötzel, in *Highlights in Condensed Matter Theory*, edited by F. Bassani, F. Fumi, and M. P. Tosi (North-Holland, New York, 1985).
- ²¹L. Vegard, *Z. Phys.* **5**, 17 (1921).
- ²²O. K. Andersen, H. L. Skriver, H. Nohl, and B. Johansson, *Pure Appl. Chem.* **52**, 93 (1979).
- ²³O. Eriksson, B. Johansson, H. L. Skriver, and M. S. S. Brooks, *Physica B+C* **144B**, 32 (1986).
- ²⁴V. L. Moruzzi, A. R. Williams, and J. F. Janak, *Phys. Rev. B* **15**, 2854 (1977); D. G. Pettifor, *J. Phys. F* **8**, 219 (1978).
- ²⁵H. L. Skriver, O. K. Andersen, and B. Johansson, *Phys. Rev. Lett.* **48**, 42 (1978).
- ²⁶S. H. Vosko and J. P. Perdew, *Can. J. Phys.* **53**, 1385 (1975); J. F. Janak, *Phys. Rev. B* **16**, 255 (1977); M. S. S. Brooks, O. Eriksson, and B. Johansson, *Phys. Scr.* **35**, 52 (1987).
- ²⁷H. L. Skriver, O. K. Andersen, and B. Johansson, *Phys. Rev. Lett.* **44**, 1230 (1980).
- ²⁸M. S. S. Brooks, *J. Phys. F* **13**, 103 (1983).
- ²⁹M. S. S. Brooks, *J. Magn. Mater.* **63/64**, 649 (1987).
- ³⁰N. E. Christensen, *J. Phys. F* **8**, L51 (1978); C. Godreche, *J. Magn. Mater.* **29**, 262 (1982).
- ³¹O. Eriksson, M. S. S. Brooks, and B. Johansson, *J. Phys. (Paris)* (to be published).
- ³²M. S. S. Brooks, B. Johansson, O. Eriksson, and H. L. Skriver, *Physica B+C* **144B**, 1 (1986).
- ³³The characteristic radius of the lattice, which is used in Eqs. (4) and (5), was chosen to be the average radius per formula unit. Normally it is chosen as the radius of the sublattice.
- ³⁴Z. W. Lu, D. J. Singh, and H. Krakauer, *Phys. Rev. B* **37**, 10045 (1988).