

Magnetic interactions and the cooperative Jahn-Teller effect in KCuF_3

M. D. Towler and R. Dovesi

Theoretical Chemistry Group, Department of Physical, Inorganic and Materials Chemistry, University of Torino, via P. Giuria 5, I-10125, Torino, Italy

V. R. Saunders

Daresbury Laboratory, Daresbury, Warrington WA4 4AD, United Kingdom

(Received 18 May 1995)

The ground-state electronic structure in various magnetic phases of the Jahn-Teller-distorted perovskite KCuF_3 has been investigated using the *ab initio* periodic unrestricted Hartree-Fock approach. The material is correctly predicted to be an orbitally ordered wide band-gap insulator with effectively one-dimensional magnetic properties, in that the estimated antiferromagnetic exchange coupling constant J_c along the c axis is much larger than the ferromagnetic exchange constant J_a perpendicular to this axis. The adiabatic potential-energy surface corresponding to cooperative distortions of CuF_6 octahedra has the form of a classical Jahn-Teller double well, with the equilibrium distortion close to that observed experimentally. The interaction of the Jahn-Teller distortion with the superexchange interaction, which is responsible for the unusual magnetic behavior, is examined both through an analysis of the kinetic, Coulomb, and exchange contributions to the total energy, and from the dependence of magnetic properties on various geometrical parameters. Two structural polytypes with and without fluorine stacking disorder are found to be virtually isoenergetic, which is consistent with the experimental difficulty of preparing single-phase crystals. Charge- and spin-density maps, and densities of states are also reported.

INTRODUCTION

The perovskite KCuF_3 has attracted significant theoretical and experimental interest since the 1960s, principally because it is one of very few materials to possess both a pseudocubic crystal structure and effectively one-dimensional magnetic properties. This is known to be a consequence of interplay between the exchange interaction and "orbital-ordering" effects associated with cooperative Jahn-Teller distortions of CuF_6 octahedra. Other members of the series, which do not contain Jahn-Teller ions, such as the cubic perovskites KNiF_3 and KMnF_3 , are regular three-dimensional antiferromagnets.¹ Although perturbation-theoretical arguments have been successfully used to explain the effect of orbital ordering on the superexchange interaction,² an accurate *ab initio* study has yet to be performed and is of fundamental interest. The theoretical study of magnetic insulators using such methods is traditionally difficult, but recent studies of NiO and other materials^{1,3-5} have demonstrated that periodic unrestricted Hartree-Fock theory is of considerable utility in this area. This is primarily for three reasons. First, the Hartree-Fock Hamiltonian correctly describes the nonlocal exchange interaction, which is responsible to first order for the magnetic properties of transition-metal compounds. Second, it avoids the well-known self-interaction problems resulting from local approximations to the exchange (such as the local spin-density approximation or LSDA) used in most density-functional studies, which lead, for example, to the lack of a gap in the band structure and incorrect relative stabilities of ferromagnetic and antiferromagnetic states.⁶ Fi-

nally, the numerical accuracy of our computational implementation of the periodic Hartree-Fock problem may be made high enough to study total-energy differences reliably down to at least 10^{-5} hartrees per cell at reasonable cost. This is particularly useful in the analysis of energy differences between magnetic states (and hence in the estimation of exchange constants), which are often of this order of magnitude.

In this paper, we present the results of a periodic unrestricted Hartree-Fock study of KCuF_3 . The crystal structure of this material (Fig. 1) is made up of an array of CuF_6 octahedra that is pseudocubic, in the sense that the distance between magnetic Cu^{2+} ions is almost the same along all three principal axes. The K^+ ions fill the empty spaces between octahedra. In the planes perpendicular to the c axis, small cooperative Jahn-Teller distortions are observed. Each CuF_6 octahedron is slightly elongated along the a or b principal axes such that the distortion is orthogonal to that of neighboring octahedra in the plane. All F ions in the ab planes are slightly displaced from the midpoint of adjacent Cu sites, whereas the F ion located between these planes occupy symmetric positions. The structure thus contains two distinct fluorine ions, which will be denoted by F1 (bond-centered F) and F2 (displaced F). For reasons to be discussed presently, this "antiferrodistortive" behavior effectively confines the magnetic interactions to isolated linear chains along the c axis; the antiferromagnetic exchange constant J_c in this direction is several orders of magnitude greater than the weakly ferromagnetic exchange constant J_a in the Jahn-Teller distorted plane.³⁵

It is known that at least two distinct types of polytype structure occur naturally in KCuF_3 . Apart from in very

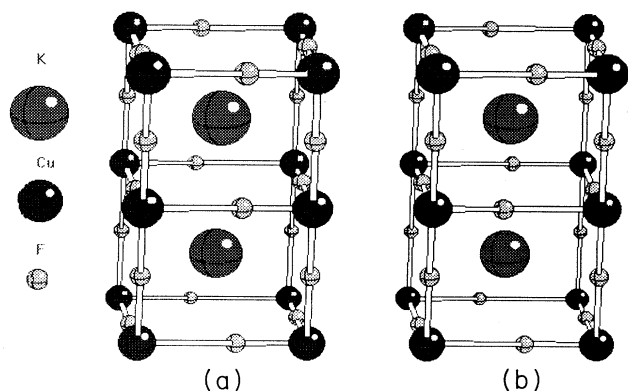


FIG. 1. Tetragonal unit cell of KCuF_3 , showing the two different polytype structures (a) untwisted, type d and (b) twisted, type a .

carefully prepared crystals, these usually coexist in any given sample. In one type [Fig. 1(b)] the direction of displacement of F ions from the midpoint of adjacent Cu sites is opposite in neighboring ab planes, whereas in the alternative structure the displacements are always in the same sense [Fig. 1(a)]. We shall refer to these as *twisted* and *untwisted* polytypes, although for historical reasons the usual designation is type a and type d .⁷ In this paper we shall be principally concerned with the untwisted polytype, which has a smaller unit cell, although total-energy comparisons between the two polytypes will be made. There are three independent structural parameters, a , c , and the F2 coordinate x_F , for which the most recent structural refinements suggest the following values. For the twisted a polytype (space group $I4/mcm$) $a = 5.8569 \text{ \AA}$, $c = 7.8487 \text{ \AA}$, and $x_F = 0.22803$ and for the untwisted d polytype (space group $P4/mbm$), $a = 5.8542 \text{ \AA}$, $c = 3.9303 \text{ \AA}$ with x_F not reported.⁸ $2x_F$ ($=X_F$) corresponds to the position of the F2 fluorine ion as a proportion of the length of the Cu-F2-Cu vector (i.e., the undistorted position 0.5 corresponds to $x_F = 0.25$).

The low-temperature experimental spin arrangement consists of strongly antiferromagnetic linear chains along the c axis coupled via a weakly ferromagnetic interaction. In order to study the magnetic interactions, calculations were performed using the ferromagnetic and two antiferromagnetic states, defined as follows. The state corresponding most closely to the experimental spin arrangement consists of ferromagnetic ab sheets with adjacent sheets having opposite spin. This will be referred to as the AF1 phase. To study the intraplane exchange interaction, we also define a hypothetical alternative phase (AF2), in which all ab planes are identical, and the nearest-neighbor superexchange contacts within these planes are antiferromagnetic. Other possible spin arrangements with larger unit cells were not considered. The origin of the anisotropic magnetic behavior in KCuF_3 is generally explained as a result of orbital-ordering effects associated with the cooperative Jahn-Teller distorted array. The hole orbital of Cu^{2+} is thought to alternate between something like " $d_{x^2-z^2}$ " and " $d_{y^2-z^2}$ " on adjacent Cu sites, a feature of the elec-

tron density that has been confirmed experimentally by Buttner, Maslen, and Spadaccini.⁸ The ordering strongly reduces the overlap between adjacent Cu sites. Kugel and Khomskii were able to demonstrate that this leads to a small ferromagnetic exchange constant in the orbitally ordered planes.² The Jahn-Teller-distorted Cu octahedra in this structure are similar to those in many high- T_c superconducting cuprate perovskites, and thus KCuF_3 models certain aspects of these materials. On this basis, Buttner, Maslen, and Spadaccini have suggested a vibrationally modulated exchange mechanism for superconductivity.^{8,9}

The only previous *ab initio* theoretical calculation for similar perovskites of which we are aware is the recent study of Eyert and Hock,⁶ who examined K_2NiF_4 and K_2CuF_4 within the local spin-density approximation (LSDA). This latter material shows similar antiferrodistortive behavior to KCuF_3 but contains well-separated two-dimensional CuF_2 planes, rather than CuF_6 octahedra. These authors came to the conclusion that "both magnetism and orthorhombic distortion [are] required in order to arrive at the insulating ground state," which they define as the presence of zero density of states at the Fermi energy; their calculations did not lead to the presence of an actual gap in the band structure. This feature of the calculations presumably results from the local approximation to the nonlocal exchange operator implicit in the LSDA.¹⁰ The current treatment of the nonlocal part of the Hamiltonian is crucial in determining the orbital dependence of the one-electron potential and thus the ordering of the d states in the eigenvalue spectrum. Orbital ordering of the K_2CuF_4 electron density was not reported in this study.

All calculations reported in the present work were performed using the program CRYSTAL95,³⁶ a development of the well-established CRYSTAL92 package.¹² This code may be used to perform open-shell calculations within the unrestricted Hartree-Fock approximation. The solid-state band-structure problem is solved in a basis of Bloch functions constructed from linear combinations of localized atomic orbitals, which are in turn a sum of Gaussian-type primitives. Reference may be made to a previous study of KNiF_3 ,¹ for computational details of the present calculations, including exponents and contraction coefficients of the K and F bases, and to Refs. 11–13 for a discussion of the theoretical method. Other applications of this method to compounds containing transition metals include MnO and NiO ,^{3–5} Fe_2O_3 ,¹⁴ FeF_2 ,³⁷ MgO-NiO thin films,¹⁵ Li-doped NiO and MnO ,¹⁶ and the perovskites KNiF_3 (Ref. 1) and K_2NiF_4 (Ref. 17). Some interesting questions relevant to the present work were addressed in the latter two studies and will be referred to in context in the discussion that follows.

The principal source of error in the Hartree-Fock approach is the neglect of electron Coulomb correlation. This is a short-range screening effect that is much less crucial to the qualitative features of the ground state of magnetic insulators than the nonlocal exchange. Recent modifications to the CRYSTAL code now permit correlation corrections to be applied to the Hartree-Fock solu-

tion, at varying levels of sophistication.^{18,19} The most approximate method involves *a posteriori* correlation corrections to the total energy using various functionals of the electron density. In this paper, we examine the effect of applying such a functional on a number of calculated ground-state properties. More sophisticated approaches that have been incorporated into the code involve the addition of correlation-only functionals into the Hamiltonian and incorporating this into the self-consistent procedure through solution of the Kohn-Sham rather than the Hartree-Fock equations. The effect of this combination of density-functional correlation and exact Hartree-Fock nonlocal exchange on results for magnetic insulators is under investigation and will be reported subsequently.

RESULTS AND DISCUSSION

Geometry

First of all, some simple calculated structural properties are compared with experimental data. In Table I, the equilibrium values of a , c , and the fluorine coordinate x_F are shown. These were calculated for the untwisted structural polytype of KCuF_3 in the AF1 spin state. The values of a and c are 2.4% and 3.8% greater than experiment. While the error in a is roughly equivalent to that found in previous studies of transition-metal compounds, such as MnO and NiO using this method,^{1,5} the error in c is substantially greater. This discrepancy is, however, in line with results for the series Li_2O , Na_2O , K_2O ,²⁰ and LiF , NaF , KF ,²¹ which indicate that the Hartree-Fock method routinely overestimates the size of large cations such as K^+ (the ion separating the ab planes in KCuF_3). In a subsequent section, we will examine the behavior of various structural and magnetic properties as a function of a , c , and x_F . Calculations of properties such as ex-

TABLE I. Calculated and experimental lattice parameters a and c (Å) and fluorine coordinate x_F for the untwisted polytype of KCuF_3 with the experimental AF1 spin structure.

	Calc.	Expt.
a	5.99	5.85
c	4.07	3.93
x_F	0.237 ^a	0.228
	0.233 ^b	

^aPure Hartree-Fock calculation.

^bHartree-Fock corrected *a posteriori* using a Perdew gradient-corrected correlation functional (Ref. 24).

change constants will be performed at the *experimental* geometry, however, since it has been shown in previous work^{1,17} that, in line with suggestions made in the literature,²² the magnitude of the exchange interaction in fully ionic compounds generally follows a d^{-x} power law, where d is the interionic distance and x is between 11 and 15.

The calculated Hartree-Fock adiabatic potential energy surface for movement of the F2 fluorine along the line separating nearest-neighbor Cu ions is the upper curve shown in Fig. 2. The Cu-Cu midpoint position is seen to be unstable, and thus this displacement coordinate corresponds to a Jahn-Teller distortion of the CuF_6 octahedra, with a classical double well containing two equivalent minima.²³ The equilibrium fluorine position (Table I) corresponding to the bottom of the well is reasonably close to the experimental value (an error of +3.4% of the nearest-neighbor Cu-F distance). The lower curve in Fig. 2 shows the effect on the shape of the double well of *a posteriori* gradient-corrected correlation corrections using the Perdew functional.²⁴ The two curves have been shifted to coincide at the undistorted configuration. Compared to the straight Hartree-Fock calculation, the depth

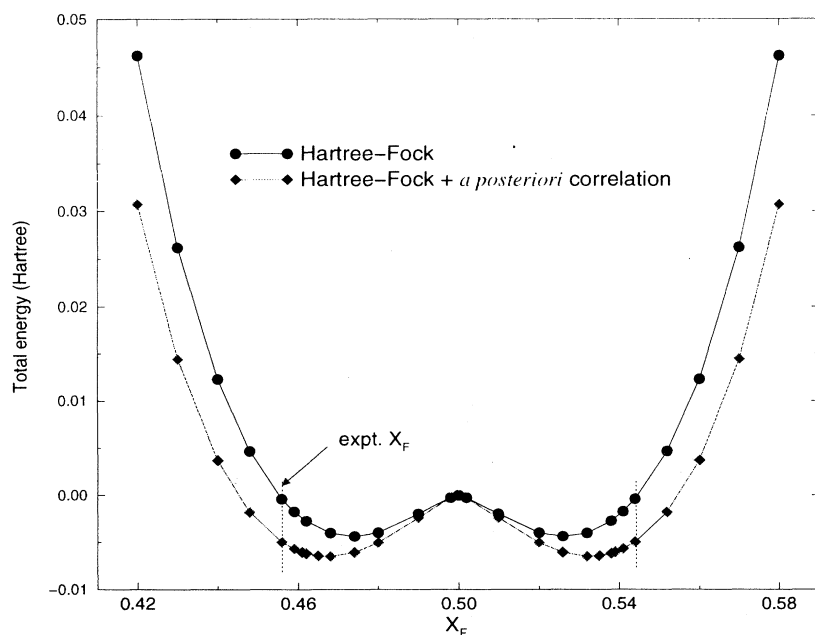


FIG. 2. Total energy (relative to the undistorted crystal) as a function of fluorine coordinate X_F in the ab plane. $X_F = 2x_F$, where x_F is the fractional F2 coordinate.

of the Jahn-Teller well is increased by around 50% (from 0.0044 to 0.0065 hartrees) and the error in the equilibrium fluorine coordinate is roughly halved in the correlation-corrected calculations. The energy scale associated with the cooperative Jahn-Teller effect in KCuF_3 is around 20 times greater than the calculated magnetic ordering energies reported later in this section.

Finally, the total-energy cost of introducing fluorine stacking disorder was estimated. The energy differences between twisted and untwisted polytypes of KCuF_3 with equivalent magnetic structure and lattice parameters was found to be extremely small (an order of magnitude lower than the energy scale associated with the magnetic ordering). This is consistent with the experimental difficulty of preparing single-phase crystals. The twisted polytype, which is the predominant phase in real crystals, was the more stable of the two by around 3×10^{-5} hartrees.

Orbital ordering and electronic structure

Table II shows the results of a Mulliken analysis of the unrestricted Hartree-Fock wave function. KCuF_3 is seen to be highly ionic, with net atomic charges close to their formal values and a single d orbital hole associated with each Cu ion. Orbital populations and the coefficients of the Fock eigenvectors indicate that the hole orbital is constructed from a linear combination of the (non degenerate) d_{z^2} and $d_{x^2-y^2}$ Bloch basis functions. The single unpaired spin associated with each hole is almost exclusively contained in the d orbitals, and there is a small amount of spin dispersion onto the fluorine ions. The data are quoted for the AF1 antiferromagnetic state only, since differences in orbital populations for alternative magnetic states were found to be negligible (less than $0.002|e|$).

The total charge density in the Jahn-Teller distorted ab plane is shown on a relatively small scale in Fig. 3(a). A closeup of a single "cell" in this plane in Fig. 3(b) shows the difference between the total charge density and a superposition of spherical ionic densities. Such plots indicate the changes in shape of the free-ion electron distribution due to the influence of the crystalline environment. The effect of orbital ordering on the density difference map in Fig. 3(b) is particularly striking; the copper hole orbital alternates between the $d_{x^2-z^2}$ and $d_{y^2-z^2}$ orbitals on adjacent Cu ions. Figure 3(c) shows the equivalent

plot for the plane perpendicular to ab containing the undisplaced F1 ions. In this case, no ordering of the electron density is associated with F1 and the Cu-F-Cu vector is a standard 180° superexchange contact, which would be expected to give rise to an antiferromagnetic spin ordering of the two coppers along the c axis.

To understand the Hartree-Fock electronic structure, it is useful to examine the calculated density of states (DOS). The standard definition of the tetragonal cell is

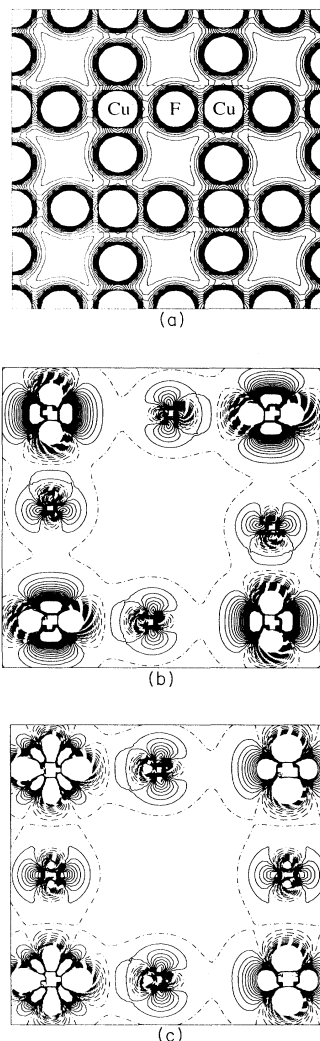


FIG. 3. (a) Total charge-density map in the ab (001) plane of KCuF_3 through the Cu and F ions. The separation between adjacent isodensity curves is $0.01 e/\text{bohr}^3$; the innermost curves in the atomic region correspond to $0.15 e/\text{bohr}^3$. The dashed box denotes the area of (b), which is a charge density difference map in the ab plane for AF1 KCuF_3 . (c) is the equivalent plot in the ac plane. Both (b) and (c) refer to the difference between the bulk density and the density obtained as a superposition of spherical ionic densities (using the same basis set in both cases). Continuous, dashed and dot-dashed lines correspond to positive, negative, and zero values, respectively. The separation between adjacent isodensity curves is $0.005 e/\text{bohr}^3$; the innermost curves in the atomic region correspond to $0.05 e/\text{bohr}^3$.

TABLE II. Mulliken charges and population data (in electrons) for AF1 antiferromagnetic KCuF_3 . Q is the net atomic charge; $q(3d)$ is the electron population of the d orbitals; δ_{ns} and $\delta_{ns}(3d)$ are the magnitudes of the corresponding spin quantities.

	K	Cu	F1	F2
Q	+1.00	+1.83	-0.95	-0.95
$q(3d)$		9.09		
δ_{ns}	0.00	0.95	0.01	0.01
$\delta_{ns}(3d)$		0.95		

such that it was necessary to rotate the Cartesian reference frame around the z axis by 45° , in order to align the lobes of the $d_{x^2-y^2}$ orbital along the Cu-F-Cu vectors. The band-projected DOS using the conventional atomic orbital symmetries could then be calculated. This unitary transformation does not, of course, affect the ground-state properties, but mixes the orbitals among themselves changing the orbital populations and the projected DOS. The valence band of the latter is plotted in Fig. 4. KCuF_3 is correctly predicted to be a wide band-gap insulator, with states at the top of the valence band of predominantly fluorine $2p$ character, and metal $3d$ states at the bottom of the conduction band. It is thus a charge-transfer insulator in the Zaanen-Sawatzky-Allen classification scheme.²⁵ The effect of the magnetic order on the density of states was found to be comparatively small. The magnitude of the band gap (which is overestimated in the Hartree-Fock method) was 0.65 hartree.

Magnetic properties

As discussed by Anderson in his original work on superexchange,²⁶ all the elements necessary to describe this interaction are present, in principle, in the unrestricted Hartree-Fock theory. In this section, therefore, we shall attempt to calculate exchange constants and describe how the interaction may be either ferromagnetic or antiferromagnetic depending on the degree of spin-orbital overlap, mediated by orbital-ordering effects.

The calculations correctly predict the antiferromagnetic (AF1) spin state to be the most stable magnetic phase, followed by the ferromagnetic, which is in turn very slightly more stable than the AF2. The differences in total energy per Cu ion between these states (ΔE) may be approximately related to data derived from various kinds of experiments.²⁷⁻³⁰ Such data are normally interpreted in terms of the magnetic coupling constants J of a model spin Hamiltonian, such as the Ising or Heisenberg models. As the solutions of the unrestricted Hartree-Fock equations are eigenfunctions of the \hat{S}_z spin operator but not of the total spin operator \hat{S}^2 , the former model is more appropriate in this case. Within the Ising model, therefore, and assuming coupling only between nearest Cu neighbors, the following expression relates J to ΔE :

$$\Delta E = 2S^2|J|z. \quad (1)$$

Here S is the total spin per Cu ion (assuming for the moment the calculated value of 0.476 from a Mulliken analysis) and z is the number of nearest neighbors of a given Cu that have differing spins in the two magnetic states. The appearance of the factor z in (1) is dependent upon the assumption that the exchange interactions are additive, that is, directly proportional to the number of nearest neighbors of a given Cu. Previous studies of KNiF_3 and K_2NiF_4 are consistent with this assumption, since, for example, the ratio of the calculated ΔE values was very close to the 6:4 ratio of the number of Ni neighbors.^{1,17}

In Table III, exchange constants estimated within the Ising model from the Hartree-Fock data are compared with the corresponding experimental values (as is cus-

TABLE III. Calculated and experimental exchange constants in KCuF_3 . Model 1 = Eq. (1), with calculated $S (=0.476)$, model 2 = Eq. (1) with experimental $S (=0.24)$.

	Exchange constants (K)		
	Experimental	Model 1	Model 2
J_a	$\sim +2^a$	+1	+6
J_c	$-187^b, -190^c, -197^d, -203^a$	-46	-182

^aNeutron-diffraction (Ref. 35) data.

^bMagnetic specific heat (Ref. 32).

^cSusceptibility (Ref. 33).

^dNeutron diffraction (Ref. 34).

tomary, the exchange constants in energy units are divided by Boltzmann's constant to yield quantities with the dimensions of temperature). The qualitative features of the calculated constants (model 1) are essentially correct; J_c is negative in sign (antiferromagnetic) and very much larger than J_a , which is small and positive (ferromagnetic). Hence, the one-dimensional nature of the magnetic interactions in KCuF_3 is reproduced. The quantitative agreement in J_c is rather poor, however, and there are likely to be a number of reasons for this. One of the principal problems appears to be the experimentally well-characterized zero-point deviations in the spin direction, which are included neither in the Hartree-Fock theory nor in the Ising model we use to interpret the data in terms of exchange constants. Such effects are particularly important in low-dimensional magnetic systems such as KCuF_3 and have two principal consequences.²⁷ The first of these is a lowering of the expected on-site magnetic moment of $\sim 2S\mu_B$ to $\sim 2(S - \Delta S)\mu_B$, where ΔS is the anisotropy-dependent spin reduction. The second effect is an enhanced stabilization of the antiferromagnetic state relative to the ferromagnetic. An interesting strategy is to consider the fully aligned Néel antiferromagnetic state assumed implicitly in our Hartree-Fock treatment as an approximate ground state and to correct the zero-point effects using corrections to the basic Ising model. The simplest modification consists of replacing S in Eq. (1) by $(S - \Delta S)$, where ΔS is calculated from the difference between the calculated Hartree-Fock magnetic moment ($0.95\mu_B$) and the spin-reduced experimental value ($0.48\mu_B$ measured at 4 K).⁷ The resulting exchange constants are shown in Table III (model 2). The quantitative agreement between theory and experiment after making this correction is good. To take into account the enhanced stabilization of the antiferromagnetic state, a model correction must be applied to the calculated value of ΔE . The relevant formula is discussed by de Jongh and Miedema,²⁷ and takes the following form:

$$\Delta E = -2S^2|J|z \left[1 + \frac{e(\alpha)}{zS} \right]. \quad (2)$$

Here α is the magnetic anisotropy and $e(\alpha)$ is a function that varies from $e(0) \approx 1/4z$ to 0 for $\alpha \rightarrow \infty$. Intermediate values of this function can be calculated from spin-

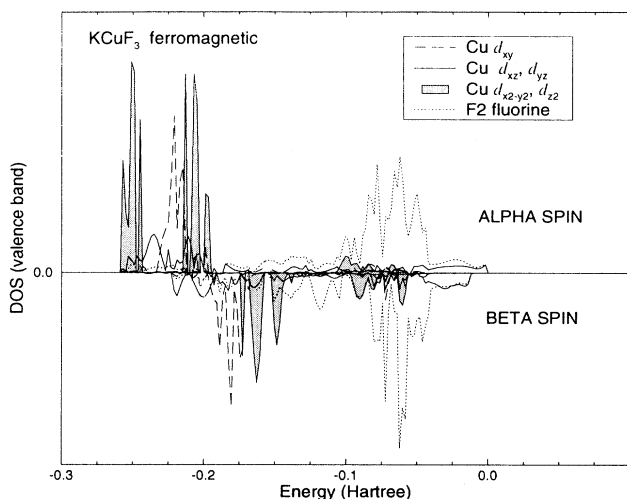


FIG. 4. Valence-band projected density of states for ferromagnetic phase of KCuF_3 . Energy relative to the highest occupied level.

wave theory. Assumption of $\alpha=0$ and the spin-reduced value of S and hence the *maximum* correction for KCuF_3 gives $J_a = +5$ and $J_c = -229$ K; both exchange constants are thus corrected in the right direction.

Apart from zero-point effects, other factors that could influence the comparison of our calculations with experiment are spin-orbit coupling, spin contamination, and the neglect of electron correlation. For systems with partly filled shells of “ e_g ” orbitals, such as the Cu^{2+} ion, the orbital angular momentum is completely quenched,³¹ and so the effect of spin orbit-coupling terms should be inconsequential. Spin contamination is associated with the fact that the unrestricted Hartree-Fock wave function is not an eigenfunction of the \hat{S}^2 operator, and involves the admixture of high-energy components with differing spin multiplicities into the wave function. We are not able to

quantify the magnitude of this effect at present.

To estimate the effect of electron correlation on the calculated values of ΔE , the gradient-corrected correlation functional proposed by Perdew *et al.*²⁴ was applied *a posteriori* to the Hartree-Fock electron density. For KCuF_3 , the correlation energy in the ferromagnetic and antiferromagnetic states was found to be the same to within 10^{-4} hartrees (the range within which the necessary numerical integration of the electron density may be considered reliable). Within the approximation of this functional, this implies a *maximum* correlation contribution to $\Delta E(\text{AF1}-\text{F})$ in KCuF_3 of around 5×10^{-5} hartrees, or 18%. Other workers have examined magnetic interactions in KNiF_3 using a cluster model³⁹ and suggest that the correlation energy evaluated with second-order perturbation theory contributes up to 50% to ΔE . This may be compared with our calculated value for the same system of around 25%. While the use of the cluster approach in modeling infinite systems requires some caution, the effect of electron correlation on the relative energies of different magnetic states remains a delicate open question.

We shall now examine the mechanism of the exchange interactions in KCuF_3 . The reason why the exchange constant $|J_a|$ is very small and ferromagnetic in the orbitally ordered plane is related to the degree of overlap of the Fock spin orbitals along the a and c axes. This may be appreciated from Fig. 5, in which the variation of the calculated ΔE with fluorine coordinate is shown. With the F2 fluorine in the undistorted position (very weak orbital ordering) the exchange is strongly antiferromagnetic, while as the octahedra are progressively distorted, it first becomes weakly ferromagnetic and then antiferromagnetic again at even higher distortions. The almost vanishing value of $|J_a|$ observed experimentally might thus be said to be an essentially “accidental” structural feature; the range of the fluorine coordinate over which ΔE is ferromagnetic is around 8% of the nearest-neighbor Cu-F distance. We will now discuss this

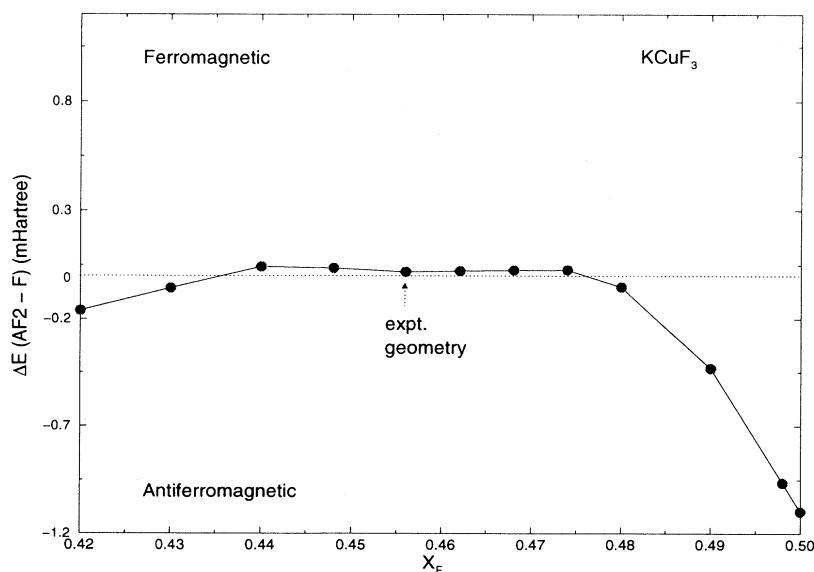


FIG. 5. Energy difference ΔE per formula unit between the ferromagnetic and AF2 antiferromagnetic phases as a function of the fluorine coordinate X_F in the ab plane ($X_F = 2x_F$).

TABLE IV. Analysis of the various contributions to the energy difference $\Delta E(\text{AF}-\text{F})$ between antiferro- and ferromagnetic states of various materials, including untwisted KCuF_3 . The various δE data are given in units of the difference in Hartree-Fock total energies, ΔE_{total} . The value of $\Delta E_{\text{correlation}}$ is the difference in correlation energy of the two magnetic states evaluated *a posteriori* using the density functional of Perdew *et al.* (Ref. 24). Only one decimal figure is given for this quantity, due to limitations in accuracy of the numerical integration of the energy functional. All energy data in both ferromagnetic and antiferromagnetic states are evaluated at the same (experimental) crystal geometry.

	ΔE_{total} (mhartree)	δE_{total}	$\delta E_{\text{kinetic}}$	$\delta E_{\text{coulomb}}$	$\delta E_{\text{exchange}}$	$\Delta E_{\text{correlation}}$ (mhartree)
$\text{KCuF}_3\text{-AF1}$	-0.265	-1.0	-15.1	+9.6	+4.5	0.0
$\text{KCuF}_3\text{-AF2}$	+0.017	+1.0	-4.7	+8.2	-2.5	0.0
KNiF_3	-1.136	-1.0	-8.4	+4.4	+3.0	-0.3
K_2NiF_4	-0.793	-1.0	-18.4	+13.7	+3.7	-0.2
NiO	-0.608	-1.0	-13.0	+8.4	+3.6	-0.1
MnO	-0.242	-1.0	-26.3	+15.8	+9.5	-0.1

behavior quantitatively through a consideration of the kinetic, Coulomb, exchange and correlation contributions to the total energy in the various magnetic states.

In a standard $M\text{-F-M}$ superexchange contact, it is well known that the predominant contribution to the additional stability of the antiferromagnetic state is the lowering of the kinetic energy in this phase.²⁶ In his original formulation of superexchange theory, Anderson introduced the concepts of “kinetic exchange” and “potential exchange” to clarify the major interaction terms.²⁶ In the

Hartree-Fock picture, kinetic exchange is a consequence of antisymmetrization and arises in the following way. If two neighboring spins are parallel, their spatial orbitals must be orthogonal, but when they are antiparallel, the spin functions are automatically orthogonal so the orbitals may overlap each other. This may be thought of as a “Pauli repulsion” between electrons of the same spin. There is a significant kinetic energy gain when antiparallel spins are present, and hence this term is antiferromagnetic in sign. The magnitude of the kinetic exchange,

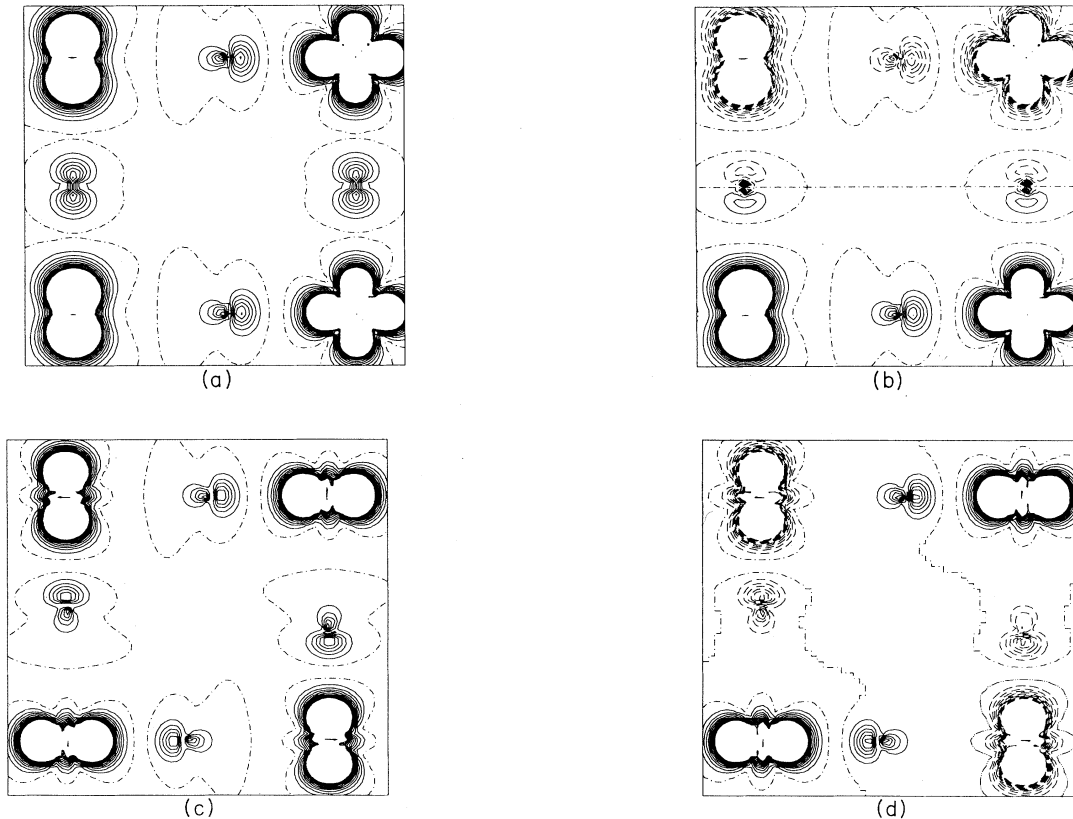


FIG. 6. Spin density maps for (a) ferromagnetic and (b) AF1 antiferromagnetic solutions in the ac plane, and (c) ferromagnetic and (d) AF2 antiferromagnetic solutions in the ab plane. Scale and symbols as in Fig. 3(b).

which is proportional to the degree of spin-orbital overlap, is normally estimated using a perturbation theoretical approximation to the Hubbard model. In the case of small overlap, the most important interaction term is the potential exchange, which is always ferromagnetic in sign.

In Table IV, an analysis of the various contributions to the total energy is given for the various magnetic states of KCuF_3 . Terms in the kinetic, Coulomb, and exchange energy are evaluated, together with an *a posteriori* evaluation of the correlation energy using the Perdew scheme. The Ewald convention used in performing the infinite lattice sums does not permit a strict partitioning of the Coulomb energy into nuclear attraction and electron repulsion terms.³⁸ For comparative purposes, we also show the equivalent data for four other antiferromagnetic

compounds investigated by us using the same method. In these latter materials, the major magnetic interactions are all through standard 180° superexchange contacts. For each system, the total-energy difference between ferromagnetic and antiferromagnetic states at the same geometry is "normalized" to -1 and differences in the various components of the total energy between the two phases defined relative to this. Apart from the interaction in the orbitally ordered plane of KCuF_3 , the dominant contribution to the energy lowering in the antiferromagnetic phase is in each case the kinetic-energy term. The ferromagnetic superexchange contact in KCuF_3 shows quite different characteristics, however. Because of the small overlap in the orbitally ordered plane, the difference in kinetic energy between the AF2 and ferromagnetic phases is relatively small, and the dominant

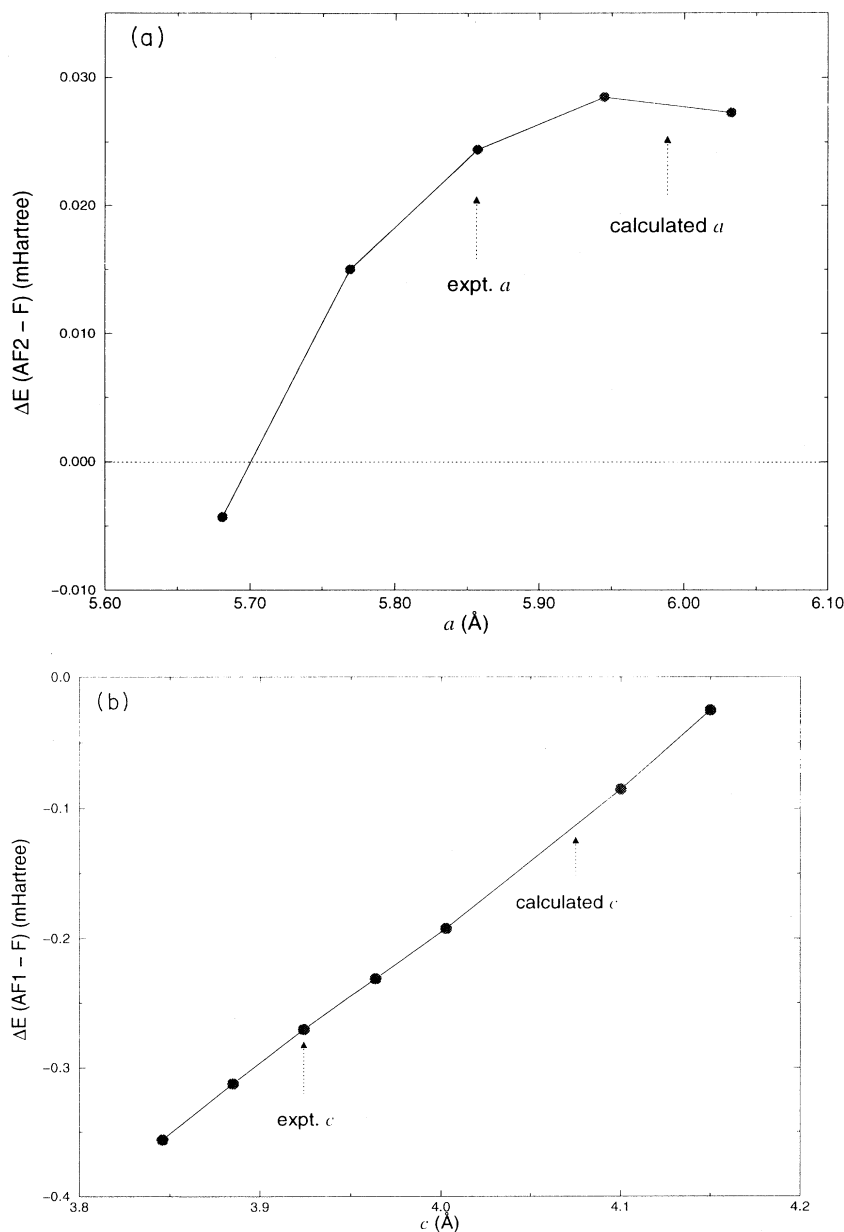


FIG. 7. Energy difference ΔE per formula unit between (a) the ferromagnetic and AF2 antiferromagnetic phases as a function of the a parameter, and (b) the ferromagnetic and AF1 antiferromagnetic phases as a function of the c parameter. In (a), the fluorine coordinate in the ab plane was the calculated equilibrium value for each geometry: the equilibrium value of X_F varied between 0.469 and 0.474 as a was changed by $\pm 3\%$.

contribution to the energy difference is the additional electron-nuclear attraction in the ferromagnetic phase. The contribution of the correlation energy to ΔE is not insignificant, but a quantitative analysis using density functional of the electron density requires higher accuracy in the numerical integration of the electron density.

The superexchange mechanism can be appreciated in a relatively simple visual way from maps of the spin density distributions. First of all, we consider the standard antiferromagnetic superexchange contact along the c axis; spin density maps in the ac plane are shown in Figs. 6(a) and 6(b). In the ferromagnetic state, the contraction of majority (α) spin density of the F1 fluorine ion (center left and center right of the figure) is very large relative to that of the β spin density. This is because of the large Pauli repulsion from unpaired α density on each of two neighboring Cu atoms. In the antiferromagnetic states, there is a *spin polarization* of the fluorine ion, since the spatial orbitals are no longer constrained to be orthogonal, and thus the exchange repulsion may be reduced by shifting the α density towards the Cu ion with β polarization, and vice versa. The closer average confinement of electrons on the fluorine site in the ferromagnetic state ensures the dominant contribution to the total energy is the kinetic energy term. Figures 6(c) and 6(d) show total spin-density maps in the ab plane for the ferromagnetic and AF2 phases of KCuF_3 . Since the spin-orbital overlap is small, no large-scale changes in spin density between the magnetic phases are observed, and the sign and magnitude of the energy difference between the two results from a delicate balance of the kinetic and potential components of the total energy.

Finally, the variation of ΔE , and hence the calculated exchange constants, is examined as a function of relatively large geometrical distortions. Figure 7(a) shows $\Delta E_{\text{AF2-F}}$ as a function of a , and Fig. 7(b) shows $\Delta E_{\text{AF1-F}}$ versus c . In each case ΔE changes markedly as the lattice parameter is varied over $\pm 3\%$, and thus the

use of the experimental crystal geometry in carrying out the exchange constant analysis is important.

CONCLUSION

The *ab initio* periodic unrestricted Hartree-Fock method has been used to examine the ground-state electronic and magnetic properties of KCuF_3 . The material is correctly predicted to be an orbitally ordered wide band-gap insulator. The Jahn-Teller distortion of the CuF_6 octahedra is reproduced, with the equilibrium distortion close to that observed experimentally. The qualitative one-dimensional features of the magnetic interactions emerge naturally from the calculation, but for a low-dimensional system such as KCuF_3 , the importance of higher-order terms in the spin is such that interpretation of the Hartree-Fock data through an Ising-type model is not appropriate. By treating the magnetic moment as a parameter and using the experimental value to take into account the observed spin reduction, we were able to get quantitative agreement of the experimental exchange constants with the *ab initio* Hartree-Fock data. The influence of cooperative Jahn-Teller distortions on the exchange interaction was also analyzed, via an analysis of the various contributions to the total energy. For antiferromagnetic superexchange contacts, the lowering of kinetic energy is the dominant contribution, while in the equivalent ferromagnetic interaction in orbitally ordered planes, the electron-nuclear repulsion predominates.

ACKNOWLEDGMENTS

M.D.T. wishes to thank the Commission of the European Communities for financial support under the Human Capital and Mobility Programme (Contract No. ERBCHBICT941605). The work was also partially supported by EC HC&M Contract No. CHRX-CT93-0155.

-
- ¹J. M. Ricart, R. Dovesi, V. R. Saunders, and C. Roetti, *Phys. Rev. B* **52**, 2381 (1995).
- ²D. I. Khomskii and K. I. Kugel, *Solid State Commun.* **18**, 433 (1976); see K. I. Kugel and D. I. Khomskii, *Sov. Phys. Usp.* **25**, 231 (1982) for a more recent review of the subject.
- ³W. C. Mackrodt, N. M. Harrison, V. R. Saunders, N. L. Allan, M. D. Towler, E. Aprà, and R. Dovesi, *Philos. Mag. A* **68**, 653 (1993).
- ⁴M. D. Towler, Ph.D. thesis, University of Bristol, 1994.
- ⁵M. D. Towler, N. L. Allan, N. M. Harrison, V. R. Saunders, W. C. Mackrodt, and E. Aprà, *Phys. Rev. B* **50**, 5041 (1994).
- ⁶V. Eyert and K. H. Hock, *J. Phys. Condens. Matter* **5**, 2987 (1993).
- ⁷M. T. Hutchings, E. J. Samuelson, G. Shirane, and K. Hirakawa, *Phys. Rev.* **188**, 919 (1969).
- ⁸R. H. Buttner, E. N. Maslen, and N. Spadaccini, *Acta Crystallogr. B* **46**, 131 (1990).
- ⁹R. H. Buttner, E. N. Maslen, and N. Spadaccini, *Acta Crystallogr. B* **48**, 21 (1992).
- ¹⁰B. Brandow, *J. Alloys Compounds* **181**, 377 (1992).
- ¹¹C. Pisani, R. Dovesi, and C. Roetti, in *Hartree-Fock ab initio Treatment of Crystalline Systems*, Lecture Notes in Chemistry, Vol. 48 (Springer, Berlin, 1988).
- ¹²R. Dovesi, V. R. Saunders, and C. Roetti, *CRYSTAL92 user documentation* (Università di Torino, Torino, 1992).
- ¹³E. Aprà, Ph.D. Thesis, Università di Torino, 1993.
- ¹⁴M. Catti, G. Valerio, and R. Dovesi, *Phys. Rev. B* **51**, 7441 (1995).
- ¹⁵M. D. Towler, N. M. Harrison, and M. I. McCarthy, *Phys. Rev. B* **52**, 5375 (1995).
- ¹⁶M. D. Towler, N. L. Allan, N. M. Harrison, V. R. Saunders, and W. C. Mackrodt (unpublished).
- ¹⁷R. Dovesi, J. M. Ricart, V. R. Saunders, and R. Orlando, *J. Phys. Condens. Matter* (to be published).
- ¹⁸M. Causà and A. Zupan, *Chem. Phys. Lett.* **220**, 145 (1994).
- ¹⁹M. Causà and A. Zupan, *Int. J. Quant. Chem.* **S28**, 633 (1995).
- ²⁰R. Dovesi, C. Roetti, C. Freyria-Fava, M. Prencipe, and V. R. Saunders, *Chem. Phys.* **156**, 11 (1991).
- ²¹M. Prencipe, A. Zupan, E. Aprà, R. Dovesi, and V. R.

- Saunders, Phys. Rev. B **51**, 3391 (1995).
- ²²L. J. de Jongh and R. Block, Physica B **79**, 568 (1975).
- ²³M. C. M. O'Brien and C. C. Chancey, Am. J. Phys. **61**, 688 (1993).
- ²⁴J. P. Perdew, J. A. Chevary, S. H. Vosko, K. A. Jackson, M. R. Pederson, D. J. Singh, and C. Fiolhais, Phys. Rev. B **46**, 6671 (1992).
- ²⁵J. Zaanen, G. A. Sawatzky, and J. W. Allen, Phys. Rev. Lett. **55**, 418 (1995).
- ²⁶P. W. Anderson, Solid State Phys. **14**, 99 (1963).
- ²⁷L. J. de Jongh and A. R. Miedema, Adv. Phys. **23**, 1 (1974), see p. 181.
- ²⁸L. J. de Jongh, in *Magnetism and Magnetic Materials (Denver, 1972)* Proceedings of the 18th Annual Conference on Magnetism and Magnetic Materials, edited by C. D. Graham and J. J. Rhyne, AIP Conf. Proc. No. 10 (AIP, New York, 1973), p. 561.
- ²⁹H. W. de Wijn, L. R. Walker, and R. F. Walstedt, Phys. Rev. B **8**, 285 (1973).
- ³⁰J. Skalyo, Jr., G. Shirane, R. J. Birgeneau, and H. J. Guggenheim, Phys. Rev. Lett. **23**, 1394 (1969).
- ³¹See, for example, A. Abragam and B. Bleaney, *Electron Paramagnetic Resonance of Transition Ions* (Clarendon, Oxford, 1970).
- ³²K. Iio, H. Hyodo, K. Nagata, and I. Yamada, J. Phys. Soc. Jpn. **44**, 1393 (1978).
- ³³S. Kadota, I. Yamada, S. Yoneyama, and K. Hirakawa, J. Phys. Soc. Jpn. **23**, 751 (1967).
- ³⁴M. T. Hutchings, H. Ikeda, and J. M. Milne, J. Phys. C **12**, L739 (1979).
- ³⁵K. Satija, J. D. Axe, G. Shirane, H. Yoshizawa, and K. Hirakawa, Phys. Rev. B **21**, 2001 (1980).
- ³⁶CRYSTAL95, University of Torino and CCLRC Daresbury Laboratory (unpublished).
- ³⁷G. Valerio, M. Catti, R. Dovesi, and R. Orlando, Phys. Rev. B **52**, 2422 (1995).
- ³⁸V. R. Saunders, C. Freyria-Fava, R. Dovesi, L. Salasco, and C. Roetti, Mol. Phys. **77**, 629 (1992).
- ³⁹J. A. Mejías and J. F. Sanz, J. Chem. Phys. **102**, 850 (1995).