

Effects of superconducting gap anisotropy on the flux flow resistivity in $Y(Ni_{1-x}Pt_x)_2B_2C$ K. Takaki,* A. Koizumi, T. Hanaguri,[†] M. Nohara, H. Takagi, and K. Kitazawa*Department of Advanced Materials Science, The University of Tokyo, 7-3-1, Hongo, Bunkyo-ku, Tokyo 113-0033, Japan*Y. Kato, Y. Tsuchiya,[‡] H. Kitano, and A. Maeda*Department of Basic Science, The University of Tokyo, 3-8-1, Komaba, Meguro-ku, Tokyo 153-8902, Japan*

(Received 19 September 2002; published 21 November 2002)

The microwave complex surface impedance Z_s of $Y(Ni_{1-x}Pt_x)_2B_2C$ was measured at 0.5 K under magnetic fields H up to 7 T. In nominally pure YNi_2B_2C , which is a strongly anisotropic s -wave superconductor, the flux flow resistivity ρ_f calculated from Z_s was twice as large as that expected from the conventional normal-state vortex core model. In Pt-doped samples where the gap anisotropy is smeared out, the enhancement of ρ_f is reduced and ρ_f approaches the conventional behavior. These results indicate that the energy dissipation in the vortex core is strongly affected by the anisotropy of the superconducting gap.

DOI: 10.1103/PhysRevB.66.184511

PACS number(s): 74.60.Ec, 74.25.Jb, 74.25.Nf, 74.70.Dd

I. INTRODUCTION

In conventional phonon-mediated superconductors, the symmetry of the pair wave function is of s -wave type, and the superconducting gap (SG) is isotropic in momentum space. However, pair wave functions with higher angular momenta are believed to occur in superconductors where strong interactions among electrons play an important role. In such unconventional superconductors, the SG's are anisotropic and can have nodes.^{1,2} In general, even in s -wave superconductors, the SG can be strongly anisotropic.³

In superconductors with anisotropic SG's, low-energy quasiparticle (QP) excitations near the gap nodes play an important role. Volovik examined the effects of gap nodes on the QP density of states (DOS) in the mixed state.⁴ He pointed out that the QP DOS at the Fermi energy ϵ_F in superconductors with line nodes varies proportionally to \sqrt{H} , in contrast to the case of conventional superconductors with an isotropic SG where the QP DOS at ϵ_F is linear in H , that is, proportional to the number of vortices. Such an enhancement of the QP DOS in anisotropic superconductors has been observed experimentally in d -wave high- T_c cuprates^{5,6} and the heavy fermion superconductor UPt_3 (Ref. 7) by electronic specific heat measurements.

Besides the QP DOS, gap nodes are expected to affect the flux flow resistivity ρ_f . Basically, ρ_f is a measure of the QP relaxation *in and around* the vortex core, and can provide different information from the QP DOS. In dirty superconductors where the QP mean free path l is shorter than the coherence length ξ , the vortex core can be treated as a bulk normal metal with a radius of the order of ξ .⁸ As a result, ρ_f is simply given by $\rho_f \sim \rho_n H/H_{c2}$ regardless of the anisotropy of the SG. In moderately clean superconductors where $\xi < l < \xi \epsilon_F/\Delta$ (Δ is the gap amplitude), however, the vortex core cannot be regarded as a simple normal metal at all, since the QP's are reflected at the edge of the vortex core before they experience impurity scattering. In this regime, ρ_f is given by $\rho_f = H/(ne\langle\omega_0\tau_c\rangle_F)$.⁹ Here n is a carrier density, e is a unit charge, $\omega_0 \sim \Delta^2/\epsilon_F$ is the precession frequency of the lowest Andreev bound state,¹⁰ τ_c is the relaxation time in the vortex

core, and $\langle\cdots\rangle_F$ denotes the average over the Fermi surface. In such a case, nodes in the SG should affect both ω_0 and τ_c . First, ω_0 in anisotropic superconductors depends on the QP momentum and should be very small near the gap nodes. Second, τ_c can be short because the QP DOS which contributes to the impurity scattering is enhanced in anisotropic superconductors. Both these factors are expected to enhance ρ_f from clean isotropic superconductors.

To date, UPt_3 is the only clean anisotropic superconductor in which ρ_f has been measured. The enhancement of ρ_f has actually been observed.^{11,12} However, since UPt_3 is a complicated odd-parity superconductor,¹³ it should be noted that many factors other than gap anisotropy can contribute to ρ_f . In fact, Lütke-Entrup *et al.* attributed the origin of the ρ_f enhancement to the unconventional vortex core structure which is brought by the two-component order parameter.¹² In addition, Kato showed that the parity and chirality of the pair wave function affect τ_c in the moderately clean regime.¹⁴ Therefore, it is still unclear whether ρ_f enhancement in UPt_3 is brought by the gap anisotropy or by the other unconventional nature of superconductivity.

To make clear the effects of gap anisotropy on ρ_f , measurement on a *clean, anisotropic, and s-wave* superconductor is indispensable. From this point of view, we measured the ρ_f of $Y(Ni_{1-x}Pt_x)_2B_2C$. The temperature and magnetic-field dependence of the electronic specific heat,^{15,16} thermal conductivity,^{17,18} and NMR relaxation rate¹⁹ indicate that there are low-lying QP states near ϵ_F even in the superconducting state. This is strong evidence for the huge anisotropy of the SG in YNi_2B_2C . Recently, Izawa *et al.* suggested, from thermal conductivity measurements under various magnetic field directions that there are point-like gap nodes along the [100] and [010] directions.¹⁸ In addition, it is reported that the introduction of impurities *reduces* the low-lying QP states and opens the gap all over the Fermi surface with little effect on T_c .^{15,20} Such a behavior is totally different from that expected in d - or p -wave superconductors,²¹ and provides strong evidence of *anisotropic s-wave* superconductivity in YNi_2B_2C . Therefore, by comparing the results in pure (anisotropic) and impurity-doped (isotropic) YNi_2B_2C , the

TABLE I. Material parameters of the $\text{Y}(\text{Ni}_{1-x}\text{Pt}_x)_2\text{B}_2\text{C}$ crystals studied. Here ρ_{res} is the residual resistivity measured just above T_c , and δ is the skin depth at 44 GHz. The QP mean free path l was estimated from ρ_{res} and a free electron model using a carrier density $n = 3 \times 10^{22} \text{ cm}^{-3}$.

x	T_c (K)	$H_{c2}(0)$ (T)	ρ_{res} ($\mu\Omega \text{ cm}$)	ξ (\AA)	l (\AA)	δ (\AA)
0	15.4	8.0	0.87	65	1500	2200
0.05	13.7	5.0	20.5	80	63	11000
0.2	12.1	4.3	35.5	90	38	14000

effects of SG anisotropy on ρ_f can be examined without the complication of other effects.

II. EXPERIMENT

Samples were cut from the same single crystal boules used in previous studies.^{15,20} As an impurity, Pt was used instead of Ni. The relevant material parameters are listed in Table I. The sample with $x=0$ is in the moderately clean regime and the impurity-doped samples are in the dirty regime. In order to avoid pinning-related effects, ρ_f should be measured at high enough currents or at frequencies higher than the pinning frequency f_p .²² We adopted the latter method to avoid the self-heating of the sample. In nominally pure $\text{YNi}_2\text{B}_2\text{C}$, f_p is estimated to be below 3 MHz.²³ In other conventional superconductors, f_p is at most of the order of 10^2 MHz.²² Consequently, pinning-related effects can be avoided completely at microwave frequencies. However, a direct resistivity measurement is difficult at microwave frequencies because of the skin effect. Therefore, we measured the surface impedance $Z_s = R_s + iX_s$ using a cavity perturbation method, and calculated the real part of the resistivity ρ_1 using the relation $\rho_1 = 2R_s X_s / \mu\omega$, where μ is the permeability and ω is the angular frequency. Samples were located at the center of a cylindrical Cu cavity which resonates at 44 GHz in the TE_{011} mode. Microwave magnetic fields were applied along the c axis of the crystal to measure the in-plane response. The surface resistance R_s and the surface reactance X_s were obtained from the changes in the quality factor and the resonance frequency of the cavity, respectively.²⁴ The absolute value of Z_s was determined by a comparison with the dc resistivity ρ above T_c assuming the Hagen-Rubens relation $R_s = X_s = \sqrt{\mu\omega\rho}/2$. This relation can be applied in the local regime where l is much shorter than the skin depth $\delta = \sqrt{2\rho/\mu\omega}$. Strictly speaking, the sample with $x=0$ is not deep in the local regime since l and δ were estimated to be of the same order of magnitude. In the nonlocal regime, X_s becomes larger than R_s , and both R_s and X_s are larger than the local value.²⁵ Therefore, the absolute value of Z_s for the sample with $x=0$ could be somewhat underestimated. In the present study, the absolute value is not crucial to the final conclusion. Samples were cooled down to 0.5 K by a laboratory-made ^3He refrigerator. In all the measurements, static magnetic fields were applied along the c axis of the crystals.

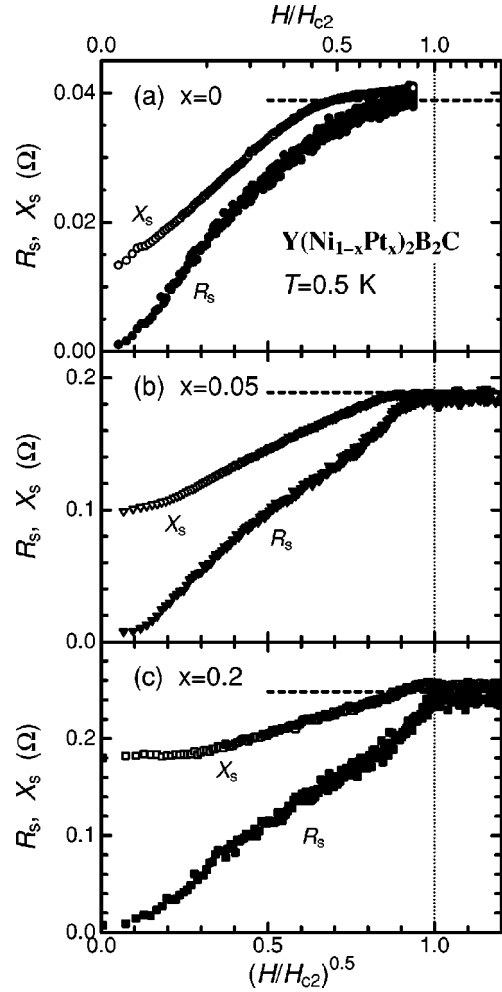


FIG. 1. Magnetic field dependence of the surface impedance of $\text{Y}(\text{Ni}_{1-x}\text{Pt}_x)_2\text{B}_2\text{C}$ plotted as a function of $\sqrt{H/H_{c2}}$. Horizontal dashed lines denote the normal state values just above T_c .

III. RESULTS AND DISCUSSION

The magnetic field dependence of the surface impedance at 0.5 K for each sample is plotted as a function of $\sqrt{H/H_{c2}}$ in Fig. 1. In the absence of magnetic fields, the response is purely reactive with $R_s \sim 0$ and $X_s = \mu\omega\lambda_0$, where λ_0 is the penetration depth in the Meissner state. We estimate λ_0 to be 500 \AA for the sample with $x=0$. This value is similar to λ_0 obtained by the previous microwave measurement,¹⁶ but is rather short compared to the other estimates.²⁶ Part of this difference may come from the nonlocality of the response.

In the mixed state, R_s and X_s increase with increasing H . At high fields, both R_s and X_s saturate to the value just above T_c , which is given by $\sqrt{\mu\omega\rho_{res}}/2$, where ρ_{res} is the resistivity just above T_c . In the sample with $x=0.2$, this saturation occurs just at H_{c2} with a clear kink, as expected. However, with decreasing impurity content or increasing SG anisotropy, both R_s and X_s saturate even below H_{c2} and the kink structure is broadened. This behavior is not caused by the inhomogeneity of the sample, since the broadening is most apparent in the cleanest sample. Therefore, we can conclude that, in clean $\text{YNi}_2\text{B}_2\text{C}$, there is a distinct field region below H_{c2} where the QP response is almost as same as that

in the normal state. In the sample with $x=0$, this region extends to about half of H_{c2} . This behavior may be related to the de Haas–van Alphen effect in the mixed state²⁷ and the large DOS at ϵ_F in the mixed state observed by scanning tunneling spectroscopy.²⁸

Next we try to extract ρ_f from R_s and X_s . In general, Z_s in the mixed state consists of several contributions and ρ_1 , which is directly calculated from Z_s , is different from ρ_f . Since our measurements were performed at low enough temperatures ($T/T_c < 0.04$), and high enough frequencies ($\omega \gg \omega_p$), contributions from thermally activated QP's and the effects of vortex pinning can be safely neglected. One of the remaining potential contributions is the effect of flux flow. Another important factor that we should consider is the contribution from delocalized QP's. In a superconductor with an isotropic SG, all the QP's in the mixed state are localized in the vortex core. On the other hand, in a strongly anisotropic superconductor, such as nominally pure $\text{YNi}_2\text{B}_2\text{C}$, QP's are generated not only in the vortex core, but also *outside* of the core by the Doppler energy shift from the supercurrent around the vortex.⁴ The existence of such delocalized QP's has been confirmed in $\text{YNi}_2\text{B}_2\text{C}$ by electronic specific heat measurements^{15,16} and in $\text{LuNi}_2\text{B}_2\text{C}$ by thermal conductivity measurements.¹⁷ To analyze Z_s in the mixed state under the influence of the delocalized QP's, we use the formulation of Z_s given by Coffey and Clem.²⁹ If we neglect the effect of vortex pinning, Z_s is given by

$$Z_s = i\mu\omega\lambda_0 \sqrt{\frac{(1-bs) - i(b+s)}{1+s^2}}, \quad (1)$$

where $b = \rho_f / \mu\omega\lambda_0^2$, $s = \mu\omega\lambda_0^2\sigma_{nf}$, and σ_{nf} is the conductivity of the delocalized QP's. Here b and s are measures of the contributions from the flux flow and the delocalized QP's, respectively. If we set $s=0$, Eq. (1) is reduced to the pure flux flow state without delocalized QP's and $b=0$ denotes the usual two-fluid response without vortices. In the latter case, all the QP's are delocalized as in the case of thermally activated QP's and $s = \omega\tau_{nf}f_{nf}/(1-f_{nf})$, where τ_{nf} is the relaxation time of the delocalized QP's and f_{nf} is the normal fluid fraction.

To judge which contribution is dominant in $\text{Y}(\text{Ni}_{1-x}\text{Pt}_x)_2\text{B}_2\text{C}$, it is useful to introduce the ‘‘impedance plane plot,’’ where $X_s/X_s(0)$ is plotted against $R_s/X_s(0)$.³⁰ Here $X_s(0) = \mu\omega\lambda_0$ is a surface reactance in the absence of a magnetic field. This plot is sensitive to the underlying mechanism that dominates Z_s . Figure 2 shows the impedance plane plots for $\text{Y}(\text{Ni}_{1-x}\text{Pt}_x)_2\text{B}_2\text{C}$. The solid and dashed curves correspond to two limiting cases of Eq. (1), namely, a pure flux flow state ($s=0$) and a two-fluid response ($b=0$), respectively. As is evident from Fig. 2, the behavior of Z_s is reproduced quite well by the assumption of pure flux flow. Small deviation can be seen at high fields where R_s and X_s are saturated. Consequently, the contribution of delocalized QP's to Z_s can be neglected in the field range where R_s and X_s is field dependent. In other words, in this field range, the real part of the resistivity ρ_1 , calculated from Z_s , can be regarded as ρ_f itself.

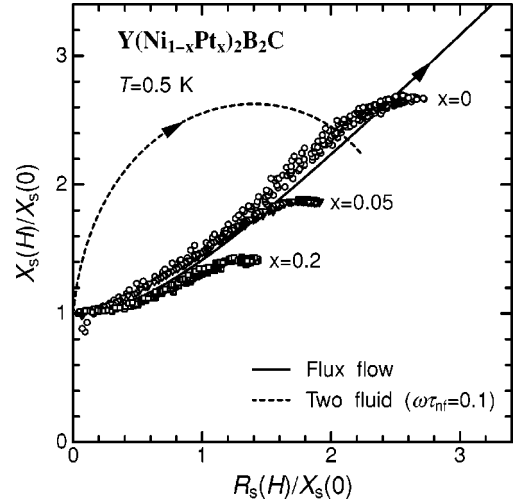


FIG. 2. Impedance plane plot of the surface impedance of $\text{Y}(\text{Ni}_{1-x}\text{Pt}_x)_2\text{B}_2\text{C}$. Solid and dashed lines denote the calculated curves in cases of pure flux flow and the two-fluid response, respectively. For the calculation of two-fluid model, we used $\omega\tau_{nf}=0.1$. (See the text.) Arrows indicate the direction when H is increased.

Figure 3 plots ρ_1/ρ_{res} as a function of H/H_{c2} . In the sample with $x=0$, in which the SG is strongly anisotropic, ρ_1 , namely, ρ_f , below about a half of H_{c2} is almost proportional to H as in the case of the usual flux flow. However, its slope is twice as large as that expected from the conventional normal core model.⁸ We note here that this enhancement is not an artifact caused by the assumption of local electro-dynamics. As described above, the absolute value of Z_s may be somewhat underestimated. Therefore, a correction for the nonlocal behavior further enhances the anomaly. The enhancement of ρ_f implies that the energy dissipation in the vortex core is strongly enhanced in $\text{YNi}_2\text{B}_2\text{C}$. In impurity-doped crystals where the anisotropy of the SG is smeared out, this enhancement is reduced except at very low fields, and ρ_f approaches the behavior expected in the normal core model.⁸ Although the origin of the residual enhancement of

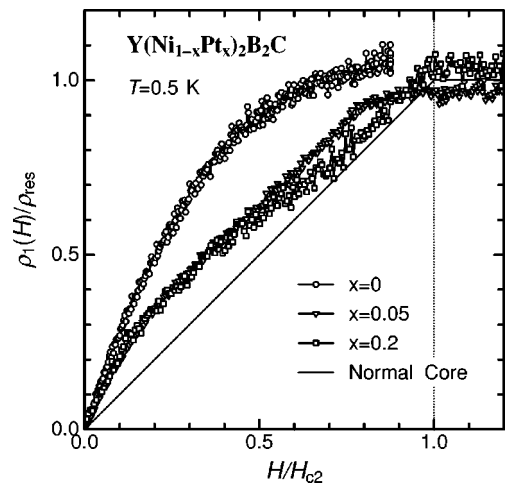


FIG. 3. Real part of the complex resistivity as a function of the magnetic field. Vertical and horizontal axes are normalized by ρ_{res} and H_{c2} , respectively.

ρ_f in impurity-doped crystals is unclear now, the effect of gap anisotropy on ρ_f is evident.

It should be noted that such an enhancement of ρ_f cannot be expected in a clean *isotropic* superconductor, since $\omega_0\tau_c$, which is inversely proportional to ρ_f , is always large over the Fermi surface in this case. At very low temperatures, it is theoretically expected that ρ_f in a clean superconductor is *reduced* from the conventional value by a small factor of $\ln(T_c/T)$ because of the so-called Kramer-Pesch effect,^{9,31} but can never be enhanced. Therefore, we can safely conclude that the observed anomaly is not related to the cleanness itself but is caused by the gap anisotropy. Here we emphasize that the anisotropic *s*-wave superconductivity is realized only in the clean sample.²¹

The observed enhancement factor of 2 is similar to that of UPt₃ (1.6–4.7).^{11,12} However, unlike in the case of UPt₃ which has a complicated superconducting order parameter, the enhancement of ρ_f in YNi₂B₂C is solely brought by the SG anisotropy, since YNi₂B₂C is a “simple” superconductor except for the huge anisotropy of the SG. As mentioned above, ρ_f is affected by the SG anisotropy through ω_0 and/or τ_c . Future work may examine which path is dominant.

Finally, we briefly comment on the absence of the contribution from delocalized QP’s to Z_s . If the parameter s is small compared to unity, the effect of delocalized QP’s on Z_s is small. To evaluate s in the present experiment, we assume that τ_{nf} in the mixed state is not so different from that in the normal state. If that is the case, τ_{nf} can be estimated from ρ_{res} . In the sample with $x=0$, $\omega\tau_{nf}$ is estimated to be of the order of 0.1 and is much smaller in the impurity-doped samples. This means that even if the normal fluid fraction f_{nf}

becomes 0.5, $s = \omega\tau_{nf}f_{nf}/(1-f_{nf})$ is only 0.1 or less. In other words, even at microwave frequencies, one can selectively extract information on the flux flow or the dynamics of the QP’s in the vortex core from Z_s measurements. This feature is complementary to that of the thermal conductivity measurement which selectively senses the dynamics of delocalized QP’s.¹⁷ Considering that the electronic specific heat measures the total QP DOS, combination of these techniques should be important for investigations of the electronic states of the mixed state.

In summary, we measured Z_s of the anisotropic *s*-wave superconductor YNi₂B₂C to study the effects of SG anisotropy on ρ_f . We found that ρ_f in the nominally pure sample, in which the SG has a huge anisotropy, is greatly enhanced from that expected from the conventional normal-state vortex core. This enhancement was reduced in impurity-doped samples where the SG anisotropy is smeared out. Such behavior indicates that the quasi-particle relaxation in and around the vortex core is sensitive to the superconducting gap anisotropy. These results imply that ρ_f measurement provides useful information for a microscopic understanding of the vortex state of anisotropic superconductors.

ACKNOWLEDGMENTS

The authors thank Y. Matsuda and K. Izawa for helpful discussions. They also thank D. G. Steel for a critical reading of the manuscript. This work was supported by SORST, the Japan Science and Technology Corporation, and a Grant-in-Aid for Scientific Research from the Ministry of Education, Science, Sports and Culture of Japan.

*Present address: Yokohama R&D Laboratories, The Furukawa Electric Co., LTD., 2-4-3, Okano, Nishi-ku, Yokohama 220-0073, Japan.

†Author to whom correspondence should be addressed.

‡Present address: Research Center for Quantum Effect Electronics, Tokyo Institute of Technology, 2-12-1, O-okayama, Meguro-ku, Tokyo 152-8552, Japan.

¹M. Sigrist and K. Ueda, *Rev. Mod. Phys.* **63**, 239 (1991).

²D. J. Scalapino, *Phys. Rep.* **250**, 329 (1995).

³L. Chen and A.-M. S. Tremblay, *J. Phys. Chem. Solids* **54**, 1381 (1993).

⁴G. E. Volovik, *Pis'ma Zh. Éksp. Teor. Fiz.* **58**, 457 (1993) [*JETP Lett.* **58**, 469 (1993)].

⁵K. A. Moler, D. J. Baar, J. S. Urbach, Ruixing Liang, W. N. Hardy, and A. Kapitulnik, *Phys. Rev. Lett.* **73**, 2744 (1994).

⁶M. Nohara, H. Suzuki, M. Isshiki, N. Mangkorntong, F. Sakai, and H. Takagi, *J. Phys. Soc. Jpn.* **69**, 1602 (2000).

⁷A. P. Ramirez, N. Stücheli, and E. Bucher, *Phys. Rev. Lett.* **74**, 1218 (1994).

⁸J. Bardeen and M. J. Stephen, *Phys. Rev.* **140**, A1197 (1965).

⁹N. B. Kopnin, *Theory of Nonequilibrium Superconductivity* (Oxford University Press, Oxford, 2001), and references therein.

¹⁰C. Caroli, P. G. de Gennes, and J. Matricon, *Phys. Lett.* **9**, 307 (1964).

¹¹S. Kambe, A. D. Huxley, P. Rodière, and J. Flouquet, *Phys. Rev. Lett.* **83**, 1842 (1999).

¹²N. Lütke-Entrup, R. Blaauwgeers, B. Plaçais, A. Huxley, S. Kambe, M. Krusius, P. Mathieu, and Y. Simon, *Phys. Rev. B* **64**, 020510(R) (2001).

¹³H. Tou, Y. Kitaoka, K. Ishida, K. Asayama, N. Kimura, Y. Onuki, E. Yamamoto, Y. Haga, and K. Maezawa, *Phys. Rev. Lett.* **80**, 3129 (1998); H. Tou, Y. Kitaoka, K. Asayama, N. Kimura, Y. Onuki, E. Yamamoto, and K. Maezawa, *ibid.* **77**, 1374 (1996).

¹⁴Y. Kato, *J. Phys. Soc. Jpn.* **69**, 3378 (2000).

¹⁵M. Nohara, H. Suzuki, N. Mangkorntong, and H. Takagi, *Physica C* **341-348**, 2177 (2000).

¹⁶K. Izawa, A. Shibata, Y. Matsuda, Y. Kato, H. Takeya, K. Hirata, C. J. van der Beek, and M. Konczykowski, *Phys. Rev. Lett.* **86**, 1327 (2001).

¹⁷E. Boaknin, R. W. Hill, C. Proust, C. Lupien, L. Taillefer, and P. C. Canfield, *Phys. Rev. Lett.* **87**, 237001 (2001).

¹⁸K. Izawa, K. Kamata, Y. Nakajima, Y. Matsuda, T. Watanabe, M. Nohara, H. Takagi, P. Thalmeier, and K. Maki, *Phys. Rev. Lett.* **89**, 137006 (2002).

¹⁹G. -q. Zheng, Y. Wada, K. Hashimoto, Y. Kitaoke, K. Asayama, H. Takeya, and K. Kadowaki, *J. Phys. Chem. Solids* **59**, 2169 (1998).

²⁰T. Yokoya, T. Kiss, T. Watanabe, S. Shin, M. Nohara, H. Takagi, and T. Oguchi, *Phys. Rev. Lett.* **85**, 4952 (2000).

²¹L. S. Borkowski and P. J. Hirschfeld, *Phys. Rev. B* **49**, 15404 (1994); R. Fehrenbacher and M. R. Norman, *ibid.* **50**, 3495 (1994).

- ²²J. I. Gittleman and B. Rosenblum, *J. Appl. Phys.* **39**, 2617 (1968).
- ²³S. Oxx, D. P. Choudhury, B. A. Willemsen, H. Srikanth, B. K. Cho, P. C. Canfield, and S. Sridhar, *Physica C* **264**, 103 (1996).
- ²⁴O. Klein, S. Donovan, M. Dressel, and G. Grüner, *Int. J. Infrared Millim. Waves* **14**, 2423 (1993).
- ²⁵A. A. Abrikosov, *Fundamentals of the Theory of Metals* (Elsevier, Amsterdam, 1988).
- ²⁶K. D. D. Rathnayaka, A. K. Bhatnagar, A. Parasiris, D. G. Naugle, P. C. Canfield, and B. K. Cho, *Phys. Rev. B* **55**, 8506 (1997); R. Cywinski, Z. P. Han ZP, R. Bewley R, R. Cubitt R, M. T. Wylie, E. M. Forgan, S. L. Lee, M. Warden, and S. H. Kilcoyne, *Physica C* **233**, 273 (1994).
- ²⁷T. Terashima, C. Haworth, H. Takeya, S. Uji, H. Aoki, and K. Kadowaki, *Phys. Rev. B* **56**, 5120 (1997).
- ²⁸H. Sakata, M. Oosawa, K. Matsuba, N. Nishida, H. Takeya, and K. Hirata, *Phys. Rev. Lett.* **84**, 1583 (2000).
- ²⁹M. W. Coffey and J. R. Clem, *Phys. Rev. Lett.* **67**, 386 (1991).
- ³⁰Y. Tsuchiya, K. Iwaya, K. Kinoshita, T. Hanaguri, H. Kitano, A. Maeda, K. Shibata, T. Nishizaki, and N. Kobayashi, *Phys. Rev. B* **63**, 184517 (2001).
- ³¹L. Kramer and W. Pesch, *Z. Phys.* **269**, 59 (1974).