

Screening of Coulomb interactions in transition metals

I. V. Solovyev* and M. Imada

Institute for Solid State Physics, University of Tokyo, Kashiwanoha 5-1-5, Kashiwa, Chiba 277-8531, Japan and PRESTO, Japan Science and Technology Agency, Japan

(Received 28 July 2004; published 7 January 2005)

We discuss different methods of calculation of the screened Coulomb interaction U in transition metals and compare the so-called constraint local-density approximation (LDA) with the GW approach. We clarify that they offer complementary methods of treating the screening and therefore should serve for different purposes. The analysis is illustrated by calculations for the ferromagnetic Ni. In the *ab initio* GW method, the renormalization of bare on-site Coulomb interactions between $3d$ electrons (being of the order of 20–30 eV) occurs mainly through the screening by the same $3d$ electrons, treated in the random-phase approximation (RPA). The basic difference of the constraint-LDA method from the GW method is that it deals with the neutral processes, where the Coulomb interactions are additionally screened by the “excited” electron, since it *continues to stay in the system*. This is the main channel of screening by the itinerant ($4sp$) electrons, which is especially strong in the case of transition metals and missing in the GW approach, although the details of this screening may be affected by additional approximations, which typically supplement these two methods. The major drawback of the conventional constraint-LDA method is that it does not allow us to treat the energy dependence of U , while the full GW calculations require heavy computations. We propose a promising approximation based on the combination of these two methods. First, we take into account the screening of Coulomb interactions in the $3d$ -electron-like bands located near the Fermi level by the states from the orthogonal subspace, using the constraint-LDA methods. The obtained interactions are further renormalized within the bands near the Fermi level in RPA. This allows the energy-dependent screening by electrons located near the Fermi level, including the same $3d$ electrons.

DOI: 10.1103/PhysRevB.71.045103

PACS number(s): 71.10.–w, 71.15.–m, 71.20.Be, 79.60.–i

I. INTRODUCTION

The description of electronic structure and properties of strongly correlated systems presents a great challenge for *ab initio* electronic structure calculations. The main complexity of the problem is related to the fact that such electronic systems typically bear both localized and itinerant character, where most conventional methods do not apply. A canonical example is the local-(spin-)density approximation [L(S)DA] in the density-functional theory (DFT).¹

The DFT, which is a ground-state theory, is based on the minimization of the total-energy functional $E[\rho]$ with respect to the electron density ρ . In the Kohn-Sham (KS) scheme, which is typically employed for practical calculations, this procedure is formulated as the self-consistent solution of single-particle KS equations,

$$(-\nabla^2 + V_{\text{KS}}[\rho])\psi_i[\rho] = \varepsilon_i\psi_i[\rho], \quad (1)$$

which are combined with the equation for the electron density:

$$\rho = \sum_i f_i |\psi_i|^2, \quad (2)$$

defined in terms of eigenfunctions (ψ_i), eigenvalues (ε_i), and the occupation numbers (f_i) of KS quasiparticles.

The LSDA provides an explicit expression for $V_{\text{KS}}[\rho]$. However, it is based on the homogeneous electron-gas model, and strictly speaking applicable only for itinerant electron compounds.

The recent progress, which gave rise to such directions as LDA+Hubbard U (Refs. 2–4) and LDA+DMFT (dynamical mean-field theory),^{5,6} is based on the idea of partitioning of electronic states. It implies the validity of the following postulates.

(i) All solutions of KS equations (1) in LDA can be divided (by introducing proper projection operators) into two subgroups: $i \in I$, for which LSDA works reasonably well, and $i \in L$, for which LSDA encounters serious difficulties and needs to be improved (a typical example is the $3d$ states in transition-metal oxides and some transition metals).

(ii) Two orthogonal subspaces, I and L , are “flexible” in the sense that they can be defined for a wider class of electron densities, which can be different from the ground-state density in LDA. This allows us to “improve” LDA by adding a proper correction $\Delta\hat{\Sigma}$ (generally, an ω -dependent self-energy) to the KS equations, which acts solely in the L subspace but may also affect the I states through the change of ρ associated with this $\Delta\hat{\Sigma}$. Thus, in the KS equations, the L and I states remain decoupled even after including $\Delta\hat{\Sigma}$: $\langle \psi_{i \in I}[\rho] | (-\nabla^2 + V_{\text{KS}}[\rho] + \Delta\hat{\Sigma}) | \psi_{i \in L}[\rho] \rangle = 0$. For many applications, the L states are atomic or Wannier-type orbitals. Then, the description of electronic states in the L space becomes equivalent to the solution of a multiorbital Hubbard-type model, and the formulation of the LDA+ U approach is basically dealing with the question of how to map the LDA band structure onto this Hubbard model. In the following, by referring to the LDA+ U we will mean not only the static version of this method, originally proposed in Ref. 2, but also its recent extensions designed to treat dynamics of cor-

related electrons and employing the same idea of partitioning of the electronic states.^{5,6}

(iii) All physical interactions, which contribute to $\Delta\hat{\Sigma}$, can be formally derived from LDA by introducing certain constraining fields $\{\delta\hat{V}_{\text{ext}}\}$ in the subspace of L states (i.e., in a way similar to $\Delta\hat{\Sigma}$). The purpose of including these $\{\delta\hat{V}_{\text{ext}}\}$ is to simulate the change of the electron density $\delta\rho$ and to extract parameters of electronic interactions by mapping the total-energy difference $E[\rho+\delta\rho]-E[\rho]$ onto the Hubbard model. The total-energy difference is typically evaluated in LDA,⁷ and the method itself is called the constraint LDA (CLDA).⁸⁻¹¹

However, despite a decade of more or less successful applications, the central question of LDA+ U is not completely solved and continues to be the subject of various disputes and controversies.¹²⁻¹⁷ This question is how to define the parameter of the effective Coulomb interaction U .

To begin with, the Coulomb U is *not* a uniquely defined quantity, as it strongly depends on the property for the description of which we want to correct our LDA scheme. One possible strategy is the excited-state properties, associated with the complete removal of an electron from (or the addition of the new electron to) the system, i.e., the processes which are described by Koopman's theorem in Hartree-Fock calculations and which are corrected in the GW method by taking into account the relaxation of the wave functions onto the created electron hole (or a new electron).^{18,19} However, the goal which is typically pursued in LDA+ U is somewhat different. Namely, one would always like to stay as close as possible to the description of the ground-state properties. The necessary precondition for this, which should be taken into account in the definition of the Coulomb U and all other interactions which may contribute to $\Delta\hat{\Sigma}$, is the conservation of the total number of particles. In principle, similar strategy can be applied for the analysis of neutral excitations (e.g., by considering the ω dependence of $\Delta\hat{\Sigma}$), for which the total number of electrons is conserved.⁶ The basic difference between these two processes is that the "excited" electron in the second case continues to stay in the system and may additionally screen the Coulomb U . This screening may also affect the relaxation effects.²⁰

The purpose of this paper is to clarify several questions related with the definition of the Coulomb interaction U in transition metals. We will discuss both the momentum (\mathbf{q}) and energy (ω) dependence of U , corresponding to the response of the Coulomb potential onto the site (\mathbf{R}) and time (t) dependent perturbation $\delta\hat{V}_{\text{ext}}$, and present a comparative analysis of the existing methods of calculations of this interaction, like CLDA and GW. We will argue that, despite a common belief, the GW method does not take into account the major effect of screening of the effective Coulomb interaction U between the $3d$ electrons by the (itinerant) $4sp$ electrons. This channel of screening is automatically included in CLDA, though it may be affected by some additional approximations, which typically supplement the CLDA approach in order to separate the $3d$ and $4sp$ states. In the GW approach, the absence of the $4sp$ screening can be compensated, to a certain extent, by a proper choice of the pseudo-

Wannier orbitals, simulating the basis of L states. On the other hand, CLDA is a static approach, which does not take into account the ω dependence of effective U .²¹ We will consider mainly the ferromagnetic (FM) fcc Ni, although similar arguments can be applied for other metallic compounds. We start with the basic definition of U for the systems with the conserving number of particles, which was originally introduced by Herring,²² and then discuss the connection of this definition with the parameters which comes out from CLDA and GW calculations.

II. HERRING'S DEFINITION AND CLDA

According to Herring,²² the Coulomb U is nothing but the energy cost for moving an L electron between two atoms, located at \mathbf{R} and \mathbf{R}' , and initially populated by $n_{L\mathbf{R}}=n_{L\mathbf{R}'}\equiv n_L$ electrons:

$$U_{\mathbf{R}\mathbf{R}'} = E(n_{L\mathbf{R}} + 1, n_{L\mathbf{R}'} - 1) - E(n_{L\mathbf{R}}, n_{L\mathbf{R}'}). \quad (3)$$

In DFT, $U_{\mathbf{R}\mathbf{R}'}$ can be expressed in terms of the KS eigenvalues, $\varepsilon_{L\mathbf{R}} = \partial E / \partial n_{L\mathbf{R}}$, using Slater's transition state arguments:¹¹

$$U_{\mathbf{R}\mathbf{R}'} = \varepsilon_{L\mathbf{R}} \left(n_{L\mathbf{R}} + \frac{1}{2}, n_{L\mathbf{R}'} - \frac{1}{2} \right) - \varepsilon_{L\mathbf{R}} \left(n_{L\mathbf{R}} - \frac{1}{2}, n_{L\mathbf{R}'} + \frac{1}{2} \right). \quad (4)$$

The final definition

$$U_{\mathbf{R}\mathbf{R}'} = \left. \frac{\partial \varepsilon_{L\mathbf{R}}}{\partial n_{L\mathbf{R}}} \right|_{n_{L\mathbf{R}} + n_{L\mathbf{R}'} = \text{const}}, \quad (5)$$

which is typically used in CLDA calculations, is obtained after replacing the finite difference between two KS eigenvalues in Eq. (4) by their derivative. The parameter $U_{\mathbf{R}\mathbf{R}'}$ depends on the atomic indices \mathbf{R} and \mathbf{R}' . This dependence has a clear physical meaning and originates from the distance dependence of intersite Coulomb interactions, which contribute to the screening of $U_{\mathbf{R}\mathbf{R}'}$. In the reciprocal (Fourier) space, it is equivalent to the \mathbf{q} dependence of U .

Owing to the existence of the second subsystem I , the reaction (3) may compete with another one,

$$U = E(n_{L\mathbf{R}} + 1, n_{I\mathbf{R}} - 1, n_{L\mathbf{R}'} - 1, n_{I\mathbf{R}'} + 1) - E(n_{L\mathbf{R}}, n_{I\mathbf{R}}, n_{L\mathbf{R}'}, n_{I\mathbf{R}'}), \quad (6)$$

corresponding to independent "charge transfer" excitations at the sites \mathbf{R} and \mathbf{R}' .²³ It can be also presented in the form (5), but with the different constraint imposed on the numbers of L and I electrons: $n_{L\mathbf{R}} + n_{I\mathbf{R}} = \text{const}$. Generally, the definitions (3) and (6) will yield two different interaction parameters. Since in the charge-transfer scenario any change of $n_{L\mathbf{R}}$ is totally screened by the change of $n_{I\mathbf{R}}$ located at the same site, the interaction (6) does not depend on \mathbf{R} .

In reality, both processes coexist and the proper interaction parameter U is given by the following equation:

$$U_{\mathbf{R}\mathbf{R}'} = E(n_{L\mathbf{R}} + 1, n_{I\mathbf{R}} - \delta, n_{L\mathbf{R}'} - 1, n_{I\mathbf{R}'} + \delta) - E(n_{L\mathbf{R}}, n_{I\mathbf{R}}, n_{L\mathbf{R}'}, n_{I\mathbf{R}'}),$$

where the amount of charge δ redistributed between two sub-

systems is determined variationally to minimize $U_{\mathbf{RR}'}$. In the CLDA scheme, it is convenient to work in the reciprocal (Fourier) space and calculate $U_{\mathbf{q}}$ as the response to the \mathbf{q} -dependent constraining field,

$$\delta\hat{V}_{\text{ext}}(\mathbf{q}, \mathbf{R}) = V_L \cos \mathbf{q} \cdot \mathbf{R}, \quad (7)$$

acting in the subspace of L states under the general condition of conservation of the total number of particles. The results of these calculations will strongly depend on how well L -electrons are screened by the I ones. In the case of perfect (100%) screening, the reaction (6) will dominate, and the parameter U will not depend on \mathbf{q} . If the screening is not perfect (e.g., the change of the number of $3d$ electrons in the transition metals is screened to only about 50% by the $4sp$ electrons at the same atom¹⁰), it is reasonable to expect a strong \mathbf{q} dependence of the effective U , because two different channels of screening, given by Eqs. (3) and (6), will work in a different way for different \mathbf{q} 's. Since the excess (or deficiency) of L electrons caused by a uniform shift of the external potential $\delta\hat{V}_{\text{ext}}$ can be only compensated from the system of I electrons, the charge-transfer mechanism (6) will always dominate for small \mathbf{q} . The mechanism (3) becomes increasingly important near the Brillouin zone (BZ) boundary, and will generally compete with the charge-transfer excitations (6), depending on the distribution of the I -electron density.¹⁰

III. GW METHOD

It was recently suggested by several authors (e.g., in Refs. 4, 15–17, and 24 that the Coulomb U in the LDA+ U approach can be replaced by the screened Coulomb interaction W taken from the *ab initio* GW method. The latter is calculated in the random-phase approximation (RPA):^{15–17}

$$\hat{W}(\omega) = [1 - \hat{u}\hat{P}(\omega)]^{-1}\hat{u}. \quad (8)$$

We adopt the orthogonal atomiclike basis of linear muffin-tin orbitals (LMTOs) $\{\chi_\alpha\}$,²⁵ which specifies all matrix notations in Eq. (8). For example, the matrix of bare Coulomb interactions $e^2/|\mathbf{r}-\mathbf{r}'|$ has the form $\langle\alpha\beta|\hat{u}|\gamma\delta\rangle = e^2\int d\mathbf{r}\int d\mathbf{r}'\chi_\alpha^*(\mathbf{r})\chi_\beta^*(\mathbf{r}')|\mathbf{r}-\mathbf{r}'|^{-1}\chi_\gamma(\mathbf{r})\chi_\delta(\mathbf{r}')$, and all other matrices are defined in a similar way. The diagonal part of \hat{u} for the $3d$ states is totally specified by three radial Slater's integrals: F^0 , F^2 , and F^4 . In the following we will identify F^0 with the parameter of bare Coulomb interaction, which has the same meaning as the Coulomb U after taking into account all screening effects. F^2 and F^4 describe nonspherical interactions, responsible for Hund's rule.

The first advantage of RPA is that it allows us to handle the ω dependence of \hat{W} , which comes from the ω dependence of the polarization matrix \hat{P} . The most common approximation for \hat{P} , which is feasible for *ab initio* GW calculations, is that of noninteracting quasiparticles:^{18,19}

$$P_{\text{GW}}(\mathbf{r}, \mathbf{r}', \omega) = \sum_{ij} \frac{(f_i - f_j)\psi_i(\mathbf{r})\psi_i^*(\mathbf{r}')\psi_j^*(\mathbf{r})\psi_j(\mathbf{r}')}{\omega - \varepsilon_j + \varepsilon_i + i\delta(f_i - f_j)}, \quad (9)$$

which is typically evaluated starting with the electronic structure in LSDA (here the spin indices are already included in the definition of i and j). Generally speaking, the use of \hat{P}_{GW} is an additional approximation, which yields a new interaction \hat{W}_{GW} . At this stage, it is not clear whether it has the same meaning as the effective U derived from CLDA and whether Eq. (9) includes all necessary channels of screening. It may also include some other effects, which should be excluded from the final definition of U , in order to avoid the double counting. One is the self-screening arising from local (on-site) interactions between localized electrons. These interactions are not accurately treated in RPA.²⁶ Therefore the basic idea is to exclude these effects from the definition of \hat{W}_{GW} and to resort this part to the interaction term of the Hubbard model.²⁴ In this respect, the second important property of RPA is that it allows us to easily partition different contributions to \hat{P} and \hat{W} . If $\hat{P} = \hat{P}_1 + \hat{P}_2$ and \hat{W}_1 is the solution of Eq. (8) for $\hat{P} = \hat{P}_1$, the total \hat{W} can be obtained from the same equation after substitution of \hat{P} by \hat{P}_2 and \hat{u} by \hat{W}_1 . For example, if $\hat{P}_2 = \hat{P}_{LL}$ is the part of \hat{P}_{GW} which includes all possible transitions between the localized states, and $\hat{P}_1 = \hat{P}_r$ is the rest of the polarization matrix, the matrix \hat{W}_r , corresponding to \hat{P}_r , can be used as the interaction part of the Hubbard model.^{16,17}

GW story for fcc Ni

The ferromagnet fcc Ni is the most notorious example where LSDA encounters serious difficulties, especially for description of spectroscopic properties. There are three major problems:¹⁹ (i) the bandwidth is too large (overestimated by $\sim 30\%$); (ii) the exchange splitting is too large (overestimated by $\sim 50\%$); and (iii) the absence of the 6-eV satellite. The *ab initio* GW approach corrects only the bandwidth (although with a certain tendency to overcorrect), whereas the other two problems remain even in GW.^{19,27} Therefore, before doing any extensions on the basis of the GW method, it is very important to have a clear idea about its limitations. In this section we would like to clarify several confusing statements about screening of W in GW. We argue that the main results of the *ab initio* GW method can be explained, even quantitatively, by retaining, instead of the full matrix \hat{u} in Eq. (8), only the site-diagonal block \hat{u}_{LL} of bare Coulomb interactions between $3d$ electrons, in the atomiclike LMTO basis set. An intuitive reason behind this observation is the form of the polarization matrix (9), which can interact only with the matrix elements of \hat{u} of the exchange type. The latter are small unless they are calculated between orbitals of the same type, corresponding to the self-interaction. The values of radial Slater's integrals calculated in the basis of atomic $3d$ orbitals are $F^0 = 24.9$, $F^2 = 11.1$, and $F^4 = 6.8$ eV, respectively. All other interactions are considerably smaller. Hence it seems to be reasonable to adopt the limit $\hat{u}_{LL} \rightarrow \infty$, which

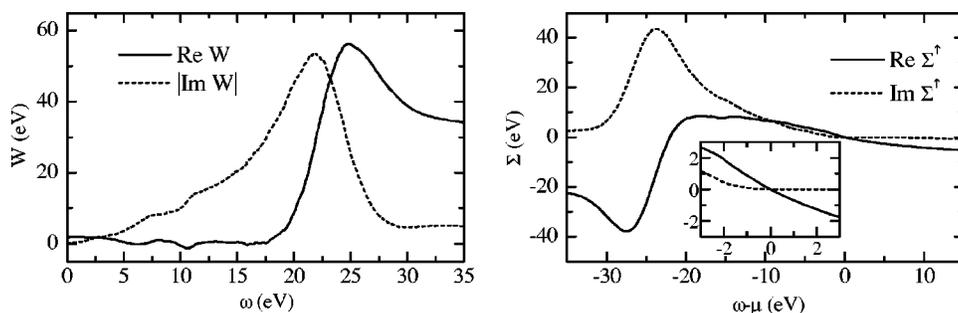


FIG. 1. Characteristic behavior of site-diagonal element of the screened Coulomb interaction $W = \langle xy | xy \rangle \hat{W}_{\mathbf{R}=0} | xy \rangle \langle xy |$ and the matrix element of the self-energy $\Sigma = \langle xy | \hat{\Sigma}_{\mathbf{q}=0}^{\uparrow} | xy \rangle$ between xy orbitals of the t_{2g} manifold in the Γ point of the Brillouin zone obtained in the GW approach with the bare Coulomb interactions between $3d$ electrons in the atomlike LMTO basis set. The inset shows amplified $\Sigma(\omega)$ near $\omega = \mu$. Matrix elements between e_g orbitals show a similar behavior.

automatically picks up in Eq. (8) only those matrix elements which are projected onto the atomic $3d$ orbitals, in the nearly-orthogonal LMTO representation (Ref. 25). In this sense the *ab initio* GW method for transition metals can be regarded as the RPA solution of the Hubbard model with the *bare* on-site interactions between $3d$ electrons defined in the basis of pseudoatomic LMTO orbitals. In the GW method, these interactions are practically not screened by outer electrons. Note, however, that the LMTO basis in the transition metals is generally different from the Wannier basis, which should be used for the construction of the Hubbard Hamiltonian. As it will become clear in Sec. VII, the Wannier representation has several additional features, which may modify conclusions of this section to a certain extent.

Results of these model GW calculations are shown in Fig. 1. In this case, the energy scale is controlled by the bare interaction F^0 , which predetermines the asymptotic behavior $\text{Re}W(\infty)$ (with W denoting the diagonal matrix element of \hat{W}) and the position of the poles of $\text{Im}W(\omega)$ (the so-called “plasmon structure”) at ~ 22 eV, which is related to the sharp increase of $\text{Re}W(\omega)$ at around 25 eV via the Kramers-Kronig transformation. At small ω , the behavior of $\hat{W}(\omega)$ is well consistent with the strong-coupling regime $F^0 \rightarrow \infty$: namely, $\hat{W}(\omega) \sim -\hat{P}^{-1}(\omega)$, which is small ($W \sim 1.8$ eV at $\omega=0$) and *does not depend on* F^0 (though it may depend on F^2 and F^4). All these features are in a good semiquantitative agreement with results of GW calculations.^{15–17,19}

The self-energy in GW is given by the convolution of \hat{W} with the one-particle Green function \hat{G} :

$$\hat{\Sigma}(\omega) = \frac{i}{2\pi} \int d\omega' \hat{G}(\omega + \omega') \hat{W}(\omega'). \quad (10)$$

Therefore the ω dependence of $\hat{\Sigma}$ should incorporate the main features of $\hat{W}(\omega')$. Indeed, the low-energy part of $\hat{\Sigma}$ (close to the Fermi energy or the chemical potential μ) is mainly controlled by $\text{Im}\hat{W}$. Since the main poles of $\text{Im}\hat{W}$ and $\text{Im}\hat{G}$ are well separated on the ω axis (the ω range of $\text{Im}\hat{G}$ is limited by the $3d$ bandwidth, ~ 4.5 eV in LSDA for fcc Ni, whereas the “plasmon peak” of $\text{Im}\hat{W}$ is located only at ~ 22 eV), one has the following relation:

$$\partial \Sigma / \partial \omega |_{\omega=\mu} \approx \frac{1}{\pi} \int_0^{\infty} d\omega \text{Im}W(\omega) / \omega^2. \quad (11)$$

This yields the renormalization factor $Z = (1 - \partial \Sigma / \partial \omega |_{\omega=\mu})^{-1} \sim 0.5$, which readily explains the reduction of the $3d$ bandwidth as well as of the intensity of the valence spectrum in *ab initio* GW calculations (Fig. 2).^{19,27}

Away from the Fermi energy (i.e., for energies $|\omega|$ which are much larger than the $3d$ bandwidth), one has another relation $\text{Re}\Sigma(\omega) \sim -\text{Re}W(\omega)$, which readily explains the existence of the deep minimum of $\text{Re}\Sigma(\omega)$ near -30 eV (see Fig. 1) as well as large transfer of the spectral weight into this region (shown in the inset of Fig. 2). The latter is expected when

$$\omega \approx \varepsilon_i + \text{Re}\Sigma(\omega),$$

which is the standard precondition for the appearance of the satellite structure in the GW approach.¹⁹ Therefore it is not quite right to say that the satellite structure is missing in the *ab initio* GW calculations for Ni. It may exist, but only in the wrong region of ω .

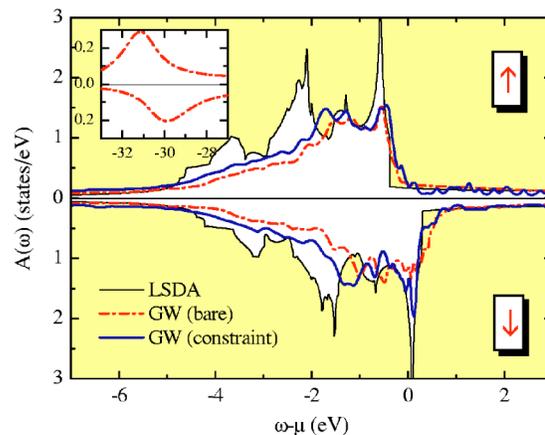


FIG. 2. The spectral function $A(\omega) = -(1/\pi) \text{Im} \text{Tr} \hat{G}(\omega) \text{sgn}(\omega - \mu)$ for fcc Ni in LSDA and two GW schemes with bare electronic interactions and parameters extracted from constraint LDA. The inset shows the satellite structure in $A(\omega)$ at the Γ point of the Brillouin zone in the bare-GW approach.

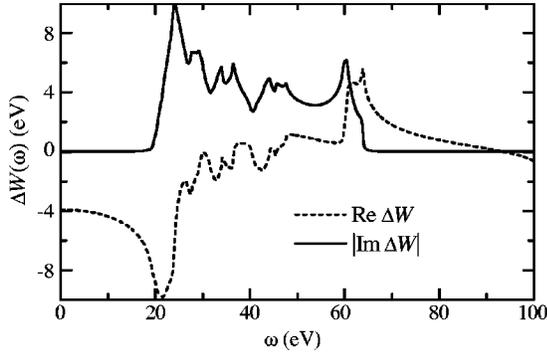


FIG. 3. The ω dependence of on-site Coulomb interaction associated with the relaxation of the $3d$ wave functions in the region of the $3d \rightarrow 4d$ transitions. The $3d \rightarrow 5d$ transitions have also been taken into account. They contribute to the region above 100 eV, which is not shown here.

Thus, even besides RPA, the major problem of the GW approach for the transition metals is the *wrong energy scale*, which is controlled by the bare on-site Coulomb interaction F^0 (~ 20 – 30 eV) between the $3d$ electrons. In summarizing this section we would like to stress again the following points:

(i) The major channel of screening of Coulomb interaction in the GW method for the transition metals originates from the $3d \rightarrow 3d$ transitions in the polarization function (calculated in the atomiclike LMTO basis). The screening by the $4sp$ electrons is practically absent;

(ii) At small ω , the deficiency of the $3d$ - $4sp$ screening is masked by the strong-coupling regime realized in RPA equations for screened Coulomb interaction, which explains a small value of $W(0)$ obtained in the GW calculations;

(iii) The main features of the ω dependence of $\hat{\Sigma}$ and \hat{W} in GW also comes from the $3d \rightarrow 3d$ transitions.

Different conclusions obtained in Refs. 16 and 17 are related with the use of different partitioning into what is called the “ $3d$ ” and “non- $3d$ ” (pseudo-)Wannier orbitals.²⁸ In light of the analysis presented in this section, the strong ω -dependent screening by the “non- $3d$ ” pseudo-Wannier states obtained in Refs. 16 and 17 means that in reality these states had a substantial weight of $3d$ character of the LMTO basis, which mainly contributed to the screening. We will return to this problem in Sec. VII.

The next important interaction, which contributes to the screening of F^0 in GW, is due to transitions between states with the same angular momentum: i.e., $3d \rightarrow nd$ ($n = 4, 5, \dots$) (see also comments in Sec. V A). In the lowest-order (non-self-consistent RPA), these contributions can be estimated as

$$\Delta W(\omega) \approx \langle 3d3d|\hat{u}|3d4d\rangle_{\text{av}}^2 P_{\text{GW}}(\omega, 3d \rightarrow 4d) + (\text{higher } n), \quad (12)$$

where $\langle 3d3d|\hat{u}|3d4d\rangle_{\text{av}} \approx 6.1$ eV is the spherical part of the exchange integral $\langle 3d3d|\hat{u}|3d4d\rangle$, corresponding to F^0 .²⁹ Results of these calculations are shown in Fig. 3. The region of $3d \rightarrow 4d$ transitions strongly overlaps with the “plasmon

peak” of $\text{Im}W(\omega)$ (Fig. 1). Therefore, in the GW calculations, these two effects are strongly mixed.^{15–17,19} The ω dependence of ΔW will also contribute to the renormalization of the low-energy part of the spectrum. In GW, this contribution can be estimated using Eq. (11), which yields $\partial \hat{\Sigma} / \partial \omega|_{\omega=\mu} \sim 0.06$. This contribution is small and can be neglected.

IV. GW VERSUS CLDA

What is missing in the *ab initio* GW method, and what is the relation between GW and CLDA? Let us consider for simplicity the static case, where $\delta \hat{V}_{\text{ext}}$ does not depend on time (the generalization to the time-dependent case is rather straightforward).

Eventually, both methods are designed to treat the response $\delta \rho(\mathbf{r})$ of the charge density (1) to the change of the external potential $\delta \hat{V}_{\text{ext}}$, which can be calculated in the first order of the regular perturbation theory. Then, $\delta \hat{V}_{\text{ext}}$ will affect both eigenvalues and eigenfunctions of the KS equations (1). The corresponding corrections are given by the matrix elements $\langle \psi_i | \delta \hat{V}_{\text{ext}} | \psi_j \rangle$ with $i=j$ and $i \neq j$, respectively. If two (or more) eigenvalues are located near the Fermi level, their shift can lead to the repopulation effects when some levels become occupied at the expense of others. This is a direct consequence of the conservation of the total number of particles, which affects the occupation numbers. Therefore, very generally, the total response $\delta \rho(\mathbf{r})$ in metals will consist of two parts, $\delta \rho(\mathbf{r}) = \delta_1 \rho(\mathbf{r}) + \delta_2 \rho(\mathbf{r})$, describing the change of the occupation numbers, $\delta_1 \rho(\mathbf{r}) = \sum_i \delta f_i |\psi_i(\mathbf{r})|^2$, and the relaxation of the wave function, $\delta_2 \rho(\mathbf{r}) = \sum_i f_i |\delta \psi_i(\mathbf{r})|^2$, respectively. Then, the polarization function P , defined as

$$\delta \rho(\mathbf{r}) = \int d\mathbf{r}' P(\mathbf{r}, \mathbf{r}', 0) \delta V_{\text{ext}}(\mathbf{r}'), \quad (13)$$

will also consist of two parts, P_1 and P_2 , which yield $\delta_1 \rho$ and $\delta_2 \rho$ after acting on δV_{ext} . Then, it is easy to verify by considering the perturbation-theory expansion for $\{\psi_i\}$ with respect to δV_{ext} that the GW approximation corresponds to the choice $P_1=0$ and $P_2=P_{\text{GW}}$. It yields $\delta_2 \rho(\mathbf{r})$, which further induces the new change of the Coulomb (Hartree) potential $\delta_2 V_{\text{H}}(\mathbf{r}) = e^2 \int d\mathbf{r}' \delta_2 \rho(\mathbf{r}') / |\mathbf{r} - \mathbf{r}'|$. By solving this problem self-consistently and taking the functional derivative with respect to $\delta_2 \rho$ one obtains the GW expression (8) for the screened Coulomb interaction $\hat{W}_{\text{GW}}(0)$. Therefore it is clear that the *ab initio* GW method takes into account only one part of the total response $\delta \rho$, describing the relaxation of the wave function with the fixed occupation numbers. Another contribution, corresponding to the change of the occupation numbers (or the charge redistribution near the Fermi level) is totally missing.

This result can be paraphrased in a different way, which clearly illustrates its connection with the definition of orthogonal subspaces, L and I , discussed in the introduction, and the partitioning of the polarization function P (Sec. III), which is used in the definition of the Hubbard model.^{16,17} First, recall that according to the main idea of the LDA+U

method (see postulates (i) – (iii) of the Introduction), $\delta\hat{V}_{\text{ext}}$ should be a projector-type operator acting in the subspace of the L states. Then, the result of the action of the polarization function $P_{\text{GW}} \equiv P_2$, given by Eq. (9), onto this $\delta\hat{V}_{\text{ext}}$ will belong to the same L space. Therefore the projection $\delta\hat{V}_{\text{ext}}$ will generate only that part of the polarization function, which is associated with the transitions between localized states (\hat{P}_{LL} in Sec. III). Meanwhile, this polarization effect should be excluded from the final definition of the parameter U in the Hubbard model to avoid the double counting.^{16,17} However, if \hat{P}_{LL} is excluded, there will be nothing left in the polarization function (9) that can interact with $\delta\hat{V}_{\text{ext}}$ and screen the change of the electron density in the L subspace. Therefore the GW scheme should correspond to the bare Coulomb interaction, that is totally consistent with the analysis presented in Sec. III.

Basic difficulties for transition metals

There is certain ambiguity in the construction of the Hubbard model for the transition metals, which is related with the fact that their LDA electronic structure cannot be described in terms of fully separated L and I states without additional approximations. In this section we briefly review two such approximations, which will explain the difference of our point of view on the screening of Coulomb interactions in the transition metals from the one proposed in Refs. 16 and 17.

The GW approach employed in Refs. 16 and 17 implies that *all* electronic structure near the Fermi level can be described in terms of *only five* pseudo-Wannier orbitals of predominantly $3d$ character, which serve as the L states in the considered model. Generally, such L states are not the same as the LMTO basis functions and take into account the effects of hybridization between $3d$ and $4sp$ states. An example of such electronic structure, obtained after elimination of the $4sp$ states near the Fermi level through the downfolding procedure,³⁰ is shown in Fig. 4. Other possibilities of defining these pseudo-Wannier functions, which have been actually used in Refs. 16 and 17, are summarized in Ref. 28. Then, the remaining electronic states, which are orthogonal to these pseudo-Wannier orbitals, represent the I states. By the construction, the I states are expected to be far from the Fermi level. This may justify the use of the GW approximation for the screening of Coulomb interactions in the $3d$ -electron-like bands, formed by the pseudo-Wannier orbitals near the Fermi level, by the remote I states. The parameters of Coulomb interactions, constructed in such a way, correspond to the original Herring definition (3) in the basis of pseudo-Wannier orbitals. Formally, it should also include the charge redistribution effects near the Fermi level. However, in this case the charge redistribution goes between pseudo-Wannier orbitals of the same (L) type, which constitutes the basis of the Hubbard model. Therefore the effects of the charge redistribution can be taken into account by including the intra- as well as intersite Coulomb interactions in the Hubbard Hamiltonian. The latter can be evaluated in the GW approach, provided that the relaxation effects are not very

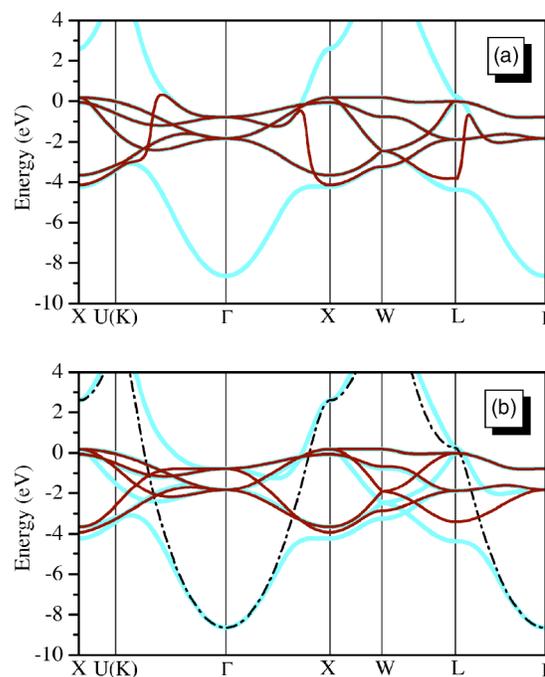


FIG. 4. Two approximate views on the electronic structure of (paramagnetic) fcc Ni underlying different schemes of calculation of the screened Coulomb interaction. The original LDA bands are shown by light color. The GW calculations are based on model (a), which implies that *all* electronic structure near the Fermi level (located at zero) can be described in terms of only *five* pseudo-Wannier orbitals of predominantly $3d$ character, simulating the L states. The dark bands show an example of such electronic structure obtained after elimination of $4sp$ states through the downfolding procedure (Ref. 30). The remaining electronic states are the I states, which are orthogonal to the pseudo-Wannier orbitals and allowed to screen the Coulomb interactions in these bands. The screening is treated in RPA. Model (b), which is used in constraint-LDA calculations, is obtained after neglecting the hybridization between $3d$ and $4sp$ states [the so-called canonical-bands approximation (Ref. 25)]. It consists of the $3d$ band (representing the L states and shown by dark color), embedded into the free-electron-like $4sp$ band (representing the I states and shown by dash-dotted line). The coexistence of two different groups of states near the Fermi level gives rise to the charge redistribution, which contribute to the screening of Coulomb interactions in the $3d$ band.

sensitive to whether the excited electron is placed on another L orbital of the same system, or completely removed from it, like in the GW method.

The model employed in CLDA calculations is obtained after neglecting the hybridization between $3d$ and $4sp$ states (the so-called canonical-bands approximation—Ref. 25). It consists of the pure $3d$ band, located near the Fermi level and representing the L states of the model, which is embedded into the free-electron-like $4sp$ band, representing the I states.³¹ Formally, these bands are decoupled and the free-electron-like $4sp$ band can be eliminated from the basis in the process of construction of the Hubbard Hamiltonian. However, in this case the definition of the screened Coulomb interaction in the $3d$ band should take into account the processes corresponding to redistribution of electrons between

$3d$ and $4sp$ bands at the low-energy cost, which is traced back to Herring's scenario of screening in the transition metals,²² and which is missing in the GW method.

However, we would like to emphasize again that both considered models are *approximations* to the real electronic structure of fcc Ni. Even in the first case [model (a) in Fig. 4], the free-electron-like $4sp$ band lies near the Fermi level (especially around the L point of the Brillouin zone). Therefore the charge redistribution effects are expected to play some role even in the basis of Wannier orbitals. On the other hand, because of strong hybridization between $3d$ and $4sp$ states in the transition metals, there is a substantial difference of electronic structure used in CLDA calculations [model (b) in Fig. 4] from the real LDA electronic structure of fcc Ni. Strictly speaking, all partial contributions to the screening of Coulomb interactions, which we will consider in the next section, will be evaluated for this particular model of the electronic structure. The values of these parameters can be revised to a certain extent after taking into account the hybridization between $3d$ and $4sp$ states. For example, with the better choice of the Wannier basis for the five $3d$ -electron-like bands in model (b) one could still possibly try to incorporate the main effects of model (a) and merge these two approaches.

V. CLDA FOR TRANSITION METALS

How important are the relaxation of the wave functions and the change of the occupation numbers in the definition of the Coulomb interaction U ? For the transition metals, both contributions can be easily evaluated in CLDA. For these purposes it is convenient to use the Hellman-Feinman theorem, which relates the static U with the expectation value of the KS potential $V_{\text{KS}} = V_{\text{H}} + V_{\text{XC}}$.¹¹

$$U = \langle 3d | \frac{\partial V_{\text{KS}}}{\partial n_{3d}} | 3d \rangle.$$

Then, the exchange-correlation (XC) part is small. δV_{H} can be expressed through $\delta\rho$. Hence the CLDA scheme provides the self-consistent solution for $\delta\rho$ associated with the change of the number of $3d$ electrons, δn_{3d} . The latter is controlled by δV_{ext} . Therefore the procedure is totally equivalent to the calculation of the polarization function P and the screened Coulomb interaction for $\omega=0$.

A. Conventions

We use a rather standard setup for the CLDA calculations. Namely, the $3d$ band of Ni should be well separated from the rest of the spectrum (otherwise, the LDA+ U strategy discussed in the Introduction does not apply). For fcc Ni this is not the case. However, this property can be enforced by using the canonical bands approximation in the LMTO method.²⁵ We employ even cruder approximation and replace the $3d$ band by the atomic $3d$ levels embedded into the $4sp$ band (in other words, we switch off the hybridization between $3d$ orbitals located at different atomic sites as well as the $3d$ and $4sp$ states).¹⁰ Then, each $3d$ orbital can be assigned to a single atomic site. By changing the number of $3d$

TABLE I. Partial contributions to the screening of the $3d$ interactions in the Γ point extracted from constraint-LDA calculations (in eV): (i) bare Coulomb integral F^0 , (ii) the screening of F^0 by the $4sp$ electrons associated with the change of occupation numbers, without relaxation of the wave functions ($\Delta^{(1)}F^0$), (iii) the additional screening of F^0 associated with relaxation of the $3d$ orbitals ($\Delta^{(2)}F^0$), and (iv) the total value of U obtained in CLDA calculations.

Compound	F^0	$\Delta^{(1)}F^0$	$\Delta^{(2)}F^0$	U
bcc Fe	22.2	-13.6	-3.5	4.5
fcc Ni	24.9	-14.2	-5.2	5.0

electrons at different atomic sites $\{\mathbf{R}\}$ in supercell calculations, one can mimic the \mathbf{q} dependence of the external potential (7). Other atomic populations (of the $4sp$ states) are allowed to relax self-consistently onto each change of the number of $3d$ electrons. Hence the contribution of the charge-transfer excitation (6) to the screening of U is unambiguously defined by the form of the external potential and details of the electronic structure of the $4sp$ states. Some aspects of treating the $3d$ states beyond the atomic approximation will be considered in Sec. VII.

The LMTO method is supplemented with an additional spherical approximation for $V_{\text{KS}}(\mathbf{r})$ inside atomic spheres, which bars small exchange interactions between $3d$ and $4sp$ electrons from the screening of U . By paraphrasing this statement in terms of the polarization function in the GW method, the spherical approximation for $V_{\text{KS}}(\mathbf{r})$ in the CLDA calculations is equivalent to retaining in P_{GW} only those contributions which are associated with transitions between states with the same angular momentum (e.g., $3d \rightarrow 4d$, etc.).

B. Screened Coulomb interaction in the Γ point

First, we evaluate the pure effect associated with the change of the occupation numbers, without relaxation of the wave functions. This mechanism is directly related with the conservation of the total number of particles, and simply means that the excess (or deficiency) of the $3d$ electrons for $\mathbf{q}=0$ is always compensated by the $4sp$ electrons, which participate in the screening of $3d$ interactions. The corresponding contribution to the screening of F^0 is given by¹¹

$$\Delta^{(1)}F^0 = \sum_{i \neq 3d} \frac{\delta f_i}{\delta n_{3d}} \langle 3di | \hat{u} | 3di \rangle_{\text{av}}.$$

In transition metals, $\Delta^{(1)}F^0$ is very large and takes into account more than 70% of screening of the bare Coulomb interaction F^0 (Table I). This contribution is missing in the GW method. The second largest effect ($\sim 25\%$ of the total screening) is caused by relaxation of the $3d$ orbitals onto the change of the Hartree potential associated with the change of these occupation numbers ($\Delta^{(2)}F^0$ in Table I). The remaining part of the screening ($\sim 5\%$) comes from the relaxation of other orbitals (including the core ones) and the change of the XC potential. In principle, the relaxation effects should be taken into account by the GW calculations. However, this

TABLE II. Coulomb interaction U (in eV) for fcc Ni in three different points of the Brillouin zone: $\Gamma=(0,0,0)$, $X=(2\pi,0,0)$, and $L=(\pi,\pi,\pi)$ (in units of $1/a$, where a is the cubic lattice parameter).

Γ	X	L
5.0	6.8	7.3

procedure strongly depends on the way it is implemented. For example, the CLDA approach is based on a direct solution of KS equations supplemented with a *flexible* atomic basis set, like in the LMTO method.²⁵ Then, the change of F^0 caused by relaxation of the $3d$ orbitals can be easily evaluated as¹¹

$$\Delta^{(2)}F^0 = \frac{n_{3d}}{2} \frac{\partial F^0}{\partial n_{3d}}.$$

Since n_{3d} is large in the fcc Ni, this contribution is also large. The situation can be different in the GW scheme, based on the perturbation theory expansion, which requires a large basis set.³² For example, in order to describe properly the same relaxation of the $3d$ wave functions, the polarization P_{GW} should explicitly include the excitation from the occupied $3d$ to the unoccupied $4d$ (and probably higher) states.¹⁹

C. \mathbf{q} dependence of Coulomb U

Since the change of the number of $3d$ electrons in transition metals is not totally screened by the $4sp$ electrons at the same atomic site,¹⁰ it is reasonable to expect an appreciable \mathbf{q} dependence of the effective U . Results of CLDA calculations for the high-symmetry points of the Brillouin zone are summarized in Table II. The effective U appears to be small in the Γ point due to the perfect screening by the $4sp$ electrons. At the Brillouin-zone boundary this channel of screening is strongly suppressed as is reflected in the larger values of the Coulomb U . The screening by intersite Coulomb interactions, which takes place in the X point of the BZ, is substantially weaker and cannot fully compensate the lack of the $4sp$ screening. In the L point of the BZ for the fcc lattice, the modulation of the $3d$ -electron density in the CLDA calculations is such that the number of nearest neighbors with an excessive and deficient number of $3d$ electrons is the same. Therefore the contributions of intersite Coulomb interactions to the screening are canceled out, resulting in the largest value of the effective U .

VI. GW STARTING WITH CLDA

In this section we discuss some relevance of parameters of effective Coulomb interactions extracted from CLDA for the analysis of electronic structure and properties of fcc Ni. We consider the “renormalized GW approach,” in which, instead of bare Coulomb interactions, we use parameters extracted from CLDA. The main difference is that the latter incorporates the screening by the $4sp$ electrons, including the effects of charge redistribution beyond the GW approximation. This strategy can be well justified within RPA, because it allows us to partition the polarization function and treat the screening effects in two steps:

(i) We take into account the screening by “non- $3d$ ” electrons using CLDA. This yields the new (“renormalized”) matrix of screened Coulomb interactions \hat{u}_{LL} between the $3d$ electrons.³³ As it was discussed in Sec. V C, the obtained interaction \hat{u}_{LL} is \mathbf{q} dependent, and this dependence is fully taken into account in our calculations.

(ii) We evaluate the screening caused by $3d \rightarrow 3d$ transitions in the polarization function (9) using Eq. (8) in which the matrix of bare Coulomb interactions \hat{u}_{LL} is replaced by \hat{u}_{LL} . This yields the new interaction $\hat{W}(\omega)$, which is used in subsequent calculations of the self-energy (10). It is reasonable to expect that the main ω dependence of \hat{W} will come from the $3d \rightarrow 3d$ transitions (see closing arguments in Sec. III), which are taken into account in the second step. The screening by “non- $3d$ ” states can be treated as static.

Results of these calculations are shown in Fig. 5. The main effect of the $4sp$ screening, beyond the standard GW approach, is the change of the energy scale, which is now controlled by the \mathbf{q} -dependent Coulomb interaction U , being of the order of 5.0–7.3 eV. It changes the asymptotic behavior $\text{Re}\bar{W}(\infty)$ as well as the position and the intensity of the “plasmon peak” of $\text{Im}\bar{W}(\omega)$, which is shifted to the lower-energies region and becomes substantially broader in comparison with the case of bare Coulomb interactions considered in Sec. III. On the other hand, the static limit $\text{Re}\bar{W} \approx 1.9$ eV is practically not affected by details of the $4sp$ screening, due to the strong-coupling regime realized in the low- ω region. The $\text{Re}\bar{W}$ exhibits a strong ω dependence at around 7 eV, which is related with the position of the plasmon peak of $\text{Im}\bar{W}(\omega)$. All these features are well reflected in the behavior of $\Sigma(\omega)$.

The main effect of the $4sp$ screening onto the spectral function in RPA consists in a somewhat milder reduction of

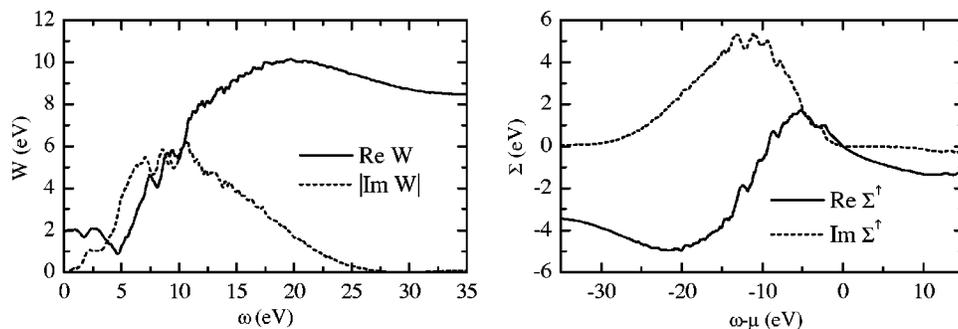


FIG. 5. The same as Fig. 1 but with parameters of Coulomb interactions extracted from CLDA.

the bandwidth, which is also related with the spectral weight transfer (Fig. 2): the new renormalization factor is $Z \sim 0.7$ against $Z \sim 0.5$ obtained with bare Coulomb interactions. However, the exchange splitting does not change and the 6-eV satellite structure does not emerge.

VII. SUMMARY AND REMAINING QUESTIONS

We have considered several mechanisms of screening of the bare Coulomb interactions between $3d$ electrons in transition metals. We have also discussed different methods of calculations of the screened Coulomb interactions. Our main results can be summarized as follows.

(i) The processes which mainly contribute to the screening of Coulomb interactions between $3d$ electrons are essentially local, meaning that the on-site Coulomb interactions are most efficiently screened by the $3d$ and $4sp$ electrons located at the same site.^{9,10,13} The most efficient mechanism of screening is basically the self-screening by the same $3d$ electrons, evaluated in some appropriate atomiclike basis, like that of the LMTO method employed in the present work. The ω dependence of the effective Coulomb interaction U also originates mainly from the self-screening.

(ii) We have clarified a fundamental difference between constraint-LDA and GW methods in calculating the effective Coulomb interaction U . The GW approximation does not take into account a screening of the on-site Coulomb interactions by the itinerant $4sp$ electrons, taking place via redistribution of electrons between $3d$ and $4sp$ bands.

In a number of cases, the GW approach may be justified by using Wannier basis functions, representing the bands near the Fermi level. If these bands are well isolated from the other bands, the redistribution of electrons between Wannier orbitals for the bands near the Fermi level and those far from the Fermi level must be negligible. Then, the remote bands can participate in the screening of Coulomb interactions in the “near-Fermi-level bands” only via virtual excitations, which can be treated on the RPA level.

However, in the case of Ni, such separation of bands is not complete, and it is essential to consider additional mechanisms of screening beyond the GW approximation. In the present work, the $4sp$ screening is automatically taken into account in the CLDA approach, which is complementary to the GW method. Due to the strong-coupling regime realized in RPA equations for the screened Coulomb interaction, the static limit appears to be insensitive to the details of the $4sp$ screening. However, from the viewpoint of the present approach, the $4sp$ screening becomes increasingly important at finite ω and controls both the asymptotic behavior and the position of the plasmon peak of the screened Coulomb interaction in RPA. The latter effect can be especially important as it predetermines the position of the satellite structure.

Finally, we would like to make several comments about implication of the parameters of screened Coulomb interaction obtained in our work for the description of electronic structure and properties of transition metals. We will also discuss some future directions and make a comparison with already existing works.

(i) Our results clearly show that RPA is not an adequate

approximation for the electronic structure of fcc Ni. Even after taking into account the additional screening of the $3d$ - $3d$ interactions by the itinerant $4sp$ electrons, beyond the GW approximation, and the \mathbf{q} dependence of the effective U , we obtain only a partial agreement with the experimental data. Namely, only the bandwidth is corrected in this “renormalized GW approach,” in a better agreement with the experimental data. However, there is only a tiny change of the spectral weight around 6 eV (Fig. 2), i.e., in the region where the satellite structure is expected experimentally. Even assuming that our parameters of Coulomb interactions may be still overestimated (due to the reasons which will be discussed below), and the satellite peak can emerge for some smaller values of U ,¹⁷ one can hardly expect the strong spin dependence of this satellite structure as well as the reduction of the exchange splitting, which are clearly seen in the experiment,³⁴ on the level of RPA calculations. Therefore it is essential to go beyond.

(ii) Even beyond RPA, do the parameters of screened Coulomb interaction $U \sim 5.0$ – 7.3 eV, obtained in the atomic approximation, provide a coherent description for the electronic structure and properties of fcc Ni? Probably this is still an open question because so far not all of the possibilities in this direction have been fully investigated. One interesting aspect suggested by our calculations is the \mathbf{q} dependence of the effective U . On the other hand, all previous calculations suggest that the Coulomb interaction of the order of 5.0–7.3 eV is probably too large; for example, the value of U , which provides a coherent description for a number of electronic and magnetic properties of fcc Ni on the level of DMFT calculations is about 3 eV,⁶ which is well consistent with the previous estimates based on the t -matrix approach.²⁶ Therefore is it reasonable to ask if there is an additional mechanism which further reduces the effective U from 5.0–7.3 to 3.0 eV? One possibility lies in the atomic approximation which neglects the hybridization effects between $3d$ and $4sp$ states, and which is a rather crude approximation for the transition metals.³¹ The hybridization will generally mix the states of the $3d$ and $4sp$ character, and therefore will affect the form of the Wannier orbitals constructed from the atomic wave functions. Since the $3d$, $4s$, and $4p$ states belong to different representations of the cubic symmetry group, they cannot mix at the same site. However, the $4s$ (or $4p$) orbital can have tails of the $3d$ character at the neighboring sites (and vice versa). These tails will additionally screen the Coulomb interactions between the (nominally) $3d$ electrons. The screening is expected to be very efficient because it operates between orbitals of the same ($3d$) type. It should explain further reduction of the static U obtained in the atomic approximation. Another feature of this screening is the ω dependence of the effective U , which comes from the $3d \rightarrow 3d$ transitions in the polarization function (namely between tails of the $4sp$ orbitals and the heads of the wave functions of the $3d$ character). In RPA, this ω dependence is directly related with the static limit of screening via the Kramers-Kronig transformation.¹⁹ We believe that the screening by the tails of the pseudo-Wannier functions was the main physical mechanism underlying the strong renormalization of the effective Coulomb interaction in Refs. 16 and 17, in the framework of the *ab initio* GW method. The

effect of charge redistribution between different states located near the Fermi level, which is not taken into account in the GW approximation, is also expected to be smaller with the proper choice of the Wannier orbitals.

Another problem is that the $3d$ and $4sp$ bands are strongly mixed in the case of pure transition metals. Therefore the construction of the separate Wannier functions of the “ $3d$ ” and “non- $3d$ ” type will always suffer from some ambiguities.²⁸ In this sense, the transition-metal oxides, whose physical properties are mainly predetermined by the behavior of a limited number of $3d$ bands, located near the Fermi level and well separated from the rest of the spectrum,

are much more interesting systems for the exploration of the idea of screening of Coulomb interactions, formulated on the basis of Wannier functions. For example, being based on the above argument, one can expect a very efficient screening of Coulomb interactions in the $3d$ band by the Wannier states constructed from the oxygen $2p$ orbitals, which have appreciable tails of the $3d$ character at the transition-metal sites. An attempt to consider this screening has been undertaken in Ref. 13, on the basis of the constraint-LDA method. A similar scheme can be formulated within RPA, which takes into account the ω dependence of the screened Coulomb interaction U . This work is currently in progress.

*Electronic address: igor@issp.u-tokyo.ac.jp

- ¹P. Hohenberg and W. Kohn, Phys. Rev. **136**, B864 (1964); W. Kohn and L. J. Sham, Phys. Rev. **140**, A1133 (1965).
- ²V. I. Anisimov, J. Zaanen, and O. K. Andersen, Phys. Rev. B **44**, 943 (1991).
- ³I. V. Solovyev, P. H. Dederichs, and V. I. Anisimov, Phys. Rev. B **50**, 16 861 (1994).
- ⁴V. I. Anisimov, F. Aryasetiawan, and A. I. Lichtenstein, J. Phys.: Condens. Matter **9**, 767 (1997).
- ⁵V. I. Anisimov, A. I. Poteryaev, M. A. Korotin, A. O. Anokhin, and G. Kotliar, J. Phys.: Condens. Matter **9**, 7359 (1997); S. Y. Savrasov, G. Kotliar, and E. Abrahams, Nature (London) **410**, 793 (2001); K. Held, G. Keller, V. Eyert, D. Vollhardt, and V. I. Anisimov, Phys. Rev. Lett. **86**, 5345 (2001).
- ⁶A. I. Lichtenstein, M. I. Katsnelson, and G. Kotliar, Phys. Rev. Lett. **87**, 067205 (2001).
- ⁷A great advantage of LSDA is that it satisfies a certain number of fundamental theorems [R. O. Jones and O. Gunnarsson, Rev. Mod. Phys. **61**, 689 (1989)], which makes the range of its applications much wider rather than the homogeneous electron gas. This probably explains why for many compounds LSDA provides a reasonable estimate for the parameter U (though there is no solid justification of why this is so).
- ⁸P. H. Dederichs, S. Blügel, R. Zeller, and H. Akai, Phys. Rev. Lett. **53**, 2512 (1984); M. Norman and A. Freeman, Phys. Rev. B **33**, 8896 (1986).
- ⁹O. Gunnarsson, O. K. Andersen, O. Jepsen, and J. Zaanen, Phys. Rev. B **39**, 1708 (1989).
- ¹⁰V. I. Anisimov and O. Gunnarsson, Phys. Rev. B **43**, 7570 (1991).
- ¹¹I. V. Solovyev and P. H. Dederichs, Phys. Rev. B **49**, 6736 (1994).
- ¹²M. Norman, Phys. Rev. B **52**, 1421 (1995); M. Brooks, J. Phys.: Condens. Matter **13**, L469 (2001).
- ¹³I. Solovyev, N. Hamada, and K. Terakura, Phys. Rev. B **53**, 7158 (1996).
- ¹⁴W. E. Pickett, S. C. Erwin, and E. C. Ethridge, Phys. Rev. B **58**, 1201 (1998).
- ¹⁵M. Springer and F. Aryasetiawan, Phys. Rev. B **57**, 4364 (1998).
- ¹⁶T. Kotani, J. Phys.: Condens. Matter **12**, 2413 (2000).
- ¹⁷F. Aryasetiawan, M. Imada, A. Georges, G. Kotliar, S. Biermann, and A. I. Lichtenstein, Phys. Rev. B **70**, 195104 (2004).
- ¹⁸L. Hedin, Phys. Rev. **139**, A796 (1965).

- ¹⁹F. Aryasetiawan and O. Gunnarsson, Rep. Prog. Phys. **61**, 237 (1998).
- ²⁰G. Onida, L. Reining, and A. Rubio, Rev. Mod. Phys. **74**, 601 (2002).
- ²¹An alternative is to calculate the response to the time-dependent (TD) external potential using TDDFT (Ref. 20).
- ²²C. Herring, in *Magnetism*, edited by G. T. Rado and H. Suhl (Academic, New York, 1966), Vol. IV.
- ²³J. Zaanen, G. A. Sawatzky, and J. W. Allen, Phys. Rev. Lett. **55**, 418 (1985).
- ²⁴S. Biermann, F. Aryasetiawan, and A. Georges, Phys. Rev. Lett. **90**, 086402 (2003).
- ²⁵O. K. Andersen, Phys. Rev. B **12**, 3060 (1975); O. Gunnarsson, O. Jepsen, and O. K. Andersen, *ibid.* **27**, 7144 (1983); O. K. Andersen and O. Jepsen, Phys. Rev. Lett. **53**, 2571 (1984).
- ²⁶A. Liebsch, Phys. Rev. Lett. **43**, 1431 (1979); Phys. Rev. B **23**, 5203 (1981).
- ²⁷A. Yamasaki and T. Fujiwara, J. Phys. Soc. Jpn. **72**, 607 (2003).
- ²⁸The scheme proposed by Kotani (Ref. 16) was based on a special construction of the LMTO basis set (Ref. 25). In the process of calculation of the screened Coulomb interaction \hat{W}_r , he excluded only the “heads” of the LMTO $3d$ -basis functions ϕ_{3d} (solutions of KS equations inside atomic spheres for a given energy E_ν), whereas the “tails” of the wave functions of the same $3d$ character, given by the energy derivatives $\dot{\phi}_{3d}$ of ϕ_{3d} , were allowed to screen \hat{W}_r . The idea was probably to go beyond the atomic approximation for the $3d$ states and to mimic the behavior of the Wannier functions. However, this procedure depends on the choice of $\{E_\nu\}$ and the LMTO representation (Ref. 25). For example, in the (most suitable for the construction of the Hubbard model) orthogonal representation, both ϕ_{3d} and $\dot{\phi}_{3d}$ can contribute to the “heads” of the basis functions as well as to their “tails.” On the other hand, Aryasetiawan and co-workers in Ref. 17 used the band picture and considered the screening of the “ $3d$ ” band by the “non- $3d$ ” (mainly $4sp$) ones. In reality, however, the $4sp$ band can carry a considerable weight of atomic $3d$ states, due to the hybridization. Moreover, the $3d$ and $4sp$ bands in the fcc Ni are well separated only along the $X\text{-}\Gamma\text{-}L$ direction of the BZ. Along other directions, there is a substantial band crossing (see Fig. 4) and this procedure is not well defined.
- ²⁹The $4d$ and $5d$ states were treated in the canonical bands approximation (Ref. 25). Since the energy distance between the $3d$ and

$4d$ (and higher) bands is much larger than the $3d$ bandwidth, one can neglect the dispersion of the $3d$ bands and relate $P_{\text{GW}}(\omega, 3d \rightarrow nd)$ with the local density of nd states.

³⁰I. V. Solovyev, Phys. Rev. B **69**, 134403 (2004).

³¹In fact, the considered example of the electronic structure where there is a narrow band, formed by some particular group of (L) states, embedded into the free-electron-like band is rather generic and equally applies to transition, rare-earth, and actinide metals. The main difference between these systems is the strength of hybridization between L and I states (which is the strongest in the case of transition metals), as well as in the system of L states.

³²M. S. Hybertsen and S. G. Louie, Phys. Rev. B **35**, 5585 (1987).

³³In addition to the parameter U , which has a meaning of screened Slater's integral F^0 , CLDA allows us to easily calculate the intra-atomic exchange coupling J (Ref. 2). The other two parameters, F^2 and F^4 , which specify the matrix \hat{u}_{LL} of screened Coulomb interactions between the $3d$ electrons, can be estimated from J using the ratio $F^4/F^2 \approx 0.63$ corresponding to the atomic limit (Ref. 3).

³⁴A. Kakizaki, J. Fujii, K. Shimada, A. Kamata, K. Ono, K.-H. Park, T. Kinoshita, T. Ishii, and H. Fukutani, Phys. Rev. Lett. **72**, 2781 (1994).