

Nanotube field of C_{60} molecules in carbon nanotubes: Atomistic versus continuous approach

B. Verberck and K. H. Michel

Department of Physics, University of Antwerp, Groenenborgerlaan 171, 2020 Antwerpen, Belgium

(Received 23 December 2005; revised manuscript received 13 April 2006; published 21 July 2006)

We calculate the van der Waals energy of a C_{60} molecule when it is encapsulated in a single-walled carbon nanotube with discrete atomistic structure. Orientational degrees of freedom and longitudinal displacements of the molecule are taken into account, and several achiral and chiral carbon nanotubes are considered. A comparison with earlier work where the tube was approximated by a continuous cylindrical distribution of carbon atoms is made. We find that such an approximation is valid for high and intermediate tube radii; for low tube radii, minor chirality effects come into play. Three molecular orientational regimes are found when varying the nanotube radius.

DOI: [10.1103/PhysRevB.74.045421](https://doi.org/10.1103/PhysRevB.74.045421)

PACS number(s): 61.48.+c

I. INTRODUCTION

The discovery of carbon nanotubes (CNTs) by Iijima¹ and their subsequent large-scale production² was followed by the synthesis of CNTs filled with atoms and/or molecules. These novel hybrid materials often exhibit one-dimensional characteristics and are presently the subject of fundamental studies as well as research aiming at their application in nanotechnology. For a review on CNTs and their filling we refer to Refs. 3–6, respectively. Self-assembled chains of C_{60} fullerene molecules inside single-walled carbon nanotubes (SWCNTs), the so-called peapods,⁷ provide a unique example of such nanoscopic compound materials, and feature unusual electronic⁸ and structural properties. High-resolution transmission electron microscopy observations on CNTs filled sparsely with C_{60} molecules⁹ demonstrate the motion of the fullerene molecules along the tube axis and imply that the interaction between C_{60} molecules and the surrounding nanotube wall is due to weak van der Waals forces and not to chemical bonds.

Recently, the way the C_{60} molecules of a $(C_{60})_N@SWCNT$ peapod^{7,10}— N C_{60} molecules inside in a SWCNT—are packed in the encapsulating tube has been investigated both experimentally and theoretically.^{11–16} Obviously, the structure of a peapod is governed by the interactions between the C_{60} molecules, and by the way a C_{60} molecule interacts with the surrounding tube wall. Already when considering the stacking of cylindrically confined hard spheres, a possible rudimentary description of a $(C_{60})_N@SWCNT$ peapod, various chiral structures of the spheres stacking for varying tube radius are obtained.¹¹ In Ref. 12, Hodak and Girifalco calculated lowest-energy $(C_{60})_N@SWCNT$ peapod configurations by means of a continuum approach for the C_{60} -tube interaction: both a SWCNT and a C_{60} molecule are approximated as a homogeneous surface—cylindrical and spherical, respectively. Although in doing so any effect of tube chirality and/or molecular orientation cannot be accounted for, such a model provides useful information about the spatial arrangement of the spherical molecules in the tube. Ten different stacking arrangements were obtained for the tube radius R_T ranging from 6.27 Å to 13.57 Å. The simplest configuration (C_{60} “spheres” aligned linearly along the tube axis) occurs for the

smallest tubes ($6.27 \text{ \AA} \leq R_T \leq 7.25 \text{ \AA}$). Other phases consist of zigzag patterns or C_{60} balls forming helices. Some of the predicted phases have been observed experimentally.¹³ Interestingly, experimental observations of similar structures formed by C_{60} molecules inside BN nanotubes have been reported as well.¹⁷ An atomistic molecular dynamics study on the arranging of C_{60} molecules inside SWCNTs was carried out by Troche *et al.*;¹⁴ the C_{60} -tube interaction was modeled by adding carbon-carbon Lennard-Jones 6-12 potentials. Troche *et al.*¹⁴ concluded that the chirality of the encapsulating SWCNT has only a minor effect on the lowest-energy configuration of the C_{60} molecules and their obtained arrangements, thus depending on the tube radius only, are in full agreement with those of Hodak and Girifalco.¹² Conclusions on the individual orientations of C_{60} molecules inside a SWCNT were not given by Troche *et al.*¹⁴—their goal was to study the packing of several molecules. Molecular orientation effects are expected to come into play at sufficiently low temperatures when orientational motion is frozen, and indeed do so as was shown in Refs. 15 and 16, where the potential energy of a single C_{60} molecule confined to the tube axis of a SWCNT, called “nanotube field,” was calculated by treating the tube as a homogeneous cylindrical carbonic surface density but retaining the icosahedral features of a C_{60} molecule. A specific dependence on the tube radius was found; three distinct molecular orientations were observed within the range $6.5 \leq R_T \leq 8.5 \text{ \AA}$. It is our opinion that, for calculating tube- C_{60} interactions, taking the detailed molecular structure of a C_{60} molecule into account has priority over the chiral structure of a nanotube. Replacing a SWCNT by a continuous cylindrical distribution of carbon atoms is intuitively justifiable, but treating a C_{60} molecule as a sphere (as in Ref. 12) with no further structure is a more questionable approximation. Indeed, whereas the carbon-carbon bonds in a CNT are of one type, a C_{60} molecule features longer (“single”) and shorter (“double”) bonds, arranged in pentagons—electron-poor regions—and hexagons—electron-rich regions. The importance of taking the detailed molecular structure properly into account follows from Refs. 15 and 16; but the neglect of the discrete atomistic structure of the tube when considering C_{60} -tube interactions, although intuitively plausible, requires solid grounds. The goal of this paper is to answer the question of

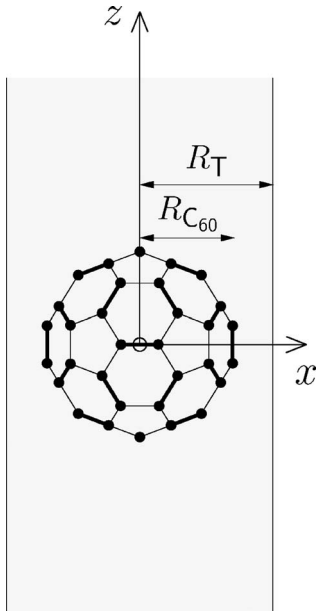


FIG. 1. A single C₆₀ molecule (radius $R_{C_{60}}$) in a SWCNT (radius R_T). Shown is a projection onto the (x, z) -plane. The center of mass of the C₆₀ molecule is chosen as the coordinate system's origin. The tube's long axis coincides with the z axis; the C₆₀ molecule is put in the standard orientation.

how good a smooth-tube approximation really is, and to confirm the relevance of the precise structure of a C₆₀ molecule, i.e., the importance of allowing for molecular orientational degrees of freedom.

The content of the paper is as follows. In Sec. II, we discuss formulas for the calculation of the nanotube field of an encapsulated C₆₀ molecule for both a “continuous” and a “discrete” tube. Then (Sec. III), we plot nanotube fields for a selection of representative nanotubes and make preliminary visual comparisons between the two approaches. In Sec. IV, we present an all-variable treatment and apply it for tubes with intermediate and small tube radii. Finally, general conclusions are given (Sec. V).

II. NANOTUBE FIELD

We consider a C₆₀ molecule in a SWCNT, the molecule assuming a centered position in the tube, and set up a Cartesian system of axes (x, y, z) so that the z axis coincides with the tube's long axis and contains the molecule's center of mass (Fig. 1). The potential energy V of the C₆₀ molecule then depends on the orientation of the molecule, which can be characterized by three Euler angles (α, β, γ) , on the position of the molecule along the tube, i.e., the z coordinate of the molecular center of mass for which we write ζ , and on the tube indices³ (n, m) :

$$V \equiv V(\alpha, \beta, \gamma; \zeta; n, m). \quad (2.1)$$

For the Euler angles we use the convention of Ref. 18: a coordinate function $f(\vec{r}=(x, y, z))$ is transformed as $\mathfrak{R}(\alpha, \beta, \gamma)f(\vec{r})=f(\mathfrak{R}^{-1}(\alpha, \beta, \gamma)\vec{r})$, where $\mathfrak{R}(\alpha, \beta, \gamma)=\mathfrak{R}_z(\gamma)\mathfrak{R}_y(\beta)\mathfrak{R}_z(\alpha)$ stands for the succession of a rotation

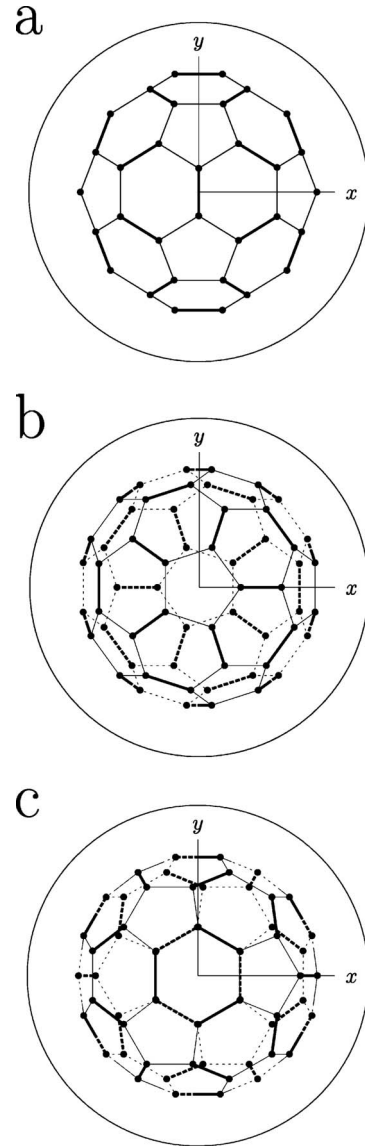


FIG. 2. Special orientations of the C₆₀ molecule: (a) standard orientation ($\alpha=\beta=\gamma=0$, double bonds perpendicular to the z axis), (b) pentagonal orientation (pentagons perpendicular to the z axis), (c) hexagonal orientations (hexagons perpendicular to the z axis). Double bonds are drawn bolder than single bonds; dashed lines are located “beneath” the (x, y) plane ($z \leq 0$). The surrounding tube is represented as a circular projection onto the (x, y) plane. Note that a rotation about the z axis over $-\alpha$ does not change double bonds, pentagons or hexagons—for parts (a), (b), and (c), respectively—being perpendicular to the z axis.

over $0 \leq \alpha < 2\pi$ about the z axis, a rotation over $0 \leq \beta \leq \pi$ about the y axis, and a rotation over $0 \leq \gamma < 2\pi$ about the z axis again. The x -, y - and z -axes are kept fixed. Note that the coordinate transform associated with the Euler angles reads $\vec{r}'=\mathfrak{R}^{-1}(\alpha, \beta, \gamma)\vec{r}=\mathfrak{R}_z(-\alpha)\mathfrak{R}_y(-\beta)\mathfrak{R}_z(-\gamma)\vec{r}$ and that the rotation of the C₆₀ molecule over $-\alpha$ about the z axis is performed last. As the starting orientation [$(\alpha=0, \beta=0, \gamma=0)$] we take the so-called standard orientation [Fig. 2(a)]: two-fold molecular symmetry axes then coincide with the Cartesian axes and every Cartesian axis intersects two opposing double bonds. (We recall that the carbon-carbon bonds of a

C₆₀ molecule can be divided into two categories: 60 single bonds, fusing pentagons and hexagons, and 30 double bonds, fusing hexagons. The latter are somewhat longer than the former.¹⁹ Bearing in mind the results of Refs. 15 and 16 and anticipating the results obtained in the present work, we point out two more molecular orientations of importance. The first is the ‘‘pentagonal’’ orientation class, obtained by the Euler transformation (α arbitrary, $\beta = \cos^{-1} \frac{2}{\sqrt{10+2\sqrt{5}}} \approx 58^\circ$, $\gamma=0$), resulting in two opposing pentagons of the C₆₀ molecule being perpendicular to the z axis [Fig. 2(b)]. The second is the category of ‘‘hexagonal’’ orientations, a result of the Euler transformation (α arbitrary, $\beta = \cos^{-1} \frac{1+\sqrt{5}}{2\sqrt{3}} \approx 21^\circ$, $\gamma=0$), making two opposing hexagons lie perpendicular to the z axis [Fig. 2(c)]. The angle $\beta_0 = \cos^{-1} \frac{1+\sqrt{5}}{2\sqrt{3}}$ is related to the dihedral angle ψ (the inner angle between adjacent faces) of a regular icosahedron: $\psi = \pi - 2\beta_0$. Other (β, γ) pairs yield pentagonal, hexagonal, and ‘‘double-bond’’ orientations as well: 12 pairs correspond to a pentagonal, 20 pairs to a hexagonal, and 30 pairs to a double-bond orientation since a C₆₀ molecule has 12 pentagons, 20 hexagons, and 30 double bonds.

For the description of the interaction between the C₆₀ molecule and the nanotube we follow earlier work²⁰ and treat the C₆₀ molecule as a rigid cluster of interaction centers (ICs). Not only C atoms (‘‘a’’) act as ICs, but also double bonds (‘‘db’’) and single bonds (‘‘sb’’). We label the 60 atoms by the index $\lambda_a = 1, \dots, 60$. In the center of every one of the 60 single bonds an IC is put, labeled by the index $\lambda_{sb} = 1, \dots, 60$. On each of the 30 double bonds, 3 ICs dividing the bond in four equal parts are put, totaling to 90 db ICs, labeled $\lambda_{db} = 1, \dots, 90$. Such a construction was originally introduced for modeling intermolecular interactions in solid C₆₀ (C₆₀ fullerite); having three ICs per double bond reflects the electronic density being smeared out along a double bond.²⁰

Every IC of the C₆₀ molecule interacts with every atom of the nanotube via a pair interaction potential $v^t(|\vec{r}_\tau - \vec{r}_{\lambda_t}|)$, depending on the type of IC ($t = a, db, sb$). The total potential energy is then obtained by summing over all pair interactions:

$$V = \sum_{\tau} \sum_{t=a,db,sb} \sum_{\lambda_t} v^t(|\vec{r}_\tau - \vec{r}_{\lambda_t}|), \quad (2.2a)$$

where τ indexes the atoms of the tube and \vec{r}_τ stands for their respective coordinates. As in Refs. 15 and 16, we use Born-Mayer-van der Waals pair interaction potentials:

$$v^t(r) = C_1^t e^{-C_2^t r} - \frac{B^t}{r^6}. \quad (2.2b)$$

Again, the use of such pair potentials was originally introduced for studying C₆₀-C₆₀ interactions in C₆₀ fullerite;²⁰ it led to a crystal field potential and a structural phase transition temperature^{21,22} in good agreement with the experiments. The potential constants C_1^t , C_2^t , and B^t used are those of Ref. 16. In Eq. (2.2a), the sum over tube atoms, labeled by the index τ and having coordinates $\vec{r}_\tau = (x_\tau, y_\tau, z_\tau)$, can be restricted to atoms in a certain vicinity of the C₆₀ molecule, realized by imposing the criterion

$$z_{\min} \leq z_\tau \leq z_{\max}, \quad (2.2c)$$

with z_{\min} and z_{\max} cutoff values ensuring convergence.

In Refs. 15 and 16, a smooth-tube approximation to Eq. (2.2a) was presented. The actual network of carbon atoms making up the SWCNT is replaced by a homogeneous, cylindrical ‘‘carbonic’’ surface density with value σ (units \AA^{-2}). The C₆₀ molecule-nanotube interaction energy is then rewritten as follows:

$$V_{\text{smooth}} = \sigma R_T \int_0^{2\pi} d\Phi \int_{-\infty}^{+\infty} dZ \sum_{t=a,db,sb} \sum_{\lambda_t} v^t(|\vec{\rho} - \vec{r}_{\lambda_t}|), \quad (2.3)$$

where $\vec{\rho} = (R_T, \Phi, Z)$ is the cylindrical coordinate of a point on the tube ($x = R_T \cos \Phi$, $y = R_T \sin \Phi$, $z = Z$) and R_T is the tube radius. The motivation for introducing approximation (2.3) is twofold. One reason is the dependence of V_{smooth} on the tube radius R_T rather than on the tube indices (n, m). Indeed, R_T remains the only relevant tube-characteristic parameter and as such simplifies a systematic investigation of carbon nanotubes. A further consequence of the tube’s cylindrical symmetry is the irrelevance of the Euler angle α (a final rotation of the C₆₀ molecule over $-\alpha$ about the tube axis does not matter) and of the z coordinate ζ (for infinite or long-enough tubes). A second advantage of the smooth-tube ansatz is the possibility of performing an expansion of V_{smooth} into symmetry-adapted rotator functions, a point we will return to in Sec. V. We stress the limited dependence of V_{smooth} by writing

$$V_{\text{smooth}} \equiv V_{\text{smooth}}(\beta, \gamma; R_T). \quad (2.4)$$

To distinguish the smooth-tube approximation from the discrete case, we add the subscript discrete:

$$V \equiv V_{\text{discrete}}(\alpha, \beta, \gamma; \zeta; n, m), \quad (2.5)$$

where the actual expression is given by Eqs. (2.2a), (2.2b), and (2.2c).

In this paper we test the validity of smooth-tube approximation (2.3) by comparing V_{discrete} and V_{smooth} for a selection of tubes. Bearing in mind the three qualitatively different radii ranges ($R_T \leq 7 \text{\AA}$, $7 \text{\AA} \leq R_T \leq 7.9 \text{\AA}$, and $7.9 \text{\AA} \leq R_T$) obtained in Ref. 16, we have selected zig-zag, armchair, and chiral tubes with radii around $R_T = 6.5 \text{\AA}$, $R_T = 7.5 \text{\AA}$, and $R_T = 8.5 \text{\AA}$. We have generated (n, m) tubes starting from a graphene sheet with basis vectors $\vec{a}_1 = a\vec{e}_x$ and $\vec{a}_2 = \frac{1}{2}a\vec{e}_x + \frac{\sqrt{3}}{2}a\vec{e}_y$, where \vec{e}_x and \vec{e}_y are planar Cartesian basis vectors, and performing the roll-up along the vector $\vec{C}(n, m) = n\vec{a}_1 + m\vec{a}_2$.^{3,23} The tube is then positioned so that the C atom originally (before rolling up) at $0\vec{e}_x + 0\vec{e}_y$ lies in the (x, y) plane with x coordinate 0 and y coordinate R_T and that the cylinder containing the C atoms has its long axis coinciding with the z axis. The C₆₀ molecule is initially positioned so that its center of mass lies at the origin ($\zeta = 0$); a translation along the z axis away from the initial position is measured via the center of mass’ z coordinate ζ . The radius

TABLE I. Characteristics of selected (n, m) tubes. Tubes of all types (zigzag, chiral, and armchair) with radii R_T as close to 6.5 Å, 7.5 Å, and 8.5 Å as possible were chosen. The angle $\Delta\alpha$ is the rotational period of the tube when performing a rotation about the z axis. An expression for the calculation of the translational periodicity Δz is given in Ref. 3.

(n, m)	Chirality	R_T (Å)	$\Delta\alpha$	Δz (Å)
(16,0)	zig-zag	6.3407	$2\pi/16$	$\sqrt{3}a=4.3128$
(14,4)	chiral	6.4876	$2\pi/2$	35.3018
(9,9)	armchair	6.1176	$2\pi/9$	$a=2.49$
(19,0)	zig-zag	7.5296	$2\pi/19$	$\sqrt{3}a$
(16,5)	chiral	7.5296	2π	81.9433
(11,11)	armchair	7.5504	$2\pi/11$	a
(21,0)	zig-zag	8.3222	$2\pi/21$	$\sqrt{3}a$
(21,1)	chiral	8.5273	2π	92.8005
(12,12)	armchair	8.2369	$2\pi/12$	a

of the tube with indices (n, m) reads $R_T = \frac{a}{2\pi} \sqrt{n^2 + nm + m^2}$, with $a = 2.49$ Å,^{3,23} the corresponding surface density has the value

$$\sigma = \frac{4}{\sqrt{3}a^2} = 0.372 \text{ Å}^{-2}. \quad (2.6)$$

A further tube parameter is its translational periodicity Δz , relevant when considering the ζ -dependence of V_{discrete} . While Δz is small for nonchiral—i.e., zigzag, $\Delta z = \sqrt{3}a$, and armchair, $\Delta z = a$ —tubes, the translational period can get very large for chiral tubes.³ A tube may also have an s -fold symmetry axis (coinciding with the z axis) and therefore a rotational period $\Delta\alpha = 2\pi/s$. When considering a tube with s -fold rotational symmetry it suffices to examine the interval $0 \leq \alpha < \Delta\alpha$. The periodicities and other tube characteristics of our selected tubes are listed in Table I.

III. MERCATOR MAPS

To get a preliminary idea of how V_{smooth} and V_{discrete} compare, we have simply plotted $V_{\text{smooth}}(\beta, \gamma, R_T)$ and $V_{\text{discrete}}(\alpha=0, \beta, \gamma; \zeta=0; n, m)$ for each of the selected (n, m) tubes in the form of Mercator maps.²⁴ We stress that $(\alpha=0, \zeta=0)$ is but a particular case and that final conclusions should be made not only on the variation of β and γ but on the varying of α and ζ as well, as we will do later on. We do point out, however, that we expect the α and ζ dependencies to be of a lesser magnitude than the β and γ dependencies since the former correspond to a (final) rotation of the molecule about the z axis (tube axis) over $-\alpha$ and a translation of the molecule along the z axis, respectively, and hence relate to the tube structure rather than to the molecule structure. (As argued in the Introduction, a carbon nanotube can be regarded as being more continuous than a C_{60} molecule.)

As for the cutoff values, we have found—for $\zeta=0$ —that $z_{\min} = -50$ Å and $z_{\max} = 50$ Å yield sufficient convergence. Note that the choice of z_{\min} and z_{\max} fixes the numbers N_T of atoms to be taken into account in sum (2.2a). In principle, the tube fragment of length $L = z_{\max} - z_{\min}$ has a surface density $\tilde{\sigma} = N_T / (2\pi R_T L)$, differing from σ . We observe that differences between σ and $\tilde{\sigma}$ are small, however. Although

possibly (slightly) enhancing the agreement between V_{discrete} and V_{smooth} , we have chosen not to calculate V_{smooth} with $\tilde{\sigma}$ since it somehow relates to the tube structure— N_T depends on (n, m) —hence surpassing the smooth-tube approach's underlying basic idea [R_T dependence rather than (n, m) dependence].

The Mercator maps $V_{\text{smooth}}(\beta, \gamma) \equiv V_{\text{smooth}}(\beta, \gamma; R_T)$ and $V_{\text{discrete}}(\beta, \gamma) \equiv V_{\text{discrete}}(\alpha=0, \beta, \gamma; \zeta=0; n, m)$, respectively calculated via Eqs. (2.2a), (2.2b), (2.2c) and (2.3) and both based on pair potential (2.2b), are shown as Figs. 3–5 for the tubes listed in Table I. Figures 3–5 are for tubes with radii around 6.5 Å, 7.5 Å, and 8.5 Å, respectively. Within each figure, subfigs. (a), (b), and (c) refer to zigzag, chiral, and armchair tubes; the left plot is V_{discrete} , the right V_{smooth} . Only the variation is plotted; for each plot the lowest occurring energy value, for which we write V^0 , has been subtracted to make the minima lie at zero. The V^0 values for V_{discrete} and V_{smooth} and the upper bounds of the left and right plots in Figs. 3–5 exhibit discrepancies. They originate from the intrinsic impossibility of the smooth-tube approximation to correctly account for the actual distribution of the carbon atoms on the cylinder. The wider the tube, the more atoms (the higher N_T), and the smaller the discrepancy: the (9,9) tube ($V_{\text{smooth}}^0 = 70\,111.5$ K, $V_{\text{discrete}}^0 = -79\,117.2$ K) exhibits the largest difference $V_{\text{discrete}}^0 - V_{\text{smooth}}^0$ while for the (21,1) tube the values V_{discrete}^0 and V_{smooth}^0 get very close ($V_{\text{smooth}}^0 = -31\,028.6$ K, $V_{\text{discrete}}^0 = -31\,033.9$ K). We point out that any continuum approach suffers from such a discrepancy, and that it cannot be resolved by replacing σ in Eq. (2.3) by the adjusted density $\tilde{\sigma} = N_T / (2\pi R_T 2z_{\max})$, a notion we illustrate in Appendix A. Nevertheless, it is not senseless at all to perform a smooth-tube approach, because conclusions are to be drawn based on the potential energy *variation*: of interest are the locations of energy minima, corresponding to molecular orientations which are most stable.

The V_{smooth} plots in Figs. 3(a)–3(c) are, apart from different energy ranges, similar. They exhibit 12 minima (white) and 20 maxima (darkest). (The γ coordinate, ranging from 0 to 2π , is cyclic, i.e., the molecular orientations at the $\gamma=0$ edge are repeated at the $\gamma=2\pi$ edge. The β coordinate is not cyclic: points along the $\beta=0$ and $\beta=\pi$ edges with equal γ refer to distinct configurations.) The 12 angle pairs

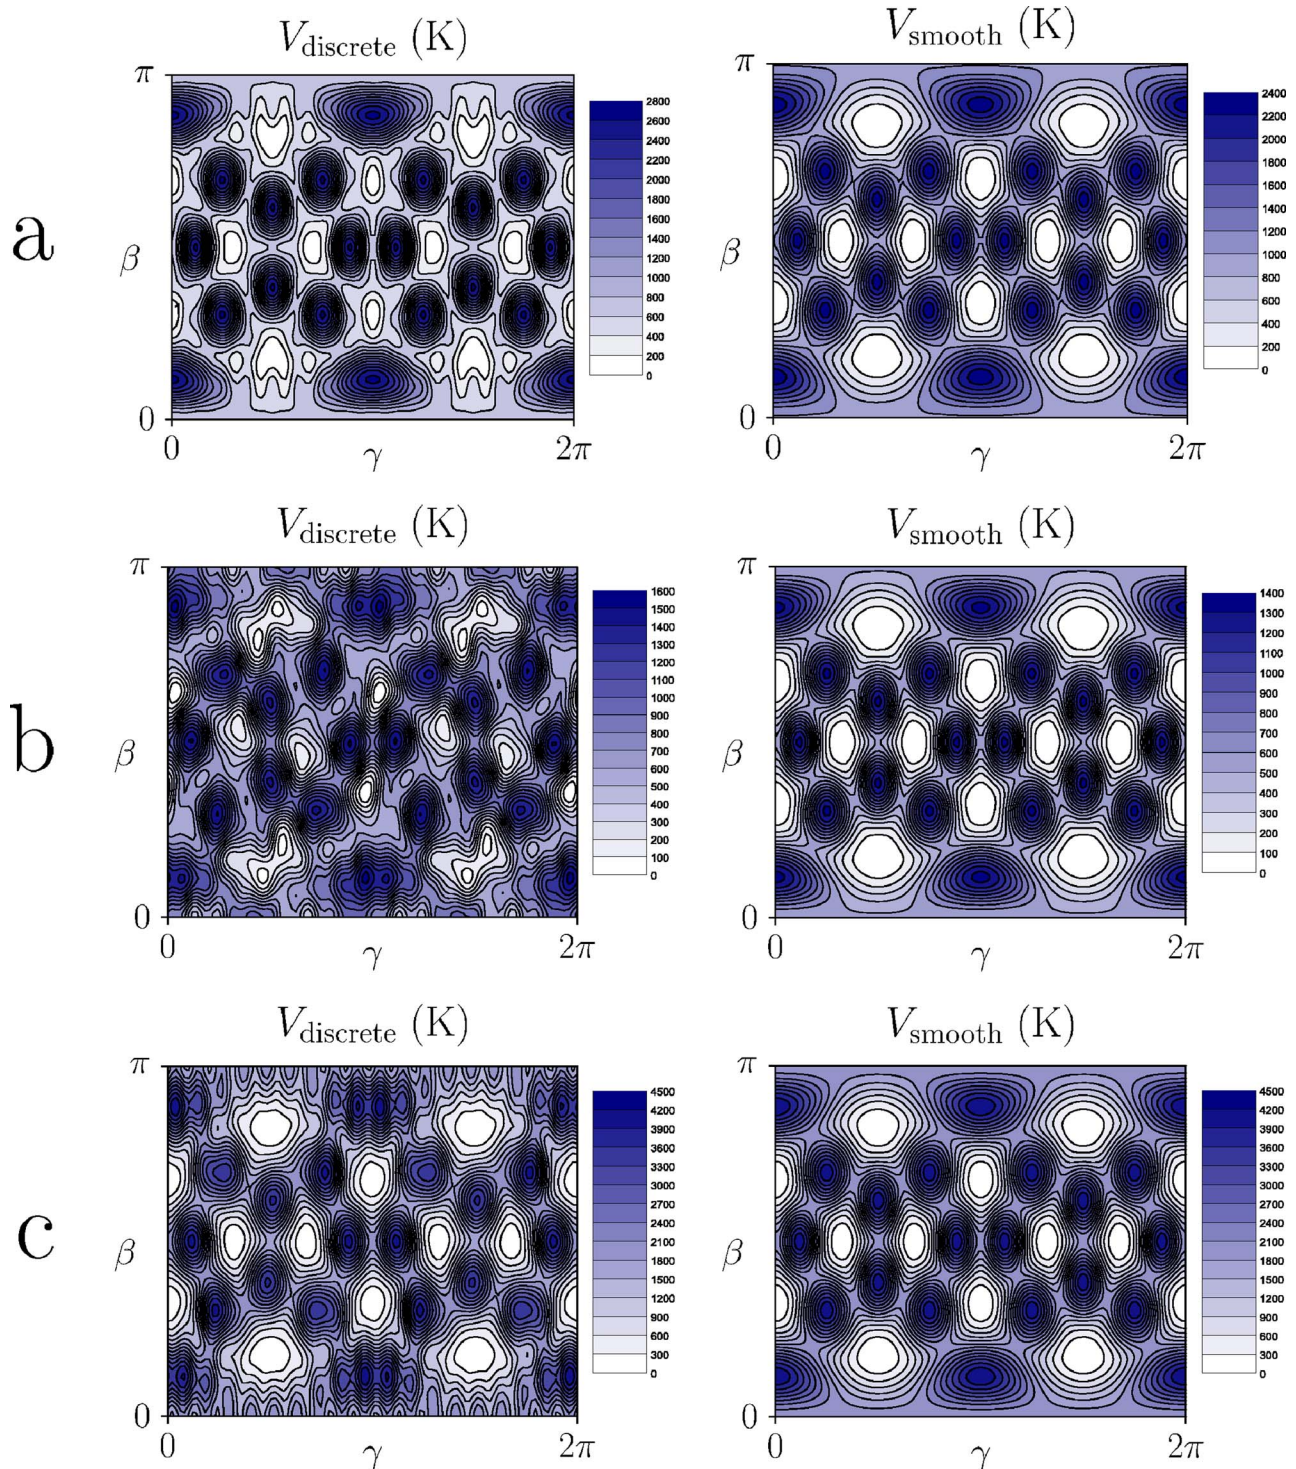


FIG. 3. (Color online) Mercator maps $V_{\text{discrete}}(\beta, \gamma)$ (left) and $V_{\text{smooth}}(\beta, \gamma)$ (right), units K: (a) $(n, m) = (16, 0)$, (b) $(n, m) = (14, 4)$, (c) $(n, m) = (9, 9)$. The absolute minima values have been subtracted.

(β_i, γ_i) corresponding to minimal-energy configurations are tabulated in Table II and indicated schematically in Fig. 6. Each of the 120 minima corresponds to a molecular orientation where two opposing pentagons of the C_{60} molecule are perpendicular to the tube axis [Fig. 2(b)]; the Euler transformations $(\alpha=0, \beta_i, \gamma_i)$, $i=1, \dots, 12$, yield four truly different types of orientations (Fig. 7 and Table II). The 20 maxima correspond to situations where two facing hexagons of the

C_{60} molecule are perpendicular to the z axis [Fig. 2(c)].

Comparing V_{discrete} and V_{smooth} of Fig. 3(a)–(16,0) tube—we see that the locations of minima and maxima hardly (or even do not) differ. For the (9,9) armchair tube, Fig. 3(c), the energy ranges coincide, and the minima locations of V_{discrete} and V_{smooth} are, if not coinciding, almost equal. Deviations are observed in Fig. 3(b) for the chiral (14,4) tube: the minima locations of V_{discrete} clearly deviate

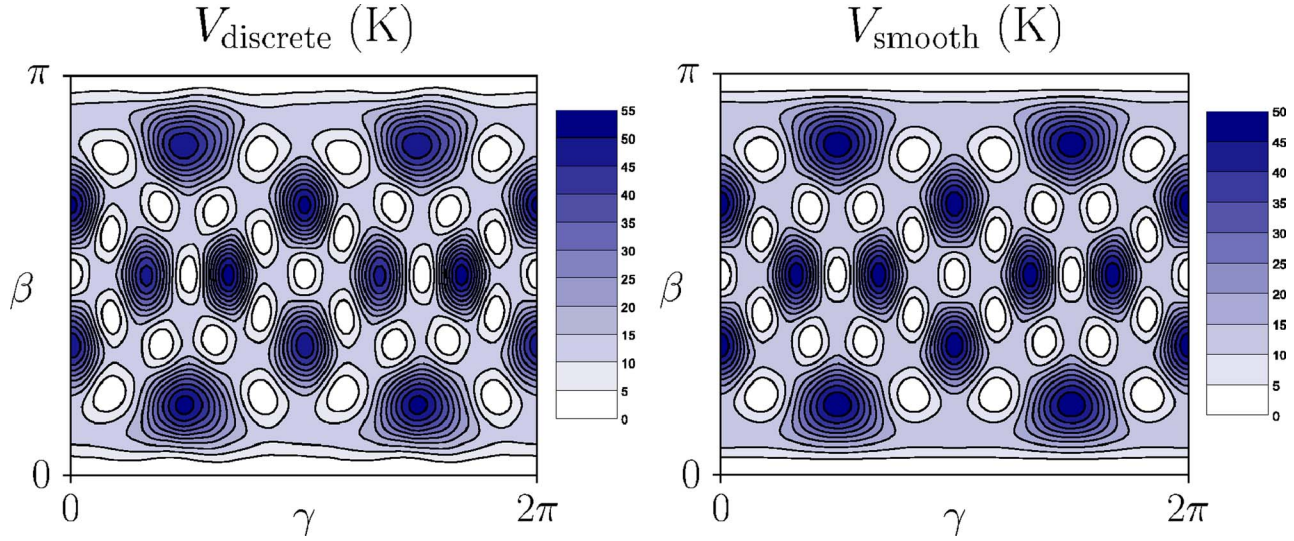


FIG. 4. (Color online) Mercator maps $V_{\text{discrete}}(\beta, \gamma)$ (left) and $V_{\text{smooth}}(\beta, \gamma)$ (right), units K, for the $(n, m)=(16, 5)$ tube. The minimal values have been subtracted. The maps for the cases $(n, m)=(19, 0)$ and $(11, 11)$ look very similar to the $(16, 5)$ maps.

somewhat from those of V_{smooth} ; some even “split into two.” The deviations are small, however: one may write the true V_{discrete} minima locations as $(\beta'_i = \beta_i + \Delta\beta_i, \gamma'_i = \gamma_i + \Delta\gamma_i)$. We estimate maximal deviation values at $|\Delta\beta_i| \approx 10^\circ$ and $|\Delta\gamma_i| \approx 12^\circ$.

For $R_T \approx 7.5 \text{ \AA}$ (Fig. 4), the V_{discrete} plots become extremely similar to the respective V_{smooth} plots. For all three investigated tubes— $(19, 0)$, $(16, 5)$, and $(11, 11)$ —the locations of minima (and maxima) can be concluded to coincide. The 30 minima correspond with two opposing double bonds being perpendicular to the tube axis [Fig. 2(a)]. Maximal energy occurs when two opposing pentagons are perpendicular to the tube axis (the 12 minimal-energy configurations for $R_T \approx 6.5 \text{ \AA}$, Fig. 3).

In Fig. 5, $R_T \approx 8.5 \text{ \AA}$, V_{discrete} and V_{smooth} match completely. With respect to Fig. 3, minima and maxima have been flipped: lowest-energy configurations now feature hexa-

gons perpendicular to the tube axis, pentagons perpendicular to the tube axis yield the highest energy.

Up to now, α and ζ have been kept fixed. To get an idea of the energy variation when α and ζ are allowed to vary, we have calculated $V_{\text{discrete}}(\alpha, \beta=0, \gamma=0; \zeta=0; n, m)$ and $V_{\text{discrete}}(\alpha=0, \beta=0, \gamma=0; \zeta; n, m)$, for $0 \leq \alpha \leq \Delta\alpha$ and $0 \leq \zeta \leq \Delta\zeta$, respectively. The tube-dependent rotational and translational periods $\Delta\alpha$ and $\Delta\zeta$ are given in Table I. In Table III, we summarize these calculations by listing the differences $\Delta_\alpha V_{\text{discrete}} = \max(V_{\text{discrete}}(\alpha, \beta=0, \gamma=0; \zeta=0; n, m)) - \min(V_{\text{discrete}}(\alpha, \beta=0, \gamma=0; \zeta=0; n, m))$ and $\Delta_\zeta V_{\text{discrete}} = \max(V_{\text{discrete}}(\alpha=0, \beta=0, \gamma=0; \zeta; n, m)) - \min(V_{\text{discrete}}(\alpha=0, \beta=0, \gamma=0; \zeta; n, m))$ conveying the energy variation. Clearly, the tubes with $R_T \approx 6.5 \text{ \AA}$ display fairly large energy fluctuations upon varying α and/or ζ , as one might intuitively guess from the jagged contours in Fig. 3 (left). For intermediate ($R_T \approx 7.5$)

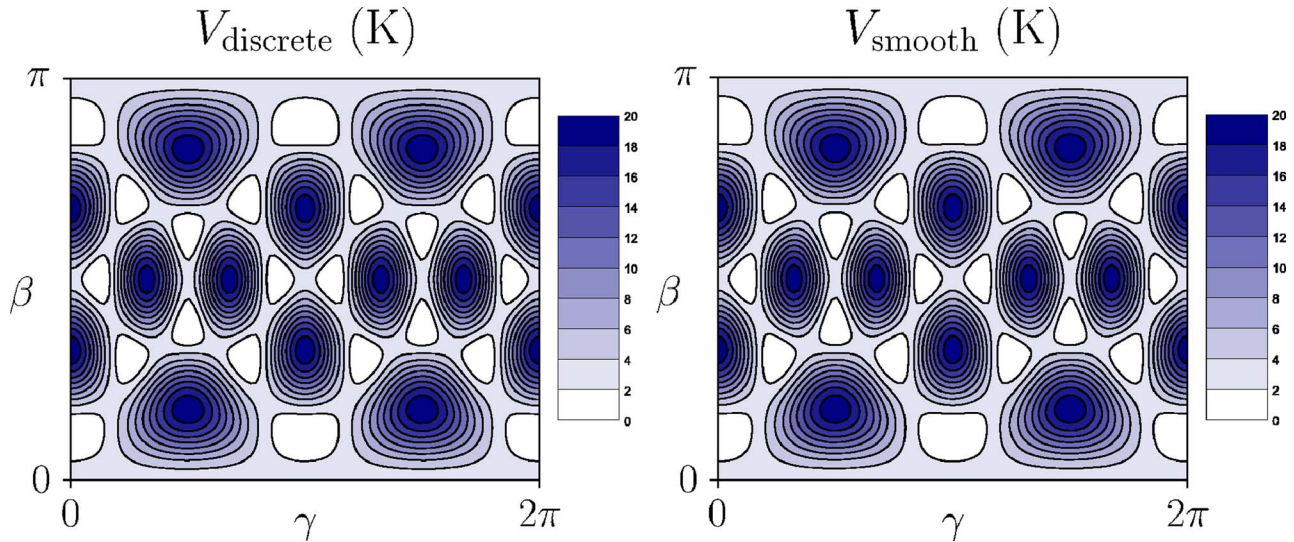


FIG. 5. (Color online) Mercator maps $V_{\text{discrete}}(\beta, \gamma)$ (left) and $V_{\text{smooth}}(\beta, \gamma)$ (right), units K, for the $(n, m)=(21, 1)$ tube. The minimal values have been subtracted. The maps for the cases $(n, m)=(21, 0)$ and $(12, 12)$ are very similar to the $(21, 1)$ maps.

TABLE II. Rotation angles β_i and γ_i , $i=1, \dots, 12$, the corresponding Euler transformations $\mathfrak{R}^{-1}(\alpha=0, \beta_i, \gamma_i)$ of which make two facing pentagons of the C₆₀ molecule lie perpendicular to the z axis. For small tubes (see Fig. 3), the minima of $V_{\text{smooth}}(\beta, \gamma)$ occur at these 12 molecular orientations. Four distinct molecular orientations, labeled I, II, III, and IV, are obtained, distinguishable by the orientation of the top ($z > 0$) pentagon (Fig. 7).

i	β_i	γ_i	Molecular Orientation
1	$\beta_0 = \cos^{-1} \frac{2}{\sqrt{10+2\sqrt{5}}} \approx 58^\circ$	0	I
2	$\pi - \beta_0$	0	II
3	$\frac{\pi}{2}$	β_0	III
4	$\frac{\pi}{2} - \beta_0$	$\frac{\pi}{2}$	II
5	$\frac{\pi}{2} + \beta_0$	$\frac{\pi}{2}$	I
6	$\frac{\pi}{2}$	$\pi - \beta_0$	IV
7	β_0	π	I
8	$\pi - \beta_0$	π	II
9	$\frac{\pi}{2}$	$\pi + \beta_0$	III
10	$\frac{\pi}{2} - \beta_0$	$\frac{3\pi}{2}$	II
11	$\frac{\pi}{2} + \beta_0$	$3\pi/2$	I
12	$\pi/2$	$2\pi - \beta_0$	IV

and large tube radii ($R_T \approx 8.5$) the energy variations are small.

We conclude that the smooth-tube approach works well for tube radii $R_T \approx 7.5$ Å and higher, as seen from the Mercator maps in Figs. 4 and 5 and the energy variations of Table III. For small-radius tubes ($R_T \leq 7$ Å), a systematic investigation addressing the variation of V_{discrete} as a function of α , β , γ , and ζ is required. In the following section we perform such a study for the (16,0), (14,4), (9,9) and three more low-radius tubes.

IV. LOW-RADIUS TUBES: FULL ENERGY VARIATION

Before proceeding to the full energy variation calculation required for peapods with $R_T \approx 6.5$ Å, we would like to reflect on actual small values of peapod radii. To our knowledge, both today's experimental and theoretical situation do not show unanimity. Theoretically, different lower

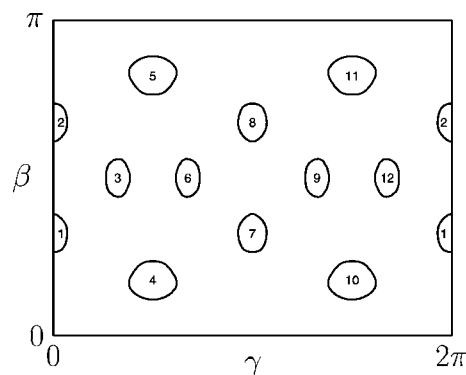


FIG. 6. Indication of the locations (β_i, γ_i) , $i=1, \dots, 12$, tabulated in Table II. For tubes with $R_T \approx 6.5$ Å (Fig. 3), these angle pairs correspond to the lowest-energy molecular orientations (Fig. 7). The contours are reproductions of the $V_{\text{smooth}}=200$ K contours of Fig. 3(a).

limits for a peapod's radius have been suggested, based on the outcome of the reaction energy ΔE in the reaction $(n, m) + C_{60} \rightarrow C_{60}@ (n, m) - \Delta E$: exo- ($\Delta E < 0$) or endothermic ($\Delta E > 0$). Okada *et al.*^{25,26} concluded from density-functional theory calculations that for $C_{60}@ (n, n)$ with $10 \leq n \leq 13$ the reaction is exothermic, and, by extrapolating the results of $n=8, 9$, and 10, obtained a minimal tube radius of $R_T^{\text{min}} \approx 6.4$ Å.²⁶ Rochefort,²⁷ performing molecular mechanics calculations, set the lower limit at $R_T^{\text{min}} \approx 5.9$ Å. From the experimental side, while it is still impossible to manufacture nanotubes—let alone peapods—with a given pair of indices (n, m) , peapod samples with a narrow radial dispersion around a mean value \bar{R}_T and good filling rates (typically, 75%) can be produced at present. We mention a few (recent) experiments on peapods. Cambedouzou *et al.*²⁸ used a sample with $\bar{R}_T \approx 6.8$ Å. Maniwa *et al.*²⁹ fitted x-ray diffraction data on $C_{60}@ \text{SWCNT}$ peapods to simulations, resulting in a mean radius $\bar{R}_T \approx 6.76$ Å. Kataura *et al.*³⁰ reported measurements on a sample having a diameter range of $6.25 \text{ Å} \leq R_T \leq 7.35 \text{ Å}$, from which we calculate $\bar{R}_T \approx 6.8$ Å. The electron diffraction studies of Hirahara *et al.*³¹ were performed on peapod samples with $\bar{R}_T \approx 7.15$ Å (SWCNTs from a same batch were used to synthesize not only C₆₀, but also C₇₀ and C₈₀ peapods). Kataura *et al.*³² reported high-yield fullerene encapsulation, controlling the tubes to be “larger than the (10, 10) tube,” i.e., $R_T^{\text{min}} \geq 6.86$ Å. Pfeiffer *et al.*³³ inferred from Raman spectroscopy their three samples to have $\bar{R}_T \approx 7$ Å, $\bar{R}_T \approx 6.52$ Å, and $\bar{R}_T \approx 6.505$ Å. From all these values one may conclude that peapods with a radius around 6.5 Å, our representative value for the “pentagonal case” (Figs. 3 and 7), although possible, are less abundant than peapods with a radius around, say, 6.75 Å. We have therefore considered a few additional tubes—(17,0), (14,5), and (10,10)—with radii around 6.75 Å; their characteristics are shown in Table IV. These tubes can be expected to be more realistic representatives of the pentagonal regime instead of the $R_T=6.5$ Å tubes of Refs. 15 and 16—we recall that the transition from the pentagonal to the double-bond lowest-energy orientation occurs around 7 Å.¹⁶ We note that

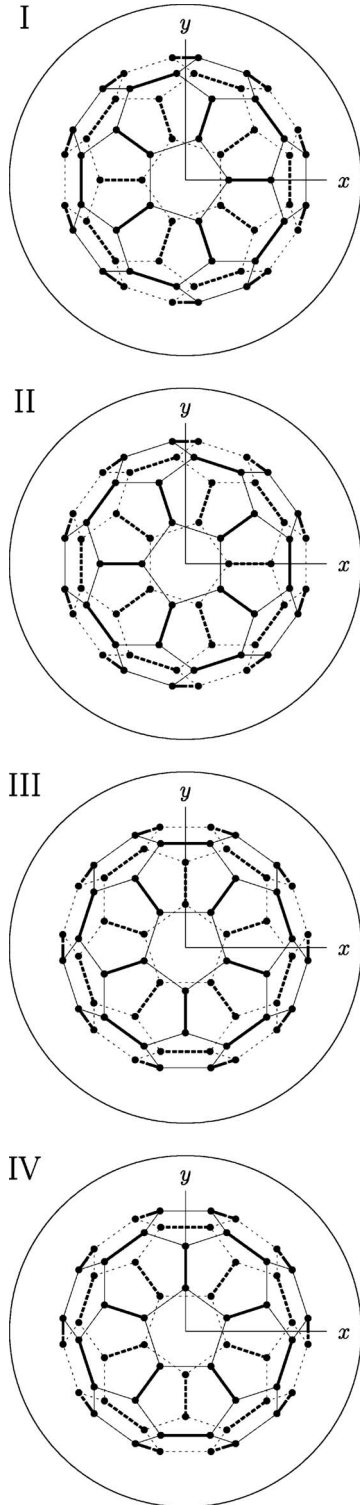


FIG. 7. When applying the 12 Euler transformations $\mathfrak{R}^{-1}(\alpha=0, \beta_i, \gamma_i)$, with (β_i, γ_i) , $i=1, \dots, 12$, from Table II, only four different molecular orientations, the projections onto the (x, y) plane of which are shown here, are obtained. Dashed (fragments of) lines have $z < 0$. The labeling I, II, III, and IV correlates with Table II.

the (10, 10) tube is of special interest since tubes with a radius close to $R_T(10, 10) = 6.86 \text{ \AA}$ are favorable for C_{60} encapsulation, as seen in both experiments—according to Kaitaura *et al.*,³⁰ peapod samples tend to have a radial dispersion

TABLE III. Energy variations $\Delta_\alpha V_{\text{discrete}}$ and $\Delta_\zeta V_{\text{discrete}}$ (units K) when varying α or ζ and keeping other variables fixed.

(n, m)	$\Delta_\alpha V_{\text{discrete}}$ (K)	$\Delta_\zeta V_{\text{discrete}}$ (K)
(16,0)	51.3	1079.3
(14,4)	643.2	639.6
(9,9)	665.9	8.3
(19,0)	<0.1	3.7
(16,5)	0.4	0.6
(11,11)	<0.1	<0.1
(21,0)	<0.1	0.1
(21,1)	<0.1	0.3
(12,12)	<0.1	<0.1

centered around $R_T(10, 10)$ —and theory—of the $C_{60}@ (n, n)$ series ($n=8, \dots, 13$), the $n=10$ peapod stands out as the most “exothermic” (see above).^{25,26}

The Mercator maps $V_{\text{discrete}}(\beta, \gamma)$ of the extra tubes are shown in Fig. 8; and the energy variations $\Delta_\alpha V_{\text{discrete}}$ and $\Delta_\zeta V_{\text{discrete}}$ are listed in Table IV. Again, minimal energies occur around (β_i, γ_i) , and maxima correspond to hexagons being perpendicular to the tube axis. The (17,0) tube’s V_{discrete} 50 K contour deviates from its smooth-tube 50 K contour [Fig. 8(a)], but there is some overall agreement. The (10,10) tube’s V_{discrete} plot [Fig. 8(c), left] features “split” minima as seen for the (14,4) tube [Fig. 3(b)]. The (14,5) tube’s V_{discrete} plot does not coincide nicely with its V_{smooth} plot, but interestingly, the two locations (β_i, γ_i) , $i=3$ and $i=9$, type III pentagonal orientations, correspond very well to their smooth-approximation counterparts. Since all other ten minima locations are related to the $i=3$ or the $i=9$ location by a molecular rotation over $\alpha = \frac{\pi}{4}$ or $\alpha = \frac{\pi}{2}$ about the z axis (see Fig. 7), any of the (β_i, γ_i) points can be made a minimal configuration by changing α . The main conclusion is that the minimal-energy orientation will always feature facing pentagons perpendicular to the z axis. The same can be said of any of the tubes of Figs. 3 and 8—tubes with $R_T \leq 7 \text{ \AA}$ —excepting the (14,4) tube.

We now turn to the α and ζ dependencies of V_{discrete} . It is sufficient to consider the intervals $0 \leq \alpha < \Delta\alpha \equiv \alpha_{\text{max}}$ and $0 \leq \zeta < \Delta\zeta \equiv \zeta_{\text{max}}$. We divide the interval $[0, \alpha_{\text{max}}] \times [0, \zeta_{\text{max}}]$ into a 10×10 grid $(\alpha_{i=1, \dots, 10}, \zeta_{j=1, \dots, 10})$, $\alpha_i = (i-1) \frac{\alpha_{\text{max}}}{10}$, $\zeta_j = (j-1) \frac{\zeta_{\text{max}}}{10}$, and construct a double Fourier series [for notational simplicity we drop the indices (n, m)],

$$\begin{aligned}
 V_{\text{discrete}}(\alpha, \beta, \gamma; \zeta) = & \sum_{p=0}^{\infty} \sum_{q=0}^{\infty} \left\{ A_{pq}(\beta, \gamma) \cos\left(p \frac{\alpha}{\alpha_{\text{max}}} 2\pi\right) \right. \\
 & \times \cos\left(q \frac{\zeta}{\zeta_{\text{max}}} 2\pi\right) \\
 & + B_{pq}(\beta, \gamma) \sin\left(p \frac{\alpha}{\alpha_{\text{max}}} 2\pi\right) \\
 & \times \cos\left(q \frac{\zeta}{\zeta_{\text{max}}} 2\pi\right) + C_{pq}(\beta, \gamma)
 \end{aligned}$$

$$\begin{aligned} & \times \cos\left(p\frac{\alpha}{\alpha_{\max}}2\pi\right)\sin\left(q\frac{\zeta}{\zeta_{\max}}2\pi\right) \\ & + D_{pq}(\beta, \gamma)\sin\left(p\frac{\alpha}{\alpha_{\max}}2\pi\right) \\ & \times \sin\left(q\frac{\zeta}{\zeta_{\max}}2\pi\right) \Big\}, \end{aligned} \quad (4.1)$$

by numerically calculating the Fourier coefficients

$$\begin{aligned} A_{pq}(\beta, \gamma) = N_{pq} \int_0^{\alpha_{\max}} d\alpha \int_0^{\zeta_{\max}} d\zeta V_{\text{discrete}}(\alpha, \beta, \gamma; \zeta) \\ \times \cos\left(p\frac{\alpha}{\alpha_{\max}}2\pi\right)\cos\left(q\frac{\zeta}{\zeta_{\max}}2\pi\right), \end{aligned} \quad (4.2)$$

via the trapezium-rule approximations

$$\begin{aligned} A_{pq}(\beta, \gamma) \approx N_{pq} \sum_{i=1}^{10} \sum_{j=1}^{10} \frac{\alpha_{\max}}{10} \frac{\zeta_{\max}}{10} V_{\text{discrete}}(\alpha_i, \beta, \gamma; \zeta_j) \\ \times \cos\left(p\frac{\alpha_i}{\alpha_{\max}}2\pi\right)\cos\left(q\frac{\zeta_j}{\zeta_{\max}}2\pi\right), \end{aligned} \quad (4.3)$$

The coefficients B_{pq} , C_{pq} , and D_{pq} are obtained by replacing $\cos(\cdot)\cos(\cdot)$ by $\sin(\cdot)\cos(\cdot)$, $\cos(\cdot)\sin(\cdot)$, and $\sin(\cdot)\sin(\cdot)$, respectively. The prefactors read

$$N_{00} = \frac{1}{\alpha_{\max}\zeta_{\max}}, \quad N_{0s} = N_{r0} = \frac{2}{\alpha_{\max}\zeta_{\max}}, \quad N_{rs} = \frac{4}{\alpha_{\max}\zeta_{\max}}, \quad (4.4)$$

where r and $s \neq 0$. In series (4.1), some terms may vanish because of symmetry reasons.

The Fourier coefficients $A_{pq}(\beta, \gamma)$, $B_{pq}(\beta, \gamma)$, $C_{pq}(\beta, \gamma)$, $D_{pq}(\beta, \gamma)$ can be interpreted as Mercator maps. The magnitude of the coefficients decreases for increasing indices p and q ; we approximate $V_{\text{discrete}}(\alpha, \beta, \gamma; \zeta)$ by

$$\begin{aligned} \tilde{V}_{\text{discrete}}(\alpha, \beta, \gamma; \zeta) = \sum_{p=0}^4 \sum_{q=0}^4 \left\{ A_{pq}(\beta, \gamma) \cos\left(p\frac{\alpha}{\alpha_{\max}}2\pi\right) \right. \\ \left. \times \cos\left(q\frac{\zeta}{\zeta_{\max}}2\pi\right) + \dots \right\}. \end{aligned} \quad (4.5)$$

For given β and γ , we scan the α and ζ intervals and define

$$\begin{aligned} \tilde{V}_{\text{discrete}}^{\min}(\beta, \gamma) \equiv \min\{\tilde{V}_{\text{discrete}}(\alpha, \beta, \gamma; \zeta); \\ 0 \leq \alpha \leq \alpha_{\max}, 0 \leq \zeta \leq \zeta_{\max}\}. \end{aligned} \quad (4.6)$$

The quantity $\tilde{V}_{\text{discrete}}^{\min}(\beta, \gamma)$, gives the lowest attainable energy $\tilde{V}_{\text{discrete}}$ when varying α and ζ . In Fig. 9, it has been plotted for each of the six tubes investigated. The plots again exhibit icosahedral symmetry as in the previous Mercator maps. The main observation here is that for all tubes, except the (9,9) tube [Fig. 9(c), left], the absolute minima do not lie precisely at the 12 (β_i, γ_i) locations

but somewhat away from them—the same effect observed for the $(\alpha=0, \zeta=0)$ V_{discrete} plots in Figs. 3 and 8. As before, we can write the actual minimum locations as $(\beta'_i = \beta_i + \Delta\beta_i, \gamma'_i = \gamma_i + \Delta\gamma_i)$. For the $R_T \approx 6.5$ Å tubes (Fig. 9, left), excepting the (9,9) tube, the (β_i, γ_i) locations (orientations) have energies ~ 300 K higher than the minimal energies. The (9,9) tube's minima are really close to—if not, coinciding with—the (β_i, γ_i) orientations. For the $R_T \approx 6.75$ Å tubes (Fig. 9, right), excepting the (10,10) tube, the (β_i, γ_i) orientations have energies ~ 20 K higher than the minimal energies. The (10,10) tube's absolute minima lie also off the (β_i, γ_i) pentagon orientations (not visible on the plot), and have energies ~ 12 K higher than the lowest energies. We must therefore conclude that chirality-dependent effects manifest themselves here. However, for $R_T \approx 6.75$ Å tubes, probably the smallest peapod tubes as discussed above, the effects can be said to be minor. As an approximation, one may consider the smooth-tube approach. We recall that for higher tube radii, the smooth-tube approximation is excellent (when the C₆₀ molecules lie on the tube axis).

To conclude this section, we come back to the four types of pentagonal orientations depicted in Fig. 7. We recall that they arise from the Euler transformations $\mathfrak{R}^{-1}(\alpha=0, \beta_i, \gamma_i)$ with the angle pairs (β_i, γ_i) , $i=1, \dots, 12$, of Table II. Clearly, all 12 $V_{\text{smooth}}(\beta_i, \gamma_i)$ values are identical because of the cylindrical symmetry. *A priori*, $V_{\text{discrete}}(\beta_i, \gamma_i)$ can be different for each of the four types I, II, III, and IV. Interestingly, depending on the tube's symmetry, some orientations sometimes are equivalent. This is illustrated in Table V, and can be understood by being aware of certain symmetry elements. Orientations I and II are related via a rotation over π about the z axis, and likewise for orientations III and IV. Orientations III and I are related by a rotation over $\pi/2$ about the z axis. The presence of a twofold symmetry axis for the (n, m) tube therefore implies equivalence of orientations I and II and of orientations III and IV, while a fourfold axis implies the equivalence of all orientations. The (16,0) tube is an example of the latter, a (14,4) tube provides an example of the former. The (16,5) tube has no pure rotational symmetry axis and exhibits therefore distinguishable V_{discrete} values. We note that any occurring energy differences as a result of the discussed inequivalences are small, however, and not seen on any of the Mercator maps since the contour values lie not sufficiently close to each other. Also note that these observations are generally true for the values $V_{\text{discrete}}(\beta_i, \gamma_i)$ —they do not need to be to minima, e.g., the (14,4) tube [Fig. 3(b)]. The equivalence relationships between the twelve (β_i, γ_i) orientations is nicely seen in the (14,5) tube's V_{discrete} plot [Fig. 8(b)]: all four types I ($\{1, 5, 7, 11\}$), II ($\{2, 4, 8, 10\}$), III ($\{3, 9\}$), and IV ($\{6, 12\}$) “behave” differently. When making the observations concerning the equality/inequality of $V_{\text{smooth}}(\beta_i, \gamma_i)$ values summarized schematically in Table V, we have made sure that sufficient numerical accuracy has been achieved. One needs accurate enough atomic coordinates of the C₆₀ molecule, so that upon explicitly applying coordinate transforms $\mathfrak{R}^{-1}(\alpha, \beta, \gamma)$ corresponding to symmetry elements of the C₆₀ molecule (i.e., of the icosahedral

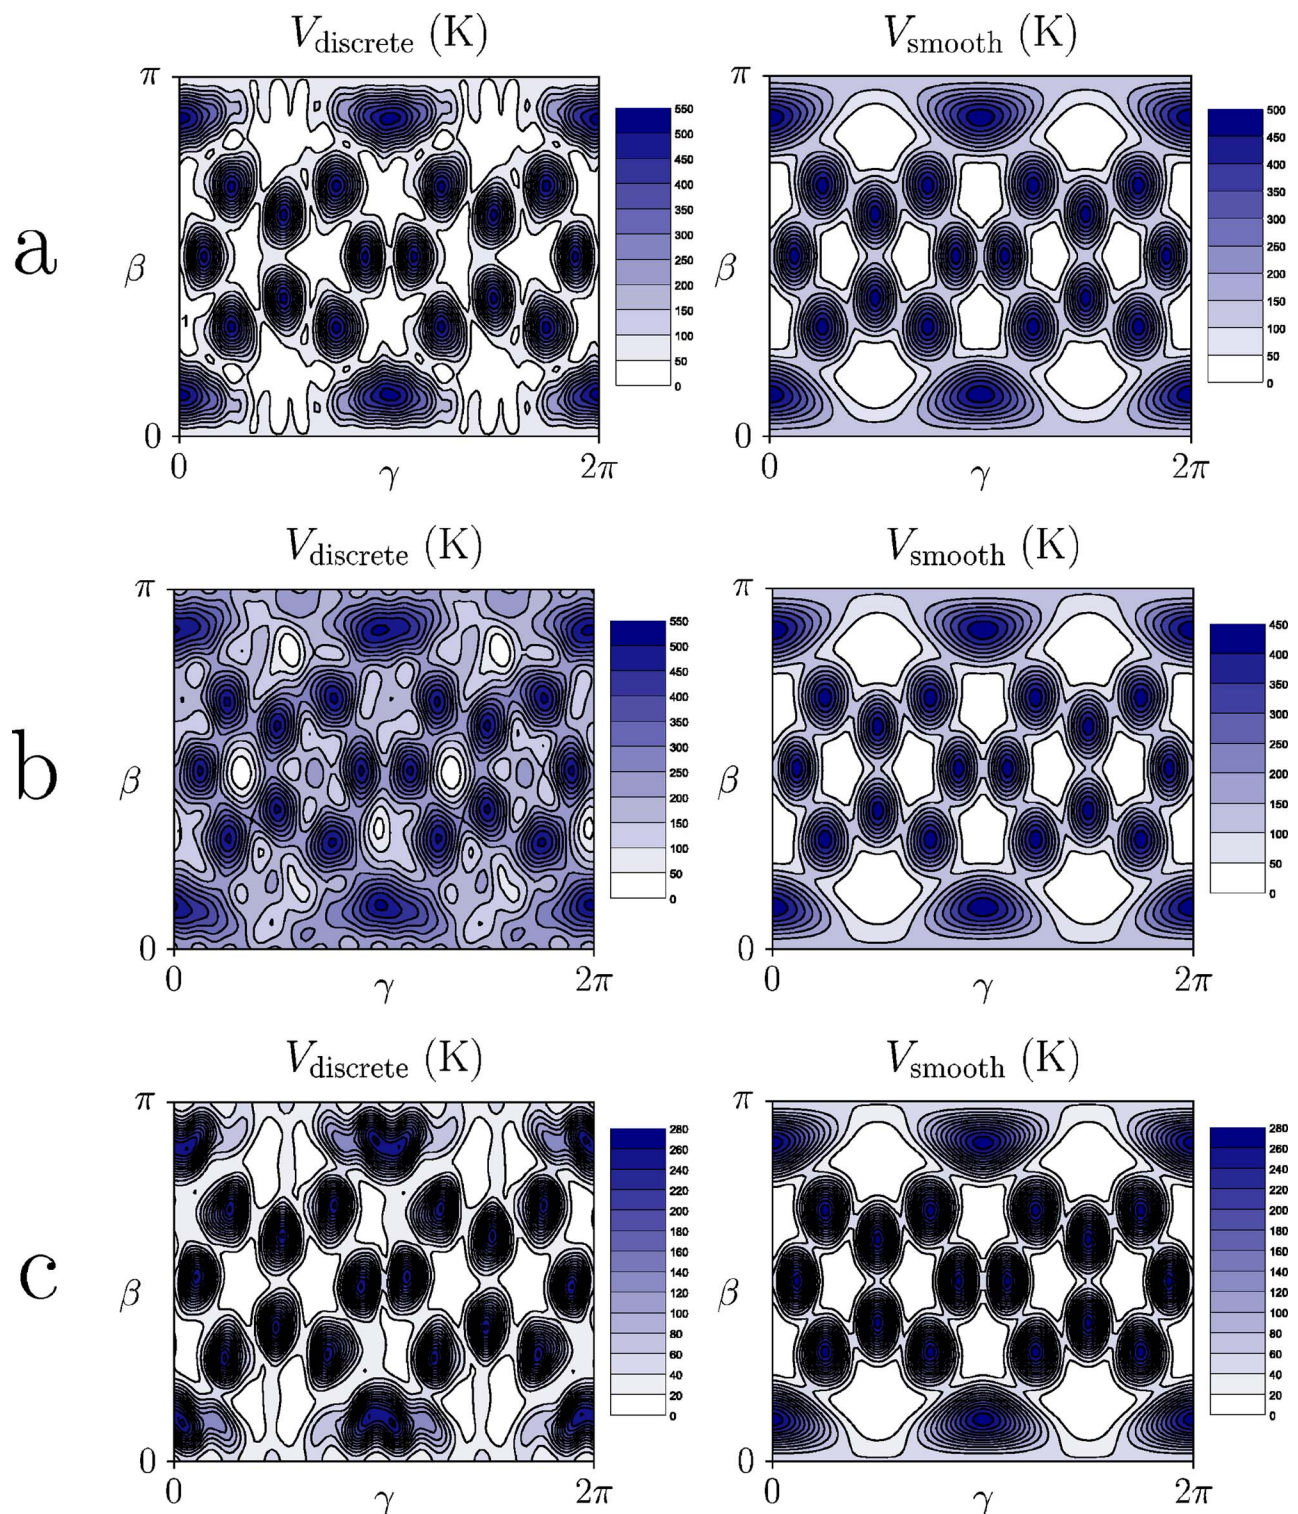


FIG. 8. (Color online) Mercator maps $V_{\text{discrete}}(\beta, \gamma)$ (left) and $V_{\text{smooth}}(\beta, \gamma)$ (right), units K: (a) $(n, m) = (17, 0)$, (b) $(n, m) = (14, 5)$, (c) $(n, m) = (10, 10)$. The minimal values have been subtracted.

TABLE IV. Characteristics of additional tubes ($R_T \approx 6.75 \text{ \AA}$). See captions to Tables I and III.

(n, m)	Chirality	R_T (\AA)	$\Delta\alpha$	$\Delta\zeta$ (\AA)	$\Delta_\alpha V_{\text{discrete}}$ (K)	$\Delta_\zeta V_{\text{discrete}}$ (K)
(17,0)	zig-zag	6.7370	$2\pi/17$	$\sqrt{3}a = 4.3128$	< 0.1	176.4
(14,5)	chiral	6.7603	2π	24.5237	36.3	36.5
(10,10)	armchair	6.8640	$2\pi/10$	$a = 2.49$	23.1	11.6

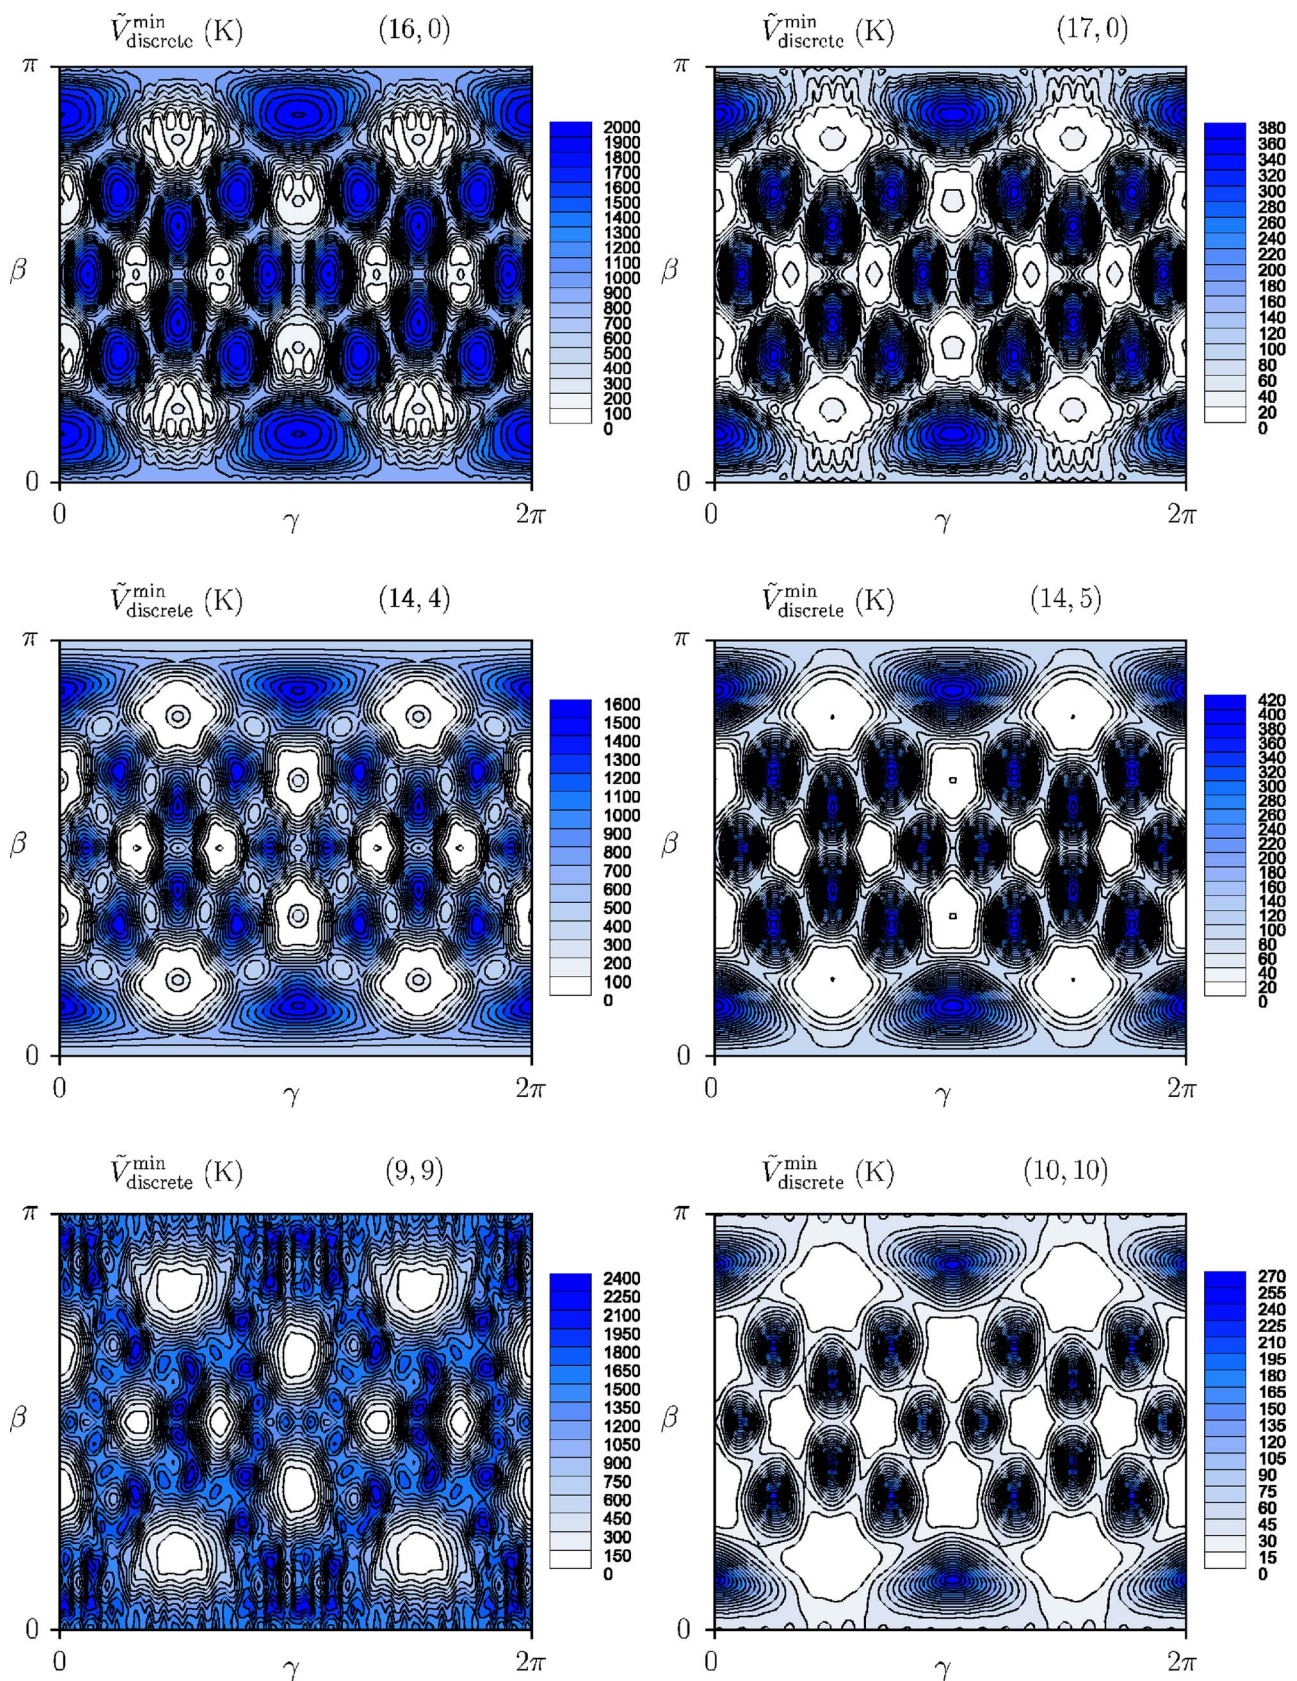


FIG. 9. (Color online) Mercator maps $\tilde{V}_{\text{discrete}}(\beta, \gamma)$, units K, for (16,0), (14,4), (9,9), (17,0), (14,5), and (10,10) peapods. The minimal values have been subtracted.

TABLE V. Schematical presentation of $V_{\text{discrete}}(\beta_i, \gamma_i)$ values for selected tubes, indicating equalities and inequalities due to the presence/absence of certain symmetries. The angles β_i and γ_i are tabulated in Table VII, the corresponding molecular orientations depicted in Fig. 2.

i (Type)	$(n, m)=(16, 0)$	$V_{\text{discrete}}(\beta_i, \gamma_i)$ $(n, m)=(14, 4)$	$(n, m)=(16, 5)$
1, 5, 7, 11 (I)	$V_1^{(16,0)}$	$V_1^{(14,4)}$	$V_1^{(16,5)}$
2, 4, 8, 10 (II)	$V_1^{(16,0)}$	$V_1^{(14,4)}$	$V_2^{(16,5)}$
3, 9 (III)	$V_1^{(16,0)}$	$V_3^{(14,4)}$	$V_3^{(16,5)}$
6, 12 (IV)	$V_1^{(16,0)}$	$V_3^{(14,4)}$	$V_6^{(16,5)}$

group I_h), the same set of coordinates is obtained up to the desired accuracy. We use coordinates with twelve significant digits.

V. DISCUSSION AND CONCLUSIONS

We have presented a systematic comparison of the potential energy of a C_{60} molecule—treated as an icosahedral cluster of ICs—encapsulated centrally in a SWCNT, when approximating the tube as a uniform cylinder and when taking the true carbon atomic network into account. The former approach results in only two variables (the Euler angles β and γ), while the latter requires in addition a third Euler angle α and the molecule's z coordinate ζ denoting its position along the tube axis. The (β, γ) dependence can be conveniently plotted as a Mercator map. Fixing (α, ζ) at $(0, 0)$ then allows a first visual comparison of the “smooth” and “discrete” Mercator maps $V_{\text{smooth}}(\beta, \gamma)$ and $V_{\text{discrete}}(\beta, \gamma)$. From these preliminary comparisons one can see that the larger the tube, the better the smooth-tube approximation. Indeed, the V_{smooth} and V_{discrete} Mercator maps for tubes with radii $R_T \geq 7.5$ Å (Figs. 4 and 5) are as good as identical. For smaller tubes, the effect of the tube structure comes into play and deviations between the smooth and discrete Mercator maps are visible (Figs. 3 and 8). While the (α, ζ) dependence of V_{discrete} can be argued to be negligible for the larger tubes ($R_T \geq 7$ Å) because of the similarity of $V_{\text{smooth}}(\beta, \gamma)$ and $V_{\text{discrete}}(\beta, \gamma)$, a full investigation of the variables α and ζ is in order for smaller tubes. We have presented a detailed study for selected zigzag, chiral and armchair tubes with radii around $R_T \approx 6.5$ Å and 6.75 Å, including the (10,10) tube, nowadays considered the ideal peapod tube.^{25,26,30}

A double Fourier series captures the (α, ζ) dependence in a manageable way. Scanning $V_{\text{discrete}}(\alpha, \beta, \gamma; \zeta; n, m)$ for its lowest attainable values when varying α and ζ yields Mercator maps similar to $V_{\text{smooth}}(\beta, \gamma; n, m)$. We see that the actual energy minima do not correspond to the 12 pentagonal (β_i, γ_i) orientations but that they lie slightly away from them (except for the (9,9) tube, where the minimal-energy molecular configurations are really close to the pentagonal orientations). Such (β, γ) orientations correspond to “tilted” molecules, where an axis connecting the midpoints of two opposing pentagons does not coincide with the tube's long axis (z axis) but makes a cone with a small opening angle if one would perform the α Euler rotation. Hence,

we conclude that for these smaller tubes [again excepting the (9,9) tube], the chirality of the tube does play a role. However, as seen from the small deviations occurring in the Mercator plots, the effect is not strong, especially for the $R_T \approx 6.75$ Å tubes (Fig. 9, right). Therefore, one may consider the smooth-tube approach if one wants to capture radius-dependent properties. In this respect, one should be aware of the present-day experimental situation: precise knowledge of the components (i.e., occurring chiralities) in a peapod sample is absent—only a determination of the tube radius distribution seems feasible up to now. The main conclusion of Refs. 15 and 16 stands: three regimes can be distinguished ($R_T \leq 7$ Å, pentagonal orientation, 7 Å $\leq R_T \leq 7.9$ Å, double-bond orientation, and $R_T \geq 7.9$ Å, hexagonal orientation). The pentagonal orientations have to be restated as tilted pentagonal orientations, though. Generally, our findings are in accordance with those of Troche *et al.*¹⁴ who concluded that the chirality of the SWCNT encapsulating the C_{60} molecule has only a minor effect.

Note that transversal motion of the C_{60} molecule (off-axis displacements) is not discussed here since our sole purpose was a direct comparison of the smooth-tube and the discrete-tube approaches for a centrally located C_{60} molecule. As expected intuitively and demonstrated in Refs. 15 and 16, from a certain radius ($R_T \approx 7$ Å) on, an off-center position is energetically more favorable. This, however, involves energy differences much larger than those seen upon varying β , γ , α , and ζ .

The smooth-tube approximation's requiring only the two Euler angles β and γ allows for the use of symmetry-adapted rotator functions. For details we refer to Refs. 15 and 16. The advantage lies in the possibility of writing $V_{\text{smooth}}(\beta, \gamma; R_T)$ as an expansion into functions $U_l(\beta, \gamma)$ taking the icosahedral molecular symmetry of the C_{60} molecule and the cylindrical symmetry of its site into account,

$$V_{\text{smooth}}(\beta, \gamma; R_T) = \sum_{l=0}^{\infty} w_l(R_T) U_l(\beta, \gamma), \quad (5.1)$$

where the coefficients w_l relate to the icosahedral symmetry and carry the details of the pair interaction potential. The molecular symmetry implies the first nonvanishing terms to be those with $l=0$, $l=6$, $l=10$, and $l=12$, and a restriction to only these four leading terms already approximates $V_{\text{smooth}}(\beta, \gamma; R_T)$ extremely well. Apart from providing mathematical/physical clarity, expansion (5.1) greatly re-

duces the calculation time. While, for a 100×100 (β, γ) grid, an implementation of Eq. (2.3) takes hours, the calculation of $V_{\text{smooth}}(\beta, \gamma; R_T)$ via Eq. (5.1) is a matter of minutes on the same machine.

It is interesting to note that double-walled carbon nanotubes (DWCNTs) allow the encapsulation of C₆₀ molecules in inner spaces smaller than observed for SWCNTs: Khlobystov *et al.*¹³ reported the insertion of C₆₀ molecules in DWCNTs with internal radii as small as 5.5 Å. Having different minimal internal radii of SWCNTs and DWCNTs for filling with C₆₀ molecules is attributed to the difference in how a C₆₀ molecule interacts with a SWCNT and a DWCNT.¹³ We have carried out calculations for C₆₀@DWCNT by treating the field on the C₆₀ molecule as a superposition of the two fields from the tubes with different radii. Although we find that the presence of a second (outer) tube decreases the energy for encapsulation when taking a tube radius difference equaling the interlayer distance of graphite (3.35 Å), the effect is rather small and not sufficient to explain the large reduction in inner tube radius.

We believe that the general conclusion—the smooth-tube approximation being justified for intermediate and large tube radii ($R_T \gtrsim 7$ Å) and possibly acceptable for smaller tube radii—reached here is relevant for other peapod systems. For example, (C₇₀)_N@SWCNT peapods feature different orientations of the encapsulated C₇₀ molecules for different tube radii,^{29,31} the so-called “lying” (for smaller tube radii) and “standing” (larger tube radii) orientations. A smooth-tube approach would make a good start for investigating these specific orientations.

ACKNOWLEDGMENTS

We thank A.V. Nikolaev for providing high-precision atomic C₆₀ coordinates. B.V. acknowledges the Fonds voor Wetenschappelijk Onderzoek—Vlaanderen.

APPENDIX A: DISCREPANCY TEST

We consider a single carbon atom in a short (16, 0) tube fragment defined by $|z_\tau| \leq a/\sqrt{3} \approx 1.42$ Å, leaving only three “rings” of 16 carbon atoms each. The tube atoms have coordinates $\vec{r}_\tau = (x_\tau, y_\tau, z_\tau)$, $\tau = 1, \dots, 48$. The single atom, put at the center of the fragment which we define to be the origin of the employed Cartesian coordinates system, has a discrete energy

$$V_{\text{discrete}} = \sum_{\tau=1}^{48} v^a(r_\tau), \quad (\text{A1})$$

approximated by the smooth energy

TABLE VI. V_{smooth} values, units K, for various tube fragments and surface densities σ and $\tilde{\sigma}$.

$[Z_{\min}, Z_{\max}]$	σ or $\tilde{\sigma}$	V_{smooth} (K)
$\left[-\frac{\sqrt{3}a}{2}, \frac{\sqrt{3}a}{2}\right]$	σ	-405.0
$\left[-\frac{\sqrt{3}a}{2}, \frac{\sqrt{3}a}{2}\right]$	$\tilde{\sigma}$	-303.7
$\left[-\frac{5a}{4\sqrt{3}}, \frac{a}{\sqrt{3}}\right]$	σ	-317.0
$\left[-\frac{5a}{4\sqrt{3}}, \frac{a}{\sqrt{3}}\right]$	$\tilde{\sigma}$	-317.0
$\left[-\frac{a}{\sqrt{3}}, \frac{a}{2\sqrt{3}}\right]$	σ	-217.1
$\left[-\frac{a}{\sqrt{3}}, \frac{a}{2\sqrt{3}}\right]$	$\tilde{\sigma}$	-325.7

$$V_{\text{smooth}} = \sigma R_T \int_0^{2\pi} d\Phi \int_{Z_{\min}}^{Z_{\max}} dz v^a(\vec{\rho}). \quad (\text{A2})$$

In both equations, the pair potential $v^a(r)$ of Sec. II is understood. In Eq. (A2), Φ and Z are defined via $x = R_T \cos \Phi$, $y = R_T \sin \Phi$, and $z = Z$. The integration boundaries Z_{\min} and Z_{\max} are not well defined. Indeed, there is a range of both lower and upper boundaries corresponding to a smooth tube fragment containing only the three rings with $z_\tau = -a/\sqrt{3}$, $z_\tau = 0$, and $z_\tau = a/(2\sqrt{3})$: $-\sqrt{3}a/2 < Z_{\min} \leq -a/\sqrt{3}$ and $a/(2\sqrt{3}) \leq Z_{\max} < \sqrt{3}a/2$. In Table VI we present V_{smooth} values calculated for a few of these $[Z_{\min}, Z_{\max}]$ intervals. For each case, both the tube surface density $\sigma = 4/(\sqrt{3}a^2)$ and the adjusted tube density $\tilde{\sigma} = 48/[2\pi R_T(Z_{\max} - Z_{\min})]$ has been considered. The discrete value, obtained via Eq. (A1), reads $V_{\text{discrete}} = -318.1$ K, and is best reproduced by the smooth value if the interval $[Z_{\min}, Z_{\max}] = \left[-\frac{5a}{4\sqrt{3}}, \frac{a}{\sqrt{3}}\right]$ is chosen. The tube fragment edges then lie precisely in the middle of two neighboring rings of atoms; the surface densities σ and $\tilde{\sigma}$ then happen to coincide. The values of Table VI suggest that some choice(s) of intervals may yield the V_{discrete} value, but the point we want to make here is that making use of the adjusted surface density $\tilde{\sigma}$ does not “convert” the V_{smooth} to the V_{discrete} value. We remark that doing the V_{smooth} calculations described in the paper with $\tilde{\sigma}$ instead of σ turned out to yield only very small differences.

- ¹S. Iijima, *Nature (London)* **354**, 56 (1991).
- ²T. W. Ebbesen and P. M. Ajayan, *Nature (London)* **358**, 220 (1992).
- ³R. Saito, G. Dresselhaus, and M. S. Dresselhaus, *Physical Properties of Carbon Nanotubes* (Imperial College Press, London, 1998).
- ⁴P. J. F. Harris, *Carbon Nanotubes and Related Structures* (Cambridge University Press, Cambridge, 1999).
- ⁵J. Sloan, A. I. Kirkland, J. L. Hutchison, and M. L. H. Green, *Chem. Commun. (Cambridge)* **2002**, 1319.
- ⁶M. Monthieux, *Carbon* **40**, 1809 (2002).
- ⁷B. W. Smith, M. Monthieux, and D. E. Luzzi, *Nature (London)* **396**, 323 (1998).
- ⁸D. J. Hornbaker, S. J. Kahng, S. Misra, B. W. Smith, A. T. Johnson, E. J. Mele, D. E. Luzzi, and A. Yazdani, *Science* **295**, 829 (2002).
- ⁹B. W. Smith, M. Monthieux, and D. E. Luzzi, *Chem. Phys. Lett.* **315**, 31 (1999).
- ¹⁰B. Burtiaux, A. Claye, B. W. Smith, M. Monthieux, D. E. Luzzi, and J. E. Fischer, *Chem. Phys. Lett.* **310**, 21 (1999).
- ¹¹G. T. Pickett, M. Gross, and H. Okuyama, *Phys. Rev. Lett.* **85**, 3652 (2000).
- ¹²M. Hodak and L. A. Girifalco, *Phys. Rev. B* **67**, 075419 (2003).
- ¹³A. N. Khlobystov, D. A. Britz, A. Ardavan, and G. A. Briggs, *Phys. Rev. Lett.* **92**, 245507 (2004).
- ¹⁴K. S. Troche, V. R. Coluci, S. F. Braga, D. D. Chinellato, F. Sato, S. B. Legoas, R. Rurali, and D. S. Galvao, *Nano Lett.* **5**, 349 (2005).
- ¹⁵K. H. Michel, B. Verberck, and A. V. Nikolaev, *Phys. Rev. Lett.* **95**, 185506 (2005).
- ¹⁶K. H. Michel, B. Verberck, and A. V. Nikolaev, *Eur. Phys. J. B* **48**, 113 (2005).
- ¹⁷W. Mickelson, S. Aloni, W. Q. Han, J. Cummings, and A. Zettl, *Science* **300**, 467 (2003).
- ¹⁸C. J. Bradley and A. P. Cracknell, *The Mathematical Theory of Symmetry in Solids* (Clarendon, Oxford, 1972).
- ¹⁹W. I. F. David, R. M. Ibberson, J. C. Matthewman, K. Prassides, T. J. S. Dennis, J. P. Hare, H. W. Kroto, R. Taylor, and D. R. M. Walton, *Nature (London)* **353**, 147 (1991).
- ²⁰D. Lamoen and K. H. Michel, *Z. Phys. B: Condens. Matter* **92**, 323 (1993); J. R. D. Copley and K. H. Michel, *J. Phys.: Condens. Matter* **5**, 4353 (1993).
- ²¹P. Launois, S. Ravy, and R. Moret, *Phys. Rev. B* **55**, 2651 (1997).
- ²²K. H. Michel and J. R. D. Copley, *Z. Phys. B: Condens. Matter* **103**, 369 (1997).
- ²³N. Hamada, S. I. Sawada, and A. Oshiyama, *Phys. Rev. Lett.* **68**, 1579 (1992); D. H. Robertson, D. W. Brenner, and J. W. Mintmire, *Phys. Rev. B* **45**, 12592 (1992).
- ²⁴Gerardus Mercator (1512–1594), Flemish cartographer, inventor of the cylindrical projection. The angles β and γ play the role of geographical latitude and longitude, respectively.
- ²⁵S. Okada, M. Otani, and A. Oshiyama, *Phys. Rev. B* **67**, 205411 (2003).
- ²⁶S. Okada, S. Saito, and A. Oshiyama, *Phys. Rev. Lett.* **86**, 3835 (2001).
- ²⁷A. Rochefort, *Phys. Rev. B* **67**, 115401 (2003).
- ²⁸J. Cambedouzou, V. Pichot, S. Rols, P. Launois, P. Petit, R. Klement, H. Kataura, and R. Almairac, *Eur. Phys. J. B* **42**, 31 (2004); J. Cambedouzou, S. Rols, R. Almairac, J.-L. Sauvajol, H. Kataura, and H. Schober, *Phys. Rev. B* **71**, 041403(R) (2005).
- ²⁹Y. Maniwa, H. Kataura, M. Abe, A. Fujiwara, R. Fujiwara, H. Kira, H. Tou, S. Suzuki, Y. Achiba, E. Nishibori, M. Takata, M. Sakata, and H. Suematsu, *J. Phys. Soc. Jpn.* **72**, 45 (2003).
- ³⁰H. Kataura, Y. Maniwa, M. Abe, A. Fujiwara, T. Kodama, K. Kikuchi, H. Imahori, Y. Misaki, S. Suzuki, and Y. Achiba, *Appl. Phys. A: Mater. Sci. Process.* **74**, 349 (2002).
- ³¹K. Hirahara, S. Bandow, K. Suenaga, H. Kato, T. Okazaki, H. Shinohara, and S. Iijima, *Phys. Rev. B* **64**, 115420 (2001).
- ³²H. Kataura, Y. Maniwa, T. Kodama, K. Kikuchi, K. Hirahara, K. Suenaga, S. Iijima, S. Susuki, Y. Achiba, and W. Krätschmer, *Synth. Met.* **121**, 1195 (2001).
- ³³R. Pfeiffer, H. Kuzmany, T. Pichler, H. Kataura, Y. Achiba, M. Melle-Franco, and F. Zerbetto, *Phys. Rev. B* **69**, 035404 (2004).