

Phase segregation on the nanoscale in Na_2C_{60}

G. Klupp,^{1,*} P. Matus,¹ D. Quintavalle,^{2,3} L. F. Kiss,¹ É. Kováts,¹ N. M. Nemes,⁴ K. Kamarás,¹ S. Pekker,¹ and A. Jánossy^{2,3}

¹Research Institute for Solid State Physics and Optics, Hungarian Academy of Sciences, P.O. Box 49, Budapest, H-1525 Hungary

²Institute of Physics, Budapest University of Technology and Economics, P.O. Box 91, Budapest, H-1521 Hungary

³Solids in Magnetic Fields Research Group of the Hungarian Academy of Sciences, P.O. Box 91, Budapest, H-1521 Hungary

⁴Instituto de Ciencia de Materiales de Madrid (CSIC), Cantoblanco, E-28049 Madrid, Spain

(Received 12 July 2006; revised manuscript received 14 September 2006; published 2 November 2006)

Na_2C_{60} is believed to be an electron-hole counterpart of the Mott-Jahn-Teller insulator A_4C_{60} salts. We present a study of infrared, ESR, NMR spectroscopy, x-ray diffraction, chemical composition and neutron scattering on this compound. Our spectroscopic results at room temperature can be reconciled in a picture of segregated regions of the size 3–10 nm. We observe a significant insulating C_{60} phase and at least two more phases, one of which we assign to metallic Na_3C_{60} . The separation disappears on heating by jump diffusion of the sodium ions, which we followed by neutron scattering. Above ~ 460 K we see infrared spectroscopic evidence of a Jahn-Teller distorted C_{60}^{2-} anion.

DOI: [10.1103/PhysRevB.74.195402](https://doi.org/10.1103/PhysRevB.74.195402)

PACS number(s): 61.48.+c, 64.75.+g, 71.70.Ej, 71.20.Tx

I. INTRODUCTION

The fullerene molecule, C_{60} , has three degenerate lowest unoccupied molecular orbitals (LUMO) and is a good electron acceptor that forms mono- through hexa-anions relatively easily. The physical properties of the salts formed by the fulleride anions with alkali cations are in sharp contrast with a simplistic view of rigid-band filling. Solid C_{60} and A_6C_{60} (with $A=\text{K}, \text{Rb}$) both have cubic structures and are nonmagnetic band insulators with an empty and full band, respectively, derived from the LUMO orbitals.¹ A rigid-band model would suggest that all materials with partial filling (and the simplest possible cubic structure with one molecule per unit cell) must be either metals or magnetic Mott insulators.² However, this is not the case. A_3C_{60} salts have a half-filled band and are metals that are superconducting at low temperature,³ but none of the other compositions have a metallic ground state. Although the low-temperature properties of cubic AC_{60} salts are difficult to establish [C_{60}^- ions polymerize below 400 K (Refs. 4 and 5)], the magnetic susceptibility of the monomeric forms at high temperature is characteristic of paramagnetic Mott insulators.⁶ The nonmagnetic insulators A_4C_{60} ($A=\text{K}, \text{Rb}, \text{Cs}$) are the most thoroughly investigated series in this family. It was for these systems that the concept of the Mott-Jahn-Teller nonmagnetic insulator⁷ has been put forward.

The argument combining Mott localization and Jahn-Teller effect can be summarized as follows. In order to minimize molecular energy, C_{60}^{n-} ions undergo Jahn-Teller distortion and subsequent splitting of the LUMO levels. The Jahn-Teller splitting is usually much smaller than the bandwidth in a conventional solid, but Mott localization can lead to band narrowing and singlet ground states for evenly charged ions. Singlet-triplet excitations in such a model correspond to a small spin gap (≈ 0.05 eV),⁸ whereas charge excitations from one molecule to the next would cause a transport and optical gap of 0.5 eV.⁹ The latter corresponds to the transition between Jahn-Teller split levels of t_{1u} origin, which would be optically forbidden on the same molecule.

Molecular calculations¹⁰ show that the most significant Jahn-Teller distortion occurs for evenly charged ions C_{60}^{2-} and C_{60}^{4-} and involves elongation and flattening, respectively, along a threefold or fivefold axis, leading to a fulleride ion with D_{3d} or D_{5d} point group. External fields, e.g., the Coulomb potential of the cations, can stabilize a distortion along a twofold axis, resulting in D_{2h} symmetry. This is the case in orthorhombic Cs_4C_{60} ,^{11,12} in K_4C_{60} and Rb_4C_{60} with average tetragonal structure¹³ a frustration exists between molecular and crystal symmetry. In these salts, there is experimental evidence for a Mott-Jahn-Teller insulator ground state with low-lying excited states^{8,9} and for the dominant role of molecular degrees of freedom over crystal field at higher temperatures in vibrational spectra.^{14,15}

The electronic structure of A_2C_{60} salts is related to that of A_4C_{60} by electron-hole symmetry and thus they should also be insulators with the Jahn-Teller distortion in C_{60}^{2-} ions lifting the degeneracy. Direct comparison is hampered by the fact that of the A_2C_{60} family only Na_2C_{60} has been prepared so far, and its natural electron-hole counterpart, Na_4C_{60} , forms a polymer at room temperature.¹⁶ Na_2C_{60} , nevertheless, is considered as an ideal material to test the role of Jahn-Teller distortions since in addition to the partial filling with an even number of electrons it crystallizes in a face-centered-cubic structure above 319 K,^{17,18} where the threefold degeneration of both t_{1u} LUMO's and T_{1u} vibrational transitions remains unchanged. Na_2C_{60} has indeed been investigated by several authors^{8,19,20} but findings and interpretations by different groups have been contradictory. A detailed NMR and ESR study⁸ interpreted the temperature dependence of the spin susceptibility in the framework of a Mott-Jahn-Teller singlet ground state with low-energy triplet excitations. The authors concluded that the similar behavior of bcc K_4C_{60} and simple cubic Na_2C_{60} proves the dominant role of molecular distortions over that of the environment. The spin-lattice relaxation at low temperature indicated that the band degeneracy is not completely lifted and the ground state might be weakly metallic. Kubozono *et al.*¹⁹ interpret a sudden change at 50 K in the susceptibility and the Raman

spectrum as a sign of a metal-insulator transition. Reference 20 reports hysteretic behavior in the ESR spectra in the temperature range 300–400 K.

In this paper, we suggest that Na_2C_{60} is not a simple electron-hole analogue of C_{60}^{4-} , but it is yet another example of inhomogeneous charge distribution on the nanoscale. Spatial inhomogeneity is not uncommon in fulleride salts. Metastable cubic CsC_{60} seems to be a nonmagnetic insulator with a charge disproportionation into C_{60}^{2-} ions and C_{60} .^{21,22} Segregation of potassium ions into K_3C_{60} within a continuous C_{60} lattice has been observed for KC_{60} .²³ Disproportionation may also play a role in A_3C_{60} : a dynamic charge fluctuation of C_{60}^{3-} ions into C_{60}^{2-} and C_{60}^{4-} would stabilize the metallic character (Ref. 24). ^{23}Na NMR and ^{13}C magic-angle-spinning NMR data²⁵ in nominally Na_3C_{60} samples also suggest formation of distinct regions of fulleride ions with various charge states. In Na_2C_{60} , we present evidence from infrared, ESR and NMR spectroscopy and neutron scattering that Na^+ ions are inhomogeneously distributed on the scale of a few lattice constants within the ordered C_{60} lattice. This inhomogeneous distribution leads to at least two phases, one of which is C_{60} and one metallic Na_3C_{60} . The material appears homogeneous above ~ 460 K where Na diffusion is fast.

Single phase alkali fulleride salts are difficult to prepare and differences in experimental findings often arise from variations in composition. However, for Na_2C_{60} most groups report the same x-ray diffraction pattern. A well-defined orientational transition is observed at 319 K,^{17,18} at room temperature and below the C_{60} molecules are ordered in a $P\bar{a}3$ structure. The multiphase structure of Na_2C_{60} resolves the controversy between results of different groups: this controversy stems more from the varying sensitivity of specific experimental methods to the presence of distinct phases than from variations in sample preparation.

II. EXPERIMENT

Na_2C_{60} was obtained by solid-state synthesis in inert gas atmosphere in a dry box. Stoichiometric amounts of Na metal and C_{60} powder were heated in a stainless steel capsule. The typical annealing sequence was first 23 days at 350 °C followed by 7 days at 450 °C. To homogenize the samples we reground them about once every five days. The progress of the reaction was monitored by x-ray diffraction (XRD) and room-temperature infrared spectroscopy. After the final step, XRD results were identical to those in the literature.¹⁸ Within the spatial resolution of XRD, a *single* $P\bar{a}3$ phase with a lattice constant of 14.18 Å was found. At this point we tested the high-temperature infrared spectrum as well, to prove that there is no residual C_{60} present. The samples were handled in inert atmosphere (He, Ar or vacuum) throughout all the following preparation and measurement procedures.

Infrared spectra were recorded on pressed KBr pellets in a Bruker IFS 28 FTIR instrument either in a cryostat under dynamic vacuum, or in argon atmosphere in a sealed sample holder with KBr windows, with 1 or 2 cm^{-1} spectral resolution. Samples for investigation by XRD were enclosed in

glass tubes and those for NMR, ESR, and SQUID in quartz tubes.

The static susceptibility was measured by a Quantum Design MPMS-5S SQUID magnetometer between 5 and 600 K. We extracted the susceptibility from fixed-temperature magnetization data between 1 and 5 T. The low-field part was omitted in order to get rid of spurious ferromagnetic contributions.

High-frequency ESR spectra were measured on about 20 mg of Na_2C_{60} powder in a home-built spectrometer operating at 225 GHz (corresponding to a resonance magnetic field of 8.1 T). The 9 GHz spectrum was recorded with a commercial Bruker ELEXSYS 500 spectrometer. α , γ -bis(diphenylene)- β -phenylallyl (BDPA) was used as standard g -factor reference ($g=2.0025$).

NMR spectra were obtained by Fourier transformation of free induction decay (FID) signals. The FID signals were collected by a Tecmag Apollo HF spectrometer in 8.9 T static magnetic field (corresponding ^{13}C frequency, 95 MHz). The frequency scales used are fractional frequency shifts $\Delta f/f$ from the standard reference solution of tetramethylsilane (TMS) with positive shifts indicating higher resonant frequencies.

For neutron scattering measurements, 1.2 g of Na_2C_{60} powder was placed in an annular aluminum sample holder. Temperature-dependent elastic fixed-window scans (EFWS) were taken on both the sample and the empty sample container on the High Flux Backscattering Spectrometer of the NIST Center for Neutron Scattering.²⁶ The individual detector counts were normalized by the neutron monitor of the direct beam and binned into 5 K intervals to improve the signal-to-noise ratio. Background correction consisted of subtracting data measured on the empty sample container under similar conditions. These corrections never exceeded one-third of the sample counts.

III. RESULTS

We investigated the samples of nominal composition Na_2C_{60} by infrared, ESR and NMR spectroscopy, direct measurement of chemical composition and neutron scattering. First we summarize the limits of quantitative determination using the methods we combine in this study. Infrared spectra yield the vibrational frequencies of individual fulleride anions, and reflect their charge and symmetry. While the intensity of a specific absorption peak assigned to a species (e.g., a molecular ion with a given charge) scales linearly with its concentration, the cross sections can differ considerably between species. In metallic systems, the free-electron background further complicates the spectra by smearing the vibrational peaks. ESR gives information on species with unpaired spins. The high-frequency resonances of various phases are well resolved and the relative spin susceptibilities can be determined. NMR intensities scale with the amount of the nucleus investigated, but in C_{60}^{n-} anions, the position of the peaks does not shift enough with charge to be resolved.

Taking into account all the limitations and combining the information from individual methods, we conclude that none of the results at room temperature are compatible with the

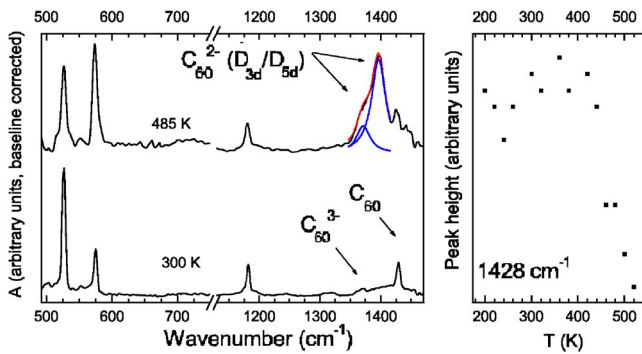


FIG. 1. (Color online) Left panel, infrared absorption of Na₂C₆₀ at 300 K and 485 K in the region of the principal C₆₀ vibrations. Right panel, temperature dependence of the intensity of the 1428 cm⁻¹ line, characteristic of neutral C₆₀.

picture of a homogeneous material containing only C₆₀²⁻ molecular ions. Below we describe the findings by individual methods in detail.

A. Infrared spectroscopy

Figure 1 shows the infrared spectra at 300 K and 485 K. There is an obvious difference between the two spectra, most remarkable in the range of the highest-frequency $T_{1u}(4)$ mode. On cooling back from 480 K to room temperature, the original 300 K spectrum reappears after about 2 weeks.

We discuss first the high-temperature spectrum which confirms the assumption of a homogeneous Na₂C₆₀ phase and then the low-temperature phase which contradicts this assumption.

Of the four infrared-active vibrations of C₆₀, the highest frequency T_{1u} mode is most sensitive to charge n when C₆₀ ^{n -} anions are formed. From the empirical linear relationship between the $T_{1u}(4)$ frequency and n ,²⁷ we estimate the frequency in C₆₀²⁻ to be about 1380 cm⁻¹, possibly with a splitting due to the molecular Jahn-Teller effect.^{14,28} Indeed, above 460 K two bands are resolved at 1369 and 1394 cm⁻¹, close to the expected position of the C₆₀²⁻ absorption. The twofold splitting of the mode indicates D_{3d} or D_{5d} molecular symmetry, i.e., a Jahn-Teller distortion of *molecular* origin.¹⁰

The room-temperature spectrum (Fig. 1) shows a strong peak at 1428 cm⁻¹, typical of neutral C₆₀, and a smeared one with a weak peak at 1370 cm⁻¹. The spectrum does not change on cooling between 300 K and 80 K. The low-temperature spectra are in contradiction with expectations for a homogeneous Na₂C₆₀ compound. The weak peak at 1370 cm⁻¹ is at the position expected for Na₃C₆₀. A₃C₆₀ salts are metallic and show less intense vibrational peaks due to the large background from free-carrier absorption.^{27,29}

The 1428 cm⁻¹ mode cannot be assigned to unreacted residual C₆₀ since it disappears on heating above 460 K and reappears on cooling back in a reproducible manner. The data rather suggest that the material contains a mixture of fulleride ions. We can positively identify neutral C₆₀ molecules and C₆₀³⁻ ions at room temperature and below, and C₆₀²⁻ dianions at higher temperature. We cannot tell from the spectra whether the different vibrational signatures come from

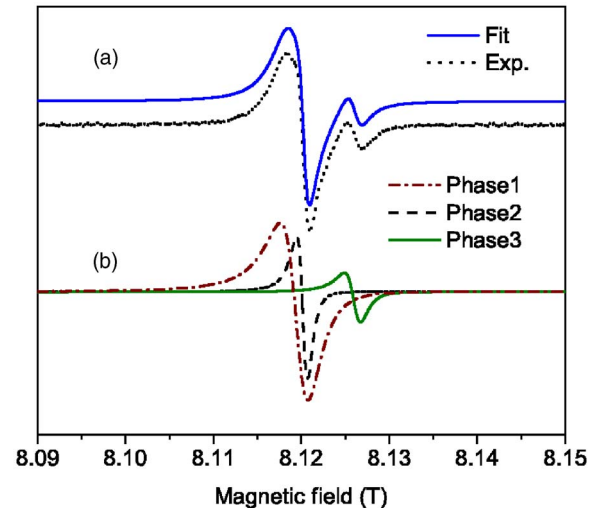


FIG. 2. (Color online) Decomposition of the 225 GHz ESR spectrum into lines corresponding to segregated phases at 40 K. (a) Experimental spectrum and sum of three fitted lines; (b) decomposition of experimental line into three segregated phases.

isolated sites embedded in some other matrix or from highly concentrated phases. However, from the metallic background it is probable that the phase containing C₆₀³⁻ is a metal, presumably Na₃C₆₀. We cannot exclude the presence of small amounts of other fulleride anions at low temperature, either; their vibrational peaks may be buried in the background around 1400 cm⁻¹.

B. Electron spin resonance and static susceptibility

The static susceptibility measured by SQUID magnetometry at 4 T shows three characteristic temperature ranges: (i) $T < 100$ K: a Curie-like paramagnetic increase with decreasing temperature; (ii) $100 \text{ K} < T < 300$ K: an approximately constant susceptibility with $\chi = 1.8 \times 10^{-7}$ emu/gOe; and (iii) $300 \text{ K} < T < 600$ K: a continuous increase to about 6×10^{-7} emu/gOe. The zero value of the static susceptibility is not corrected for core electron effects. The temperature-dependent part of the susceptibility measured by ESR at 9 GHz in Ref. 8 shows the same three characteristic ranges.

In the 225 GHz high-frequency ESR spectra, lines of three phases were resolved at all temperatures between 5 and 450 K. In a conventional spectrometer at 9 GHz, these lines were not resolved; a single line of 9 G peak-to-peak derivative linewidth was found at 300 K. A 225 GHz spectrum taken at 40 K is shown as an example in Fig. 2. We attribute the three lines to three different segregated phases in the nominally Na₂C₆₀ material. The ESR line intensities are proportional to the spin susceptibilities of the various phases and are shown in Fig. 3. The full ESR spectra were decomposed into three Lorentzian lines and the fractional intensities for each line i , $I_i = \chi_i V_i / C$ (the spin susceptibility, χ_i , times the fractional volume, V_i) were determined. The temperature dependence of the full ESR intensity, $C = \sum I_i$, was not measured directly, instead, we normalized the total ESR intensity data at each temperature to the static susceptibilities measured by SQUID.

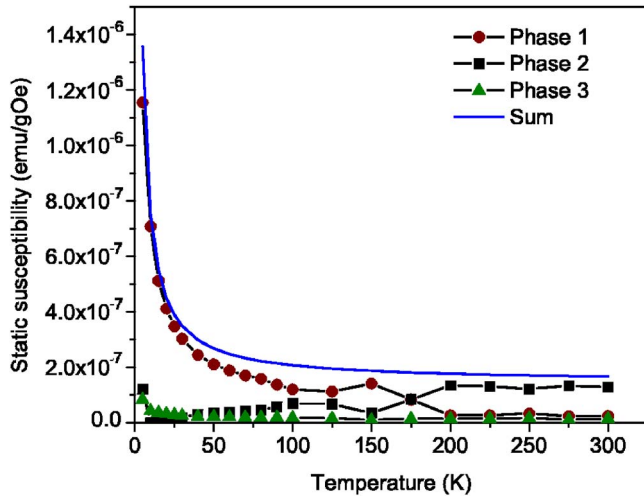


FIG. 3. (Color online) Decomposition of static spin susceptibility into various phases from ESR. The absolute values of the susceptibility were determined from the static (SQUID) measurements.

At low temperature (Fig. 2), the static susceptibility is dominated by a single phase (phase 1) with a Curie-like susceptibility corresponding to 1.3% of C_{60}^- (or other spin- $\frac{1}{2}$) free radicals with respect to the entire C_{60} content of the sample. We denote by phase 2 the phase with the largest ESR intensity at ambient temperature. Phase 3 has a smaller g factor than phases 1 and 2 and could be followed in a wide temperature range despite the small intensity. Since the corresponding susceptibility does not vary strongly, it is possible that phase 3 is metallic and may be assigned to the Na_3C_{60} observed by infrared spectroscopy.

At about 450 K a structural transition takes place, the three low-temperature phases disappear and are replaced by a new phase (Fig. 4). This is the same temperature region where the 1428 cm^{-1} infrared line decreases. The single Lorentzian line indicates an increased homogeneity. The material is, however, still somewhat inhomogeneous between 450 and 500 K since spectra on heating and cooling are different. On rapid cooling (2.5 K/min) the sample is quenched into a homogeneous metastable state. The original phase-segregated material reappears after about 2 weeks at room temperature.

The main conclusion to be drawn from the ESR spectra is that in equilibrium the sample is inhomogeneous below 450 K. C_{60}^{n-} paramagnetic ions with different g factors due to differing environments will show a single resonance at an average g factor if exchange interaction energies between them are larger than $(\Delta g/g)\hbar\omega_L$ where Δg is the difference in g factors and ω_L is the Larmor frequency. Fulleride metals or semiconductors with localized C_{60}^{n-} ions therefore exhibit a single line from the conduction and localized electrons. Neighboring paramagnetic C_{60}^{n-} ions will not show separate resonances even if they are embedded in an insulator. Thus paramagnetic C_{60}^{n-} ions in phase 1 must be isolated from phase 2 by nonmagnetic C_{60}^{n-} ions. The simplest assignment is that phase 1 is solid neutral C_{60} doped with a low concentration of isolated Na^+ ions or small groups of Na^+ ions. Phase 1 must be a non-negligible fraction of the material

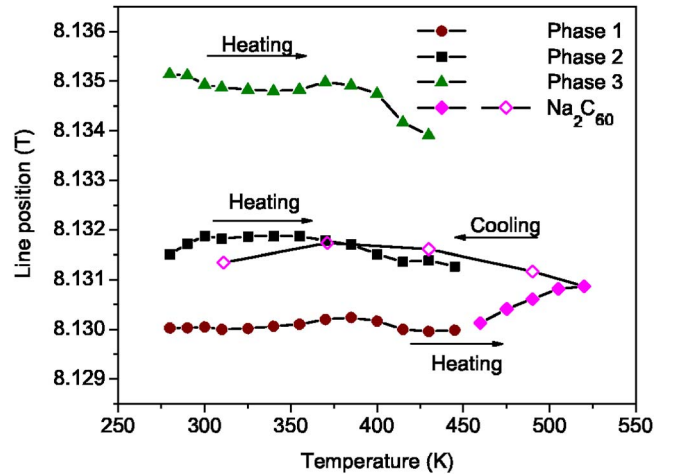


FIG. 4. (Color online) Temperature dependence of 225 GHz ESR line positions of nominal Na_2C_{60} (g factor of phase 1 at 300 K, 2.0012). Full (empty) symbols refer to heating (cooling). The three lines corresponding to various segregated phases merge into a single line on heating above 450 K indicating an increased homogeneity due to Na^+ diffusion. On cooling to 300 K, a metastable phase is established that disappears after a few days.

since it contains over 1% isolated free paramagnetic C_{60}^{n-} ions surrounded by a shell of nonmagnetic ions. We believe this phase is the neutral C_{60} phase detected by ^{13}C NMR containing a small concentration of Na^+ ions and ESR active C_{60}^- . A mixture of phase 2 and phase 3 appears to be the phase studied in detail by ^{13}C and ^{23}Na NMR and attributed to Na_2C_{60} by Brouet *et al.*⁸ Above 450 K the Na^+ ions diffuse rapidly in the crystal lattice and the sample becomes homogeneous.

C. Nuclear magnetic resonance

Infrared absorption measurements detected C_{60}^{n-} molecular ions with various charge states below 460 K and high-frequency ESR experiments revealed several phases in nominal Na_2C_{60} . The C_{60} concentration can be determined using NMR spectroscopy. Figure 5 shows the ^{13}C NMR spectrum of a powder sample at 300 K. With conventional repetition rates of about 1 s^{-1} we observe a single NMR line around 178 ppm with chemical-shift anisotropy (shown in the lower panel of Fig. 5). This spectrum is very similar to that already presented by Rachdi *et al.*³⁰ With a much longer repetition time (250 seconds), however, a further line appears at 143 ppm (upper panel of Fig. 5), which we assign to neutral C_{60} .³¹ As expected for pure C_{60} , the ^{13}C spin-lattice relaxation time is long, about 50 seconds at 300 K. We used a repetition time more than 5 times the T_1 spin-lattice relaxation time of this slowly relaxing spectral component to determine the spectral weights and estimate $25\% \pm 5\%$ neutral C_{60} content in the material. This high value is in agreement with the determination of chemical composition (see below).

Unlike the three phases in high-frequency ESR spectra, only two are resolved by NMR. We assign these as containing neutral and charged C_{60} , respectively, where the charged part contains a mixture of phases, including both Na_3C_{60} and

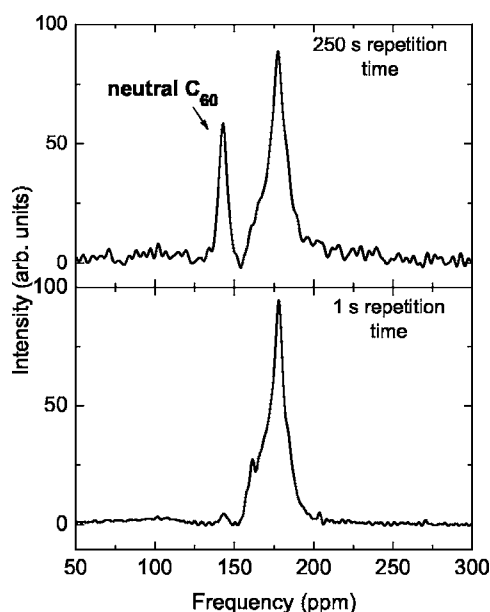


FIG. 5. NMR spectra at 300 K with two different repetition rates. At fast repetition rates only C_{60}^{n-} ions with short spin-lattice relaxation time are recorded. At slow repetition rates the spectrum of neutral C_{60} is also observed.

phase 2. The ^{13}C spin-lattice relaxation of charged C_{60}^{n-} is many orders of magnitude faster than that of C_{60} (T_1 roughly 100 ms compared to 100 s), because of the hyperfine interaction with conducting electrons. The large difference in relaxation rates indicates that cross coupling between nuclei in the charged and neutral phases is small, so these nuclei must be well separated in space. More refined methods, e.g., magic angle spinning NMR, would probably be able to resolve more phases.

D. Chemical composition

In usual multiphase fulleride samples the simplest method to separate pristine C_{60} from its salts is extraction by toluene.³² We extracted C_{60} from the nominally Na_2C_{60} material by soaking it in toluene for 11 days. Following this treatment, we determined the C_{60} content of the solution by high-pressure liquid chromatography (HPLC). The weight percentage of C_{60} can be calculated from the concentration of the C_{60} solution and the weight of the starting material. To obtain the mole percentage of C_{60} we assume that the material contains only one Na_xC_{60} phase besides the C_{60} phase, but we do not assume that the total stoichiometry of the material is nominal Na_2C_{60} . If the Na-fulleride phase in the material were NaC_{60} then the C_{60} content would be 27 mole percent. The other extreme, $\text{Na}_{12}\text{C}_{60}$, would give 33 mole percent. This estimated composition of 27%–33% C_{60} is in reasonable agreement with the NMR results.

E. Neutron scattering

Diffusion of sodium was directly observed using neutron scattering. In this measurement, the incident neutron energy is fixed at 2.08 meV and scattering processes are detected

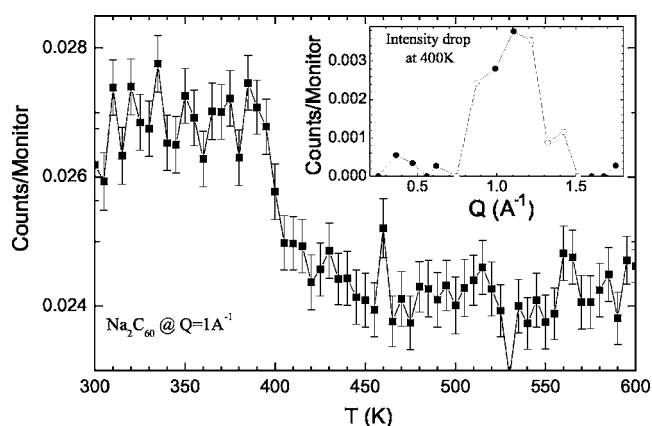


FIG. 6. Elastic fixed-window scan (EFWS) intensity of Na_2C_{60} at $Q=1 \text{ \AA}^{-1}$. Inset, Q dependence of the drop in EFWS intensity around 400 K (with empty circles indicating detectors obscured by Na_2C_{60} diffraction peaks).

near the elastic line within the energy window of the resolution of the instrument ($1 \mu\text{eV}$). Thus when a dynamic process, such as sodium jump diffusion, becomes faster than the corresponding time scale of 0.8 ns, the measured EFWS intensity decreases.³³ Figure 6 shows the temperature dependence of the elastic line intensity at $Q=1 \text{ \AA}^{-1}$. This intensity shows typical Debye-Waller type decrease overall, but an unusual drop appears around 400 K over approximately 20 K. Our interpretation is that the jump diffusion of sodium ions between tetrahedral and octahedral sites becomes fast enough above 400 K to be resolved by the instrument and thus the incoherent scattering contribution of the sodium ions is removed from the EFWS intensity. The EFWS intensity of the background is much smaller than that of Na_2C_{60} and its temperature dependence is featureless.

We can get an idea of the nature of the Na^+ motion by looking at the Q dependence of the anomalous drop of the EFWS intensity, shown in the inset of Fig. 6. The largest drop of the elastic intensity occurs near $Q=1.1 \text{ \AA}^{-1}$, which in a jump-diffusion model corresponds to a jump distance of $4.0 \pm 0.5 \text{ \AA}$.³⁴ The Q resolution is determined by the fact that the detectors of the spectrometer integrate over 0.2 \AA^{-1} regions in Q . Diffraction peaks of Na_2C_{60} (Ref. 35) between 0.5 \AA^{-1} and 0.9 \AA^{-1} and also between 0.2 \AA^{-1} and 1.6 \AA^{-1} obscure the EFWS, as indicated by empty circles, so these points are less reliable and we cannot make further inferences from these data about the nature of the Na^+ jumps.

Due to steric hindrance, the diffusion of Na^+ ions can only proceed through the trigonal point between the tetrahedral and octahedral voids, i.e., in the $\langle 111 \rangle$ direction. In this direction, removed 4.0 \AA from the tetrahedral site, there is an off-centered octahedral site. This site is special because it has the same nearest-neighbor distances as the tetrahedral site, so that the Coulomb interaction between the Na^+ cation and the fulleride anions remains optimal. Occupation of low-symmetry octahedral positions by Na^+ ions was previously suggested by Schurko *et al.*,²⁵ based on ^{23}Na NMR experiments on samples with nominal composition Na_3C_{60} .


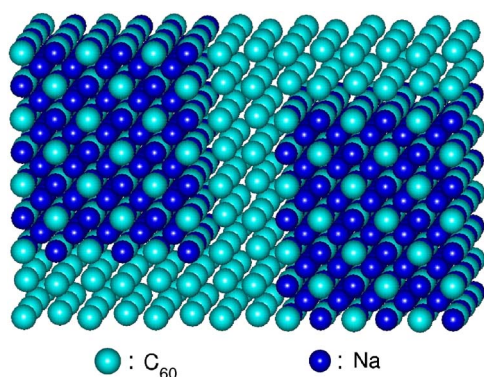


FIG. 7. (Color online) Schematic view of segregated regions with and without sodium ions. Estimated area of the regions is between 3 and 10 nm.

IV. DISCUSSION

All the results presented above can be reconciled if we assume a synproportion and/or disproportion reaction



taking place on cooling after preparation from left to right and on heating from right to left. Combining the data, we can also draw quantitative conclusions as to the stoichiometry, the size of the domains, and the time scale of the dynamics.

ESR, infrared and NMR measurements all confirm the presence of neutral C_{60} in the material. While the former two methods yield qualitative results, NMR also provides quantitative data. From NMR and chemical composition studies, we obtain the range for the C_{60} content to be between 20 and 33 mole percent at room temperature. We illustrate an idealized picture of the fully nanosegregated phases in Fig. 7, consisting of 33% C_{60} and 67% Na_3C_{60} . In reality at finite temperatures the reaction is probably not complete, partly because of entropy reasons and partly because the interfaces between the segregated regions must consist of fulleride ions only partially surrounded by sodium ions. These interfaces may be responsible for the additional ESR signal, the broad NMR line and the broad background of the infrared spectrum between 1350 and 1440 cm^{-1} .

The spectroscopic results apparently contradict the x-ray diffraction data which see the material as a single phase. We must take into account, though, that while diffraction measures the average crystal structure, over a relatively large area, spectroscopy is sensitive to local structure, i.e., domains of a few molecules. X-ray diffraction averages out inhomogeneities less than about 100 Å, especially if the structure of the constituting phases is similar. In Na_3C_{60} , the fulleride ions occupy fcc sites identical to those of C_{60} molecules in a C_{60} crystal, and the lattice constant of Na_3C_{60} of 14.19 Å is very close to that of C_{60} , 14.15 Å.

The lower size limit of the homogeneous domains can be estimated from the metallic nature of the Na_3C_{60} phase. For metallic behavior, a thickness of a few molecules is required. The lattice constants are about 1.4 nm and the size of homogeneous domains must be in the range 3–10 nm.

At high temperature the nanosegregated phase changes into a homogeneous phase by sodium diffusion in a more or less unaltered C_{60} lattice. We observed in the neutron scattering experiments that sodium ions jump from site to site on the time scale of 0.8 ns at 400 K. In a nanosegregated structure with mobile sodium ions, diffusion leads to homogenization. The extra electrons migrate along with the ions because of Coulomb attraction, eventually leading to charge equilibrium in the system. Once the diffusion rate is high enough to achieve this equilibrium, the diffusion does not cause further charge migration and the material appears homogeneous by all spectroscopic methods. ESR shows a hysteretic phase segregation: on heating we observe segregated phases up to 450 K. Above 450 K there are no well separated conducting and insulating regions and the resonance is narrowed into a single line by electronic spin diffusion. This close-to-homogeneous phase is preserved for some time on cooling. A metastable phase with a single ESR line is observed on cooling rapidly from 520 K to 300 K. Infrared spectra also show homogeneous charge distribution above 460 K, with indications of a metastable phase surviving on the time scale of weeks after cooling to room temperature.

The twofold splitting of the $T_{1u}(4)$ infrared line at high temperature suggests that the symmetry of the molecules in the homogeneous phase is D_{3d} or D_{5d} . At first sight, this symmetry seems to contradict the cubic crystal structure, but can be explained as follows. Since in the high-temperature phase of Na_2C_{60} the molecules show quasifree rotation,^{17,18} the distorting effect of the crystal field is averaged out. The absence of crystal field, however, does not mean that the shape of the molecule will stay spherical; it will be determined by the interaction of molecular vibrations with the two extra electrons occupying the LUMO (the molecular Jahn-Teller interaction).¹⁰ In case of dianions, the result is a set of equivalent D_{3d} or D_{5d} distortions in different (symmetry-related) directions. These equivalent distortions transform into each other by a special motion called *pseudorotation*,¹⁰ and their average will be icosahedral. (Tomita *et al.*³⁶ present a detailed explanation of the effect and provide experimental evidence from near-infrared spectroscopy of isolated C_{60}^{2-} ions.) Nevertheless, if the time scale of a measurement is smaller than that of the pseudorotation, the distorted structure will be detected. This must be the case of the infrared spectra. The high-temperature phase of Na_2C_{60} is another example of the dynamical Jahn-Teller effect in fulleride salts. The resulting symmetry strongly resembles that occurring in the high-temperature phase of $A_4\text{C}_{60}$ compounds,¹⁵ proving the argument by Brouet *et al.* about the molecular interactions dominating over crystal field effects in both systems.⁸

V. CONCLUSIONS

We have presented ample evidence from a wide range of analytical and spectroscopic methods that the fulleride salt with nominal composition Na_2C_{60} at room temperature

forms nanosegregated domains with a large portion of C₆₀ (containing Na⁺ ions in a low concentration) and other phases with high Na⁺ ion concentration, including metallic Na₃C₆₀. We estimate the amount of C₆₀ in the material to be 20%–33% at 300 K. A synproportion reaction takes place on warming, homogeneity is achieved by the diffusion of sodium ions. In the homogeneous material, the C₆₀²⁻ anions undergo dynamic Jahn-Teller distortion to D_{3d}/D_{5d} symmetry.

Our samples showed the same x-ray diffraction pattern, 9 GHz ESR spectrum and low retention time NMR spectrum as those investigated previously. We expanded these experiments to different measuring conditions and employed additional methods such as infrared spectroscopy, chemical composition determination and neutron scattering. All these experiments can be reconciled by assuming the nanosegregation model at low temperature and homogeneous Na₂C₆₀ at high temperature. The results clarify the main reason for the

contradictory results in the literature. They also underline the necessity of new experiments for the verification of the Mott-Jahn-Teller picture of insulating fulleride salts.

ACKNOWLEDGMENTS

The authors gratefully acknowledge the help of G. Oszlányi with x-ray diffraction measurements and extensive discussions. Work in Hungary was supported by the Hungarian National Research Fund under Grants Nos. OTKA T049338, T046700, TS049881, and T043255. This work also utilized neutron research facilities of the National Institute of Standards and Technology, U.S. Department of Commerce, supported in part by the NSF Grant No. DMR-0454672. One of the authors (N.N.M.) is supported by the Juan de la Cierva Program of the Spanish Ministry of Education.

*Electronic address: klupp@szfki.hu; URL: www.szfki.hu/~klupp
¹S. C. Erwin, in *Buckminsterfullerenes*, edited by W. A. Billups and M. Ciuffolini (VCH, New York, 1992), p. 217.
²J. P. Lu, *Phys. Rev. B* **49**, 5687 (1994).
³A. F. Hebard, M. J. Rosseinsky, R. C. Haddon, D. W. Murphy, S. H. Glarum, T. T. M. Palstra, A. P. Ramirez, and A. R. Kortan, *Nature (London)* **350**, 600 (1991).
⁴P. W. Stephens, G. Bortel, G. Faigel, M. Tegze, A. Jánossy, S. Pekker, G. Oszlányi, and L. Forró, *Nature (London)* **370**, 636 (1994).
⁵S. Pekker, L. Forró, L. Mihály, and A. Jánossy, *Solid State Commun.* **90**, 349 (1994).
⁶F. Bommeli, L. Degiorgi, P. Wachter, Ö. Legeza, A. Jánossy, G. Oszlányi, O. Chauvet, and L. Forro, *Phys. Rev. B* **51**, 14794 (1995).
⁷M. Fabrizio and E. Tosatti, *Phys. Rev. B* **55**, 13465 (1997).
⁸V. Brouet, H. Alloul, S. Garaj, and L. Forró, *Phys. Rev. B* **66**, 155122 (2002).
⁹M. Knupfer and J. Fink, *Phys. Rev. Lett.* **79**, 2714 (1997).
¹⁰C. C. Chancy and M. C. M. O'Brien, *The Jahn-Teller Effect in C₆₀ and Other Icosahedral Complexes* (Princeton University Press, Princeton, NJ, 1997).
¹¹P. Dahlke, P. F. Henry, and M. J. Rosseinsky, *J. Mater. Chem.* **8**, 1571 (1998).
¹²P. Dahlke and M. J. Rosseinsky, *Chem. Mater.* **14**, 1285 (2002).
¹³C. A. Kuntscher, G. M. Bendele, and P. W. Stephens, *Phys. Rev. B* **55**, R3366 (1997).
¹⁴K. Kamarás, G. Klupp, D. B. Tanner, A. F. Hebard, N. M. Nemes, and J. E. Fischer, *Phys. Rev. B* **65**, 052103 (2002).
¹⁵G. Klupp, K. Kamarás, N. M. Nemes, C. M. Brown, and J. Leão, *Phys. Rev. B* **73**, 085415 (2006).
¹⁶G. Oszlányi, G. Baumgartner, G. Faigel, and L. Forró, *Phys. Rev. Lett.* **78**, 4438 (1997).
¹⁷T. Yildirim, J. E. Fischer, P. W. Stephens, and A. R. McGhie, in *Progress in Fullerene Research*, edited by H. Kuzmany, J. Fink, M. Mehring, and S. Roth (World Scientific, Singapore, 1994), p. 235.
¹⁸T. Yildirim, J. E. Fischer, A. B. Harris, P. W. Stephens, D. Liu, L. Brard, R. M. Strongin, and A. B. Smith III, *Phys. Rev. Lett.* **71**, 1383 (1993).

¹⁹Y. Kubozono, Y. Takabayashi, S. Fujiki, S. Kashino, T. Kambe, Y. Iwasa, and S. Emura, *Phys. Rev. B* **59**, 15062 (1999).
²⁰P. Petit, J. Robert, J.-J. André, and J. E. Fischer, in *Progress in Fullerene Research*, edited by H. Kuzmany, J. Fink, M. Mehring, and S. Roth (World Scientific, Singapore, 1994), p. 478.
²¹V. Brouet, H. Alloul, F. Quéré, G. Baumgartner, and L. Forró, *Phys. Rev. Lett.* **82**, 2131 (1999).
²²V. Brouet, H. Alloul, and L. Forró, *Phys. Rev. B* **66**, 155123 (2002).
²³G. Faigel, G. Bortel, M. Tegze, L. Granasy, S. Pekker, G. Oszlányi, O. Chauvet, G. Baumgartner, L. Forro, P. W. Stephens, G. Mihaly, and A. Janossy, *Phys. Rev. B* **52**, 3199 (1995).
²⁴V. Brouet, H. Alloul, T.-N. Le, S. Garaj, and L. Forró, *Phys. Rev. Lett.* **86**, 4680 (2001).
²⁵R. W. Schurko, M. J. Willans, B. Skadtchenko, and D. M. Antonelli, *J. Solid State Chem.* **177**, 2255 (2004).
²⁶A. Meyer, R. M. Dimeo, P. M. Gehring, and D. A. Neumann, *Rev. Sci. Instrum.* **74**, 2759 (2003).
²⁷T. Pichler, R. Winkler, and H. Kuzmany, *Phys. Rev. B* **49**, 15879 (1994).
²⁸V. C. Long, J. L. Musfeldt, K. Kamarás, A. Schilder, and W. Schütz, *Phys. Rev. B* **58**, 14338 (1998).
²⁹M. C. Martin, D. Koller, and L. Mihaly, *Phys. Rev. B* **47**, 14607 (1993).
³⁰F. Rachdi, L. Hajji, M. Galtier, T. Yildirim, J. E. Fischer, C. Goze, and M. Mehring, *Phys. Rev. B* **56**, 7831 (1997).
³¹R. Tycko, G. Dabbagh, R. M. Fleming, R. C. Haddon, A. V. Makhija, and S. M. Zahurak, *Phys. Rev. Lett.* **67**, 1886 (1991).
³²M. Carrard, L. Forro, L. Mihaly, and S. Pekker, *Synth. Met.* **80**, 29 (1996).
³³T. Becker and J. C. Smith, *Phys. Rev. E* **67**, 021904 (2003).
³⁴J. DeWall, R. M. Dimeo, and P. E. Sokol, *J. Low Temp. Phys.* **129**, 171 (2002).
³⁵M. J. Rosseinsky, D. W. Murphy, R. M. Fleming, R. Tycko, A. P. Ramirez, T. Siegrist, G. Dabbagh, and S. E. Barrett, *Nature (London)* **356**, 416 (1992).
³⁶S. Tomita, J. U. Andersen, E. Bonderup, P. Hvelplund, B. Liu, S. B. Nielsen, U. V. Pedersen, J. Rangama, K. Hansen, and O. Echt, *Phys. Rev. Lett.* **94**, 053002 (2005).