

# Extremely strong-coupling superconductivity and anomalous lattice properties in the $\beta$ -pyrochlore oxide $\text{KOs}_2\text{O}_6$

Z. Hiroi, S. Yonezawa, Y. Nagao, and J. Yamaura

*Institute for Solid State Physics, University of Tokyo, Kashiwa, Chiba 277-8581, Japan*

(Received 31 October 2006; published 25 July 2007)

Superconducting and normal-state properties of the  $\beta$ -pyrochlore oxide  $\text{KOs}_2\text{O}_6$  are studied by means of thermodynamic and transport measurements. It is shown that the superconductivity is of conventional  $s$ -wave type and lies in the extremely strong-coupling regime. Specific heat and resistivity measurements reveal that there are characteristic low-energy phonons that give rise to unusual scattering of carriers due to strong electron-phonon interactions. The entity of the low-energy phonons is ascribed to the heavy rattling of the K ion confined in an oversized cage made of  $\text{OsO}_6$  octahedra. It is suggested that this electron-rattler coupling mediates the Cooper pairing, resulting in the extremely strong-coupling superconductivity.

DOI: [10.1103/PhysRevB.76.014523](https://doi.org/10.1103/PhysRevB.76.014523)

PACS number(s): 74.70.-b, 74.25.Kc, 74.25.Bt, 74.25.Fy

## I. INTRODUCTION

The study of non-Cu-based oxide superconductors has been extended during the past decade, aiming at understanding the role of electron correlations in the mechanism of superconductivity or searching for a novel pairing mechanism, hopefully to reach a higher  $T_c$ . An interesting example recently found is a family of pyrochlore oxide superconductors. The first discovered is  $\alpha$ -pyrochlore rhenate  $\text{Cd}_2\text{Re}_2\text{O}_7$  with  $T_c=1.0$  K (Refs. 1–3) and the second  $\beta$ -pyrochlore osmate  $\text{AOs}_2\text{O}_6$  with  $T_c=3.3, 6.3,$  and  $9.6$  K for  $A=\text{Cs}, \text{Rb},$  and  $\text{K},$ <sup>8</sup> respectively. They crystallize in the cubic pyrochlore structure of space group  $Fd\bar{3}m$  and commonly possess a three-dimensional skeleton made of  $\text{ReO}_6$  or  $\text{OsO}_6$  octahedra.<sup>9</sup> The “pyrochlore” sublattice occupied by the transition-metal ions is comprised of corner-sharing tetrahedra that are known to be highly frustrating for a localized spin system with antiferromagnetic nearest-neighbor interactions.

A unique structural feature for the  $\beta$ -pyrochlores is that a relatively small  $A$  ion is located in an oversized atomic cage made of  $\text{OsO}_6$  octahedra (Fig. 1). Due to this large size mismatch, the  $A$  atom can rattle in the cage.<sup>10</sup> The rattling has been recognized recently as an interesting phenomenon for a class of compounds like filled skutterudites<sup>11</sup> and Ge/Si clathrates<sup>12</sup> and has attracted many researchers, because it may suppress thermal conductivity, leading to an enhanced thermoelectric efficiency. On the other hand, the rattling is also intriguing from the viewpoint of lattice dynamics: it gives an almost localized mode even in a crystalline material and often exhibits unusual anharmonicity.<sup>11</sup> Hence, it is considered that the rattling is a new type of low-lying excitations that potentially affects various properties in a crystal at low temperature.

In the  $\beta$ -pyrochlores, specific-heat experiments found low-energy contributions that could be described approximately by the Einstein model and determined the Einstein temperature  $T_E$  to be 70, 60, and 40 or 31 K for  $A=\text{Cs}, \text{Rb},$  and  $\text{K},$  respectively.<sup>13,14</sup> This tendency illustrates the uniqueness of the rattling, because, on the contrary, one expects a higher frequency for a lighter atom in the case of conventional phonons. Moreover, it was demonstrated that the spe-

cific heat shows an unusual  $T^5$  dependence at low temperature below 7 K for  $A=\text{Cs}$  and  $\text{Rb},$  instead of a usual  $T^3$  dependence from a Debye-type phonon.<sup>13</sup> On one hand, structural refinements revealed large atomic displacement parameters at room temperature of  $100U_{\text{iso}}=2.48, 4.26,$  and  $7.35 \text{ \AA}^2$  for  $A=\text{Cs}, \text{Rb},$  and  $\text{K},$  respectively,<sup>10</sup> and  $3.41 \text{ \AA}^2$  for  $\text{Rb}.$ <sup>15</sup> Particularly, the value for  $\text{K}$  is enormous and may be the largest among rattlers so far known in related compounds. This trend over the  $\beta$ -pyrochlore series is ascribed to the fact that an available space for the  $A$  ion to move in a rather rigid cage increases with decreasing the ionic radius of the  $A$  ion.<sup>10</sup> Kuneš *et al.* calculated an energy potential for each  $A$  ion and found, in fact, a large anharmonicity, that is, a deviation from a quadratic form expected for the harmonic oscillator approximation.<sup>16</sup> Especially for the smallest  $\text{K}$  ion, they found four shallow potential minima located away from the center ( $8b$  site) along the  $\langle 111 \rangle$  directions pointing to the nearest  $\text{K}$  ions, as schematically shown in Fig. 1. The potential minima are so shallow that the  $\text{K}$  ion may not stop at one of them even at very low temperature.

The electronic structures of  $\alpha$ - $\text{Cd}_2\text{Re}_2\text{O}_7$  and  $\beta$ - $\text{AOs}_2\text{O}_6$  have been calculated by first-principles density-functional methods, which reveal that a metallic conduction occurs in the (Re, Os)-O network:<sup>16–20</sup> electronic states near the Fermi level originate from transition metal  $5d$  and O  $2p$  orbitals. Although the overall shape of the density of states (DOS) is similar for the two pyrochlores, a difference in band filling

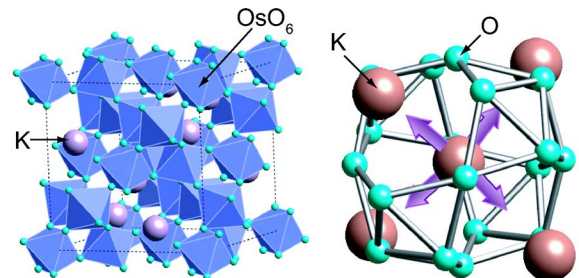


FIG. 1. (Color online) Crystal structure of the  $\beta$ -pyrochlore oxide  $\text{KOs}_2\text{O}_6$ . The  $\text{K}$  ion (big ball) is located in an oversized atomic cage made of  $\text{OsO}_6$  octahedra and can move along the four  $\langle 111 \rangle$  directions pointing to the neighboring  $\text{K}$  ions in adjacent cages.

may result in different properties;  $\text{Re}^{5+}$  for  $\alpha\text{-Cd}_2\text{Re}_2\text{O}_7$  has two 5d electrons, while  $\text{Os}^{5.5+}$  for  $\beta\text{-AOs}_2\text{O}_6$  has two and a half. Moreover, a related  $\alpha$ -pyrochlore  $\text{Cd}_2\text{Os}_2\text{O}_7$  with  $\text{Os}^{5+}$  ( $5d^3$ ) exhibits a metal-to-insulator transition at 230 K.<sup>21,22</sup>

Various experiments have been carried out on the pyrochlore oxide superconductors to elucidate the mechanism of the superconductivity. Most of the results obtained for  $\alpha\text{-Cd}_2\text{Re}_2\text{O}_7$  indicate that it is a weak-coupling BCS-type superconductor.<sup>23,24</sup> In contrast, results on the  $\beta$ -pyrochlores are somewhat controversial. Although the  $T_c$  increases smoothly from Cs to K, the jump in specific heat at  $T_c$ , the upper critical field, and the Sommerfeld coefficient all exhibit a large enhancement toward K.<sup>25</sup> Thus, the K compound is always distinguished from the others. Pressure dependence of  $T_c$  was also studied for the two pyrochlores, showing a common feature: as pressure increases,  $T_c$  first increases, exhibits a broad maximum, and goes to zero above a critical pressure that depends on the system, for example, about 6 GPa for the K compound.<sup>26–29</sup>

On the symmetry of the superconducting gap for the  $\beta$ -pyrochlores, Rb-NMR and muon spin rotation ( $\mu\text{SR}$ ) experiments gave evidence for  $s$ -wave superconductivity for  $\text{RbOs}_2\text{O}_6$ .<sup>30–32</sup> In contrast, Arai *et al.* carried out K-NMR experiments and found no coherence peak in the relaxation rate below  $T_c$  for  $\text{KOs}_2\text{O}_6$ , which seemed to indicate unconventional superconductivity.<sup>32</sup> However, their recent interpretation is that the absence of a coherence peak does not necessarily mean non- $s$  pairing, because the relaxation rate probed by the K nuclei can be affected dominantly by strongly overdamped phonons.<sup>33</sup> Kasahara *et al.* measured thermal conductivity using a  $\text{KOs}_2\text{O}_6$  single crystal and concluded a full gap from the insensitivity of thermal conductivity to magnetic fields.<sup>34</sup> Moreover, very recent photoemission spectroscopy (PES) experiments revealed the opening of a large isotropic gap below  $T_c$ .<sup>35</sup> On one hand, a  $\mu\text{SR}$  experiment claimed that the gap of  $\text{KOs}_2\text{O}_6$  is anisotropic, or otherwise, there are two gaps.<sup>36</sup> Therefore, the pairing symmetry of the  $\beta\text{-AOs}_2\text{O}_6$  superconductors may be of the conventional  $s$  wave, aside from minor aspects such as anisotropy or multigaps, which means that the fundamental pairing mechanism is ascribed to phonons. Then, an important question is what kind of phonons are relevant for the occurrence. To find out the reason for the observed singular appearance toward K in the series must be the key to understanding the interesting physics involved in this system.

Previous studies have suffered from poor quality of samples, because only polycrystalline samples were available. The Sommerfeld coefficient  $\gamma$  was estimated from specific heat, by extracting contributions from Os metal impurity, to be  $40 \text{ mJ K}^{-2} \text{ mol}^{-1}$  for both Cs and Rb,<sup>13</sup> and  $34 \text{ mJ K}^{-2} \text{ mol}^{-1}$  for Rb.<sup>7</sup> Recently, Brühwiler *et al.* obtained large values of  $\gamma=76\text{--}110 \text{ mJ K}^{-2} \text{ mol}^{-1}$  for  $\text{KOs}_2\text{O}_6$  by collecting five dozen tiny crystals.<sup>14</sup> However, there is an ambiguity in their values, because of uncertainty in their extrapolation method. They also reported strong-coupling superconductivity with a coupling constant  $\lambda_{ep}=1.0\text{--}1.6$ .<sup>14</sup> Recently, we successfully prepared a large single crystal of 1 mm size for  $\text{KOs}_2\text{O}_6$  and reported two intriguing phenomena: one is a sharp and huge peak in specific heat at  $T_p=7.5\text{--}7.6 \text{ K}$  below  $T_c$ , indicative of a first-order structural

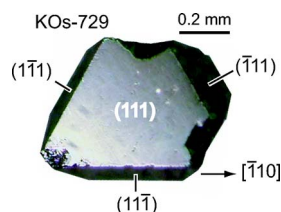


FIG. 2. (Color online) Photograph of the KOs-729 crystal used in the present study. It possesses a truncated octahedral shape with 111 facets. The approximate size is  $1.0 \times 0.7 \times 0.3 \text{ mm}^3$ . Resistivity measurements were carried out with a current flow along the  $[\bar{1}10]$  direction.

transition,<sup>37,38</sup> and the other is anisotropic flux pinning at low magnetic fields around 2 T.<sup>39</sup> It was suggested that the former is associated with the rattling freedom of the K ion. Moreover, anomalous concave-downward resistivity was observed down to  $T_c$ , suggesting a peculiar scattering mechanism of carriers.

In this paper, we present specific heat, magnetization, and resistivity measurements on the same high-quality single crystal of  $\text{KOs}_2\text{O}_6$ . Reliable data on the superconducting and normal-state properties are obtained, which provide evidence for an extremely strong-coupling superconductivity realized in this compound. We discuss the role of rattling vibrations of the K ion on the mechanism of the superconductivity.

## II. EXPERIMENT

### A. Sample preparation

A high-quality single crystal was prepared and used for all the measurements in the present study, which was named KOs-729 after the date July 29, 2005 when the first experiment was performed on this crystal. It was grown from a pellet containing an equimolar mixture of  $\text{KOsO}_4$  and Os metal in a sealed quartz tube at 723 K for 24 h. Additional oxygen was supplied by using the thermal decomposition of  $\text{AgO}$  placed away from the pellet in the tube. The  $\text{KOsO}_4$  powder had been prepared in advance from  $\text{KO}_2$  and Os metal in the presence of excess oxygen. It was necessary to pay attention to avoid the formation of  $\text{OsO}_4$  in the course of preparation, which is volatile even at room temperature and highly toxic to the eyes or nose. After the reaction, several tiny crystals had grown on the surface of the pellet. Although the mechanism of the crystal growth has not yet been understood clearly, it probably occurs through partial melting and the following reaction with a vapor phase.

The KOs-729 crystal possesses a truncated octahedral shape with a large (111) facet as shown in Fig. 2 and is approximately  $1.0 \times 0.7 \times 0.3 \text{ mm}^3$  in size and 1.302 mg in weight. The high quality of the crystal has been demonstrated by a sharp peak at  $T_p$  in specific heat,<sup>38</sup> which was absent in the previous polycrystalline samples or appeared as broad humps in our previous aggregate of tiny crystals<sup>37</sup> or in five dozen tiny crystals by Brühwiler *et al.*<sup>14</sup> Moreover, a dramatic angle dependence of flux-flow resistance was observed on this crystal, indicating that flux pinning is enhanced in magnetic fields along certain crystallographic di-

rections such as [110], [001], and [112].<sup>39</sup> This evidences the absence of domains in this relatively large crystal.

Special care has been taken to keep the crystal always in a dry atmosphere, because it readily undergoes hydration in air, as reported in isostructural compounds such as  $\text{KNbWO}_6$ .<sup>40,41</sup> Once partial hydration takes place in  $\text{KOs}_2\text{O}_6$ , the second sharp anomaly in specific heat tends to collapse. In contrast, the superconducting transition was robust, just slightly broadened after hydration. The hydration must be relatively slow in a single crystal compared with the case of polycrystalline samples, which may be the reason for the broad anomaly or the absence in previous samples.

## B. Physical property measurements

Both specific heat and electrical resistivity were measured in a temperature range between 300 and 0.4 K, and in magnetic fields of up to 14 T in a Quantum Design Physical Property Measurement System (PPMS) equipped with a  $^3\text{He}$  refrigerator. The magnetic fields had been calibrated by measuring the magnetization of a standard Pd specimen and also by measuring the voltage of a Hall device (F.W. BELL, BHA-921). Specific-heat measurements were performed by the heat-relaxation method. The  $\text{KOs}_2\text{O}_6$  crystal was attached to an alumina platform by a small amount of Apiezon N grease. In each measurement, heat capacity was obtained by fitting a heat-relaxation curve recorded after a heat pulse, giving a temperature rise of approximately 2%. The heat capacity of an addendum had been measured in a separate run without a sample, and was subtracted from the data. The measurements were done three times at each temperature, with a scatter less than 0.3% at most.

Resistivity measurements were carried out by the four-probe method with a current flow along the  $[\bar{1}10]$  direction and magnetic fields along the [111], [110], [001], or [112] direction of the cubic crystal structure. All the measurements were done at a current density of  $1.5 \text{ A cm}^{-2}$ . Magnetization was measured in magnetic fields up to 7 T in a Quantum Design magnetic property measurement system and also up to 14 T in PPMS. The magnetic fields were applied approximately along the [111] or  $[\bar{1}10]$  direction.

## III. RESULTS

### A. Superconducting properties

#### 1. Specific heat

First of all, we analyze specific-heat data in order to obtain a reliable value of the Sommerfeld coefficient  $\gamma$ . There are two obstacles: one is the large upper critical field  $H_{c2}$  that is approximately two times greater than our experimental limit of 14 T. Brühwiler *et al.* reported  $\gamma = 76$  (110)  $\text{mJ K}^{-2} \text{ mol}^{-1}$  assuming  $\mu_0 H_{c2} = 24$  (35) T by an extrapolation method.<sup>14</sup> Their values should be modified to  $\gamma \sim 100 \text{ mJ K}^{-2} \text{ mol}^{-1}$ , because recent high-magnetic-field experiments revealed  $\mu_0 H_{c2} = 30.6$  or 33 T.<sup>42,43</sup> Nevertheless, there are still large ambiguities in their extrapolation method using specific-heat data obtained only at  $H/H_{c2} < 0.5$ . The other difficulty comes from unusual lattice contributions in

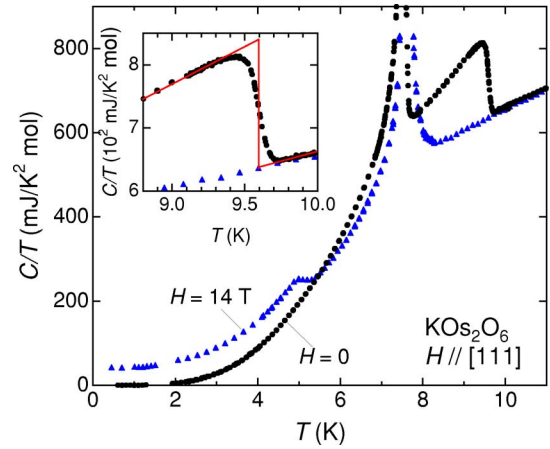


FIG. 3. (Color online) Specific heat divided by temperature measured at zero field (circle) and a magnetic field of 14 T (triangle) applied along the [111] direction. The inset shows an enlargement of the superconducting transition with an entropy-conserving construction.

specific heat at low temperature and the existence of a sharp peak at  $T_p$ . Thus, it is not easy to extract the lattice contribution in a standard way used so far. Here, we carefully analyze specific-heat data and reasonably divide them into electronic and lattice parts, from which a reliable value of  $\gamma$  is determined and information on the superconducting gap is attained.

Figure 3 shows the temperature dependence of specific heat of the  $\text{KOs}_2\text{O}_6$  crystal measured on cooling at zero field and in a magnetic field of 14 T applied along the [111] direction. A superconducting transition at zero field takes place with a large jump, followed by a huge peak due to the second phase transition at  $T_p = 7.5 \text{ K}$ . The entropy-conserving construction shown in the inset gives  $T_c = 9.60 \text{ K}$ ,  $\Delta C/T_c = 201.2 \text{ mJ K}^{-2} \text{ mol}^{-1}$ , which is close to the values previously reported,<sup>14,37</sup> and a transition width ( $\Delta T_c$ ) of 0.3 K.  $T_c$  is reduced to 5.2 K at 14 T, which is evident as a bump in the 14 T data shown in Fig. 3. In contrast, Brühwiler *et al.* reported  $T_c = 6.2 \text{ K}$  at 14 T, though the transition was not clearly observed in their specific-heat data. The  $C/T$  at zero field rapidly decreases to zero as  $T$  approaches absolute zero. The absence of a residual  $T$ -linear contribution in specific heat indicates the high quality of the crystal.

The specific heat of a crystal ( $C$ ) is the sum of an electronic contribution ( $C_e$ ) and a  $H$ -independent lattice contribution ( $C_l$ ). The former becomes  $C_{en}$  for the normal state above  $T_c$ , which is taken as  $\gamma T$ , and  $C_{es}$  for the superconducting state below  $T_c$ . The  $\gamma$  is assumed to be  $T$ -independent, though it cannot be the case for compounds with strong electron-phonon couplings.<sup>44</sup> In the case of  $\text{KOs}_2\text{O}_6$ ,  $C_l$  is large relative to  $C_e$ : for example,  $C_l$  is as large as  $\sim 90\%$  of the total  $C$  at just above  $T_c$ , as will be shown later. In order to determine the value of  $\gamma$ , it is crucial to know the low-temperature form of  $C_l$ . Since the minimum  $T_c$  attained at 14 T is 5.2 K, one has to estimate the  $C_l$  from the  $T$  dependence of the total  $C$  above  $\sim 5.5 \text{ K}$ . Two terms in the harmonic-lattice approximation are often required for an adequate fit;  $C_l = \beta_3 T^3 + \beta_5 T^5$ . The first term comes from a



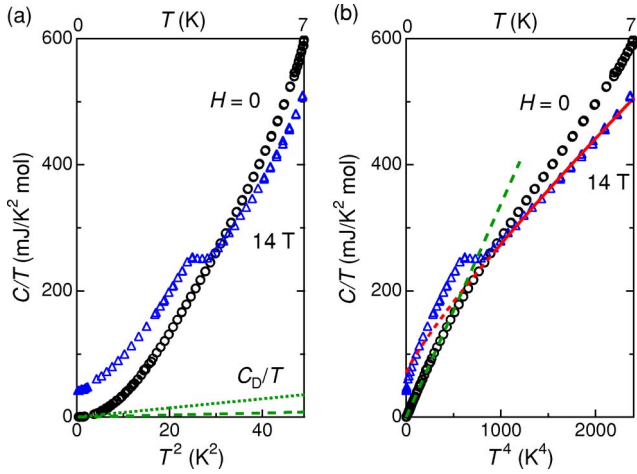


FIG. 4. (Color online) Low-temperature specific heat below 7 K plotted as functions of (a)  $T^2$  and (b)  $T^4$ . The broken and dotted lines in (a) show calculated contributions from Debye  $T^3$  phonons of  $\Theta_D=460$  and 300 K, respectively, which are much smaller than the experimental values. The broken line in (b) is a linear fit to the zero-field data as  $T \rightarrow 0$ , which gives a coefficient of the  $T^5$  term,  $\beta_5=0.3481(6)$   $\text{mJ K}^{-2} \text{mol}^{-1}$ . The solid and dotted line is a fit to  $C_l = \beta_5 T^5 f(T)$ . See text for detail.

Debye-type acoustic phonon, and thus is dominant at low temperature, while the second term expresses a deviation at high temperature. Actually, this approximation is valid for  $\alpha\text{-Cd}_2\text{Re}_2\text{O}_7$ , where  $\beta_3=0.222$   $\text{mJ K}^{-4} \text{mol}^{-1}$  and  $\beta_5=2.70 \times 10^{-6}$   $\text{mJ K}^{-6} \text{mol}^{-1}$  are obtained by a fit to the data below 10 K.<sup>1</sup> The Debye temperature  $\Theta_D$  is 458 K from the  $\beta_3$  value. In strong contrast, it was found for two members of  $\beta\text{-AOs}_2\text{O}_6$  that the  $T^5$  term prevails in a wide temperature range;  $\beta_5=14.2 \times 10^{-3}$   $\text{mJ K}^{-6} \text{mol}^{-1}$  below 5 K for  $\text{CsOs}_2\text{O}_6$  and  $\beta_5=30.2 \times 10^{-3}$   $\text{mJ K}^{-6} \text{mol}^{-1}$  below 7 K for  $\text{RbOs}_2\text{O}_6$ .<sup>13</sup>

The  $C/T$  at  $H=0$  below 7 K shown in Fig. 3 is again plotted in two ways as functions of  $T^2$  and  $T^4$  in Fig. 4. It is apparent from the  $T^2$  plot that possible  $T^3$  terms expected for  $\Theta_D=458$  and 300 K are negligibly small compared with the whole magnitude of specific heat, just as observed in other members. On the other hand, in the  $T^4$  plot, there is distinct linear behavior at low temperature below 4 K, indicating that the  $C$  approaches asymptotically to  $T^5$  behavior as  $T \rightarrow 0$  with a large slope of  $0.3481(6)$   $\text{mJ K}^{-6} \text{mol}^{-1}$ . It is reasonable to ascribe this  $T^5$  contribution to the lattice, because  $C_{es}$  should decrease quickly as  $T \rightarrow 0$ . Note that the value of the  $\beta_5$  for  $\text{KOs}_2\text{O}_6$  is more than 1 order larger than those in other members. At high temperatures above 4 K, a downward deviation from the initial  $T^5$  behavior is observed in Fig. 4(b). The temperature dependence of the 14 T data above 5.5 K, which is taken as  $\gamma T + C_l$ , is also close to  $T^5$ , but with a smaller slope, which means that a single  $T^5$  term is not appropriate to describe the  $C_l$  in such a wide temperature range and also that an inclusion of higher-order term of  $T^n$  is not helpful. Therefore, we adopt expediently an alternative empirical form to express this strange lattice contribution;  $C_l = \beta_5 T^5 f(T)$ , where  $f(T) = [1 + \exp(1 - pT^{-q})]^{-1}$ . Since the  $f(T)$  is almost unity below a certain temperature and decreases gradually with increasing  $T$ , this  $C_l$  can reproduce  $T^5$  behav-

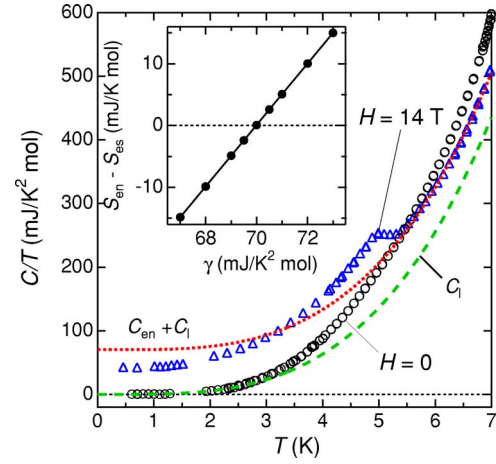


FIG. 5. (Color online) Specific-heat data same as shown in Fig. 3. The dotted line shows the estimated contribution of  $C_{en} + C_l$ , and the broken line represents  $C_l$  in the case of  $\gamma=70$   $\text{mJ K}^{-2} \text{mol}^{-1}$ . The inset shows a change of entropy balance as a function of  $\gamma$ , from which the value of  $\gamma$  is decided to be  $70$   $\text{mJ K}^{-2} \text{mol}^{-1}$ .

ior at low temperatures and a weaker  $T$  dependence at high temperatures. As shown in Fig. 4(b), the 14 T data in the 5.5–7 K range can be fitted well by the function for a value of  $\beta_5$  fixed to the initial slope of  $0.3481$   $\text{mJ K}^{-6} \text{mol}^{-1}$  and a given value of  $\gamma$  for example,  $p=6.96(3)$  and  $q=1.09(1)$  for  $\gamma=70$   $\text{mJ K}^{-2} \text{mol}^{-1}$ .

In order to determine the value of  $\gamma$  univocally, the entropy conservation is taken into account for the 14 T data, as shown in Fig. 5: since the normal-state specific heat expected for the case of  $T_c=0$  is given by  $(C_{en} + C_l)$  (dotted line in Fig. 5), the integration of  $[C_{en} + C_l - C(14\text{ T})]/T$  should become zero due to entropy balance. It is shown in the inset of Fig. 5 that the integrated value changes almost linearly with  $\gamma$  and vanishes around  $\gamma=70$   $\text{mJ K}^{-2} \text{mol}^{-1}$ . Hence, one can determine the value of  $\gamma$  unambiguously. A certain ambiguity may arise from the assumed lattice function. However, since the temperature dependence of  $C_l$  is substantially weak in the  $T$  range of interest, a possible correction on the  $\gamma$  value must be minimal, say, less than  $1$   $\text{mJ K}^{-2} \text{mol}^{-1}$ .

Next we determine  $C_{es}$  at zero field by subtracting the  $C_l$  estimated above. The temperature dependence of  $C_{es}$  does have the BCS form,  $a \exp(-\Delta/k_B T_c)$ , as shown in Fig. 6. The energy gap  $\Delta$  obtained by fitting is 22.5 K, which corresponds to  $2\Delta/k_B T_c=4.69$ , much larger than the BCS value of 3.53. The above  $C_{es}$  at low temperature, below 7 K, is again plotted in Fig. 7 together with high-temperature  $C_{es}$  above 5.5 K, which is obtained by subtracting the 14 T data from the zero-field data as  $C_{es}=C(0)-C(14\text{ T})$ . The two data sets obtained independently overlap well in the 5.5–7 K range, assuring the validity of the above analyses. Because of the existence of the second peak and its small shifts under magnetic fields, the data between 7 and 8.3 K are to be excluded in the following discussion. Taking  $\gamma=70$   $\text{mJ K}^{-2} \text{mol}^{-1}$ , the jump in specific heat at  $T_c$ ,  $\Delta C/\gamma T_c$ , reaches 2.87, much larger than 1.43 expected for a weak-coupling superconductor, indicating that  $\text{KOs}_2\text{O}_6$  lies in the strong-coupling regime. Comparisons to other typical strong-coupling superconductors are made in Sec. IV B.

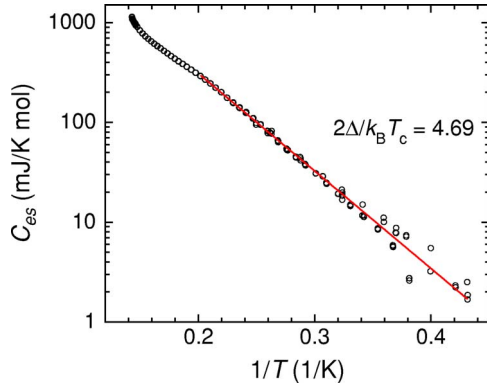


FIG. 6. (Color online) Temperature dependence of electronic specific heat measured at  $H=0$  for the superconducting state showing an exponential decrease at low temperature. A magnitude of the gap obtained is  $2\Delta/k_B T_c = 4.69$ .

Here we analyze the data based on the  $\alpha$  model that was developed to provide a semiempirical approximation to the thermodynamic properties of strongly coupled superconductors in a wide range of coupling strengths with a single adjustable parameter,  $\alpha = \Delta_0/k_B T_c$ .<sup>45</sup> Recently, it was generalized to a multigap superconductor and successfully applied to the analyses on  $\text{MgB}_2$  or  $\text{Nb}_3\text{Sn}$ .<sup>46,47</sup> Using the  $\alpha$  model, the data in the vicinity of  $T_c$  are well reproduced, as shown in Fig. 7, and we obtain  $\alpha = 2.50$  ( $2\Delta_0/k_B T_c = 5.00$ ), slightly larger than the value obtained above from the temperature dependence of  $C_{es}$ . One interesting point to be noted is that there is a significant deviation between the data and the fitting curve at intermediate temperatures, suggesting the existence of an additional structure in the gap. Presumably, this enhancement would be explained if one assumes the coexistence of another smaller gap (not so small as in  $\text{MgB}_2$ , but intermediate). This possibility has already been pointed out in the previous  $\mu\text{SR}$  experiment.<sup>36</sup> However, ambiguity as-

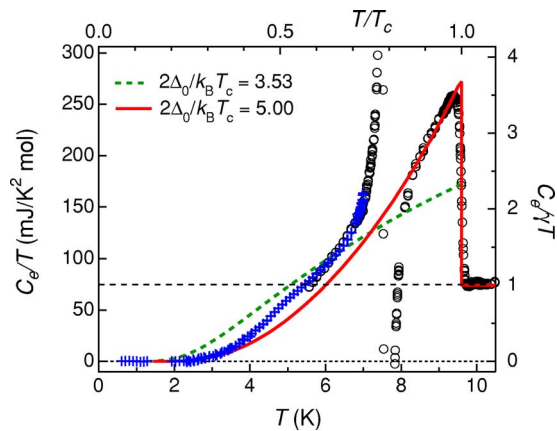


FIG. 7. (Color online) Electronic specific heat of  $\text{KO}_s\text{O}_6$  at zero field. The data points above 5.5 K (open circle) are obtained by subtracting the 14 T data from the zero-field data, and those below 7 K (cross) are obtained by subtracting the estimated lattice part  $C_l$  from the zero-field data. The broken line shows an ideal curve expected for a weak-coupling BCS superconductor, and the solid curve is a fit by the  $\alpha$  model with a large value of gap;  $2\Delta/k_B T_c = 5.00$ .

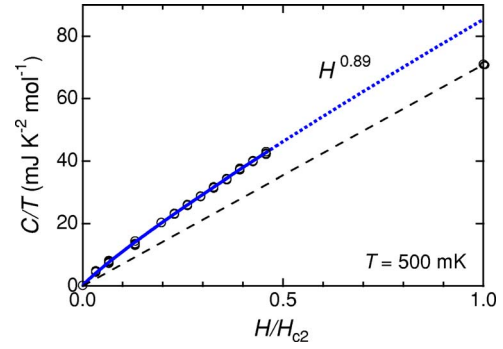


FIG. 8. (Color online) Magnetic-field dependence of  $C/T$  at  $T = 500$  mK. The abscissa axis is normalized by the value of  $\mu_0 H_{c2} = 30.6$  T. The broken line assumes a linear  $H$  dependence with  $\gamma = 70$   $\text{mJ K}^{-2} \text{mol}^{-1}$  at  $H/H_{c2} = 1$ . The fit to the power law of  $H^n$  gives  $n = 0.89$  and a large value of  $\gamma = 85.4$   $\text{mJ K}^{-2} \text{mol}^{-1}$  at  $H/H_{c2} = 1$ .

sociated with the second peak in the present data prevents us from further analyzing the data. This important issue will be revisited in future work, where the second peak in specific heat would be suppressed by hydration or a small amount of Rb substitution for K.

The thermodynamic critical field  $H_c$  is one of the most important parameters to characterize the nature of the superconducting ground state. It is determined from specific-heat data taken at  $H=0$  using the relation,

$$\int_T^{T_c} dT \int_T^{T_c} \frac{C(T') - C_{en}(T')}{T'} dT' = \frac{H_c^2}{8\pi}. \quad (1)$$

However, in the present case,  $H_c$  can be determined only in the vicinity of  $T_c$  due to the second anomaly in specific heat. Since  $H_c$  can also be determined by magnetization measurements, we will return to this issue in a later section.

In the vortex state under magnetic fields, a finite amount of  $T$ -linear term  $\gamma(H)T$  appears in specific heat well below  $T_c$ . Since the  $C/T$  is almost constant below 1 K, we take the value of  $C/T$  at 0.5 K as approximately giving  $\gamma(H)$  at each field and plot the magnetic-field dependence in Fig. 8. It increases with a negative curvature and is approximately proportional to  $H^{0.89}$ . An extrapolation of the curve to  $H=H_{c2}$  (30.6 T) would result in  $\gamma = 85.4$   $\text{mJ K}^{-2} \text{mol}^{-1}$ , which is larger than our estimate of  $\gamma = 70$   $\text{mJ K}^{-2} \text{mol}^{-1}$ . In a similar analysis, Brühwiler *et al.* found an  $H^{0.95}$  curve with an extrapolated  $\gamma = 76$  (110)  $\text{mJ K}^{-2} \text{mol}^{-1}$  for  $\mu_0 H_{c2} = 24$  (35) T.<sup>14</sup> The fact that  $\gamma = 70$   $\text{mJ K}^{-2} \text{mol}^{-1}$  in our experiments means that the magnetic-field dependence is first expressed by a power of  $H$  and tends to saturate near  $H_{c2}$ . In general,  $\gamma(H)$  is considered to probe the quasiparticle DOS in the vortex state: it is expected to increase linearly with  $H$  for a simple  $s$ -wave gap, while increase more rapidly for gaps with nodes. However, a recent study on  $\text{YNi}_2\text{B}_2\text{C}_2$  and  $\text{NbSe}_2$  has demonstrated that a nonlinear dependence actually appears even for an  $s$ -wave superconductor when the system approaches the clean limit.<sup>48</sup> As will be mentioned later, the present superconductor lies in the very clean limit, and thus, the ob-

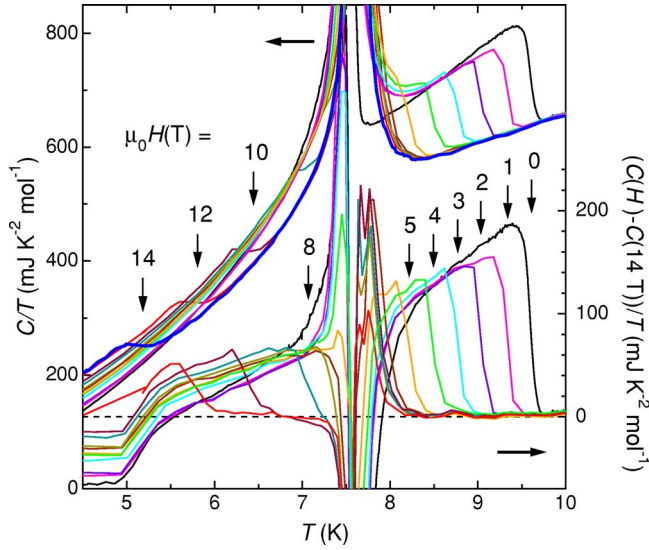


FIG. 9. (Color online)  $C/T$  measured at various magnetic fields on the left axis and the same data after subtraction of the 14 T data on the right. The magnetic fields are 0, 1, 2, 3, 4, 5, 6, 7, 8, 10, 12, and 14 T from right to left.

served nonlinear behavior may be reconciled with an  $s$ -wave gap.

Let us describe next the superconducting transitions in specific heat under various magnetic fields. As shown in Fig. 9, the jump at  $T_c$  systematically shifts to lower temperatures with increasing  $H$ , though the transition becomes obscure on the way in the vicinity of  $T_p$ . It is clearly observed that there are substantial differences between the transitions above and below  $T_p$ : in the case of  $T_c > T_p$ , the jump is large and sharp with a small  $\Delta T_c$ , while it becomes small and broad for  $T_c < T_p$ . The  $H$  dependences of the mean-field  $T_c$  and  $\Delta C/T_c$  are plotted in Figs. 10 and 11, respectively. In the  $H$ - $T$  diagram of Fig. 10, the superconducting phase is separated into two regions, I and II, by an almost vertical  $T_p$  line.<sup>38</sup> The  $H_{c2}$

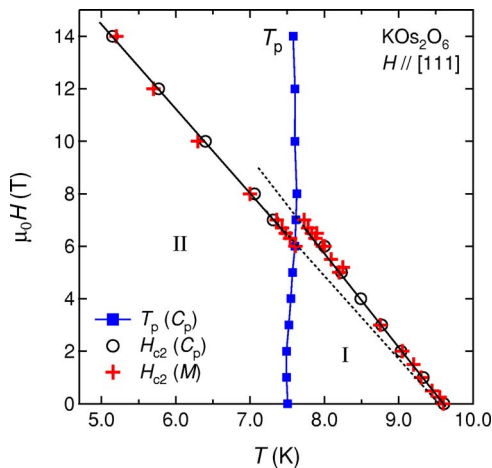


FIG. 10. (Color online) Magnetic-field-temperature phase diagram obtained at  $H \parallel [111]$  showing  $H_{c2}$  lines determined by specific heat (circle) and magnetization measurements (cross). The vertical line (square) indicates the position of the peak in specific heat associated with the second phase transition.

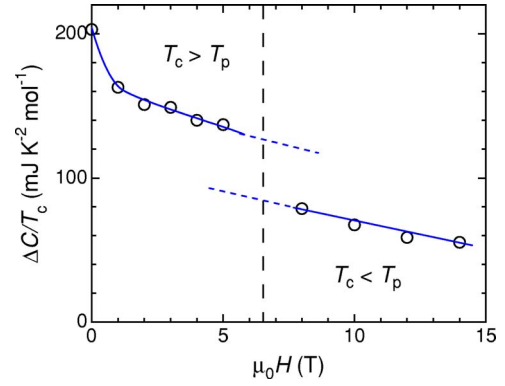


FIG. 11. (Color online) Magnetic-field dependence of the magnitude of the jump in specific heat at  $T_c$  obtained from the data sets shown in Fig. 9. The vertical broken line shows a critical field at which  $T_c$  and  $T_p$  coincide with each other.

increases first linearly, suddenly drops by 15% at  $T_p$ , and increases again linearly but with a smaller slope below  $T_p$ . The values of  $-dH_{c2}/dT$  are 3.61(4) and 3.20(5) T/K above and below  $T_p$ , respectively. The former value agrees with that reported by Brühwiler *et al.*, though they did not find a change in the slope across the  $T_p$  line.<sup>14</sup> A linear extrapolation of the low-temperature  $H_{c2}$  line intersects with the abscissa axis at  $T=9.5$  K, which is close to  $T_c=9.60$  K. This naturally demands the two superconducting states to be essentially identical in origin, but with slightly different parameters affected by the second phase transition. Details will be discussed later. On the other hand, a linear extrapolation of the two  $H_{c2}$  lines to  $T=0$  gives  $\mu_0 H_{c2}(0)=34.7$  and 30.5 T, the latter of which agrees with the value obtained by high-magnetic-field experiments.<sup>42</sup> This fact suggests that the degradation of a sample that suppresses the second phase transition would enhance  $H_{c2}(0)$ . Certainly, a larger value of 33 T for  $H_{c2}(0)$  was reported in another high-magnetic-field experiment.<sup>43</sup>

Another dramatic change at  $T_p$  is shown in Fig. 11 in the magnetic-field dependence of the magnitude of the jump in specific heat. The  $\Delta C/T_c$  decreases suddenly around a critical field of 6.5 T, where the  $H_{c2}$  and the  $T_p$  lines intersect. Linear extrapolations of the curves above and below the critical field give a marginal discontinuity of approximately 42  $\text{mJ K}^{-2} \text{mol}^{-1}$ , which means a reduction by 33% from the low-field value.  $\Delta C/T_c$  is related to the slope of  $H_{c2}$  and the Maki parameter  $\kappa_2$  as in the formula,

$$\frac{\Delta C}{T_c} = \frac{1}{4\pi\beta_A(2\kappa_2^2 - 1)} \left( \frac{dH_{c2}}{dT} \right)_{T_c}^2, \quad (2)$$

where  $\beta_A=1.16$  for a triangular vortex lattice.<sup>49</sup> Thus, the reduction of  $\Delta C/T_c$  must be partly due to the reduction of  $-dH_{c2}/dT$  observed in Fig. 10. However, since the change of  $-dH_{c2}/dT$  is only  $\sim 15\%$  [ $\sim 2.3\%$  in  $(dH_{c2}/dT)^2$ ], it is required to assume a large enhancement of  $\kappa_2$  at  $T_p$ . The  $T$  dependence of  $\kappa_2$  is determined by Eq. (2) and is plotted in Fig. 12. The  $\kappa_2$  increases with decreasing  $T$  from  $T_c$ , followed by an increment around  $T_p$ , and shows a further increase at low temperature. The observed enhancement of  $\kappa_2$



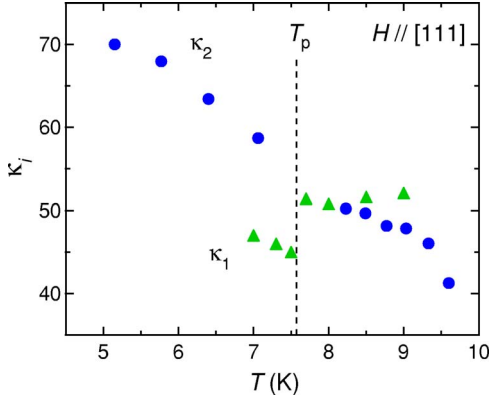


FIG. 12. (Color online) Temperature dependence of the Maki parameters,  $\kappa_1$  and  $\kappa_2$ .

below  $T_p$  may indicate that the system moves closer to the clean limit as a result of the second transition. Characteristic changes for various quantities observed at  $T_p$  are summarized and discussed in Sec. IV D. The  $T$  dependence of another Maki parameter  $\kappa_1$  is also plotted in Fig. 12, which will be described later in Sec. III A 3.

### 2. Resistivity-anisotropy

The superconducting transition of the KOs-729 crystal observed by resistivity measurements has already been reported in our previous paper for magnetic fields parallel to the [111] direction.<sup>38</sup> Here, we report further results for various field directions to reveal the anisotropy of the superconductivity. Figure 13 shows the temperature dependence of resistivity measured in magnetic fields along four principal directions of the cubic crystal: [111], [112], [110], and [001], which was obtained by rotating the crystal along the  $\bar{1}10$  direction that was also the direction of current flow. It

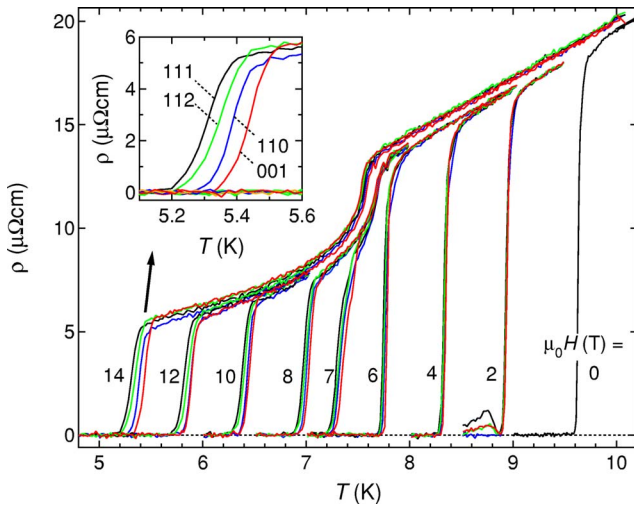


FIG. 13. (Color online) Temperature dependence of resistivity measured under various magnetic fields of up to 14 T in four crystallographic directions: [111], [112], [110], and [001]. The inset shows an enlargement near  $T_c$  for the 14 T data. Small humps observed just below  $T_c$  at 2 T are due to flux-flow resistance coming from weak and anisotropic pinning (Ref. 39).

is apparent from Fig. 13 that there are only small anisotropy in the superconducting transition. The  $T_c$  always becomes higher in the sequence of  $H \parallel [111]$ , [112], [110], and [001], though the difference is small within 0.12 K even at the maximum field, as shown in the inset of Fig. 13. Therefore,  $\text{KOs}_2\text{O}_6$  is an isotropic superconductor, reflecting the cubic symmetry of the crystal structure and also round Fermi surfaces predicted in the band-structure calculations.<sup>16,19,20,25</sup> Nevertheless, it is surprising that there is a distinct anisotropy in flux pinning as reported previously.<sup>39</sup> A sign is also shown in Fig. 13 in the sets of 2 T curves: there is a relatively large hump below a sharp drop for  $H \parallel [111]$ , intermediate ones for [112] and [001], and no hump for [110]. Such a hump was detected only around  $H=1-2$  T.

### 3. Magnetization

We have carried out magnetization measurements on the KOs-729 crystal. An advantage compared with specific heat is that magnetization is sensitive to the occurrence of superconductivity but may not be affected by the second phase transition in the normal state, as shown for the 7 T data in Fig. 14(a). This enables one to probe a superconducting transition near  $T_p$ . First, we describe the temperature dependence of magnetization measured in various magnetic fields on cooling. The  $T_c$  determined as an onset of diamagnetic signals due to the Meissner effect agrees with that from specific-heat measurements at each field up to 14 T, as shown in the  $H$ - $T$  diagram of Fig. 10. Figure 14(a) shows typical data in the vicinity of the second transition. For example, at  $\mu_0 H = 5.5$  T, a diamagnetic response starts at  $T_c(I) = 8.1$  K and grows almost linearly on cooling, followed by a sudden upward departure at  $T = 7.75$  K. Essentially the same temperature dependence was observed for data obtained below this field. Figure 14(b) shows the deviation of magnetization from the initial linear relation below  $T_c(I)$ . It is apparent that the deviation always takes place at  $T'_p = 7.7$  K at any magnetic fields. Hence, it is reasonable to correlate this  $H$ -independent anomaly in magnetization to the second peak in specific heat. Possibly, the superconducting volume fraction is partly suppressed at around  $T_p$ , associated with the reduction of  $H_{c2}$ . At higher magnetic fields above 6.0 T, another diamagnetic onset appears at a temperature below  $T_p$ , as shown in Fig. 14(a). For example, at  $\mu_0 H = 6.0$  T, there is a clear downturn at  $T_c(II) = 7.6$  K. The two onset temperatures are plotted in the  $H$ - $T$  diagram of Fig. 10, which exactly fall on the two  $H_{c2}$  lines above and below  $T_p$  determined by specific-heat measurements, providing strong evidence for a discontinuity in  $H_{c2}$  at  $T_p$ . There must be an interesting vortex state between  $T_p$  and  $T_c(II)$  associated with the phase transition.

Next, we tried to determine the lower critical field  $H_{c1}$  from a magnetic-field dependence of magnetization. Figure 15 shows a typical  $M$ - $H$  curve measured at 2 K and  $H \parallel [111]$  after zero-field cooling. The correction due to the geometric demagnetization effect was determined from the initial slope assuming the perfect diamagnetism: the demagnetization factor was 0.586 and 0.269 for  $H \parallel [111]$  and [110], respectively, larger for the former case as expected from the platelike

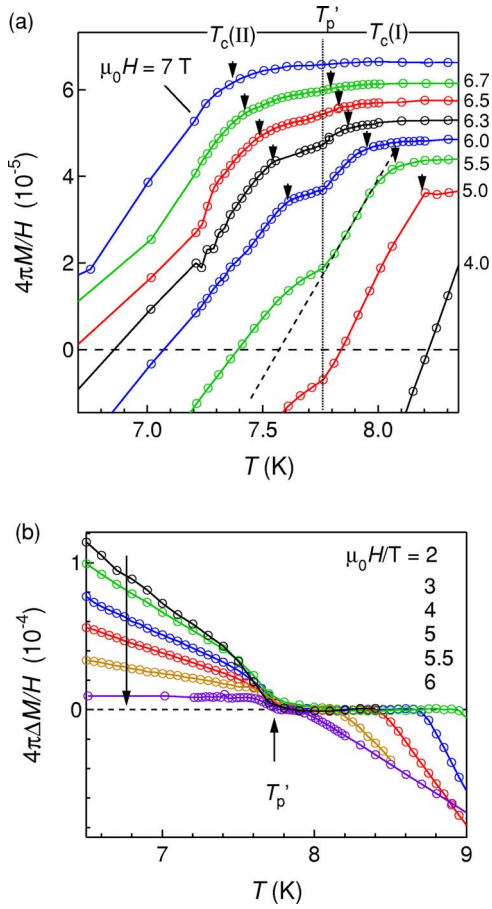


FIG. 14. (Color online) (a) Temperature dependence of magnetization measured on cooling at magnetic fields of up to 7.0 T in the [111] direction. Data sets at  $\mu_0 H = 5.5, 6.0, 6.3, 6.5, 6.7,$  and  $7.0$  T are shifted upward relatively by an offset of  $3 \times 10^{-6}$  for clarity. (b) Deviation of the diamagnetic signal from the initial linear behavior such as shown in (a) for the 5.5 T data by a broken line. It always takes place at  $T_p'$  near  $T_p$ , independent of  $H$ .

shape of the crystal (Fig. 2).  $H_{c1}$  is to be defined as a magnetic field where a deviation from the linear behavior starts. In fact, we observed a clear anomaly or a jump at  $\mu_0 H = 35\text{--}40$  mT, as shown in the inset of Fig. 15. However,

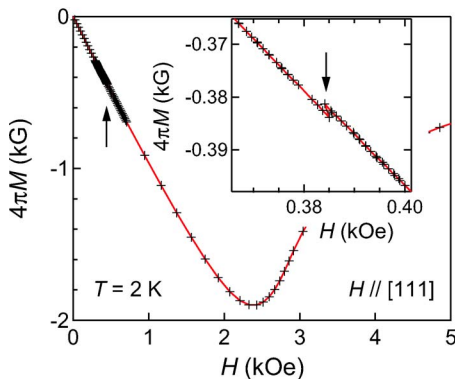


FIG. 15. (Color online) Virgin  $M$ - $H$  curve measured at  $H \parallel [111]$  and  $T = 2.0$  K after zero-field cooling. The inset shows an enlargement around an anomaly marked by an arrow.

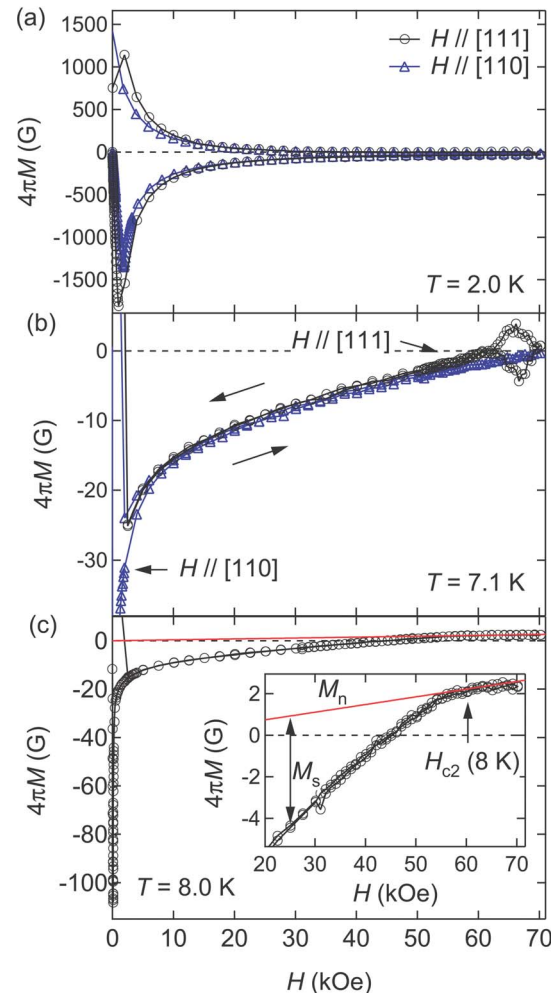


FIG. 16. (Color online)  $M$ - $H$  curves measured at  $H \parallel [111]$  (circle) and  $[110]$  (triangle) after zero-field cooling at (a)  $T = 2.0$  K, (b)  $7.1$  K just below  $T_p$ , and (c)  $8.0$  K above  $T_p$ . There is a hysteresis at  $2.0$  K, while an almost reversible change is observed at the two high temperatures. In (b), a peak effect is found near  $H_{c2}$  only at  $H \parallel [111]$ . The inset shown in (c) is an enlargement near  $\mu_0 H_{c2} = 6.0$  T at  $8.0$  K.  $M_s$  and  $M_n$  are magnetizations for the superconducting and normal states, respectively.

since the values scattered from experiment to experiment even in the same experimental setup, we could not determine a reliable value for  $H_{c1}$ . Possibly, this scattering is caused by a small misalignment of the crystal in a magnetic field. It is inferred from this that the effect of a surface barrier to flux inclusion is significantly large for this crystal. An expected value for  $H_{c1}$  from the Ginzburg-Landau (GL) relation is much smaller,  $\sim 10$  mT, as will be described later.

Figure 16 shows the  $H$  dependence of magnetization measured at  $H \parallel [111]$  and  $[110]$  and at  $T = 2.0, 7.1,$  and  $8.0$  K, after cooling in zero field. The shape of the  $M$ - $H$  curves for  $T = 2.0$  K shown in Fig. 16(a) is typical for a type-II superconductor with a flux pinning. Since the area of the hysteresis loop is slightly larger for  $H \parallel [111]$  than  $[110]$ , the critical current density is larger for the former, though the anisotropy is small. At high temperatures just below  $T_p$ ,  $M$ - $H$  curves become almost reversible, as shown in Fig. 16(b), indicating



a weak pinning. However, there is a small hysteresis loop appearing at high fields around 6.5 T only for  $H\parallel[111]$ , which means that a specific mechanism is working to enhance flux pinning. Such a peak effect has been discussed a lot in many superconductors and ascribed to various mechanisms. We think that in the present case a certain microstructure associated with the second phase transition at  $T_p$  is related to this peak effect. Details will be described elsewhere.

The Maki parameter  $\kappa_2$  can be estimated in magnetization measurements near  $H_{c2}$  by the relation

$$\left(\frac{dM}{dH} - \frac{dM_n}{dH}\right)_{H_{c2}} = \frac{1}{4\pi\beta_A(2\kappa_2^2 - 1)}, \quad (3)$$

where  $M$  is the magnetization of the vortex phase and  $M_n$  the magnetization of the normal phase.<sup>49</sup> As shown in Fig. 16(c) for  $T=8.0$  K,  $M$  increases with  $H$  and intersects an  $M_n$  line around 6.0 T, which is the  $H_{c2}$  determined by specific-heat measurements. Since  $dM/dH$  near the  $H_{c2}$  is approximately  $1.6 \times 10^{-5}$ , and  $dM_n/dH$  is  $2.9 \times 10^{-6}$ ,  $\kappa_2$  is determined to be 50.8, which is in good agreement with that from specific-heat measurements shown in Fig. 12. In other words, a thermodynamic relation<sup>49</sup>

$$\frac{1}{V_m} \left(\frac{\Delta C}{T}\right)_{T_H} = \left(\frac{dH_{c2}}{dT}\right)^2 \left(\frac{dM}{dH} - \frac{dM_n}{dH}\right)_{H_{c2}} \quad (4)$$

holds, where  $V_m$  is the mol volume ( $V_m=77.277$  cm<sup>3</sup>/mol), which confirms the reliability of our specific heat and magnetization data.

The thermodynamic critical field  $H_c$  is now determined in the vicinity of  $T_c$ , where hysteresis due to flux pinning is almost negligible, using the relation

$$\int_0^{H_{c2}} (M - M_n) dH = \frac{H_c^2}{8\pi} \quad (5)$$

and is plotted in Fig. 17, together with the  $H_c$  determined by specific-heat measurements using Eq. (1). The data from specific heat are limited above 8.5 K because of the existence of the second peak, while the data from magnetization below 7.0 K may be overestimated because of hysteresis due to flux pinning. As shown in the inset of Fig. 17, the two sets of data fall on the same line, showing a linear increase with an initial slope of  $-53.06$  mT/K. This quantity is related to the jump in specific heat at  $T_c$  by a thermodynamic relation

$$\frac{1}{V_m} \frac{\Delta C}{T_c} = \frac{1}{4\pi} \left(\frac{dH_c}{dT}\right)_{T_c}^2. \quad (6)$$

Using  $\Delta C/T_c=201.2$  mJ K<sup>-2</sup> mol<sup>-1</sup>, we obtain  $-(dH_c/dT)_{T_c}=57.2$  mT/K, reasonably close to the above value. The temperature dependence of  $H_c$  is generally discussed in terms of a deviation function  $D(t)$ :  $D(t)=H_c(t)/H_c(0)-(1-t^2)$ , where  $t=T/T_c$ . It is known that  $D(t)$  is always negative for a weak-coupling superconductor, while positive for a strong-coupling one.<sup>49</sup> In the present case, however, we cannot obtain  $D(t)$  in a wide  $T$  range, though  $D(t)$  is expected to be positive for such a strong-coupling superconductor. Instead, we estimate  $H_c(0)$  from the initial slope using a relation

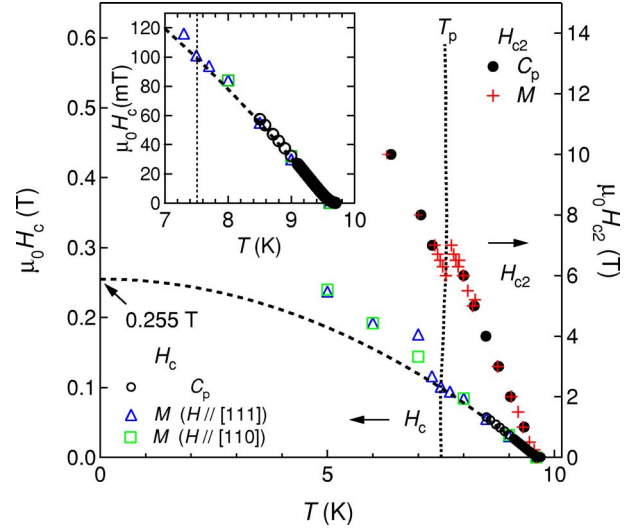


FIG. 17. (Color online) Thermodynamic critical field  $H_c$  determined by specific heat (open circle) and magnetization measurements at  $H\parallel[111]$  (triangle) and  $H\parallel[110]$  (square). The inset shows an enlargement near  $T_c$  and  $T_p$ . The broken line is a fit to the deviation function  $D(t)=0$ , which gives  $\mu_0 H_c(0)=0.255$  T.

$H_c(0)=-\langle T_c/2 \rangle dH_c(T)/dT$  to be 0.255 T, which is to be used to deduce important parameters in the GL formulation.

It is also noted in Fig. 17 that the  $H_c$  is likely unaffected by the second phase transition. It seems that at least there is no reduction in  $H_c$  corresponding to the reduction in  $H_{c2}$  at  $T_p$ , which suggests no substantial differences in the condensation energy between the two superconducting states. From the values of  $H_{c2}$  and  $H_c$ , another Maki parameter  $\kappa_1$  is calculated by  $H_{c2}=\sqrt{2}\kappa_1 H_c$ , and its temperature dependence is shown in Fig. 12. The  $\kappa_1$  is almost constant,  $\sim 51$ , above  $T_p$  and coincides with  $\kappa_2$  just above  $T_p$ , followed by a sudden reduction to 45 below  $T_p$ , corresponding to the change in  $H_{c2}$ . Thus, the ratio of  $\kappa_2/\kappa_1$  is increased from  $\sim 1$  at 8 K to 1.25 at 7 K. It is known for a conventional type-II superconductor such as Nb that the ratio of  $\kappa_2/\kappa_1$  is sensitive to the purity of specimens and is enhanced for a specimen with a large mean free path.<sup>50</sup> Consequently, the enhanced  $\kappa_2/\kappa_1$  ratio below  $T_p$  for  $\text{KOs}_2\text{O}_6$  must imply that the electron mean free path is elongated below the second transition, which means that the system becomes cleaner below  $T_p$ .

## B. Normal-state properties

### 1. Specific heat

Figure 18 compares the specific heat of the normal state in a wide temperature range for  $\text{KOs}_2\text{O}_6$ ,  $\text{CsOs}_2\text{O}_6$ , and  $\text{Cd}_2\text{Re}_2\text{O}_7$ . It is obvious that, compared with  $\text{Cd}_2\text{Re}_2\text{O}_7$ , both  $\beta$ -pyrochlores possess a large weight at low temperature, especially for  $\text{KOs}_2\text{O}_6$ , indicating the presence of low-energy phonons. Moreover, the specific heat at 300 K is considerably smaller than an ideal value of  $27R$  per 1 mol of formula unit (f.u.) expected by the Dulong-Petit law. The reduction is greater toward  $\text{KOs}_2\text{O}_6$ . Since the Dulong-Petit limit should be attained for most solids in which the harmonic oscillator approximation for atomic vibrations is valid, this reduction

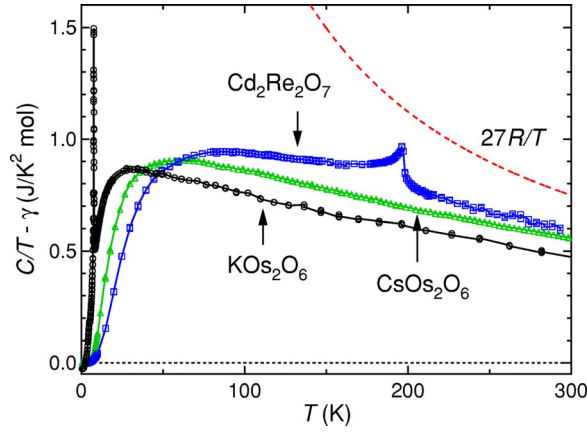


FIG. 18. (Color online) Specific heat in a wide temperature range below room temperature for  $\text{KO}_2\text{O}_6$  (KOs-729),  $\text{CsOs}_2\text{O}_6$  (polycrystalline sample), and  $\text{Cd}_2\text{Re}_2\text{O}_7$  (single crystal, reduced by 9/11 for comparison). The  $\gamma$  value has been subtracted. The broken line represents the Dulong-Petit limit.

means that the anharmonicity of the lattice is essentially large for pyrochlore oxides and more enhanced in the  $\beta$ -pyrochlores with larger rattlings.

In order to estimate the specific energy of rattling vibrations, we have fitted the data following the method adopted for a similar analysis on filled skutterudites or Si/Ge clathrates.<sup>11,51</sup> Although the anharmonicity must be crucial for rattling vibrations, it is difficult to take into account in the analysis. Thus, we assume that the rattler presents an Einstein oscillator, because it may be almost localized in a cage, and the Os-O framework gives a Debye phonon. Two terms are included for each contribution to reproduce the data, and thereby, specific heat  $C$  per mol is given by

$$C = \gamma T + aC_{E1} + (1-a)C_{E2} + bC_{D1} + (8-b)C_{D2}, \quad (7)$$

where  $C_{D1}$  and  $C_{D2}$  are contributions from Debye phonons of the  $\text{Os}_2\text{O}_6$  cage, and  $C_{E1}$  and  $C_{E2}$  are those from Einstein oscillators for the A cation, which take the form

$$C_E = 3R \left( \frac{\Theta_E}{T} \right)^2 \frac{\exp(\Theta_E/T)}{[\exp(\Theta_E/T) - 1]^2}, \quad (8)$$

where  $R$  is the gas constant and  $\Theta_E$  is the Einstein temperature. The results of fitting are satisfactory, as shown in Fig. 19. In the case of  $\text{CsOs}_2\text{O}_6$ , the second Einstein contribution was not required to fit the data in the whole temperature range, and we obtained  $b=3.05(3)$ ,  $\Theta_{E1}=70.5(2)$  K,  $\Theta_{D1}=280(2)$  K, and  $\Theta_{D2}=1000(6)$  K. The last term of such a large Debye temperature may be unrealistic, but is necessary to allow for the reduction from the Dulong-Petit limit at high temperatures. In contrast, we cannot fit the data of  $\text{KO}_2\text{O}_6$  above 8.5 K without the second Einstein term. Although the results of fitting is improved by including the second term, there still remains a significant deviation for K, compared with the case for Cs. This implies that anharmonicity is greater in K. We finally obtain for K that  $a=0.24(3)$ ,  $b=2.55(4)$ ,  $\Theta_{E1}=22(2)$  K,  $\Theta_{E2}=61(1)$  K,  $\Theta_{D1}=280(3)$  K, and  $\Theta_{D2}=1180(13)$  K. The value of  $\Theta_{E1}=22$  K is smaller

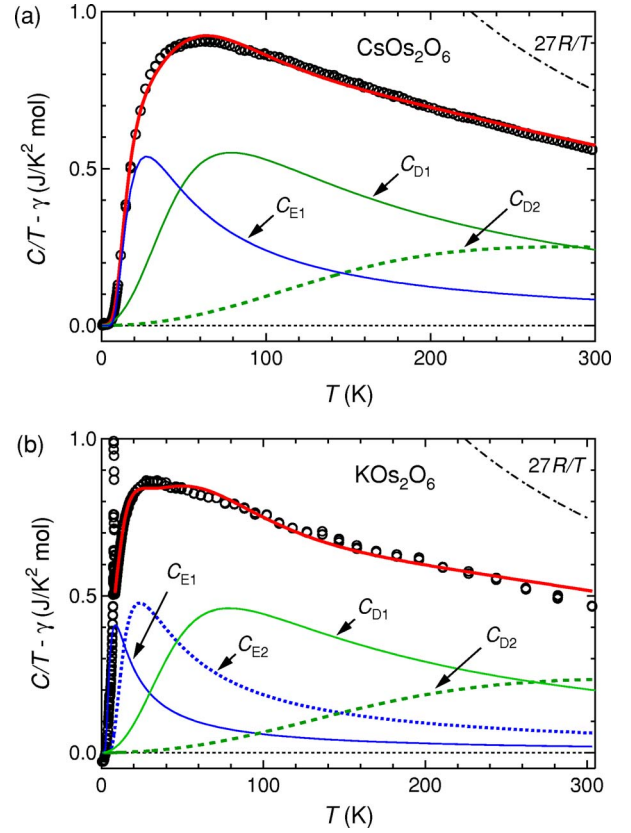


FIG. 19. (Color online) Results of fitting to the model described in the text for (a)  $\text{CsOs}_2\text{O}_6$  and (b)  $\text{KO}_2\text{O}_6$ . Separated contributions are shown below the raw data.

than the previous estimations giving 40 K (Ref. 13) and 31 K,<sup>14</sup> which assumed a single Einstein term. Although this harmonic approximation is not enough to describe the rattling, the obtained lowest value of  $\Theta_{E1}$  may give a rough estimate for the characteristic energy of the rattling.

The fact that the rattling frequency is lower for K than Cs reveals one interesting aspect of rattling. In the ordinary solid, an atom with a smaller mass  $M$  gives a higher frequency  $\omega$ , as  $\omega$  is proportional to  $M^{-1/2}$ . For the rattling, in contrast, frequency must be determined by the shape of energy potential in an oversized cage, just as in an electron confined in a quantum well. Indeed, Kuneš *et al.* found such a quantum-well-like potential for the K cation and calculated the energy diagram, where a triplet state exists above a singlet ground state separated by a small energy difference of 15 K.<sup>16</sup> According to their energy diagram, we calculated the specific heat, but could not reproduce the experimental curve. Further experimental and theoretical studies would be necessary to elucidate the nature of the rattling phenomena.

The origin of the  $T^5$  behavior observed at low temperature is another mystery. In general, specific heat is proportional to  $T^{3/n}$  for an excitation wave in three dimensions with a dispersion relation of  $\hbar\omega=q^n$  in the low-temperature limit. For example, a Debye phonon with  $\hbar\omega=q$  gives the  $T^3$  law, while spin waves in ferromagnetic materials with  $\hbar\omega=q^2$  gives  $C$  proportional to  $T^{3/2}$ . In this context, the present  $T^5$  behavior means a strange excitation with  $\hbar\omega=q^{3/5}$ , though such an excitation wave with a power smaller than unity

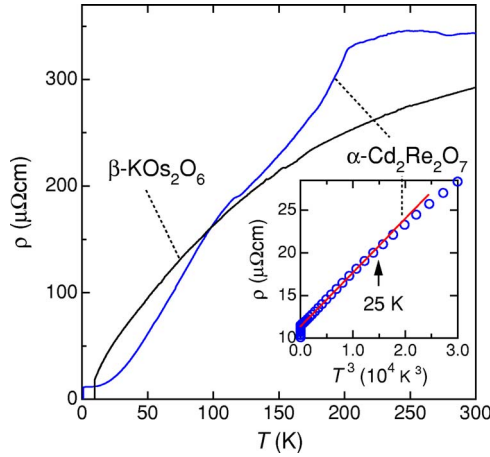


FIG. 20. (Color online) Resistivity in a wide temperature range for  $\beta$ - $\text{KOs}_2\text{O}_6$  and  $\alpha$ - $\text{Cd}_2\text{Re}_2\text{O}_7$ . The former always exhibits a concave-downward curvature down to  $T_c$ , while the latter shows a  $T^3$  dependence at low temperature below 25 K, as represented in the  $T^3$  plot of the inset. Two anomalies at 120 and 200 K for the latter are due to structural transitions (Ref. 52).

seems unrealistic. The fact that the coefficient  $\beta_5$  of the  $T^5$  term increases from Cs to K and is enhanced much for K suggests that the origin is also related to the rattling. We should bear in mind that the  $T^5$  behavior is not directly related to the presence of the second transition present only for  $\text{KOs}_2\text{O}_6$ .

## 2. Resistivity

Since the rattler has a bare 1+ charge that must be screened effectively by the surrounding conduction electrons in the cage, one expects significantly large scattering of carriers due to an electron-phonon or electron-rattler coupling. This is possibly related to the anomalous temperature dependence of electrical resistivity commonly observed for the  $\beta$ -pyrochlore oxides. The resistivity of  $\text{CsOs}_2\text{O}_6$  and  $\text{RbOs}_2\text{O}_6$  exhibits a concave-downward curvature at high temperature, followed by  $T^2$  behavior at low temperature below  $T^* \sim 20$  and  $\sim 15$  K, respectively.<sup>25</sup> In contrast, such a crossover to a  $T^2$  dependence is absent in  $\text{KOs}_2\text{O}_6$ , always concave-downward down to  $T_c$ , as shown in Fig. 20. On the other hand,  $\alpha$ - $\text{Cd}_2\text{Re}_2\text{O}_7$  exhibits quite different behavior in resistivity that is proportional to  $T^3$  below 25 K after two reductions at 120 and 200 K due to structural transitions, as also shown in Fig. 20.<sup>52</sup> The origin of this  $T^3$  behavior has not yet been understood, but is probably ascribed to an electron-phonon scattering due to certain low-energy phonons. The effect of electron correlations may be minor in  $\alpha$ - $\text{Cd}_2\text{Re}_2\text{O}_7$ .

As already shown in Fig. 13, the normal-state resistivity drops suddenly at  $T_p$  in high magnetic fields. Figure 21 reproduces the 14 T data plotted as a function of  $T^2$ , where the  $T_c$  is reduced to 5.2 K. The magnitude of the drop observed at  $T_p$  is approximately 30%, which corresponds to an enhancement in conductivity by 27%. Moreover, the temperature dependence below  $T_p$  is apparently proportional to  $T^2$ , as shown in Fig. 21. These changes of the normal-state resistiv-

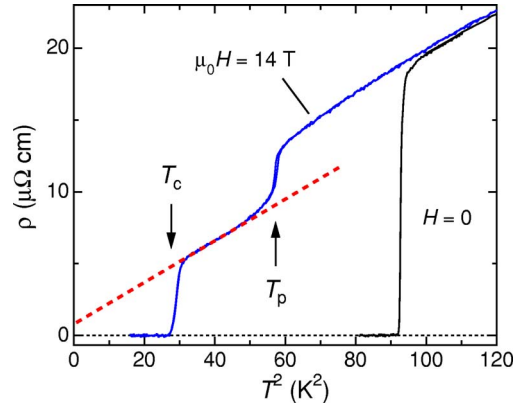


FIG. 21. (Color online) Resistivity plotted against  $T^2$  near  $T_c$  for  $\text{KOs}_2\text{O}_6$ . A large reduction is observed at  $T_p$  in the 14 T data, where a small thermal hysteresis is detected between the cooling and heating curves. A change from concave-downward to  $T^2$  behavior across  $T_p$  is observed at the 14 T data. An extrapolation to  $T=0$  gives a residual resistivity  $\rho_0=1 \mu\Omega \text{ cm}$ .

ity must imply that the scattering mechanism of carriers is substantially changed at  $T_p$ . Consequently, commonly observed in the resistivity of the  $\beta$  pyrochlores is the change from high-temperature concave-downward to low-temperature  $T^2$  behavior, which takes place as a crossover at  $T^*$  for Cs and Rb, while as a phase transition at  $T_p$  for K. The former temperature dependence suggests a strong electron-phonon interaction possibly ascribed to the rattling of the A cations, while the latter may indicate that electron-electron scattering dominates at low temperature, as suggested also by recent thermal conductivity measurements.<sup>34</sup> However, there is no corresponding enhancement in  $\chi$ , as will be described later. We think, alternatively, that certain electron-phonon scatterings give rise to the  $T^2$  resistivity, as in the case of another strong-coupling superconductor with the A-15 structure.<sup>53</sup>

A  $T^2$  extrapolation to  $T=0$  gives a small residual resistivity,  $\rho_0 \sim 1 \mu\Omega \text{ cm}$ . Since the room-temperature resistivity is  $\sim 300 \mu\Omega \text{ cm}$ , the residual resistivity ratio (RRR) reaches 300, which is unusually large for transition-metal oxides. For example, the RRR of a  $\text{Cd}_2\text{Re}_2\text{O}_7$  crystal shown in Fig. 20 is only 30. The residual resistivity is generally given as

$$\rho_0 = \frac{\hbar(3\pi^2)^{1/3}}{e^2 \ell n^{2/3}}, \quad (9)$$

where  $l$  and  $n$  are the mean free path and the density of carriers, respectively. Although the latter has not yet been determined experimentally, band-structure calculations gave  $n=2.8 \times 10^{21} \text{ cm}^{-3}$  (18% per Os).<sup>25</sup> Assuming this value, we obtain a large  $l$  of 640 nm, which is comparable to the value of the cleanest crystal of  $\text{Sr}_2\text{RuO}_4$ .<sup>54</sup> Since the superconducting coherence length  $\xi$  is 3.3 nm, much smaller than  $l$ ,  $\text{KOs}_2\text{O}_6$  lies definitely in the regime of the clean limit.

Next we will extract more information from the anomalously  $T$ -dependent resistivity. It is known that a class of intermetallic compounds having the A-15 structure such as  $\text{Nb}_3\text{Sn}$  show a similar temperature dependence of



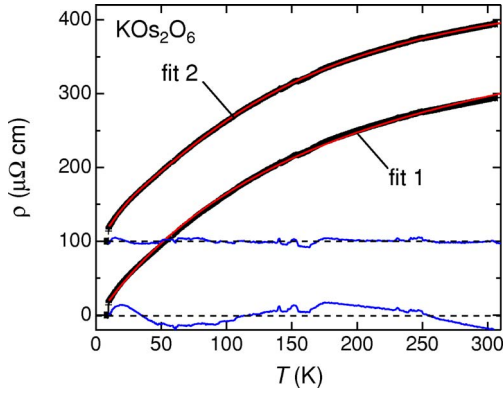


FIG. 22. (Color online) Results of two kinds of fitting to the resistivity data shown in Fig. 20. In each case, a solid line on the data points shows a fit, and a curve near  $\rho=0(100) \mu\Omega \text{ cm}$  in fit 1 (2) shows a deviation that is expanded by a factor of 5.

resistivity.<sup>55</sup> It shows  $T^2$  or  $T^3$  behavior above  $T_c$  up to  $\sim 50$  K and then a concave-downward increase to be saturated at around  $\rho=100\text{--}150 \mu\Omega \text{ cm}$ .<sup>56</sup> This saturation has been interpreted to be the Ioffe-Regel limit:<sup>57</sup> the electron mean free path becomes of the order of the interatomic spacing of the compound. It was pointed out that such an extremely short phonon-limited mean free path occurs when the Fermi velocity  $v_F$  is small and the electron-phonon coupling constant  $\lambda_{ep}$  is large ( $v_F/\lambda_{ep}$  is small).<sup>58</sup> That is really the case for the A-15 compounds;  $v_F \sim 2 \times 10^7 \text{ cm/s}$  and  $\lambda_{ep} \sim 1.5$ .

Wiesmann *et al.* analyzed the resistivity of A-15 compounds and introduced a phenomenological formula,<sup>59</sup>

$$\frac{1}{\rho} = \frac{1}{\rho_{\text{ideal}}} + \frac{1}{\rho_{\text{max}}}, \quad (10)$$

where the saturation resistivity  $\rho_{\text{max}}$  is presumed to be independent of temperature. At high temperature, the “ideal” resistivity can be written as  $\rho_{\text{ideal}} = \rho_0 + \rho_1 T$ , with  $T$  linear behavior as expected from the Bloch-Grüneisen theory. By fitting experimental data for  $\text{Nb}_3\text{Sn}$ , they obtained  $\rho_0 = 57 \mu\Omega \text{ cm}$ ,  $\rho_1 = 0.532 \mu\Omega \text{ cm/K}$ , and  $\rho_{\text{max}} = 130 \mu\Omega \text{ cm}$ , which corresponds to a phonon-limited mean free path  $l_{ep} \sim 5 \text{ \AA}$ .

We apply Eq. (10) to the resistivity of  $\text{KOs}_2\text{O}_6$ . The results of fitting is fairly good, as shown in Fig. 22 (fit 1), yielding  $\rho_0 = -4.9(3) \mu\Omega \text{ cm}$ ,  $\rho_1 = 2.535(7) \mu\Omega \text{ cm/K}$ , and  $\rho_{\text{max}} = 487(5) \mu\Omega \text{ cm}$ . The Ioffe-Regel (IR) limit  $\rho_{\text{IR}}$  is given as  $\rho_{\text{IR}} = 3\hbar a/e^2$ , where  $a$  is the interatomic distance. The  $\rho_{\text{IR}}$  of the pyrochlore oxides becomes  $430 \mu\Omega \text{ cm}$  with  $a = 3.6 \text{ \AA}$ , which is nearly equal to the above experimental value of  $\rho_{\text{max}}$ . Therefore, the observed saturation of resistivity in  $\text{KOs}_2\text{O}_6$  is well understood as indicating an extremely short mean free path limited by electron-phonon scatterings. In fact, for  $\text{KOs}_2\text{O}_6$ ,  $v_F$  is small,  $\sim 1.5 \times 10^7 \text{ cm/s}$ ,<sup>20</sup> and  $\lambda_{ep}$  is large, 2.4, as will be deduced later, which makes the ratio of  $v_F/\lambda_{ep}$  a factor of 2 smaller than in A-15 compounds.

Although the above fit 1 is satisfactory and reasonable at high temperature, it shows a slight deviation in the intermediate temperature range. An alternative analysis carried out

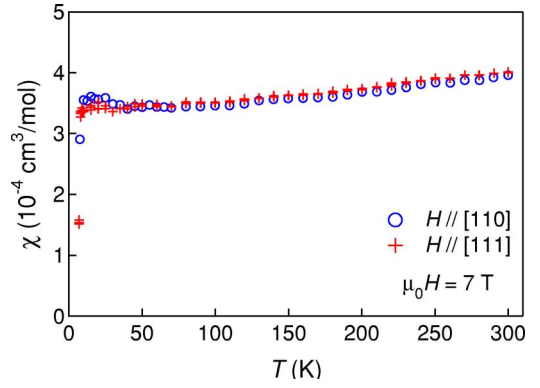


FIG. 23. (Color online) Magnetic susceptibility of the normal state measured at 7 T and  $H \parallel [111]$  and  $[110]$ .

by Woodard and Cody on the resistivity of A-15 compounds was to assume a selective electron-phonon scattering.<sup>55</sup> They found an empirical formula

$$\rho = \rho_0 + \rho_1 T + \rho_2 \exp(-T_0/T) \quad (11)$$

and could reproduce well the experimental curve for  $\text{Nb}_3\text{Sn}$  with  $\rho_0 = 10 \mu\Omega \text{ cm}$ ,  $\rho_1 = 0.0466 \mu\Omega \text{ cm/K}$ ,  $\rho_2 = 74.7 \mu\Omega \text{ cm}$ , and  $T_0 = 85 \text{ K}$ . The characteristic energy  $k_B T_0$  was interpreted as the energy of relevant phonons effective for scattering. In this analogy, we fit our data for  $\text{KOs}_2\text{O}_6$  by assuming two exponential terms,

$$\rho_2 \exp(-T_{R1}/T) + \rho_2' \exp(-T_{R2}/T), \quad (12)$$

with characteristic temperatures of  $T_{R1}$  and  $T_{R2}$ , as shown in Fig. 22 (fit 2). The results are almost perfect, giving  $\rho_0 = 12.6(3) \mu\Omega \text{ cm}$ ,  $\rho_1 = -0.081(4) \mu\Omega \text{ cm/K}$ ,  $\rho_2 = 131(1) \mu\Omega \text{ cm}$ ,  $T_{R1} = 27.6(3) \text{ K}$ ,  $\rho_2' = 326(2) \mu\Omega \text{ cm}$ , and  $T_{R2} = 171(1) \text{ K}$ . The  $T_{R1}$  is much smaller than  $T_0$  for  $\text{Nb}_3\text{Sn}$  and close to the Einstein temperature  $T_{E1} = 22 \text{ K}$  from specific heat. It follows from this that the low-energy phonons detected in specific heat is probably responsible for the strong electron-phonon scattering resulting in the observed anomalous concave-downward temperature dependence of resistivity for  $\text{KOs}_2\text{O}_6$ .

### 3. Magnetic susceptibility

We have measured the normal-state magnetic susceptibility  $\chi$  of the KOs-729 crystal. Previously, we measured  $\chi$  using a polycrystalline sample and found a large temperature dependence. However, it turned out to be due to a small amount of an impurity phase that was a magnetic insulator. Here, we carefully carried out  $\chi$  measurements using the KOs-729 crystal and could obtain reliable data.

Figure 23 shows  $\chi$  measured in a magnetic field of 7 T applied along the two crystallographic directions,  $[111]$  and  $[110]$ . The anisotropy is negligibly small. They show essentially a  $T$ -independent Pauli paramagnetism with no signature of Curie-Weiss behavior at high temperature such as observed in a related  $\alpha$ -pyrochlore oxide  $\text{Cd}_2\text{Os}_2\text{O}_7$ .<sup>22</sup> Therefore, electron correlations are not so large in  $\text{KOs}_2\text{O}_6$ . Nevertheless, it exhibits a weak temperature dependence with a positive slope, the origin of which is not known. We take the

TABLE I. Superconducting and normal-state parameters for  $\alpha$ -pyrochlore  $\text{Cd}_2\text{Re}_2\text{O}_7$  and  $\beta$ -pyrochlore  $\text{KOs}_2\text{O}_6$ .

	$\alpha$ - $\text{Cd}_2\text{Re}_2\text{O}_7$	$\beta$ - $\text{KOs}_2\text{O}_6$
$T_c$ (K)	1.0	9.6
$\mu_0 H_{c2}$ (0) (T)	0.29	30.6 <sup>a</sup>
$\mu_0 H_c$ (0) (mT)	15	255
$\mu_0 H_{c1}$ (0) (mT)	2	9.4
$\xi$ (nm)	34	3.3
$\lambda$ (nm)	460	270 <sup>b</sup>
GL parameter	14	84
$\Delta C / \gamma T_c$	1.15	2.87
$2\Delta(0) / k_B T_c$	3.5	5.0
$\gamma_{\text{exp}}$ ( $\text{mJ K}^{-2} \text{mol}^{-1}$ )	30.2	70
$\gamma_{\text{band}}$ ( $\text{mJ K}^{-2} \text{mol}^{-1}$ )	11.5	9.6–11.4
$\chi_s$ ( $10^{-4} \text{cm}^3 \text{mol}^{-1}$ )	3.16	1.4 <sup>c</sup>
$\chi_{\text{band}}$ ( $10^{-4} \text{cm}^3 \text{mol}^{-1}$ )	1.8	1.5–1.8

<sup>a</sup>From high-magnetic-field experiments by Ohmichi *et al.* (Ref. 42).

<sup>b</sup>From  $\mu\text{SR}$  measurements by Koda *et al.* (Ref. 36).

<sup>c</sup>Approximate value obtained by subtracting  $\chi_{\text{orb}}=3.16 \times 10^{-4} \text{cm}^3/\text{mol}$ .

value of  $\chi$  as  $\chi=3.4 \times 10^{-4} \text{cm}^3/\text{mol}$  at  $T=10$  K. This value is small compared with those for metallic  $3d$  transition-metal oxides and is slightly smaller than that of  $\text{Cd}_2\text{Re}_2\text{O}_7$ ,  $\chi=4.8 \times 10^{-4} \text{cm}^3/\text{mol}$ .

In general, the magnetic susceptibility of metallic compounds is given as the sum of three terms:  $\chi=\chi_s+\chi_{\text{dia}}+\chi_{\text{orb}}$ , where they come from electron spins, core diamagnetism, and orbitals, respectively. We would like to know the first spin term from the experimental value.  $\chi_{\text{dia}}$  is determined from literature to be  $-1.2 \times 10^{-4} \text{cm}^3/\text{mol}$  for  $\text{KOs}_2\text{O}_6$ . The orbital term must be significantly large for such a  $5d$  transition-metal oxide with a large spin-orbit interaction. In fact, in the case of  $\text{Cd}_2\text{Re}_2\text{O}_7$ ,  $\chi_{\text{orb}}$  was determined to be  $3.16 \times 10^{-4} \text{cm}^3/\text{mol}$  from the  $K$ - $\chi$  plot using the temperature dependence of Knight shift  $K$  from Cd NMR measurements.<sup>60</sup> Thus,  $\chi_s=3.16 \times 10^{-4} \text{cm}^3/\text{mol}$  was obtained for  $\text{Cd}_2\text{Re}_2\text{O}_7$  ( $\chi_{\text{dia}}=-1.52 \times 10^{-4} \text{cm}^3/\text{mol}$ ). In the case of  $\text{KOs}_2\text{O}_6$ , the value of  $\chi_{\text{orb}}$  has not yet been determined. If one assumes the same value as for  $\text{Cd}_2\text{Re}_2\text{O}_7$ ,  $\chi_s=1.4 \times 10^{-4} \text{cm}^3/\text{mol}$  would be obtained, while  $\chi_s=4.6 \times 10^{-4} \text{cm}^3/\text{mol}$  when  $\chi_{\text{orb}}$  is ignored. Pauli paramagnetic susceptibility  $\chi_P$  expected from band-structure calculations is  $\chi_P=2\mu_B^2 N(0)=1.58 \times 10^{-4} \text{cm}^3/\text{mol}$ , which is close to the former value. It seems that the Stoner enhancement may not be so large in the present compound.

## IV. DISCUSSION

### A. Critical fields and fundamental superconducting parameters

In this section, we collect the values of the main thermodynamic and superconducting parameters obtained experimentally, which are listed in Table I, and discuss them and their relations to each other in the framework of the GL

theory. In the extreme type-II limit, three critical magnetic fields  $H_{c2}$ ,  $H_c$ , and  $H_{c1}$  are related to each other by only two characteristic length scales, superconducting coherence length  $\xi$  and magnetic penetration depth  $\lambda$ , and their ratio  $\kappa=\lambda/\xi$  by the equations<sup>49</sup>

$$H_{c2} = \frac{\phi_0}{2\pi\xi^2}, \quad (13)$$

$$H_c = \frac{\phi_0}{2\pi\sqrt{2}\lambda\xi}, \quad (14)$$

$$H_{c1} = \frac{\phi_0}{4\pi\lambda^2} \left[ \ln\left(\frac{\lambda}{\xi}\right) + 0.08 \right], \quad (15)$$

where  $\phi_0$  is the quantum flux.

Although the  $H_{c2}$  of  $\text{KOs}_2\text{O}_6$  is much larger than our experimental limit of 14 T, two high-magnetic-field experiments have already been reported. Ohmichi measured a magnetic penetration by the rf impedance method using a tunnel diode oscillator on a single crystal in high magnetic fields of up to 40 T and obtained  $\mu_0 H_{c2}(0)=30.6$  T.<sup>42</sup> On the other hand, Shibauchi *et al.* carried out similar measurements as well as resistivity measurements up to 50 T and determined  $\mu_0 H_{c2}(0)=33$  T.<sup>43</sup> It seems that there are some scatters in the value of  $H_{c2}$ , possibly resulting from the quality of crystals or the effects of the second phase transition. In fact,  $H_{c2}$  is lowered in a sample with a clear sign of the second transition, as shown in Fig. 10. It is well known that  $H_{c2}$  depends on the magnitude of the mean free path; a cleaner sample shows a lower  $H_{c2}$ .<sup>49</sup> Thus, we take the lowest value of  $\mu_0 H_{c2}(0)=30.6$  T in the following discussion, which gives  $\xi=3.3$  nm. Note that this may be the value for the low-temperature phase II, and that of the high-temperature phase I can be slightly smaller because of the larger  $H_{c2}$ .

We have obtained  $\mu_0 H_c(0)=0.255$  T from the initial slope of  $H_c(T)$  determined by specific heat and magnetization measurements. Thus,  $\lambda$  is calculated to be 278 nm from Eq. (14), which is in good agreement with  $\lambda=270$  nm from  $\mu\text{SR}$  measurements.<sup>36</sup> It follows from these values that the GL parameter  $\kappa$  is  $\kappa=\lambda/\xi=84$ , certainly indicating that  $\text{KOs}_2\text{O}_6$  is a type-II superconductor.

$H_{c1}$  is estimated from Eq. (15) to be 9.4 mT, which is much smaller than found in our magnetization measurements. However, as already mentioned, this discrepancy may be due to an extrinsic effect.

The large value of  $H_{c2}$  for  $\text{KOs}_2\text{O}_6$  was first considered as a sign of exotic superconductivity, because it was much larger than a Pauli limiting field  $\mu_0 H_P=18.6$  T expected from  $\mu_0 \mu_B H_{c2}=\Delta(0)/\sqrt{2}$  for  $\Delta(0)=1.76k_B T_c$ .<sup>8</sup> However, the actual value of  $H_P$  should be greater than this due to the larger gap, the strong-coupling correction by a factor of  $(1+\lambda_{ep})^{1/2}$ , and the effect of spin-orbit scattering. Taking  $2\Delta(0)=4.57k_B T_c$  and  $\lambda_{ep}=1.6$  led Brühwiler *et al.* to obtain  $\mu_0 H_P=37$  T.<sup>14</sup> Alternatively, we obtain  $\mu_0 H_P=47$  T based on our estimations of  $2\Delta(0)=5.00k_B T_c$  and  $\lambda_{ep}=2.4$ . It is known that spin-orbit scattering can also enhance  $H_{c2}$  in a dirty superconductor by reducing the effects of spin

paramagnetism.<sup>49</sup> However, this effect may not be crucial in the present compound in the clean limit. Therefore, the experimental value of  $H_{c2}$  should be considerably smaller than  $H_p$ , and may be understood within the spin singlet scenario.

On the other hand, Shibauchi *et al.* estimated the value of  $H_p$  in a different way.<sup>43</sup>  $H_p$  is defined as a field where the condensation energy of Cooper pairs becomes comparable with the Zeeman energy of electron spins. Using equation

$$H_c^2/8\pi = \chi_n H_p^2/2, \quad (16)$$

where  $\chi_n$  is the susceptibility in the normal state and  $\chi_n = 4.2 \times 10^{-4}$  cm<sup>3</sup>/mol, and  $\mu_0 H_c = 0.26$  T, they obtained  $\mu_0 H_p = 31$  T. We obtain a similar value from the corresponding values of  $\chi_n = 4.6 \times 10^{-4}$  cm<sup>3</sup>/mol and  $\mu_0 H_c = 0.255$  T in the present work. However, in order to estimate a true value of  $H_p$  in this way, one has to take spin susceptibility  $\chi_s$  instead of  $\chi_n$ . Although there is some ambiguity in the value of  $\chi_s$ , as mentioned before,  $\chi_s$  may be smaller than  $\chi_n$ , as in the case of  $\alpha$ -Cd<sub>2</sub>Re<sub>2</sub>O<sub>7</sub>. Thus,  $H_p$  is expected to be larger than 31 T. For example, taking  $\chi_s = 1.4 \times 10^{-4}$  cm<sup>3</sup>/mol yields  $H_p = 53$  T, which is close to the above estimation from the large gap and the strong-coupling correction. In any case, the actual value of  $H_{c2}$  is significantly smaller than  $H_p$ . Shibauchi *et al.* also pointed out that the temperature dependence of  $H_{c2}$  is somewhat strange, exhibiting an almost linear increase without saturation as  $T \rightarrow 0$ , and suggested an exotic mechanism for the enhancement based on the missing spatial inversion symmetry.<sup>43</sup>

### B. Strong-coupling superconductivity

Present specific-heat measurements as well as previous  $\mu$ SR, PES, and thermal conductivity measurements all gave strong evidence for an *s*-wave superconductivity occurring in KO<sub>2</sub>O<sub>6</sub>. In addition, there is no evidence to show the existence of exotic excitations such as magnetic or charge fluctuations that can mediate the Cooper pairing. Thus, it is most likely to assume a phonon-mediated superconductivity for KO<sub>2</sub>O<sub>6</sub>.

Three important quantities to characterize an isotropic superconducting ground state are  $\Delta C(T_c)/\gamma T_c$ ,  $2\Delta(0)/k_B T_c$ , and  $\gamma T_c^2/H_c(0)^2$ . Obtained in the present study are  $\Delta C(T_c)/\gamma T_c = 2.87$ ,  $2\Delta(0)/k_B T_c = 5.00$  and 4.69 from the analysis of specific-heat data by the  $\alpha$  model and the temperature dependence of  $C_{es}$ , respectively, and  $\gamma T_c^2/H_c(0)^2 = 0.128$ . These values are compared in Fig. 24 and Table II with those for typical strong-coupling superconductors such as Pb and its alloys, A-15 and Chevrel phase compounds.<sup>44,61</sup> Among all the known phonon-mediated superconductors, KO<sub>2</sub>O<sub>6</sub> possesses almost the largest values for  $\Delta C(T_c)/\gamma T_c$  and  $2\Delta(0)/k_B T_c$ , while the smallest value for  $\gamma T_c^2/H_c(0)^2$ , except for some Pb-Bi alloys, indicating that it is to be classified as an extremely strong-coupling superconductor. Then, a crucial question is what kind of phonons are relevant for such an extremely strong-coupling superconductivity. Particularly, the role of low-energy phonons suggested by specific heat and resistivity measurements is to be considered.

We investigate the characteristic phonon frequency  $\omega_{\text{ln}}$  and the electron-phonon coupling strength following the pre-

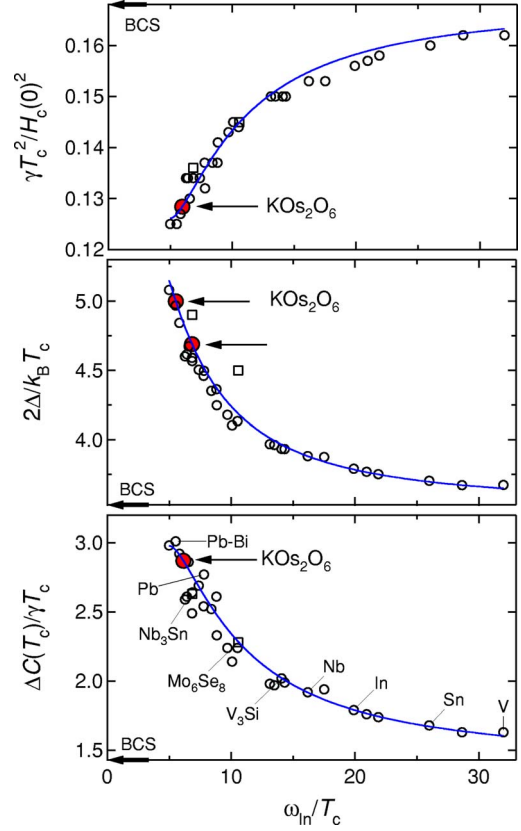


FIG. 24. (Color online) Three important quantities characterizing the strong-coupling superconductivity as a function of the average phonon frequency  $\omega_{\text{ln}}$  normalized by  $T_c$ . Each mark represents a superconductor: open circle corresponds to those studied by Carbotte (Ref. 44) and squares to some Chevrel phase compounds (Ref. 60). The data of KO<sub>2</sub>O<sub>6</sub> are represented by a large solid circle. There are two data points in the middle panel: the upper one is obtained from the analysis of specific-heat data using the  $\alpha$  model (Fig. 7) and the lower from the low-temperature fit shown in Fig. 6. A curve on each plot shows an analytical form given in the text which represents a strong-coupling correction to a BCS ratio.

vious analyses developed for superconductors in the strong-coupling regime.<sup>44</sup> The corrections of the BCS values by strong electron-phonon interactions have been deduced in the following approximate analytic formulas that link a single parameter  $x = \omega_{\text{ln}}/T_c$  to experimental thermodynamic quantities:

$$\frac{\Delta C(T_c)}{\gamma T_c} = 1.43 \left[ 1 + \frac{53}{x^2} \ln\left(\frac{x}{3}\right) \right], \quad (17)$$

$$\frac{2\Delta(0)}{k_B T_c} = 3.53 \left[ 1 + \frac{12.5}{x^2} \ln\left(\frac{x}{2}\right) \right], \quad (18)$$

$$\frac{\gamma T_c^2}{H_c(0)^2} = 0.168 \left[ 1 - \frac{12.2}{x^2} \ln\left(\frac{x}{3}\right) \right]. \quad (19)$$

$\omega_{\text{ln}}$  is the average phonon frequency given by



TABLE II. Comparison of superconducting parameters for typical strong-coupling superconductors.

	KOs <sub>2</sub> O <sub>6</sub>	Cu <sub>1.8</sub> Mo <sub>6</sub> S <sub>8</sub>	Mo <sub>6</sub> Se <sub>8</sub>	Nb <sub>3</sub> Sn	Nb	Pb	Pb <sub>0.8</sub> Bi <sub>0.2</sub>	α-Pb <sub>0.45</sub> Bi <sub>0.55</sub>	BCS
$T_c$ (K)	9.6	10.8	6.34	18.1	9.25	7.20	7.95	7.0	
$\lambda_{ep}$	2.38	1.20	1.26	1.67	0.85	1.55	1.88	2.59	
$\omega_{in}$ (K)	58.9	74	67	125	166	56	46	29	
$\gamma$ (mJ K <sup>-2</sup> mol <sup>-1</sup> )	70	36.9	47.2	52.4	7.79	2.98	2.92		
$\Delta C/\gamma T_c$	2.87	2.63	2.28	2.5	1.87	2.71	1.43		1.43
$2\Delta(0)/k_B T_c$	5.00	4.9	4.5	4.7	3.66	3.95	4.843		3.53
$\gamma T_c^2/H_c^2$	0.128	0.136	0.145	0.134	0.155	0.132	0.127		0.168

$$\omega_{in} = \exp \left[ 2 \int_0^\infty d\omega \alpha^2 F(\omega) \frac{\ln \omega}{\lambda_{ep} \omega} \right], \quad (20)$$

where  $\alpha^2$  is the average electron-phonon interaction,  $F(\omega)$  is the phonon DOS, and  $\lambda_{ep}$  is the electron-phonon coupling constant. The three quantities for various superconductors are plotted as a function of  $\omega_{in}/T_c$  together with the corresponding analytical curve in Fig. 24.

For KOs<sub>2</sub>O<sub>6</sub>, using Eq. (17) and  $\Delta C(T_c)/\gamma T_c = 2.87$ , one obtains  $x = 6.14$  or  $\omega_{in} = 58.9$  K. Using Eq. (18) and the gap values  $2\Delta(0)/k_B T_c = 5.00$  and 4.69 from the analysis of specific-heat data by the  $\alpha$  model and the temperature dependence of  $C_{es}$ , respectively, one arrives at  $\omega_{in} = 53.0$  and 65.7 K. Equation (19) and  $\gamma T_c^2/H_c(0)^2 = 0.128$  give  $\omega_{in} = 57.2$  K. Thus the obtained three values of  $\omega_{in}$  are in good agreement with each other, which confirms the validity of applying the above strong-coupling corrections to KOs<sub>2</sub>O<sub>6</sub>. On one hand, if one takes the value of  $\Delta C(T_c)/\gamma T_c = 2.87$  as the most reliable experimental data, the values of  $\Delta(0)$  and  $H_c(0)$  are determined alternatively by Eqs. (18) and (19) with  $\omega_{in} = 58.9$  K,  $2\Delta(0)/k_B T_c = 4.84$ , and  $\gamma T_c^2/H_c(0)^2 = 0.129$  [ $\mu_0 H_c(0) = 0.254$  T].

Next, an electron-phonon coupling constant  $\lambda_{ep}$  can be estimated from the McMillan-Allen-Dynes equation with  $\omega_{in} = 58.9$  K,<sup>62</sup>

$$T_c = \frac{\omega_{in}}{1.2} \exp \left[ \frac{-1.04(1 + \lambda_{ep})}{\lambda_{ep} - \mu^*(1 + 0.62\lambda_{ep})} \right], \quad (21)$$

where  $\mu^*$  is the Coulomb coupling constant and has been estimated to be 0.091 for KOs<sub>2</sub>O<sub>6</sub>.<sup>20</sup> We obtain  $\lambda_{ep} = 2.38$ , which is much larger than  $\lambda_{ep} = 1.6$  reported previously.<sup>14</sup> It is also surprisingly large compared with those for typical strong-coupling superconductors such as Pb ( $\lambda_{ep} = 1.55$ ,  $\omega_{in} = 50$  K), Mo<sub>6</sub>Se<sub>8</sub> ( $\lambda_{ep} = 1.27$ ,  $\omega_{in} = 70$  K), and a Bi-Pb alloy ( $\lambda_{ep} = 1.7-2.1$ ,  $\omega_{in} = 50-45$  K), as compared in Fig. 25 and Table II. An exceptionally large value of  $\lambda_{ep} = 2.59$  was reported for an amorphous Pb<sub>0.45</sub>Bi<sub>0.55</sub> thin film that was prepared by rapid quenching beyond the solubility limit.<sup>62</sup> It is interesting to note in Fig. 25 that the data point of KOs<sub>2</sub>O<sub>6</sub> seems to lie slightly apart from a universal curve for other compounds, suggesting the uniqueness of the electron-phonon coupling in this compound. In the case of  $\lambda_{ep} > 2$ , however, there is a question about the validity of applying

Eq. (21). Thus, assuming  $\omega_{in} = 58.9$  on the universal curve in Fig. 25, one obtains  $\lambda_{ep} = 1.8$  alternatively. Anyway, since the  $\lambda_{ep}$  is relatively large, this assures us that there is a very strong electron-phonon coupling in KOs<sub>2</sub>O<sub>6</sub>.

The origin of the large  $\lambda_{ep}$  cannot be attributed to usual phonons. Saniz and Freeman calculated the value using  $\Theta_D = 285$  K in a standard phonon-mediated pairing scenario and obtained a much smaller value of  $\lambda_{ep} = 0.85$ .<sup>20</sup> Since the  $\lambda_{ep}$  is expressed by

$$\lambda_{ep} = 2 \int d\omega \alpha^2 F(\omega)/\omega, \quad (22)$$

a low-energy phonon may enhance  $\lambda_{ep}$  effectively: the low-energy part of  $\alpha^2 F(\omega)$  becomes dominant due to the denominator  $\omega$ . In fact, many strong-coupling superconductors with large values of  $\lambda_{ep}$  possess various low-energy phonons. For example, the A-15 compounds show soft phonon modes associated with a cubic-to-tetragonal transition,<sup>63</sup> while the Chevrel phase compounds are assumed to be “molecular crystals” with low-lying phonon modes.<sup>64</sup> The role of such low-energy phonons on the mechanism of superconductivity has been studied extensively in these strong-coupling superconductors.

It is reasonable for KOs<sub>2</sub>O<sub>6</sub> to ascribe such a low-energy phonon to the rattling vibration. The relevant phonon fre-

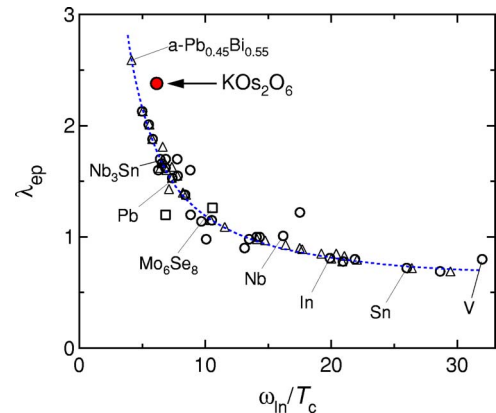


FIG. 25. (Color online) Electron-phonon coupling constant  $\lambda_{ep}$  versus  $\omega_{in}/T_c$ . Triangles are from Allen and Dynes (Ref. 62), and the other marks are the same as in Fig. 24. The broken line is a guide for the eyes. KOs<sub>2</sub>O<sub>6</sub> possesses the second largest  $\lambda_{ep}$ , next to an amorphous Pb<sub>0.45</sub>Bi<sub>0.55</sub> film.

quency  $\omega_n=58.9$  K obtained from the above strong-coupling corrections should give an exponential average over the whole phonon DOS. The lower bound has been estimated to be  $T_{E1}=22$  K from specific heat and  $T_{R1}=27.6$  K from resistivity, which must enhance  $\lambda_{ep}$  effectively. Moreover, one expects large electron-phonon couplings for  $\text{KOs}_2\text{O}_6$  because of the low Fermi velocity, as discussed for the saturated behavior of resistivity: slower electrons feel more the motion of surrounding ions, especially when the ions also move slowly with low energy.

It should be emphasized that in most cases the lattice itself becomes unstable when the electron-phonon coupling becomes too strong. In the present compound, however, conduction electrons are located on the hard skeleton made of  $\text{OsO}_6$  octahedra, while low-energy phonons are associated with the rattling K ions that are weakly, structurally coupled to the skeleton (Fig. 1). This structural duality must give rise to such an unusually large coupling constant over 2. It would be intriguing to investigate further in detail how this rattling, which is an essentially anharmonic vibration almost localized in a cage, can mediate the Cooper pairing in  $\text{KOs}_2\text{O}_6$ . More experimental information, particularly from neutron-diffraction experiments that can determine the low-energy phonon DOS, is required for further discussion.

### C. Electronic structure and mass enhancement

According to electronic band-structure calculations,  $5d$  pyrochlore oxides possess commonly a strongly hybridized band made of transition-metal  $5d$  and O  $2p$  states near the Fermi level, which is a manifold of 12 bands with a total bandwidth of  $\sim 3$  eV. Because of the large bandwidth, they may not be classified as strongly correlated electron systems in the ordinary sense. However, since the profile of the DOS exhibits many sharp peaks due to a large degeneracy coming from the high symmetry of the pyrochlore structure, the magnitude of electron correlations may depend on the band filling. A calculated DOS at the Fermi level is  $N(0)=2.45$  states/eV f.u. ( $\gamma_{\text{band}}=11.6$  mJ K $^{-2}$  mol $^{-1}$ ) for  $\text{KOs}_2\text{O}_6$  with  $\text{Os}^{5.5+}$  ( $5d^{2.5}$ ),<sup>20</sup> which is larger than  $N(0)=1.14$  states/eV f.u. ( $\gamma_{\text{band}}=5.4$  mJ K $^{-2}$  mol $^{-1}$ ) for  $\text{Cd}_2\text{Re}_2\text{O}_7$  with  $\text{Re}^{5+}$  ( $5d^2$ ) (Ref. 17) and smaller than  $N(0)=6.35$  states/eV f.u. ( $\gamma_{\text{band}}=29.9$  mJ K $^{-2}$  mol $^{-1}$ ) for  $\text{Cd}_2\text{Os}_2\text{O}_7$  with  $\text{Os}^{5+}$  ( $5d^3$ ).<sup>22</sup> Thus, one may expect a moderately large electron correlation for  $\text{KOs}_2\text{O}_6$ .

The calculated Fermi surface of  $\beta$ - $\text{AOs}_2\text{O}_6$  consists of a pair of closed sheets around the zone center and a holelike sheet near the zone boundary.<sup>16,19,20,25</sup> The former Fermi surface possesses a characteristic shape: each sheet is not spherical but close to an octahedron with flat surfaces, suggesting an electronic instability due to Fermi-surface nesting.<sup>19</sup> However, there has been no experimental evidence to show the nesting instability. It would be interesting if these two Fermi surfaces are related to the two superconducting gaps suggested in the specific-heat data shown in Fig. 7.

The Sommerfeld coefficient calculated from the values of  $N(0)$  given by the band-structure calculations is approximately 10 mJ K $^{-2}$  mol $^{-1}$ , which is a factor of 7 smaller than the present experimental value. On the other hand, Pauli

paramagnetic susceptibility calculated by  $\chi_P=2\mu_B^2N(0)$  is  $1.58 \times 10^{-4}$  cm $^3$ /mol, which may be similar or not so small compared with the experimental value. As a result, the Wilson ratio  $R_W$ , which is given by

$$R_W = (\pi^2/3)(k_B/\mu_0)^2(\chi_s/\gamma) = 72.949(\chi_s/\gamma), \quad (23)$$

is estimated to be 0.15 (0.48) from  $\gamma=0.070$  J K $^{-2}$  mol $^{-1}$  and  $\chi_s=1.4$  (4.6)  $\times 10^{-4}$  cm $^3$ /mol, smaller than unity. This small  $R_W$  means that only  $\gamma$  is enhanced. Therefore, the source of the mass enhancement should not be usual electron correlations, but probably electron-phonon interactions. The renormalization factor  $(1+\lambda_{ep})$  due to electron-phonon interactions becomes 3.4 for  $\lambda_{ep}=2.4$  from the above estimation, which is still a factor of 2 smaller than the observed mass enhancement. Brühwiler *et al.* assumed a mass enhancement by a factor of  $(1+\lambda_{ep})(1+\lambda_c)$  with an additional enhancement by  $(1+\lambda_c)$  that is ascribed to electron correlations. This may give a reasonable explanation, because we observed in fact a  $T^2$  dependence for low-temperature resistivity. The coefficient  $A$  of the  $T^2$  term is  $0.143$   $\mu\Omega$  cm K $^{-2}$  and the  $\gamma$  value of  $70$  mJ K $^{-2}$  mol $^{-1}$  yield the Kadowaki-Woods ratio of  $A/\gamma^2=2.8 \times 10^{-5}$ , close to the universal value of  $10^{-5}$  for the strongly correlated electron system. Recent thermal conductivity experiments also pointed out the importance of electron correlations in  $\text{KOs}_2\text{O}_6$ .<sup>34</sup> Then, we obtain  $\lambda_c=1.1$ . Nevertheless, it should be kept in mind that there is already a factor of 3 enhancement in  $\gamma$  for  $\text{Cd}_2\text{Re}_2\text{O}_7$  that lacks electron correlations (no  $T^2$  dependence in resistivity) as well as low-energy phonons such as observed in  $\text{KOs}_2\text{O}_6$ .

A large mass enhancement that is possibly associated with rattling vibrations has been found in the filled skutterudite  $\text{SmOs}_4\text{Sb}_{12}$ .<sup>65</sup> Hattori *et al.* studied an impurity four-level Kondo model, in which an atom is tunneling among four stable sites and interacting with surrounding conduction electrons, and found that the interaction can result in a moderate enhancement of the quasiparticle mass.<sup>66</sup> It is likely that the same mechanism is responsible for the mass enhancement for  $\text{KOs}_2\text{O}_6$ , because a similar situation is realized in  $\text{KOs}_2\text{O}_6$ , where four shallow potential minima for the K ion exist in a cage that allow a large excursion for the K ion from the center of the cage, as schematically illustrated in Fig. 1. It is likely that some entropy associated with the rattling survives at low temperature and gives rise to a heavy quasiparticle mass through a strong electron-rattler interaction. It would be necessary to test theoretically how large the enhancement is, in fact, attainable through this exotic mechanism.

### D. Effects of the second phase transition

Finally, we discuss on what happens to the superconducting and normal-state properties at the second phase transition that is presumably of structural origin. Thermal hysteresis observed in resistivity and specific heat implies that it is of first order. In our recent structural analysis, neither symmetry change nor cell doubling was detected. However, we found that the intensity of some reflections changed slightly at the transition. Details of the structural refinements are described elsewhere.<sup>67</sup> It is remarkable that such a structural transition

occurs below a superconducting transition, because in most cases an inherent lattice instability has already been lifted by coupling with electrons to induce superconductivity. It is also surprising that the superconductivity is certainly affected, but the influence is very small. Although the origin of the transition is so interesting, we leave the door to this issue open for future study.

Here, we describe the observed effects of the transition on various properties. There must be little change in the band structure, especially in the DOS at the transition, because the normal-state susceptibility is scarcely affected by the transition, as shown for the 7 T data in Fig. 14(a). Moreover, the fact that the specific heat at 14 T shown in Fig. 3 seems to be smoothly connected across the peak at  $T_p$  means no large change in the  $\gamma$  value. Consequently, the observed reduction in the normal-state resistivity at  $T_p$  must be ascribed to the enhancement of the mean free path or the lifetime of carriers: the associated increase of the mean free path is estimated to be  $\Delta l \sim 27\%$ . In addition, the observed change in the temperature dependence from concave-downward to  $T^2$  behavior means that an incoherent electron-rattler scattering has disappeared below  $T_p$ , resulting in this large enhancement of mean free path. Recent thermal conductivity experiments indicated, in fact, that the lifetime of carriers is largely enhanced below  $T_p$ .<sup>34</sup>

For the superconducting properties, on the other hand, the  $H_{c2}$  is decreased by 15% at  $T_p$ , and the ratio of the Maki parameters  $\kappa_2/\kappa_1$  is increased by approximately 25%. In contrast, the fundamental superconducting parameters are preserved across the transition: both the  $T_c$  and  $H_c$  may be identical. Therefore, the observed changes in  $H_{c2}$  and the Maki parameters just imply that the system becomes closer to the clean limit and are compatible with the enhancement of the mean free path. Since  $H_{c2}$  is expressed as

$$H_{c2} = \frac{\phi_0}{2\pi\xi^2} \approx \frac{\phi_0}{2\pi\xi_0\ell} \approx 3 \times 10^4 \frac{T_c}{v_F\ell}, \quad (24)$$

where  $\xi_0$  is the BCS coherence length<sup>68</sup>;  $\Delta H_{c2} = -15\%$  means that the  $\ell$  is enhanced by 17% at  $T_p$ . Therefore, all the observed changes at the second phase transition are at least qualitatively understood by assuming an enhancement in the

mean free path, suggesting that a strong incoherent electron-rattler scattering has gone at the transition. This suggests that there is a substantial difference in the dynamics of rattlers across the transition.

## V. CONCLUSION

We have studied the superconducting and normal-state properties of the  $\beta$ -pyrochlore oxide  $\text{KOs}_2\text{O}_6$  by means of specific heat, magnetization, and resistivity measurements. Various superconducting parameters are successfully determined, all of which give evidence for an extremely strong-coupling  $s$ -wave superconductivity. It is demonstrated that low-energy phonons having an average frequency of 58.9 K are responsible for the pairing mechanism. Moreover, a very large electron-phonon coupling constant  $\lambda_{ep}$  of 2.38 is deduced from the strong-coupling corrections for the BCS values. The existence of the corresponding low-lying phonons is found in specific heat as well as resistivity that exhibits a concave-downward temperature dependence due to a large electron-phonon interaction.

The source of the low-lying phonons is ascribed to the rattling vibration of the K ion. Since the K ion is located in a highly anharmonic potential generated by the surrounding oversized metallic cage, it can rattle even at low temperature and gives rise to an anomalous electron scattering. A first-order phase transition probably associated with the rattlers is observed at  $T_p = 7.5$  K, below which the mean free path of quasiparticles are enhanced significantly. The reason why such a large electron-phonon coupling is realized in this compound may be found in the structural and electronic duality.  $\text{KOs}_2\text{O}_6$  presents a unique playground for superconductivity in the sense that an electron-rattler coupling can mediate Cooper pairing in the extremely strong-coupling regime.

## ACKNOWLEDGMENTS

We wish to thank M. Takigawa, T. Shibauchi, Y. Matsuda, and H. Harima for fruitful discussions. This research was supported by a Grant-in-Aid for Scientific Research B (16340101) provided by the Ministry of Education, Culture, Sports, Science and Technology, Japan.

<sup>1</sup>M. Hanawa, Y. Muraoka, T. Tayama, T. Sakakibara, J. Yamaura, and Z. Hiroi, Phys. Rev. Lett. **87**, 187001 (2001).

<sup>2</sup>H. Sakai, K. Yoshimura, H. Ohno, H. Kato, S. Kambe, R. E. Walstedt, T. D. Matsuda, Y. Haga, and Y. Onuki, J. Phys.: Condens. Matter **13**, L785 (2001).

<sup>3</sup>R. Jin, J. He, S. McCall, C. S. Alexander, F. Drymiotis, and D. Mandrus, Phys. Rev. B **64**, 180503(R) (2001).

<sup>4</sup>S. Yonezawa, Y. Muraoka, and Z. Hiroi, J. Phys. Soc. Jpn. **73**, 1655 (2004).

<sup>5</sup>S. Yonezawa, Y. Muraoka, Y. Matsushita, and Z. Hiroi, J. Phys. Soc. Jpn. **73**, 819 (2004).

<sup>6</sup>S. M. Kazakov, N. D. Zhigadlo, M. Brühwiler, B. Batlogg, and J. Karpinski, Supercond. Sci. Technol. **17**, 1169 (2004).

<sup>7</sup>M. Brühwiler, S. M. Kazakov, N. D. Zhigadlo, J. Karpinski, and B. Batlogg, Phys. Rev. B **70**, 020503(R) (2004).

<sup>8</sup>S. Yonezawa, Y. Muraoka, Y. Matsushita, and Z. Hiroi, J. Phys.: Condens. Matter **16**, L9 (2004).

<sup>9</sup>For  $\text{KOs}_2\text{O}_6$ , Yamaura *et al.*, reported the space group  $Fd\bar{3}m$  in their single-crystal x-ray diffraction (XRD) experiments [J. Yamaura, S. Yonezawa, Y. Muraoka, and Z. Hiroi, J. Solid State Chem. **179**, 336 (2005)], while, recently, Schuck *et al.*, claimed a different space group of  $F\bar{4}3m$  that lacks inversion symmetry in their XRD study at room temperature [G. Schuck, S. M. Kazakov, K. Rogacki, N. D. Zhigadlo, and J. Karpinski, Phys. Rev. B **73**, 144506 (2006)]. We carefully reexamined the crystal structure using a high-quality crystal and came to a conclusion



- that  $Fd\bar{3}m$  is the most probable space group for  $\text{KOs}_2\text{O}_6$  at room temperature as well as at low temperatures below  $T_p$ , in spite of the fact that we observed some forbidden reflections due to double diffractions. We also confirmed this result by using the convergent beam electron diffraction and Raman scattering techniques that are known to be sensitive to the symmetry of a crystal.
- <sup>10</sup>J. Yamaura, S. Yonezawa, Y. Muraoka, and Z. Hiroi, *J. Solid State Chem.* **179**, 336 (2005).
  - <sup>11</sup>V. Keppens, D. Mandrus, B. C. Sales, B. C. Chakoumakos, P. Dai, R. Coldea, M. B. Maple, D. A. Gajewski, E. J. Freeman, and S. Bennington, *Nature (London)* **395**, 876 (1998).
  - <sup>12</sup>G. S. Nolas, J. L. Cohn, G. A. Slack, and S. B. Schujman, *Appl. Phys. Lett.* **73**, 178 (1998).
  - <sup>13</sup>Z. Hiroi, S. Yonezawa, T. Muramatsu, J. Yamaura, and Y. Muraoka, *J. Phys. Soc. Jpn.* **74**, 1255 (2005).
  - <sup>14</sup>M. Brühwiler, S. M. Kazakov, J. Karpinski, and B. Batlogg, *Phys. Rev. B* **73**, 094518 (2006).
  - <sup>15</sup>R. Galati, R. W. Hughes, C. S. Knee, P. F. Henry, and M. T. Weller, *J. Mater. Chem.* **17**, 160 (2007).
  - <sup>16</sup>J. Kuneš, T. Jeong, and W. E. Pickett, *Phys. Rev. B* **70**, 174510 (2004).
  - <sup>17</sup>H. Harima, *J. Phys. Chem. Solids* **63**, 1035 (2002).
  - <sup>18</sup>D. J. Singh, P. Blaha, K. Schwarz, and J. O. Sofo, *Phys. Rev. B* **65**, 155109 (2002).
  - <sup>19</sup>R. Saniz, J. E. Medvedeva, L. H. Ye, T. Shishidou, and A. J. Freeman, *Phys. Rev. B* **70**, 100505(R) (2004).
  - <sup>20</sup>R. Saniz and A. J. Freeman, *Phys. Rev. B* **72**, 024522 (2005).
  - <sup>21</sup>A. W. Sleight, J. L. Gilson, J. F. Weiher, and W. Bindloss, *Solid State Commun.* **14**, 357 (1974).
  - <sup>22</sup>D. Mandrus, J. R. Thompson, R. Gaal, L. Forro, J. C. Bryan, B. C. Chakoumakos, L. M. Woods, B. C. Sales, R. S. Fishman, and V. Keppens, *Phys. Rev. B* **63**, 195104 (2001).
  - <sup>23</sup>Z. Hiroi and M. Hanawa, *J. Phys. Chem. Solids* **63**, 1021 (2002).
  - <sup>24</sup>O. Vyaselev, K. Kobayashi, K. Arai, J. Yamazaki, K. Kodama, M. Takigawa, M. Hanawa, and Z. Hiroi, *J. Phys. Chem. Solids* **63**, 1031 (2002).
  - <sup>25</sup>Z. Hiroi, J. Yamaura, S. Yonezawa, and H. Harima, *Physica C*, (in press).
  - <sup>26</sup>Z. Hiroi, T. Yamauchi, T. Yamada, M. Hanawa, Y. Ohishi, O. Shimomura, M. Abliz, M. Hedo, and Y. Uwatoko, *J. Phys. Soc. Jpn.* **71**, 1553 (2002).
  - <sup>27</sup>T. Muramatsu, S. Yonezawa, Y. Muraoka, and Z. Hiroi, *J. Phys. Soc. Jpn.* **73**, 2912 (2004).
  - <sup>28</sup>T. Muramatsu, N. Takeshita, C. Terakura, H. Takagi, Y. Tokura, S. Yonezawa, Y. Muraoka, and Z. Hiroi, *Phys. Rev. Lett.* **95**, 167004 (2005).
  - <sup>29</sup>R. Khasanov, D. G. Eshchenko, J. Karpinski, S. M. Kazakov, N. D. Zhigadlo, R. Brutsch, D. Gavillet, D. DiCastro, A. Shengelaya, F. LaMattina, A. Maisuradze, C. Baines, and H. Keller, *Phys. Rev. Lett.* **93**, 157004 (2004).
  - <sup>30</sup>K. Magishi, J. L. Gavilano, B. Pedrini, J. Hinderer, M. Weller, H. R. Ott, S. M. Kazakov, and J. Karpinski, *Phys. Rev. B* **71**, 024524 (2005).
  - <sup>31</sup>R. Khasanov, D. G. Eshchenko, D. DiCastro, A. Shengelaya, F. LaMattina, A. Maisuradze, C. Baines, H. Luetkens, J. Karpinski, S. M. Kazakov, and H. Keller, *Phys. Rev. B* **72**, 104504 (2005).
  - <sup>32</sup>K. Arai, J. Kikuchi, K. Kodama, M. Takigawa, S. Yonezawa, Y. Muraoka, and Z. Hiroi, *Physica B* **359-361**, 488 (2005).
  - <sup>33</sup>M. Yoshida, K. Arai, R. Kaido, M. Takigawa, S. Yonezawa, Y. Muraoka, and Z. Hiroi, *Phys. Rev. Lett.* **98**, 197002 (2007).
  - <sup>34</sup>Y. Kasahara, Y. Shimono, T. Shibauchi, Y. Matsuda, S. Yonezawa, Y. Muraoka, and Z. Hiroi, *Phys. Rev. Lett.* **96**, 247004 (2006).
  - <sup>35</sup>T. Shimojima, Y. Shibata, K. Ishizaka, T. Kiss, T. Togashi, S. Watanabe, J. Yamaura, S. Yonezawa, Y. Muraoka, Z. Hiroi, T. Saitoh, and S. Shin, *Phys. Rev. Lett.* (in press).
  - <sup>36</sup>A. Koda, W. Higemoto, K. Ohishi, S. R. Saha, R. Kadono, S. Yonezawa, Y. Muraoka, and Z. Hiroi, *J. Phys. Soc. Jpn.* **74**, 1678 (2005).
  - <sup>37</sup>Z. Hiroi, S. Yonezawa, J. Yamaura, T. Muramatsu, and Y. Muraoka, *J. Phys. Soc. Jpn.* **74**, 1682 (2005).
  - <sup>38</sup>Z. Hiroi, S. Yonezawa, and J. Yamaura, *J. Phys.: Condens. Matter* **19**, 145283 (2007).
  - <sup>39</sup>Z. Hiroi and S. Yonezawa, *J. Phys. Soc. Jpn.* **75**, 043701 (2006).
  - <sup>40</sup>B. Darriet, M. Rat, J. Galy, and P. Hagenmüller, *Mater. Res. Bull.* **6**, 1305 (1971).
  - <sup>41</sup>D. W. Murphy, R. J. Cava, K. Rhyne, R. S. Roth, A. Santoro, S. M. Zahurak, and J. L. Dye, *Solid State Ionics* **18&19**, 799 (1986).
  - <sup>42</sup>E. Ohmichi, T. Osada, S. Yonezawa, Y. Muraoka, and Z. Hiroi, *J. Phys. Soc. Jpn.* **75**, 045002 (2006).
  - <sup>43</sup>T. Shibauchi, L. Krusin-Elbaum, Y. Kasahara, Y. Shimono, Y. Matsuda, R. D. McDonald, C. H. Mielke, S. Yonezawa, Z. Hiroi, M. Arai, T. Kita, G. Blatter, and M. Sigrist, *Phys. Rev. B* **74**, 220506(R) (2006).
  - <sup>44</sup>J. P. Carbotte, *Rev. Mod. Phys.* **62**, 1027 (1990).
  - <sup>45</sup>H. Padamsee, J. E. Neighbor, and C. A. Shiffman, *J. Low Temp. Phys.* **12**, 384 (1973).
  - <sup>46</sup>F. Bouquet, Y. Wang, R. A. Fisher, D. G. Hinks, J. D. Jorgensen, A. Junod, and N. E. Phillips, *Europhys. Lett.* **56**, 856 (2001).
  - <sup>47</sup>V. Guritanu, W. Goldacker, F. Bouquet, Y. Wang, R. Lortz, G. Goll, and A. Junod, *Phys. Rev. B* **70**, 184526 (2004).
  - <sup>48</sup>M. Nohara, M. Isshiki, F. Sakai, and H. Takagi, *J. Phys. Soc. Jpn.* **68**, 1078 (1999).
  - <sup>49</sup>A. L. Fetter and P. C. Hohenberg, in *Superconductivity*, edited by R. D. Parks (Dekker, New York, 1969), p. 817.
  - <sup>50</sup>T. McConville and B. Serin, *Phys. Rev.* **140**, A1169 (1965).
  - <sup>51</sup>S. Paschen, W. Carrillo-Cabrera, A. Bentiën, V. H. Tran, M. Baenitz, Y. Grin, and F. Steglich, *Phys. Rev. B* **64**, 214404 (2001).
  - <sup>52</sup>Z. Hiroi, M. Hanawa, Y. Muraoka, and H. Harima, *J. Phys. Soc. Jpn.* **72**, 21 (2003).
  - <sup>53</sup>G. W. Webb, Z. Fisk, J. J. Engelhardt, and S. D. Bader, *Phys. Rev. B* **15**, 2624 (1977).
  - <sup>54</sup>A. P. Mackenzie, R. K. W. Haselwimmer, A. W. Tyler, G. G. Lonzarich, Y. Mori, S. Nishizaki, and Y. Maeno, *Phys. Rev. Lett.* **80**, 161 (1998).
  - <sup>55</sup>D. W. Woodard and G. D. Cody, *Phys. Rev.* **136**, A166 (1964).
  - <sup>56</sup>Z. Fisk and G. W. Webb, *Phys. Rev. Lett.* **36**, 1084 (1976).
  - <sup>57</sup>A. Ioffe and A. R. Regel, *Prog. Semicond.* **4**, 237 (1960).
  - <sup>58</sup>P. B. Allen, W. E. Pickett, K. M. Ho, and M. L. Cohen, *Phys. Rev. Lett.* **40**, 1532 (1978).
  - <sup>59</sup>H. Wiesmann, M. Gurvitch, H. Lutz, A. Ghosh, B. Schwarz, M. Strongin, P. B. Allen, and J. W. Halley, *Phys. Rev. Lett.* **38**, 782 (1977).
  - <sup>60</sup>O. Vyaselev, K. Arai, K. Kobayashi, J. Yamazaki, K. Kodama, M. Takigawa, M. Hanawa, and Z. Hiroi, *Phys. Rev. Lett.* **89**, 017001 (2002).
  - <sup>61</sup>M. Furuyama, N. Kobayashi, and Y. Muto, *Phys. Rev. B* **40**, 4344 (1989).

<sup>62</sup>P. B. Allen and R. C. Dynes, Phys. Rev. B **12**, 905 (1975).

<sup>63</sup>L. R. Testardi, Rev. Mod. Phys. **47**, 637 (1975).

<sup>64</sup>S. D. Bader, G. S. Knapp, S. K. Sinha, P. Schweiss, and B. Renker, Phys. Rev. Lett. **37**, 344 (1976).

<sup>65</sup>S. Sanada, Y. Aoki, A. Tsuchiya, D. Kikuchi, H. Sugawara, and H. Sato, J. Phys. Soc. Jpn. **74**, 246 (2005).

<sup>66</sup>K. Hattori, Y. Hirayama, and K. Miyake, J. Phys. Soc. Jpn. **74**, 3306 (2005).

<sup>67</sup>J. Yamaura and Z. Hiroi (unpublished).

<sup>68</sup>M. Tinkham, *Introduction to Superconductivity* (Dover, New York, 1996).