

Singlet-triplet relaxation in two-electron silicon quantum dots

M. Prada,¹ R. H. Blick,² and R. Joynt¹

¹Physics Department, University of Wisconsin-Madison, 1150 University Avenue, Wisconsin 53705, USA

²Electric and Computer Engineering, University of Wisconsin-Madison, 1415 Engineering Drive, Madison, Wisconsin 53705, USA

(Received 9 January 2008; revised manuscript received 28 January 2008; published 21 March 2008)

We investigate the singlet-triplet relaxation process of a two-electron silicon quantum dot. In the absence of a perpendicular magnetic field, we find that spin-orbit coupling is not the main source of singlet-triplet relaxation. Relaxation in this regime occurs mainly via virtual states, and is due to nuclear hyperfine coupling. In the presence of an external magnetic field perpendicular to the plane of the dot, the spin-orbit coupling is important and virtual states are not required. We find that there can be strong anisotropy for different field directions: parallel magnetic field can increase substantially the relaxation time due to Zeeman splitting, but when the magnetic field is applied perpendicular to the plane, the enhancement of the spin-orbit effect shortens the relaxation time. We find the relaxation to be orders of magnitude longer than for GaAs quantum dots, due to weaker hyperfine and spin-orbit effects.

DOI: 10.1103/PhysRevB.77.115438

PACS number(s): 68.65.Hb, 72.25.Rb, 03.67.Pp, 85.35.Be

I. INTRODUCTION

A promising technology for the implementation of quantum computation (QC) involves the storage of quantum information in the spin of electrons in quantum dots (QDs). The key requirement is that the lifetime of the spins is long compared with the time required for the operation of logic gates. This has motivated the development of dots in silicon, where spin-orbit coupling is weak and isotopic enrichment can eliminate hyperfine coupling (HC). Indeed, recent experiments demonstrate the presence of long-lived spin states in silicon QDs.¹ Understanding the processes that relax spins can point to strategies for minimizing relaxation and coherence times, thereby improving coherent control of quantum systems. In the case of electron spins embedded in semiconductor nanostructures, the relaxation properties are strongly affected by the regime of operation. Thus, it is important to identify the dominant sources of fluctuations in these systems and the mechanisms by which they couple to the spins, and to analyze the nonequilibrium decay laws in different regimes of external fields. Considerable theoretical work has been performed on lifetimes for single-electron spin flip T_1 and dephasing T_2 for GaAs (Refs. 2–4) and for Si.⁵ In GaAs, these times have been measured. Single-spin values for T_1 of about 0.5 ms at a field of 10 T up to 170 ms at 1.75 T were obtained,^{6,7} while for T_2 , one finds a value of about 1 μ s.⁸ A qubit consisting of the singlet and triplet states of a two-electron system is also proposed for QC. The singlet-triplet lifetime has been studied in GaAs.^{9–12} In particular, Hanson *et al.* found T_1 for the singlet-triplet transition in a two-electron GaAs dot to be 2.6 ms at $B=0.02$ T. We shall call this T_{ST} . Extensive theoretical work has been done for T_{ST} in GaAs,^{4,13–16} and our methods are similar to those found in these references.

In this paper, we study the relaxation process for a doubly occupied Si QD in an excited (triplet) state to the ground (singlet) state, focusing on the computation of T_{ST} . Our main motivation is to understand transport through double quantum dots. Thus, we are concerned with lateral dots defined by gates in strained silicon quantum wells. Such dots have a

twofold valley degeneracy as well as spin degeneracy, but we will deal here with dots where the valley splitting is large compared with the first orbital excitation energy. We will focus on natural Si with a 4% concentration of ²⁹Si nuclei, since this is the material on which experiments have been performed,¹⁷ but we comment on isotopically enriched Si below.

We assume the levels to be ordered as shown in Fig. 1: The relevant energy scales are then the exchange, $J=E_{S'}-E_T$, and the difference between the ground singlet and the first triplet, $\epsilon_{ST}=E_T-E_{S_g}$, where the triplet is formed with a higher energy orbital, as depicted in Fig. 1(a). The dominant mechanism available in the absence of an external magnetic field is the hyperfine coupling with nuclei^{18,19} via a virtual state²⁰ [left arrows of Fig. 1(b)]. HC cannot cause a direct $T \rightarrow S$ transition because the nuclei cannot absorb the energy. So the change in energy of the electron spin must be accompanied by the emission of a phonon.^{20–22} The electron-phonon interaction mixes, thus, different orbital states via a deformation potential in this process, while the spin flip is provided by the HC. This is the dominant process at zero applied magnetic field. A second relaxation channel is through spin-orbit (SO) coupling. SO coupling mixes differ-

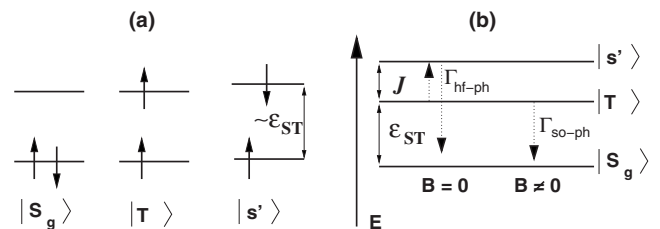


FIG. 1. (a) Level scheme for a doubly occupied silicon QD: the ground singlet involves only one orbital, whereas an additional orbital is needed to form the triplet and higher states, increasing the level separation. (b) Dominant processes in the quantum dot. The two rates indicated are the combined hyperfine and phonon rates, $\Gamma_{\text{hf-ph}}$, and the combined spin-orbit and phonon rates, $\Gamma_{\text{so-ph}}$. The energy separation of the ground-state singlet and first triplet is denoted by $\epsilon_{ST}=E_T-E_{S_g}$, and the exchange splitting by J .

ent spin states through the *Rashba* SO coupling.²³ This leads to a nonvanishing matrix element for the phonon-assisted transition between a singlet and a triplet state *in the absence of time-reversal symmetry* (right of Fig. 1), leading to an increase in the relaxation rate Γ_{ST} as the field is increased. Our aim here is to compute the singlet-triplet relaxation rates due to these two mechanisms as a function of external field.

We outline the method in the following section, and justify the approximations that are made. We then present results and discussion.

II. METHOD AND RESULTS

We consider first the case of low fields. For reasons to be discussed below, we may neglect the spin-orbit coupling, and the Hamiltonian is written as $H_0 + \delta H$, where H_0 contains the confining potential of the QD and $\delta H = H_{hc} + H_{ph}$. Here, H_{ph} corresponds to the electron-phonon coupling (which conserves spin), and H_{hc} is the hyperfine coupling that causes spin mixing in the dot. The confining potential is taken as parabolic with circular symmetry. We do not consider the Coulomb interaction explicitly in the Hamiltonian, as was done, for example, by Golovach *et al.*,¹⁷ whose main interest was in the regime close to the singlet-triplet crossing. Instead, the interaction is included phenomenologically through a parameter J , which denotes the singlet-triplet splitting. This is a crude form of mean field theory, but is reasonable as long as we are far from the singlet-triplet crossing point. Far from this point, there are no energy denominators that depend sensitively on the interaction strength, and matrix elements depend smoothly on the strength.

For the purpose of this paper (QD formed in a biaxially strained quantum well grown along the z axis), we consider the lowest electric subband, so that the wave function $\chi(z)$ in the z direction is fixed. We utilize the Fock–Darwin states for the lateral dimensions $\phi^{(n,m)}(x,y)$ to construct our wave functions, $\{\Psi_i\}$, that diagonalize H_0 . For these states, orbital and spin degrees of freedom factorize: $|\Psi_{S_g}\rangle = \chi(z) \times [|1\rangle|1\rangle] \otimes |S\rangle$, $|\Psi_T\rangle = \chi(z) \times [|1\rangle|2\rangle - |2\rangle|1\rangle] / \sqrt{2} \otimes |T\rangle$, and $|\Psi_{S'}\rangle = \chi(z) \times [|1\rangle|2\rangle + |2\rangle|1\rangle] / \sqrt{2} \otimes |S\rangle$. Here, $|S\rangle \equiv [|\uparrow\downarrow\rangle - |\downarrow\uparrow\rangle] / \sqrt{2}$ and $|T^{+,0,-}\rangle \equiv [|\uparrow\uparrow\rangle; (|\uparrow\downarrow\rangle + |\downarrow\uparrow\rangle) / \sqrt{2}; |\downarrow\downarrow\rangle]$ denote spin states, $|1\rangle \equiv \phi^{(0,0)}(r)$ and $|2\rangle \equiv \phi^{(0,\pm 1)}(r)$, so $|1\rangle|2\rangle \equiv \phi^{(0,0)}(r_1)\phi^{(0,\pm 1)}(r_2)$. The electron-electron interaction is taken into account through the parameter J . The amplitude of a transition between the triplet $|\Psi_T\rangle$ and singlet $|\Psi_{S_g}\rangle$ ground state via an excited $|\Psi_{S'}\rangle$ state is given in second-order perturbation theory,

$$\langle \Psi_{S_g} | \delta H | \Psi_T \rangle \approx \frac{\langle \Psi_{S_g} | H_{ph} | \Psi_{S'} \rangle \langle \Psi_{S'} | H_{hc} | \Psi_T \rangle}{E_T - E_{S'}}. \quad (1)$$

The transition rate from $|\Psi_T\rangle$ to $|\Psi_{S_g}\rangle$ is then given by Fermi's golden rule:

$$\Gamma_{ST} = \frac{2\pi}{\hbar} |\langle \Psi_{S_g}^f | \delta H | \Psi_T^i \rangle_{av}|^2 \delta(E_i - E_f). \quad (2)$$

In this notation, $|\Psi_T^i\rangle$ denotes the initial state of electron, nuclei, and phonons, $|\Psi_T^i\rangle \equiv |\Psi_T\rangle \otimes |i_n\rangle \otimes |i_{ph}\rangle$; likewise,

$|\Psi_{S_g}^f\rangle \equiv |\Psi_{S_g}\rangle \otimes |f_n\rangle \otimes |f_{ph}\rangle$. The *av* subscript indicates that the initial states of the nuclear and phonon systems are averaged over thermal ensembles, and that the final states of these systems are summed over. In this paper, we take the temperature to be 100 mK, as this is roughly the temperature at which experiments are done. The chief approximations involved in the calculation are the use of second-order perturbation theory and the truncation of the Hilbert space to just two singlet states and one triplet state. The first approximation is excellent—the rates turn out to be on the order of seconds; at those time scales, the Born–Markov approximation implicit in golden-rule calculations is surely valid—the time scales in the bath are probably of the order of the time for a phonon to traverse the dot. The validity of the second approximation is less clear—in high-symmetry dots such as we are considering here, the phonons do not couple to highly excited states in the dipole approximation, but real dots may be more disordered.

For silicon under compressive stress along [001], the electron interacts with a phonon of momentum \mathbf{q} via deformation potentials^{5,24,25} so the Hamiltonian reads

$$H_{ph} = \sum_{s,\mathbf{q}} i [a_{qs}^* e^{-i\mathbf{q}\cdot\mathbf{r}} + a_{qs} e^{i\mathbf{q}\cdot\mathbf{r}}] q [\Xi_d \hat{e}_x^s \hat{q}_x + \Xi_d \hat{e}_y^s \hat{q}_y + (\Xi_d + \Xi_u) \hat{e}_z^s \hat{q}_z], \quad (3)$$

where $\langle n_q - 1 | a_q | n_q \rangle = \sqrt{\hbar n_q / 2 M_c \omega_q}$, M_c is the mass of the unit cell, n_q is the phonon occupation number, and $\hbar \omega_q$ is the phonon energy. Here, s denotes the polarization of the phonon (two transverse and one longitudinal), \mathbf{q} is the wave vector, and Ξ_u and Ξ_d are the electron-phonon coupling parameters. This is slightly simpler than the corresponding Hamiltonian in GaAs because of the absence of the piezoelectric coupling in (centrosymmetric) Si.

Next, we evaluate the spin-flip matrix element given by $\langle \Psi_{S'} | H_{hc} | \Psi_T \rangle$, which is provided, at low magnetic fields, by the bath of nuclear spins of the ²⁹Si isotope.¹⁸ Accordingly, we consider a contact Hamiltonian,

$$\hat{H}_{hc} = \sum_{i,j} \frac{4\mu_0}{3I} \mu_B \mu_I \eta \mathbf{S}_i \cdot \mathbf{I}_j \delta(\mathbf{r}_i - \mathbf{R}_j) = A \sum_{i,j} \mathbf{S}_i \cdot \mathbf{I}_j \delta(\mathbf{r}_i - \mathbf{R}_j), \quad (4)$$

where \mathbf{S}_i (\mathbf{I}_j) and \mathbf{r}_i (\mathbf{R}_j) denote the spin and position of the i th electron (j th nuclei), and η and A are hyperfine coupling constants. Inserting Eqs. (4) and (3) into Eq. (2), we get an expression for the singlet-triplet rate:

$$\Gamma_{ST} = \Gamma_{ph} \left(\frac{A}{2J} \right)^2 \sum_{i,j} [| \langle T | [S_i^+ I_j \delta(\mathbf{r}_i - \mathbf{R}_j)] | S' \rangle |^2]. \quad (5)$$

Γ_{ph} describes the phonon rate derived from Eq. (3) and mixes the different orbitals contained in $|S'\rangle$ and $|S_g\rangle$. We use the electric dipole approximation ($e^{\pm i\mathbf{q}\cdot\mathbf{r}} \approx 1 \pm i\mathbf{q}\cdot\mathbf{r}$) in Eq. (3) which is valid for the range of energies considered here [$\sim 200 \mu\text{eV}$ (Ref. 1)],

$$\begin{aligned} \Gamma_{\text{ph}} \approx & \frac{(n_q + 1)}{2\rho_{\text{Si}}(2\pi)^2} \sum_s \int d\Omega \int_0^\infty \frac{dq q^6}{\omega_q} [\Xi_d \hat{e}_x^s \hat{q}_x \\ & + \Xi_d \hat{e}_y^s \hat{q}_y + (\Xi_d + \Xi_u) \hat{e}_z^s \hat{q}_z]^2 [|\langle s' | x | S_g \rangle|^2 (\hat{e}_x^s)^2 \\ & + |\langle s' | y | S_g \rangle|^2 (\hat{e}_y^s)^2 + |\langle s' | z | S_g \rangle|^2 (\hat{e}_z^s)^2] \delta[\hbar\omega - (J + \epsilon_{\text{ST}})]. \end{aligned} \quad (6)$$

To evaluate the integral over momenta of Eq. (6), we assume an isotropic phonon spectrum, $E_{\text{ph}} = \hbar\omega_{qs}$, and a linear dispersion relation, $\omega_{qs} = v_s q$, where v_s is being the sound velocity of the mode s .

The sum over j of Eq. (5) can be transformed to an integral by introducing C_n as the volume density of ^{29}Si nuclei, resulting in a compact expression for triplet-singlet relaxation:

$$\begin{aligned} \Gamma_{\text{ST}} \approx & \left(\frac{A}{2J}\right)^2 C_n \left(\int d^3R_j [|\phi^{(0,0)}(R_j)|^2 \right. \\ & \left. - |\phi^{(0,\pm 1)}(R_j)|^2] \right) \frac{1}{2\rho_{\text{Si}}\hbar} \left(\frac{J + \epsilon_{\text{ST}}}{\hbar}\right)^5 \sum_{i,s} \frac{\gamma_{si} \langle X_i^2 \rangle}{v_s^7}, \end{aligned} \quad (7)$$

where γ_{si} contains the result of the angular integral which depends on the mode s along the coordinate i : $\gamma_{ix} = \gamma_{iy} = 4\pi[(\Xi_d^2/3) + (2\Xi_d\Xi_u/15) + (\Xi_u^2/35)]$, $\gamma_{iz} = 4\pi[(\Xi_d^2/3) + (\Xi_d\Xi_u/5) + (\Xi_u^2/7)]$, $\gamma_{ix} = \gamma_{iy} = 4\pi\Xi_u^2/35$, and $\gamma_{iz} = 4\pi\Xi_u^2/70$.

It is important to note that Γ_{ST} is proportional to C_n , i.e., to the total number of nuclei N_n with which the electrons interact. This is consistent with the simple picture that the relaxation rate is proportional to the mean-square fluctuations in the random hyperfine field. Formulas for spin relaxation rates due to hyperfine coupling that give an apparent proportionality to $N_n^{-1/2}$ are common in the literature, and have given rise to the incorrect notion that some sort of motional narrowing is at work. This is not possible, since the fluctuations in the nuclear spin system are slow. In any case, the rate must vanish as $N_n \rightarrow 0$. These formulas are correct, but they generally involve other parameters that actually vary with N_n .

Figure 2 represents $T_{\text{ST}} = \Gamma_{\text{ST}}^{-1}$ obtained as described in Eq. (7), as a function of the level separation, $J = E_{s'} - E_T$ for a given ϵ_{ST} . In the case of Si, $\eta = 186$,²⁶ yielding $A \approx 2 \times 10^{-7} \text{eV nm}^3$. Only about 4% of the nuclei have spin, so $C_n \approx 0.04(8/v_0) \approx 2 \text{ nm}^{-3}$ ($v_0 \approx 0.17 \text{ nm}^3$). Other parameters used are $\Xi_u = 9.29 \text{ eV}$, $\Xi_d = -10.7 \text{ eV}$, $\rho_i = 2330 \text{ kg m}^{-3}$, $v_l = 9330 \text{ ms}^{-1}$, $v_t = 5420 \text{ ms}^{-1}$, and $\epsilon_{\text{ST}} = 200 \mu\text{eV}$. At small J , T_{ST} increases as a function of J : the triplet $|T_{\pm,0}\rangle$ and singlet $|S'\rangle$ levels are strongly mixed by the hyperfine interaction, and the phonon density of states increases as a function of level separations. In the limit $J=0$, the rate is given by phonon emission, which we found to be of the order of 10^{12} s^{-1} . Thus, T_{ST} appears very small as $J \rightarrow 0$ in Fig. 2, but it is not zero. At large J , spin mixing is lessened because there is an energy denominator, and phonon relaxation is then suppressed by spin conservation.

The calculations are obviously consistent with the observed lower bound of $T_{\text{ST}} > 15 \mu\text{s}$ given in Ref. 1. It is

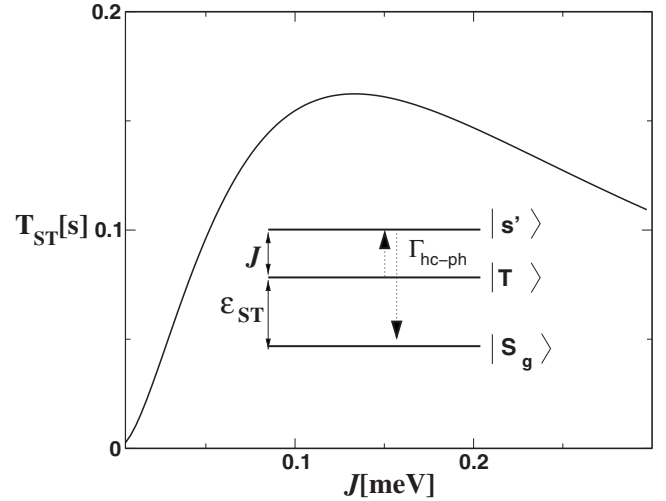


FIG. 2. T_{ST} as a function of J for the process depicted in the inset: when levels $|T\rangle$ and $|s'\rangle$ are close in energy ($J \rightarrow 0$), the process is dominated by hyperfine coupling (fast), and as this energy splits, the process is dominated by the phonon emission, J (Ref. 5). For higher energies, the dipole approximation breaks down (Ref. 27).

expected that more stringent bounds, hopefully also upper bounds, will be available soon.

We now move to the case of finite applied magnetic field B . We first take the field along the growth direction [perpendicular to the two-dimensional electron gas (2DEG)]: $\vec{B} = B\hat{z}$. This allows a direct $T \rightarrow S$ transition to occur in the presence of a Rashba SO coupling.²⁸ The Rashba field is a consequence of structural inversion asymmetry²³ in the heterostructure. Note that no bulk inversion asymmetry (BIA) needs to be considered in a centrosymmetric crystal like Si. The SO Hamiltonian due to the full confining potential for the device considered here, where $l_\alpha/r_{\text{QD}} \gg 1$, l_α being the Data-Das device length,³⁰ is then given by²⁹

$$H^{\text{SO}} = \alpha(\vec{\sigma} \times \vec{p})_z. \quad (8)$$

H^{SO} mixes the spin states $|S_g\rangle$ and $|T^\pm\rangle$, and the orbital wave functions as well, so virtual transition to a higher state $|s'\rangle$ is no longer needed and we have

$$\langle S_g | \delta H_{\text{SO}} | T^\pm \rangle \approx \frac{\langle i_{\text{ph}} | H_{\text{ph}} | f_{\text{ph}} \rangle \langle S_g | H^{\text{SO}} | T^\pm \rangle}{\epsilon_{\text{ST}} + \Delta^\pm}, \quad \Delta^\pm = \pm g\mu_B B. \quad (9)$$

Here, the phonon just ensures energy conservation. Notice that $\langle S_g | \delta H_{\text{SO}} | T \rangle$ is zero if $B=0$. This ‘‘Van Vleck cancellation’’ has been known for decades,^{31,32} but has been clarified in recent years,³⁴ particularly by performing a spin-dependent unitary transformation in which the first-order term in α is eliminated.³³ In explicit calculations in the original basis, the cancellation occurs due to the fact that the admixture of T^+ and T^- is equivalent in magnitude but opposite in sign. The key point is that spin-orbit-induced transition rates are always proportional to B^2 (or higher powers of B in the case of spin 1/2 dots).⁵

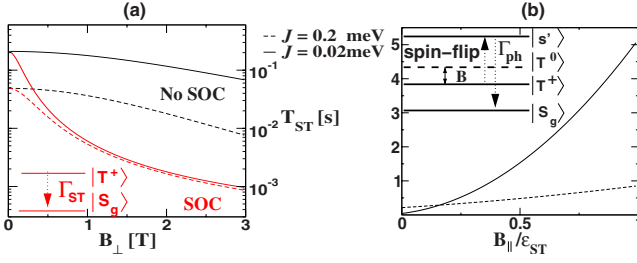


FIG. 3. (Color online) T_{ST} as a function of B for two values of J : The solid lines correspond to a plausible value of $J=0.02$ meV and the broken lines to $J=\epsilon_{ST}=0.2$ meV for comparison, (a) as a function of B_{\parallel} and (b) as a function of B_{\perp} , including Rashba (red) and without Rashba (black). T_{ST} increases with B_{\parallel} and decreases with B_{\perp} .

Proceeding as in Eqs. (1)–(5), we find the rate for the direct transition:

$$\Gamma_{ST}^D = \Gamma_{ph}^D \left| \sum_{i=\pm} \frac{\langle S_g | H^{SO} | T^i \rangle}{\epsilon_{ST} + \Delta^i} \right|^2.$$

Note that for $B=0$, Γ_{ST}^D vanishes. Since the phonon does not mix different orbitals in zeroth order in the multipole expansion to zeroth order (i.e., $e^{\pm iqr} \approx 1$), Γ_{ph}^D now reads

$$\Gamma_{ph}^D \approx \frac{(n_q + 1)}{2\rho_{Si}(2\pi)^2} \sum_s \int d\Omega \int_0^{\infty} \frac{dq q^4}{\omega_q} [\Xi_d \hat{e}_x^s \hat{q}_x + \Xi_d \hat{e}_y^s \hat{q}_y + (\Xi_d + \Xi_u) \hat{e}_z^s \hat{q}_z]^2 \delta(\hbar\omega - \epsilon_{ST}). \quad (10)$$

Inserting Eq. (9) into Eq. (2) and evaluating Eq. (10), we get the spin-orbit-induced relaxation rate, which is quadratic in B and α , in agreement with earlier treatments:⁴

$$\Gamma_{ST}^D \approx \left(\frac{4\Delta m \alpha}{\hbar^3} \right)^2 \langle r^2 \rangle \sum_s \frac{\gamma_s}{v_s^5}, \quad (11)$$

with $\gamma_l = 4\pi[\Xi_d^2 + (\Xi_d \Xi_u/2) + (\Xi_u^2/5)]$ and $\gamma_t = 4\pi[(\Xi_d^2/5) + (4\Xi_d \Xi_u/15) + (2\Xi_u^2/15)]$. Here, we use $\alpha \approx 50$ m/s, following Ref. 5 and adapting the result to an electric field of 10^{-7} V/m, an estimate for E_z for a QD with a 2DEG density of $\sim 4 \times 10^{11}$ cm⁻³. (One should note, however, that this value of α is very uncertain.) Figure 3(a) shows in black the relaxation in the absence of the Rashba coupling ($\alpha=0$), and in red the relaxation with the additional Γ_{ST}^D ($\Gamma_{ST} + \Gamma_{ST}^D$). We plot the results for two values of J . For $\alpha=0$, T_{ST} is a relatively weak function of J , since the hyperfine interaction is not very sensitive to field. At finite α , B_{\perp} activates the mixing and T_{ST} decreases rapidly.

If the magnetic field B_{\parallel} is parallel to the 2DEG, the only effect is that the spin splitting increases, and larger relaxation times are obtained [Fig. 3(b)], as this increases, on average, the energy separation $E_{|T^{\pm}\rangle} - E_{|S_g\rangle}$ (see diagram). In contrast, the perpendicular magnetic field B_{\perp} decreases the relaxation time, as we have seen. This anisotropy in applied field of T_{ST} would be a critical signature of the spin-orbit effect. We compare our result for a $B_{\parallel}=0.02$ T ($T_{ST} \approx 500$ ms) to the

experimental value obtained for GaAs [2.6 ms (Ref. 10)] and find that Si has a singlet-triplet relaxation time more than 2 orders of magnitude larger than GaAs.

Note that the behavior of T_{ST} here is different to the much studied GaAs-based devices^{4,12,16} because of the nature of spin-orbit coupling and electron-phonon coupling in noncentrosymmetric materials: The BIA is absent and there are no piezophonons; also, avoided crossings of the singlet and triplet energy levels do not occur for the magnetic fields considered here, giving a monotonous behavior.

III. DISCUSSION

There are several ways to measure Γ_{ST} . In single-dot systems, this can be realized using a single pulse.⁹ Alternatively, one may use the following sequence: in the first phase, the state can be prepared so that only one electron is present in the QD, and in the next phase, the triplet would be available for conductance, unless it relaxes to the singlet. Measurement of the current for different values of the pulse duration then gives a direct method to determine Γ_{ST} . The latter experiment has been performed in GaAs.¹² In double-dot experiments, Γ_{ST} is one of the parameters in the rate equations that determine the measured current, so these experiments also provide an avenue for the determination of the singlet-triplet lifetime.¹

One should note immediately that T_{ST} is considerably longer in natural Si than in GaAs, generally by orders of magnitude. This is expected in a system with weaker spin-orbit coupling and fewer spinful nuclei. The times we find are of the order of seconds for the most part. It is possible to reduce the time by applying a perpendicular field, which can serve as a very useful diagnostic. It is also possible to lengthen T_{ST} by the use of isotopically enriched Si, i.e., pure ²⁸Si. This would eliminate the hyperfine mechanism, but it would not get rid of spin relaxation entirely, as higher-order effects of spin-orbit coupling are still present even at $B=0$. However, these effects are quite small in Si. It seems likely that other effects such as flux noise will be the limiting factor in isotopically enriched Si.

In summary, we have calculated the dominant rates for phonon-assisted triplet-singlet relaxation of a silicon quantum dot. T_{ST} is found to be of the order of hundreds of milliseconds, very sensitive to the exchange energy J , and even longer in the presence of a B_{\parallel} , of seconds. In the presence of a B_{\perp} , a direct transition becomes possible, increasing (decreasing) Γ_{ST} (T_{ST}). Due to weak spin-orbit and hyperfine coupling, silicon offers very long coherence times, which are required for solid state qubits.

ACKNOWLEDGMENTS

We gratefully acknowledge conversations with M. Friesen, S. N. Coppersmith, A. Vorontsov, M. G. Vavilov, and M. A. Eriksson. We acknowledge financial support from the Spanish Ministry of Education and Science (MEC), from NSA and ARDA under ARO Contract No. W911NF-04-1-0389, and from the National Science Foundation through the ITR (DMR-0325634) and EMT (CCF-0523675) programs.

- ¹N. Shaji, C. B. Simmons, M. Thalakulam, L. J. Klein, H. Qin, H. Luo, D. E. Savage, M. G. Lagally, A. J. Rimberg, R. Joynt, M. Friesen, R. H. Blick, S. N. Coppersmith, and M. A. Eriksson, arXiv:0708.0794 (unpublished).
- ²A. V. Khaetskii and Y. V. Nazarov, Phys. Rev. B **64**, 125316 (2001).
- ³L. M. Woods, T. L. Reinecke, and Y. Lyanda-Geller, Phys. Rev. B **66**, 161318(R) (2002).
- ⁴V. N. Golovach, A. Khaetskii, and D. Loss, Phys. Rev. Lett. **93**, 016601 (2004).
- ⁵C. Tahan, M. Friesen, and R. Joynt, Phys. Rev. B **66**, 035314 (2002).
- ⁶J. M. Elzerman, R. Hanson, L. H. Willems van Beveren, B. Witkamp, L. M. K. Vandersypen, and L. P. Kouwenhoven, Nature (London) **430**, 431 (2004).
- ⁷S. Amasha, K. MacLean, Iuliana Radu, D. M. Zumbuhl, M. A. Kastner, M. P. Hanson, and A. C. Gossard, arXiv: cond-mat/0607110 (unpublished).
- ⁸J. R. Petta, A. C. Johnson, J. M. Taylor, E. A. Laird, A. Yacoby, M. D. Lukin, C. M. Marcus, M. P. Hanson, and A. C. Gossard, Science **309**, 2180 (2005).
- ⁹T. Fujisawa, D. G. Austing, Y. Tokura, Y. Hirayama, and S. Tarucha, Nature (London) **419**, 276 (2002).
- ¹⁰R. Hanson, L. H. Willems van Beveren, I. T. Vink, J. M. Elzerman, W. J. M. Naber, F. H. L. Koppens, L. P. Kouwenhoven, and L. M. K. Vandersypen, Phys. Rev. Lett. **94**, 196802 (2005).
- ¹¹S. Sasaki, T. Fujisawa, T. Hayashi, and Y. Hirayama, Phys. Rev. Lett. **95**, 056803 (2005).
- ¹²T. Meunier, I. T. Vink, L. H. Willems van Beveren, K. J. Tielrooij, R. Hanson, F. H. L. Koppens, H. P. Tranitz, W. Wegscheider, L. P. Kouwenhoven, and L. M. K. Vandersypen, Phys. Rev. Lett. **98**, 126601 (2007).
- ¹³S. Dickmann and P. Hawrylak, J. Supercond. **16**, 387 (2003).
- ¹⁴M. Florescu and P. Hawrylak, Phys. Rev. B **73**, 045304 (2006).
- ¹⁵D. Chaney and P. A. Maksym, Phys. Rev. B **75**, 035323 (2007).
- ¹⁶J. I. Climente, A. Bertoni, G. Goldoni, M. Rontani, and E. Molinari, Phys. Rev. B **75**, 081303(R) (2007); **76**, 085305 (2007).
- ¹⁷V. N. Golovach, A. Khaetskii, and D. Loss, Phys. Rev. B **77**, 045328 (2008).
- ¹⁸S. Saykin, D. Mozysky, and V. Privman, Nano Lett. **2**, 651 (2002).
- ¹⁹A. Khaetskii, D. Loss, and L. Glazman, Phys. Rev. B **67**, 195329 (2003).
- ²⁰S. I. Erlingsson, Y. V. Nazarov, and V. I. Fal'ko, Phys. Rev. B **64**, 195306 (2001).
- ²¹A. V. Khaetskii and Y. V. Nazarov, Phys. Rev. B **61**, 12639 (2000).
- ²²V. A. Abalmassov and F. Marquardt, Phys. Rev. B **70**, 075313 (2004).
- ²³R. Winkler, *Spin-Orbit Coupling Effects in Two-Dimensional Electron and Hole Systems*, edited by G. Höhler (Springer-Verlag, Berlin, 2003).
- ²⁴C. Herring and E. Vogt, Phys. Rev. **101**, 944 (1955).
- ²⁵H. Hasegawa, Phys. Rev. **118**, 1523 (1960).
- ²⁶R. G. Shulman and B. J. Wyluda, Phys. Rev. **103**, 1127 (1957).
- ²⁷C. Tahan, Ph.D. thesis, UWM, 2005.
- ²⁸C. Tahan and R. Joynt, Phys. Rev. B **71**, 075315 (2005).
- ²⁹C. F. Destefani, S. E. Ulloa, and G. E. Marques, Phys. Rev. B **69**, 125302 (2004).
- ³⁰S. Datta and B. Das, Appl. Phys. Lett. **56**, 665 (1990).
- ³¹E. Abrahams, Phys. Rev. **107**, 491 (1957).
- ³²J. H. Van Vleck, Phys. Rev. **57**, 426 (1940).
- ³³I. L. Aleiner and V. I. Fal'ko, Phys. Rev. Lett. **87**, 256801 (2001).
- ³⁴B. I. Halperin, A. Stern, Y. Oreg, J. N. H. J. Cremers, J. A. Folk, and C. M. Marcus, Phys. Rev. Lett. **86**, 2106 (2001).