



Magnetic order in quasi-two-dimensional molecular magnets investigated with muon-spin relaxation

A. J. Steele,¹ T. Lancaster,¹ S. J. Blundell,¹ P. J. Baker,² F. L. Pratt,² C. Baines,³ M. M. Conner,⁴ H. I. Southerland,⁴ J. L. Manson,⁴ and J. A. Schlueter⁵

¹*Oxford University Department of Physics, Clarendon Laboratory, Parks Road, Oxford OX1 3PU, United Kingdom*

²*ISIS Pulsed Neutron and Muon Source, STFC Rutherford Appleton Laboratory, Harwell Science and Innovation Campus, Didcot, Oxfordshire OX11 0QX, United Kingdom*

³*Paul Scherrer Institut, Laboratory for Muon-Spin Spectroscopy, CH-5232 Villigen PSI, Switzerland*

⁴*Department of Chemistry and Biochemistry, Eastern Washington University, Cheney, Washington 99004, USA*

⁵*Materials Science Division, Argonne National Laboratory, Argonne, Illinois 60439, USA*

(Received 15 April 2011; revised manuscript received 6 June 2011; published 19 August 2011)

We present the results of a muon-spin relaxation (μ^+ SR) investigation into magnetic ordering in several families of layered quasi-two-dimensional molecular antiferromagnets based on transition-metal ions such as $S = \frac{1}{2}$ Cu^{2+} bridged with organic ligands such as pyrazine. In many of these materials magnetic ordering is difficult to detect with conventional magnetic probes. In contrast, μ^+ SR allows us to identify ordering temperatures and study the critical behavior close to T_N . Combining this with measurements of in-plane magnetic exchange J and predictions from quantum Monte Carlo simulations we may assess the degree of isolation of the 2D layers through estimates of the effective inter-layer exchange coupling and in-layer correlation lengths at T_N . We also identify the likely metal-ion moment sizes and muon stopping sites in these materials, based on probabilistic analysis of the magnetic structures and of muon-fluorine dipole-dipole coupling in fluorinated materials.

DOI: [10.1103/PhysRevB.84.064412](https://doi.org/10.1103/PhysRevB.84.064412)

PACS number(s): 76.75.+i, 75.50.Xx, 75.10.Jm, 75.50.Ee

I. INTRODUCTION

The $S = \frac{1}{2}$ two-dimensional square-lattice quantum Heisenberg antiferromagnet (2DSLQHA) continues to be one of the most important theoretical models in condensed matter physics.¹ Experimental realizations of the 2DSLQHA in crystals also contain an interaction between planes, so that the relevant model describing the coupling of electronic spins S_i gives rise to the Hamiltonian²

$$\mathcal{H} = J \sum_{\langle i,j \rangle_{xy}} \mathbf{S}_i \cdot \mathbf{S}_j + J_{\perp} \sum_{\langle i,j \rangle_z} \mathbf{S}_i \cdot \mathbf{S}_j, \quad (1)$$

where J (J_{\perp}) is the strength of the in- (inter-) plane coupling and the first (second) summation is over neighbors parallel (perpendicular) to the 2D xy plane. Any 2D model ($J_{\perp} = 0$) with continuous symmetry will not show long-range magnetic order (LRO) for $T > 0$ due to a divergence of infrared fluctuations.^{3,4} However, layered systems approximating 2D models ($J_{\perp} \neq 0$) will inevitably enjoy some degree of inter-layer coupling and this will lead to magnetic order, albeit at a reduced temperature due to the influence of quantum fluctuations. Quantum fluctuations are also predicted to reduce the value of the magnetic moment in the ground state of the 2DSLQHA to around 60% of its classical value,¹ and this reduction is often seen in the ordered moments of real materials. In layered materials that approximate the 2DSLQHA, the measurement of the antiferromagnetic ordering temperature T_N is often problematic due not only to this reduction of the magnetic moment, but also to short-range correlations that build up in the quasi-2D layers above T_N . These correlations lead to a reduction in the size of the entropy change that accompanies the phase transition, reducing the size of the anomaly in the measured specific heat.⁵ We have shown in a number of previous cases that muon-spin relaxation (μ^+ SR) measurements do not suffer from these effects and therefore represent an effective method for detecting magnetic order in complex anisotropic systems.⁶⁻⁹

The rich chemistry of molecular materials allows for the design and synthesis of a wide variety of highly tunable magnetic model systems.¹⁰ Magnetic centers, exchange paths, and the surrounding molecular groups can all be systematically modified, allowing investigation of their effects on magnetic behavior. In particular, the existence of different exchange paths along different spatial directions can result in quasi-low-dimensional magnetic behavior (i.e., systems with magnetic interactions constrained to act in a two-dimensional plane or along a one-dimensional chain). Such systems have the potential to better approximate low-dimensional models than many traditional inorganic materials. In addition, these molecular materials can have exchange energy scales of order $J/k_B \sim 10$ K which are accessible with typical laboratory magnetic fields⁷ of $B \sim 10$ T allowing an additional avenue for their experimental study. This contrasts with typical inorganic low-dimensional systems where the exchange is found to be $J/k_B \sim 1000$ K and fields of $B \sim 1000$ T would be needed to significantly perturb the spin system.

It has also been shown^{11,12} that a small XY -like anisotropy exists in some molecular materials. Although J_{\perp} is the decisive energy scale for the magnetic ordering, this anisotropy has been shown to have an influence on the ordering temperature¹¹ and determines the shape of the low-field B - T phase diagram of these systems.¹²

Several classes of molecular magnetic material closely approximate the 2DSLQHA model and in this paper we report the results of μ^+ SR measurements performed on several such materials. These systems are self-assembled coordination polymers, based around paramagnetic ions such as Cu^{2+} , linked by neutral bridging ligands and coordinating anion molecules. Our materials are based on combinations of three different ligands: (i) pyrazine ($\text{N}_2\text{C}_4\text{H}_4$, abbreviated pyz) and (ii) pyridine- N -oxide ($\text{C}_5\text{H}_5\text{NO}$, abbreviated pyo), both of which are planar rings; and (iii) the linear bifluoride ion $[(\text{HF}_2)^-]$, which is bound by strong hydrogen bonds $\text{F}^{\cdots}\text{H}\cdots\text{F}$.

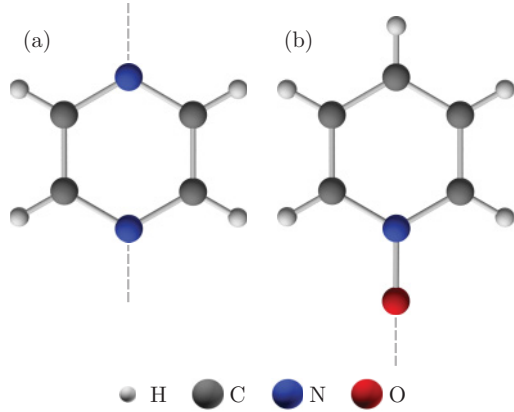


FIG. 1. (Color online) Bridging ligands used in the compounds described in this paper: (a) pyrazine ($\text{N}_2\text{C}_4\text{H}_4$, abbreviated pyz); and (b) pyridine-*N*-oxide ($\text{C}_5\text{H}_5\text{NO}$, abbreviated pyo). Dashed lines indicate where the ligands bond to other parts of molecular structures.

The pyz and pyo ligands are shown in Fig. 1. Specifically, we investigate the molecular system $[M(\text{HF}_2)(\text{pyz})_2]X$, where $M^{2+} = \text{Cu}^{2+}$ is the transition-metal cation and X^- is one of various anions (e.g., BF_4^- , ClO_4^- , PF_6^-). We also report the results of our measurements on other quasi-2D systems. First, $[\text{Cu}(\text{pyz})_2(\text{pyo})_2]Y_2$, with $Y^- = \text{BF}_4^-$ or PF_6^- , in which pyo ligands bridge $\text{Cu}(\text{pyz})_2$ planes. Then, the quasi-2D nonpolymeric compounds $[\text{Cu}(\text{pyo})_6]Z_2$, where $Z^- = \text{BF}_4^-$, ClO_3^- , or PF_6^- are examined. We also investigate materials in which either Ni^{2+} ($S = 1$) or Ag^{2+} ($S = \frac{1}{2}$) form the magnetic species in the quasi-2D planes rather than Cu^{2+} .

This paper is structured as follows. In Sec. II we outline the μ^+ SR technique and describe our experimental methods. The $[\text{Cu}(\text{HF}_2)(\text{pyz})_2]X$ family of materials is then discussed in Sec. III, where muon data are used to determine T_N and critical parameters. Muon-fluorine dipole-dipole oscillations in the paramagnetic regime are found for these materials which we use, in conjunction with dipole field simulations, to investigate possible muon sites and constrain the copper moment. In Sec. IV we explore the related 2D system $[\text{Cu}(\text{pyz})_2(\text{pyo})_2]Y_2$. Section V details measurements of $[\text{Cu}(\text{pyo})_6]Z_2$. Section VI examines a highly two-dimensional silver-based molecular material, $\text{Ag}(\text{pyz})_2(\text{S}_2\text{O}_8)$. Finally, data from the $[\text{Ni}(\text{HF}_2)(\text{pyz})_2]X$ ($X^- = \text{PF}_6^-$, SbF_6^-) family of molecular magnets is presented in Sec. VII.

II. EXPERIMENTAL DETAILS

Zero-field (ZF) μ^+ SR measurements were made on powder samples of the materials at the ISIS facility, Rutherford Appleton Laboratory, UK, using the MuSR and EMU instruments and the Swiss Muon Source (S μ S), Paul Scherrer Institut, Switzerland, using the General-Purpose Surface-Muon (GPS) instrument and Low-Temperature Facility (LTF). For measurements at temperatures $T \geq 1.8$ K powder samples were packed in a $25 \mu\text{m}$ Ag foil packet and mounted on a Ag backing plate. For measurements at $T < 1.8$ K the samples were mounted directly on an Ag plate and covered with a $12.5 \mu\text{m}$ Ag foil mask. Ag is used since it has only a small

nuclear magnetic moment, and so minimizes the background depolarization of the muon spin ensemble.

In a μ^+ SR experiment,¹³ spin-polarized positive muons are stopped in a target sample. The positive muons are attracted to areas of negative charge density and often stop at interstitial positions. The observed property of the experiment is the time evolution of the muon-spin polarization, the behavior of which depends on the local magnetic field at the muon site. Each muon decays with an average lifetime of $2.2 \mu\text{s}$ into two neutrinos and a positron, the latter particle being emitted preferentially along the instantaneous direction of the muon spin. Recording the time dependence of the positron emission directions therefore allows the determination of the spin polarization of the ensemble of muons. In our experiments, positrons are detected by detectors placed forward (F) and backward (B) of the initial muon polarization direction. Histograms $N_F(t)$ and $N_B(t)$ record the number of positrons detected in the two detectors as a function of time following the muon implantation. The quantity of interest is the decay positron asymmetry function, defined as

$$A(t) = \frac{N_F(t) - \alpha N_B(t)}{N_F(t) + \alpha N_B(t)}, \quad (2)$$

where α is an experimental calibration constant. The asymmetry $A(t)$ is proportional to the spin polarization of the muon ensemble.

A muon spin will precess around the local magnetic fields at its stopping site at a frequency $\nu = \gamma_\mu B / 2\pi$, where the muon gyromagnetic ratio $\gamma_\mu = 2\pi \times 135.5 \text{ MHz T}^{-1}$. In the presence of LRO in a material we often measure oscillations in $A(t)$. These result from a significant number of muons stopping at sites with a similar internal field, giving rise to a coherent precession of the ensemble of muon spins. Since the spins precess in local magnetic fields directed perpendicularly to the spin polarization direction, we would expect that for a powder sample with a static magnetic field distribution, $\frac{2}{3}$ of the total spin components should precess and the remaining $\frac{1}{3}$ should be nonrelaxing. The nonrelaxing third of muon-spin components give rise to the so-called $\frac{1}{3}$ tail in $A(t)$, whose presence therefore provides additional evidence for a static field distribution in powder sample. Taken together, these effects provide an unambiguous method for sensitively identifying a transition to LRO. An example of typical spectra above and below the magnetic ordering temperature is shown for $[\text{Cu}(\text{HF}_2)(\text{pyz})_2]\text{BF}_4$ in Fig. 2; the oscillations above T_N are characteristic of a quantum-entangled $F\mu$ state (see Sec. III D).

III. $[\text{Cu}(\text{HF}_2)(\text{pyz})_2]X$

The synthesis of the $[M(\text{HF}_2)(\text{pyz})_2]X$ system^{7,14,15} represented the first example of the use of a bifluoride building block to make a three-dimensional coordination polymer. This class of materials possesses a highly stable structure due to the exceptional strength of the bifluoride hydrogen bonds. The structure of the $[M(\text{HF}_2)(\text{pyz})_2]X$ system^{14,15} comprises infinite 2D $[M(\text{pyz})_2]^{2+}$ sheets which lie in the ab plane, with bifluoride ions $(\text{HF}_2)^-$ above and below the metal ions, acting as bridges between the planes to form a pseudocubic network. The X^- anions occupy the body-center positions within each

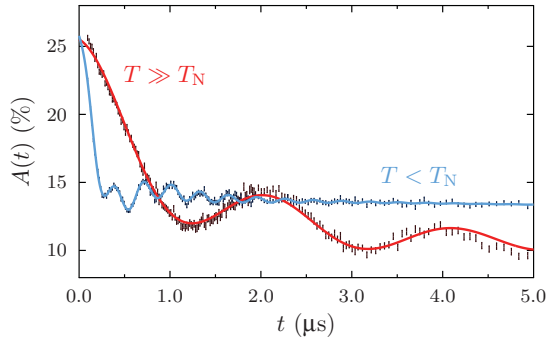


FIG. 2. (Color online) Example $A(t)$ spectra with fits above ($T = 25$ K) and below ($T = 0.35$ K) the magnetic transition temperature $T_N = 1.4$ K for $[\text{Cu}(\text{HF}_2)(\text{pyz})_2]\text{BF}_4$. Note the approximately equal initial asymmetry, and the oscillations and “ $\frac{1}{3}$ tail” observed in the ordered phase. The slow oscillation observed for $T > T_N$ is due to muon-fluorine dipole-dipole oscillations.

cubic pore. An example structure, for $[\text{Cu}(\text{HF}_2)(\text{pyz})_2]\text{PF}_6$, is shown in Fig. 3. Samples are produced in polycrystalline form via aqueous chemical reactions between MX_2 salts and stoichiometric amounts of ligands. Preparation details for the compounds are reported in Refs. 14–16.

In this section we consider those materials where the M cations are Cu^{2+} $3d^9$ $S = \frac{1}{2}$ centers. It is thought that the magnetic behavior of these materials results from the $3d_{x^2-y^2}$ orbital of the Cu at the center of each CuN_4F_2 octahedron lying in the CuN_4 plane so that the spin exchange interactions

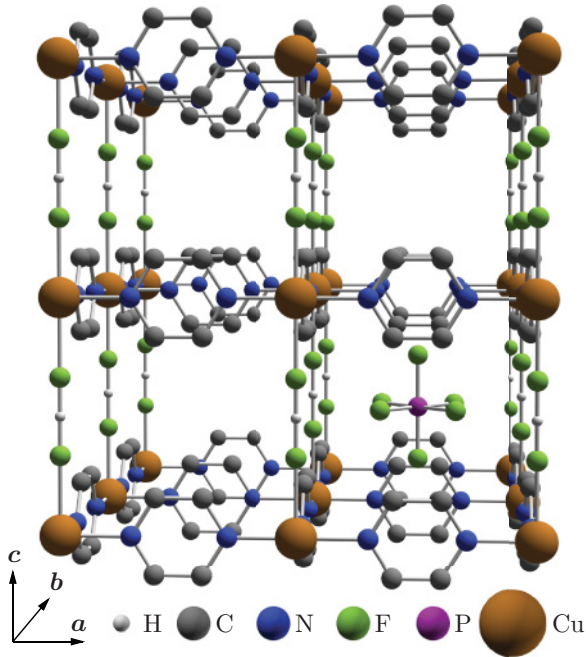


FIG. 3. (Color online) The structure of $[\text{Cu}(\text{HF}_2)(\text{pyz})_2]\text{PF}_6$, as an example of the $[\text{M}(\text{HF}_2)(\text{pyz})_2]\text{X}$ series. Copper ions are joined in a 2D square lattice by pyrazine ligands to form $\text{Cu}(\text{pyz})_2^{2+}$ sheets; the 2D layers are joined in the third dimension by HF_2^- groups, making a pseudocubic 3D structure; and this structure is stabilized by a PF_6^- anion at the center of each cubic pore. For clarity, hydrogen atoms attached to pyrazine rings have been omitted, and only one PF_6^- anion is shown.

between neighboring Cu^{2+} ions occur through the s -bonded pyz ligands.¹⁴ The interplane exchange through the HF_2 bridges connecting two Cu^{2+} ions should be very weak as these bridges lie on the fourfold rotational axis of the Cu $3d_{x^2-y^2}$ magnetic orbital, resulting in limited overlap with the fluorine p_z orbitals. Therefore to a first approximation, the magnetic properties of $[\text{M}(\text{HF}_2)(\text{pyz})_2]\text{X}$ can be described in terms of a 2D square lattice.

Measurements for $\text{X}^- = \text{BF}_4^-$, ClO_4^- , and SbF_6^- were made using the MuSR spectrometer at ISIS, while PF_6^- , AsF_6^- , NbF_6^- , and TaF_6^- were measured using GPS at PSI.

A. Long-range magnetic order

The main result of our measurements on these systems is that below a critical temperature T_N , oscillations in the asymmetry spectra $A(t)$ are observed at two distinct frequencies, for all materials in the series. This shows unambiguously that each of these materials undergoes a transition to a state of LRO. Example asymmetry spectra are shown in the left-hand column of Figs. 4 and 5. They were found to be best fitted with a relaxation function

$$A(t) = A_0[p_1 e^{-\lambda_1 t} \cos(2\pi \nu_1 t + \phi_1) + p_2 e^{-\lambda_2 t} \cos(2\pi P_2 \nu_1 t + \phi_2) + p_3 e^{-\lambda_3 t}] + A_{\text{bg}} e^{-\lambda_{\text{bg}} t}, \quad (3)$$

where A_0 represents the contribution from those muons which stop inside the sample and A_{bg} accounts for a relaxing background signal due to those muons that stop in the silver sample holder or cryostat tails, or with their spin parallel to the local field. Of those muons which stop in the sample, p_1 indicates the weighting of the component in an oscillating state with frequency ν_1 ; p_2 is the weighting of a lower frequency oscillating state with frequency ν_2 ; and p_3 represents the weighting of a component with a large relaxation rate λ_3 . All parameters were initially left free to vary. The second frequency was found to vary with temperature in fixed proportion to ν_1 via $\nu_2 = P_2 \nu_1$ for each material. The parameter P_2 was identified by fitting the lowest temperature $A(t)$ spectra where Eq. (3) would be expected to most accurately describe the data, and subsequently held fixed during the fitting procedure. Phase factors ϕ_i were also found to be necessary in some cases to obtain a reliable fit. The parameters resulting from these fits are listed in Table I, and data with fits are shown in Figs. 4 and 5. We also note here that the discontinuous nature of the change in all fitted parameters and the form of the spectra at T_N strongly suggest that these materials are magnetically ordered throughout their bulk.

The frequencies and relaxation rates as a function of temperature extracted from these fits are shown in the central column of Figs. 4 and 5. The muon precession frequency, which is proportional to the internal field in the material, can be considered an effective order parameter for the system. Consequently, fitting extracted frequencies as a function of temperature to the phenomenological function

$$\nu(T) = \nu(0) \left[1 - \left(\frac{T}{T_N} \right)^\alpha \right]^\beta \quad (4)$$

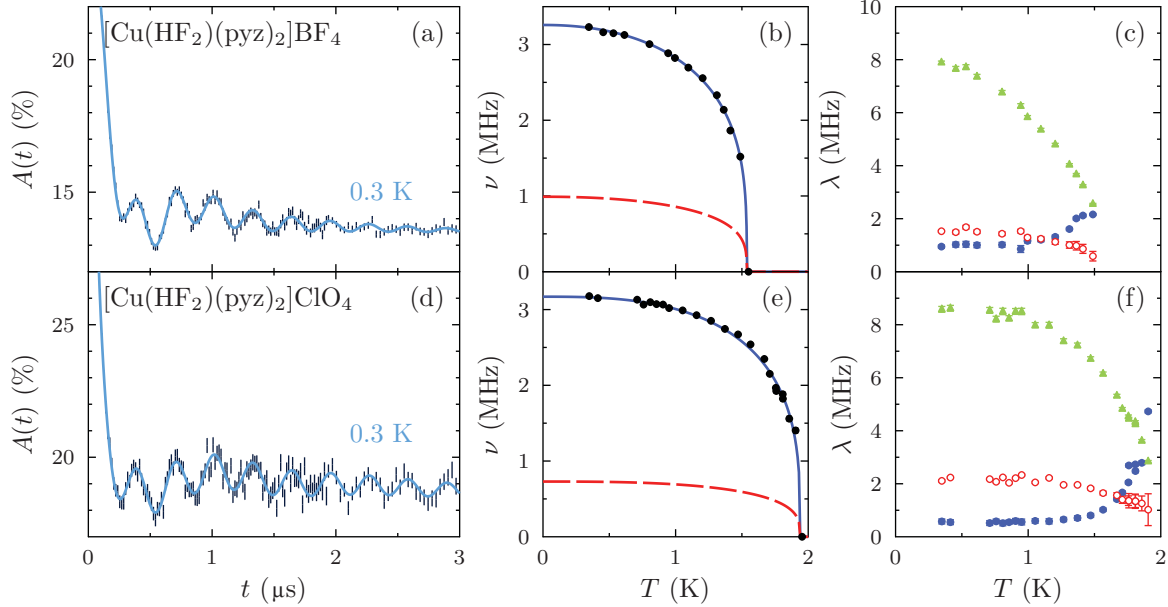


FIG. 4. (Color online) Data and the results of fits to Eq. (3) for $[\text{Cu}(\text{HF}_2)(\text{pyz})_2]\text{X}$ magnets with tetrahedral anions X^- . From left to right: (a) and (d) show sample asymmetry spectra $A(t)$ for $T < T_N$ along with a fit to Eq. (3); (b) and (e) show frequencies as a function of temperature [no data points are shown for the second line because this frequency ν_2 was held in fixed proportion to the first, ν_1 (see text)]; and (c) and (f) show relaxation rates λ_i as a function of temperature. In the $\nu(T)$ plot, error bars are included on the points but in most cases they are smaller than the marker being used. The solid line representing ν_1 in (b) and (e) corresponds to the filled circles in the third column of graphs [(c) and (f)] for that component's relaxation, λ_1 , while the dashed line and unfilled circles correspond to ν_2 and λ_2 , respectively. The filled triangles correspond to the fast relaxation λ_3 .

allows an estimate of the critical temperature and the exponent β to be extracted. Our results fit well with a previous observation⁷ that the compounds divide naturally into two classes: those with tetrahedral anions $\text{X}^- = \text{BF}_4^-, \text{ClO}_4^-$ and those with octahedral anions $\text{X}^- = \text{AF}_6^-$. The tetrahedral compounds have lower transition temperatures $T_N \lesssim 2$ K, as compared to the octahedral compounds' $T_N \gtrsim 4$ K; and the tetrahedral compounds also display slightly lower oscillation frequencies than their octahedral counterparts.⁷

This difference has been explained in terms of differences in the crystal structure between the two sets of compounds. First, the octahedral anions are larger than their tetrahedral counterparts. Second, the pyrazine rings are tilted by differing amounts with respect to the normal to the 2D layers: those in the octahedral compounds are significantly more upright. Since the Cu $3d_{x^2-y^2}$ orbitals point along the pyrazine directions, these tilting angles might be expected, to first order, to make little difference to nearest-neighbor exchange because such rotation is about a symmetry axis as viewed from the copper site. However, it may be that the different direction of the delocalized orbitals above and below the rings through which exchange probably occurs, possibly in conjunction with hybridization with the anion orbitals, results in an altered next-nearest neighbor or higher order interactions, changing the transition temperature.

Within the tetrahedral compounds, the difference in the weighting of the oscillatory component ($p_1 + p_2$) in $\text{X}^- = \text{BF}_4^-$ and ClO_4^- probably results from the difficulty in fitting the fast-relaxing component. Even with little change in the size of the oscillations, any error assigning the magnitude of

this component will affect the proportion of the $A(t)$ signal attributed to them. This difficulty is partly due to the resolution-limited nature of ISIS arising from the pulsed beam structure. In the octahedral compounds, we found that $\text{X}^- = \text{SbF}_6^-$ and TaF_6^- did not have a resolvable fast-relaxing component, and consequently p_3 was set to zero during the fitting procedure. This is reflected by dashes in the p_3 and λ_3 columns in Table I.

The fact that two oscillatory frequencies are observed points to the existence of at least two magnetically distinct classes of muon site. In general we find that $p_1 \approx p_2$ for these materials, making the probability of occupying the sites giving rise to magnetic precession approximately equal. The weightings $p_{1,2}$ were found to be significantly less than the weighting p_3 relating to the fast-relaxing site. This, in combination with the magnitude of the fast relaxation $\lambda_3(T=0) \gtrsim 10$ MHz, suggests that this term should not be identified with the $\frac{1}{3}$ tail which results from muons with spins parallel to their local field. [If that were the case then we would expect $(p_1 + p_2)/p_3 = 2$, which we do not observe.] It is likely that each of the components, p_1 , p_2 , and p_3 , therefore reflect the occurrence of a separate class of muon site in this system. We investigate the possible positions of these three classes of sites in Sec. III E.

The temperature evolution of the relaxation rates λ_i is shown in the right-hand columns of Figs. 4 and 5. In the fast-fluctuation limit, the relaxation rates are expected¹⁷ to vary as $\lambda \propto \Delta^2 \tau$, where $\Delta = \sqrt{\gamma_\mu^2 \langle (B - B_0)^2 \rangle}$ is the second moment of the local magnetic field distribution (whose mean is B_0) in frequency units, and τ is the correlation time. In

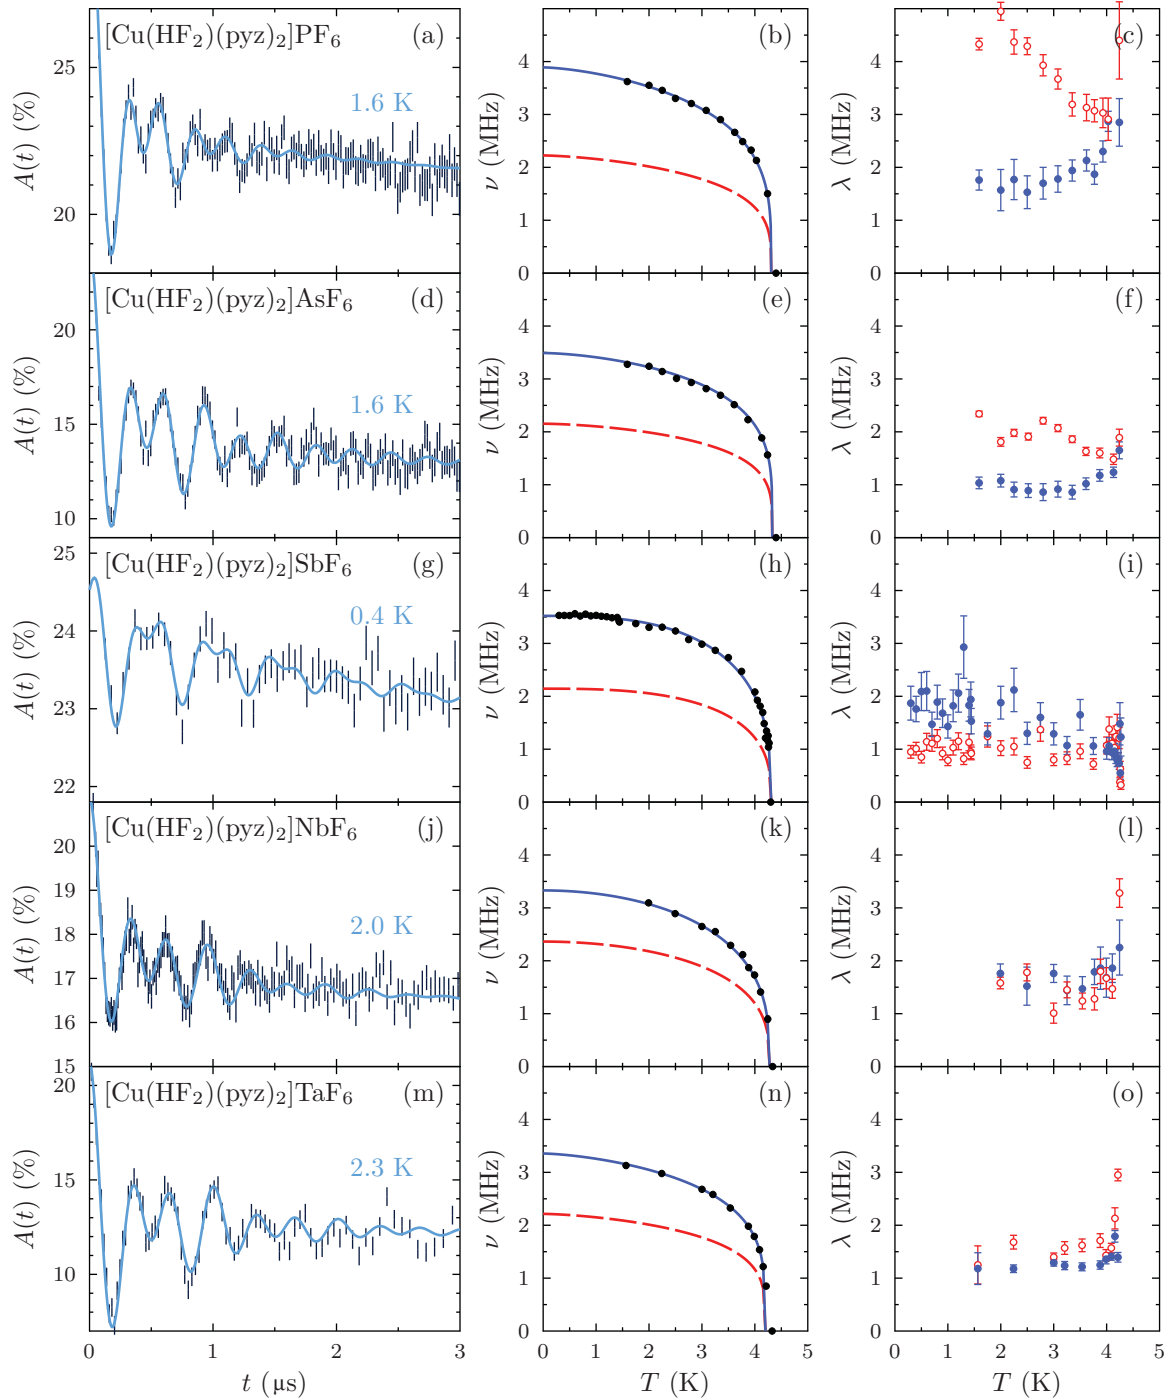


FIG. 5. (Color online) Example data and fits for $[\text{Cu}(\text{HF}_2)(\text{pyz})_2]X$ magnets with octahedral anions X^- . From left to right: (a), (d), (g), (j), and (m) show sample asymmetry spectra $A(t)$ for $T < T_N$ along with a fit to Eq. (3); (b), (e), (h), (k), and (n) show frequencies as a function of temperature [no data points are shown for the second line because this frequency ν_2 was held in fixed proportion to the first, ν_1 (see text)]; and (c), (f), (i), (l), and (o) show relaxation rates λ_i as a function of temperature. In the $\nu(T)$ plot, error bars are included on the points but in most cases they are smaller than the marker being used. The solid line representing ν_1 in (b), (e), (h), (k), and (n) corresponds to the filled circles in the third column of graphs [(c), (f), (i), (l), and (o)] for that component's relaxation, λ_1 , while the dashed line and unfilled circles correspond to ν_2 and λ_2 , respectively.

all measured materials, the relaxation rate λ_1 , corresponding to the higher oscillation frequency, starts at a small value at low temperature and increases as T_N is approached from below. This is the expected temperature-dependent behavior and most likely reflects a contribution from critical slowing

down of fluctuations near T_N (described, e.g., in Ref. 18). In contrast, the relaxation rate λ_2 (associated with the lower frequency) starts with a higher magnitude at low temperature and decreases smoothly as the temperature is increased. This is also the case for the relaxation rate λ_3 of the fast-relaxing

TABLE I. Fitted parameters for molecular magnets in the $[\text{Cu}(\text{HF}_2)(\text{pyz})_2]\text{X}$ family. The first parameters shown relate to fits to Eq. (3), which allow us to derive frequencies at $T = 0$, ν_i ; probabilities of stopping in the various classes of stopping site, p_i , in percent; and phases associated with fitting the oscillating components ϕ_i . Then, the temperature dependence of ν_i is fitted with Eq. (4), extracting values for the Néel temperature, T_N , critical exponent β , and parameter α . Finally, the quoted J/k_B is obtained from pulsed-field experiments,⁷ and the ratio of inter- to in-plane coupling, J_\perp/J , is obtained by combining T_N and J with formulas extracted from quantum Monte Carlo simulations (see Sec. III B, and Ref. 7). Dashes in the λ_3 column for the SbF_6 and TaF_6 compounds indicate that no fast-relaxing component was used to fit those data. Dashes in the J/k_B and J_\perp/J columns for NbF_6 and TaF_6 indicate a lack of pulsed-field data for these materials.

X	ν_1 (MHz)	ν_2 (MHz)	λ_3 (MHz)	p_1	p_2	p_3	ϕ_1 (°)	ϕ_2 (°)	T_N (K)	β	α	J/k_B (K)	$ J_\perp/J $
BF_4	3.30(6)	0.95(3)	8	15	15	70	-57(1)	26(2)	1.54(2)	0.18(4)	1.6(7)	6.3	9×10^{-4}
ClO_4	3.2(1)	0.64(1)	8	2	2	96	-94(1)	104(4)	1.91(1)	0.25(2)	2.6(3)	7.3	2×10^{-3}
PF_6	3.89(6)	2.23(5)	25	30	30	40	-53(3)	37(6)	4.37(2)	0.26(2)	1.5(3)	12.4	1×10^{-2}
AsF_6	3.49(9)	2.15(2)	40	25	25	50	-14(2)	14(3)	4.32(3)	0.23(3)	1.6(5)	12.8	1×10^{-2}
SbF_6	3.51(2)	2.14(2)	-	50	50	-	-46(3)	-20(2)	4.29(1)	0.34(2)	2.8(3)	13.3	9×10^{-3}
NbF_6	3.33(7)	2.36(5)	1	40	20	40	0	-30(5)	4.28(1)	0.33(3)	2.0(4)	-	-
TaF_6	3.33(9)	2.21(5)	-	50	50	-	0	0	4.22(1)	0.25(1)	1.5(3)	-	-

component. This smooth decrease of these relaxation rates with temperature has been observed previously in magnetic materials^{19,20} and seems to roughly track the magnitude of the local field. It is possible that muon sites responsible for λ_1 and λ_3 lie further from the 2D planes than those sites giving rise to λ_2 , and are thus less sensitive to 2D fluctuations, reducing the influence of any variation in τ . The temperature evolution of λ_1 and λ_3 might then be expected to be dominated by the magnitude of Δ , which scales with the size of the local field and would therefore decrease as the magnetic transition is approached from below.

The need for nonzero phases ϕ_i has been identified in previous studies of molecular magnets,^{8,9,21,22} but never satisfactorily explained. One possible explanation for these might be that the muon experiences delayed state formation. However, we can rule out the simplest model of this as the phases appear not to correlate with ν_i . Such a correlation would be expected since a delay of t_0 before entering the precessing state would give rise to a component of the relaxation function $a_i(t) = \cos[2\pi\nu_i(t + t_0)] = \cos(2\pi\nu_i t + \phi_i)$, with $\phi_i \propto \nu_i$, which is not observed. This does not completely rule out delayed state formation, as t_0 could be a function of temperature (although this seems unlikely at these temperatures). Nonzero phases are also sometimes observed when attempting to fit data with sinusoidal relaxation functions from systems having incommensurate magnetic structures. The phase then emerges as an artifact of fitting, as a cosine with a $\frac{\pi}{4}$ phase shift approximates the zeroth-order Bessel function of the first kind $J_0(\omega t)$ which is obtained from μ^+ SR of an incommensurately ordered system.^{23,24} The Bessel function arises because the distribution of fields seen by muons at sites is asymmetric. However, attempts to fit the data with a pair of damped Bessel functions produced consistently worse fits than fits to Eq. (3), suggesting that a simple incommensurate structure is not a satisfactory explanation. It is also possible that several further magnetically inequivalent muon sites exist, resulting in multiple, closely spaced frequencies which give the spectra a more complex character which is not reflected in the fitting function. The simpler relaxation function would then obtain a better fit if the phase were allowed to vary. This has been observed,²⁵ for example, in LiCrO_2 . A final possibility is that

the distribution of fields at muon sites is asymmetric for another reason, perhaps arising from a complex magnetic structure. This may give rise to a Fourier transform which is only able to be fitted with phase-shifted cosines. However, the mechanism by which this would occur is unclear.

B. Parametrizing exchange anisotropy

The extent to which these systems approximate the 2DSLQHA can be quantified by comparing the transition temperature T_N to the exchange parameter J . The temperature T_N can be extracted using μ^+ SR, while J can be obtained reliably from pulsed-field magnetization measurements,⁷ heat capacity, or magnetic susceptibility.

Mean-field theory predicts a simple relationship for the ratio of the transition temperature T_N and the exchange J given by²⁶

$$\frac{k_B T_N}{J} = \frac{2}{3} z S(S + 1), \quad (5)$$

where k_B is Boltzmann's constant, z is the number of nearest neighbors, and S is the spin of the magnetic ions. In the pseudocubic $[\text{Cu}(\text{HF}_2)(\text{pyz})_2]\text{X}$ systems, $S = \frac{1}{2}$ and $z = 6$, and Eq. (5) yields $k_B T_N/J = 3$. However, the reduced dimensionality increases the prevalence of quantum fluctuations, depressing the transition temperature, and in $[\text{Cu}(\text{HF}_2)(\text{pyz})_2]\text{BF}_4$, we find $k_B T_N/J \approx 0.25$, which is indicative of large exchange anisotropy.

Combining the experimental measures of T_N and J with the results of quantum Monte Carlo (QMC) simulations allows us to deduce the exchange anisotropy J_\perp/J in the system.⁷ Specifically, QMC simulations²⁷ for 2DSLQHA where $10^{-3} \leq J_\perp/J \leq 1$ are well described by the expression

$$\frac{J_\perp}{J} = e^{b - 4\pi\rho_s/T_N}, \quad (6)$$

where ρ_s is the spin stiffness and b is a numerical constant. For $S = \frac{1}{2}$, the appropriate parameters are $\rho_s/J = 0.183$ and $b = 2.43$. This expression allows a better estimate of $k_B T_N/J$ in a 3D magnet: Evaluating for $J_\perp/J = 1$ yields $k_B T_N/J = 0.95$. This is lower than the crude mean-field estimate because mean-field theory takes no account of fluctuations. Estimates of J for our materials, from pulsed magnetic field studies

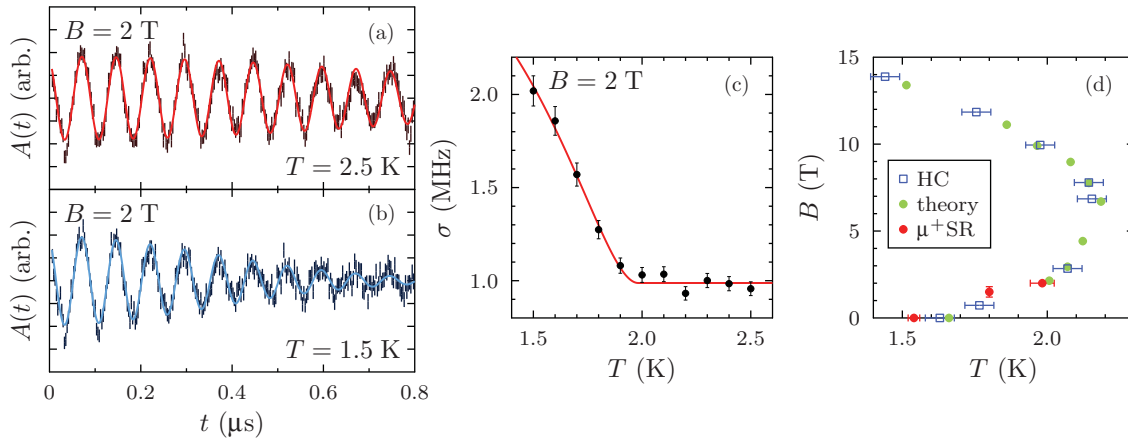


FIG. 6. (Color online) Sample TF μ^+ SR data measured for $[\text{Cu}(\text{HF}_2)(\text{pyz})_2]\text{BF}_4$ in an applied field of 2 T are shown in (a) and (b). Data are shown in the “rotating reference frame,” rotating at $\gamma_\mu \times 1.9 \text{ T} = 257 \text{ MHz}$, nearly canceling out spin precession induced by the 2 T applied transverse field. (c) The evolution of the magnetic broadening σ with T , showing a magnetic transition at 1.98 K in 2 T. (d) The B - T phase diagram from Ref. 12 showing the nonmonotonic behavior at low applied magnetic field. In the key, HC is heat capacity, theory represents the results of computational modeling, and μ^+ SR shows our results from TF measurements (see main text).

except where noted, along with calculated J_\perp/J ratios, are shown in the summary tables throughout this paper.

Another method of parametrizing the exchange anisotropy is to consider the predicted correlation length of two-dimensional correlations in the layers at the temperature at which we observe the onset of LRO. The larger this length, the better isolated the layers can be supposed to be. This can be estimated by combining an analytic expression for the correlation length, in a pure 2DSLQHA,²⁸ ξ_{2D} , with quantum Monte Carlo simulations to obtain an expression^{29,30} appropriate for $1 \leq \xi_{2D}/a \leq 350\,000$,

$$\frac{\xi_{2D}}{a} = 0.498e^{1.131J/k_B T} \left[1 - 0.44 \left(\frac{k_B T}{J} \right) + O \left(\frac{k_B T}{J} \right)^2 \right], \quad (7)$$

where a is the square lattice constant, and T is the temperature. This formula yields $\xi_{2D}(T_N) \approx 0.5a$ for the mean-field model ($k_B T_N/J = 3$), and $\xi_{2D}(T_N) \approx a$ for $k_B T_N/J = 0.95$ from quantum Monte Carlo simulations [i.e., Eq. (6) with $J_\perp/J = 1$]. By comparison, in $[\text{Cu}(\text{HF}_2)(\text{pyz})_2]\text{BF}_4$ Eq. (7) gives $\xi_{2D}(T_N) \approx 50a$, showing a dramatic increase in the size of correlated regions which build up in the quasi-2D layers before the onset of LRO.

C. Nonmonotonic field dependence of T_N

Although we expect the interplane exchange coupling J_\perp to have a large amount of control of the thermodynamic properties of these materials, it may be the case that single-ion anisotropies are also responsible for deviations in the behavior of our materials from the predictions of the 2DSLQHAF model. In particular, these anisotropies have been demonstrated to show a crossover to magnetic behavior consistent with the 2D XY model.¹¹ It was recently reported¹² that $[\text{Cu}(\text{HF}_2)(\text{pyz})_2]\text{BF}_4$ exhibits an unusual nonmonotonic dependence of T_N as a function of applied magnetic field B [see Fig. 6(d)]. This behavior was explained as resulting from the

small XY -like anisotropy of the spin system in these systems. The physics of the unusual field dependence then arises due to the dual effect of B on the spins, both suppressing the amplitude of the order parameter by polarizing the spins along a given direction, and also reducing the phase fluctuations by changing the order parameter phase space from a sphere to a circle. A more detailed explanation for the behavior¹² reveals that the energy scales of the physics are controlled by a Kosterlitz-Thouless-like mechanism, along with the interlayer exchange interaction J_\perp .

The measurement of the B - T phase diagram in $[\text{Cu}(\text{HF}_2)(\text{pyz})_2]\text{BF}_4$ reported in Ref. 12 was made by observing a small anomaly in specific heat. In order to test whether the phase boundary could be determined using muons, we carried out transverse-field (TF) μ^+ SR measurements using the LTF instrument at S μ S. In these measurements, the field is applied perpendicular to the initial muon spin direction, causing a precession of the muon spins in the sum of the applied and internal field directed perpendicular to the muon-spin orientation. Example TF spectra measured in a field of 2 T are shown in Figs. 6(a) and 6(b). We find that the spectra are well described by a function

$$A(t) = A(0)e^{-\sigma^2 t^2/2} \cos(2\pi \nu t + \phi), \quad (8)$$

where the phase factor depends on the details of the detector geometry, and σ is proportional to the second moment of the internal field distribution via $\sigma^2 = \gamma_\mu^2 \langle B^2 \rangle$. Upon cooling through T_N we see a large increase in σ , as shown in Fig. 6(c). This approximately resembles an order parameter, and we identify the discontinuity at the onset of the increase with T_N by fitting σ with the above- T_N relaxation adding in quadrature to the additional relaxation present below the transition. The resulting point at $T_N(B = 2 \text{ T}) = 1.98(4) \text{ K}$ is shown to be consistent with the predicted low-field phase boundary in Fig. 6(d). A further point, identifiable by its vertical rather than horizontal error bar, was found by performing a field scan at a fixed temperature of $T = 1.8 \text{ K}$. The field dependence of

the relaxation rate shows a sharp increase at the transition, at $B = 1.5 \pm 0.3$ T.

Points derived from μ^+ SR measurements possibly lie slightly lower in T than both that predicted by theory and the line predicted on the basis of the specific-heat measurements. The theoretical calculations use $J/k_B = 5.9$ K and $J_{\perp}/J = 2.5 \times 10^{-3}$, while our estimates suggest $J/k_B = 6.3$ K and $J_{\perp}/J = 0.9 \times 10^{-3}$. Performing these calculations for a purely 2D system results in the entire curve shifting to the left,¹² and consequently the leftward shift of our data points is consistent with our finding of increased exchange anisotropy. It is clear that the TF μ^+ SR technique may be used in future to measure the B - T phase diagram and enjoys some of the same advantages it has in ZF over specific heat and susceptibility in anisotropic systems.

D. Muon response for $T > T_N$

Above T_N , the character of the measured spectra changes considerably and we observe lower frequency oscillations characteristic of the dipole-dipole interaction between muons and fluorine nuclei.³¹ The Cu^{2+} electronic moments, which dominate the spectra for $T < T_N$, are disordered in the paramagnetic regime and fluctuate very rapidly on the muon time scale. They are therefore motionally narrowed from the spectra, leaving the muon sensitive to the quasistatic nuclear magnetic moments.

A muon and nucleus interact via the two-spin Hamiltonian

$$\hat{H} = \sum_{i>j} \frac{\mu_0 \gamma_i \gamma_j \hbar}{4\pi r^3} [\mathbf{S}_i \cdot \mathbf{S}_j - 3(\mathbf{S}_i \cdot \hat{\mathbf{r}})(\mathbf{S}_j \cdot \hat{\mathbf{r}})], \quad (9)$$

where the spins $\mathbf{S}_{i,j}$ with gyromagnetic ratios $\gamma_{i,j}$ are separated by the vector \mathbf{r} . This gives rise to a precession of the muon spin, and the muon-spin polarization along a quantization axis z varies with time as

$$D_z(t) = \frac{1}{N} \left\langle \sum_{m,n} |\langle m | \sigma_q | n \rangle|^2 e^{i\omega_{m,n}t} \right\rangle_q, \quad (10)$$

where N is the number of spin states, $|m\rangle$ and $|n\rangle$ are eigenstates of the total Hamiltonian \hat{H} , σ_q is the Pauli spin matrix corresponding to the direction q , and $\langle \dots \rangle_q$ represents an appropriately weighted powder average. The vibrational frequency of the muon-fluorine bond exceeds by orders of magnitude both the frequencies observable in a μ^+ SR experiment, and the frequency appropriate to the dipolar coupling in Eq. (9); the bond length probed via these entangled states is thus time-averaged over thermal fluctuations. Fluorine is an especially strong candidate for this type of interaction first because it is highly electronegative causing the positive muon to stop close to fluorine ions, and second because its nuclei are 100% ^{19}F , which has $I = \frac{1}{2}$.

Data were fitted to a relaxation function

$$A(t) = A_0(p_1 e^{-\lambda_F - \mu t} D_z(t) + p_2 e^{-\sigma^2 t^2}) + A_{\text{bg}} e^{-\lambda_{\text{bg}} t}, \quad (11)$$

where the amplitude fraction $p_1 \approx 70\%$ reflects the muons stopping in a site or set of sites near to a fluorine nucleus, which result in the observed oscillations $D_z(t)$; the weak relaxation of the muon spins is crudely modeled by a decaying exponential.

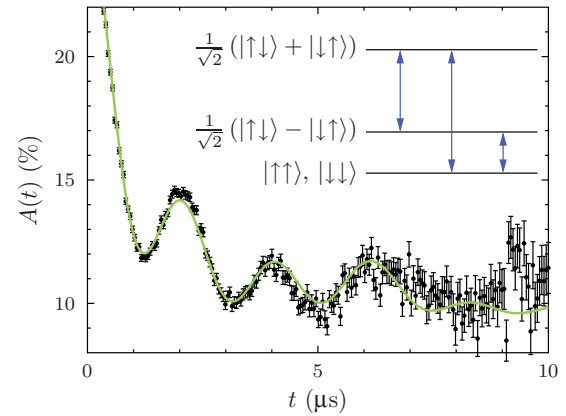


FIG. 7. (Color online) Data taken at $T = 15$ K $\gg T_N = 1.4$ K for $[\text{Cu}(\text{HF}_2)(\text{pyz})_2]\text{BF}_4$, showing $\text{F}\mu$ oscillations along with a fit to Eq. (11). The inset shows the energy levels present in a simple system of two $S = \frac{1}{2}$ spins, along with the allowed transitions.

The fraction $p_2 \approx 30\%$ describes those muons stopping in a class of sites primarily influenced by the randomly orientated fields from other nuclear moments, giving rise to a Gaussian relaxation with $\sigma \approx 0.3$ MHz. Example data and a fit are shown in Fig. 7, while parameters extracted by fitting this function to data from each compound are shown in Table II.

Fits to a variety of different $D_z(t)$ functions were attempted, including that resulting from a simple $\text{F}\mu$ bond (previously observed in some polymers³²) and the better known $\text{F}\mu\text{F}$ complex comprising a muon and two fluorine nuclei in linear symmetric configuration, which is seen in many alkali fluorides.³³ This latter model was also modified to include the possibilities of asymmetric and nonlinear bonds. Previous measurements³¹ made in the paramagnetic regime of $[\text{Cu}(\text{HF}_2)(\text{pyz})_2]\text{ClO}_4$ suggested that the muon stopped close to a single fluorine in the HF_2 group and also interacted with the more distant proton.

TABLE II. Muon-fluorine dipole-dipole interaction fitted parameters in the family $[\text{M}(\text{HF}_2)(\text{pyz})_2]\text{X}$, extracted from fitting data to Eq. (12). In addition to separation by metal ion, Cu compounds are grouped by the temperature at which the measurement was made: Those compounds measured over a range of temperatures appear in both sections of the table.

M	X	$r_{\mu-\text{F}}$ (nm)	p_1 (%)	σ (MHz)	T (K)
Cu	BF_4	0.1038(1)	77(1)	0.29(1)	5.1
Cu	ClO_4	0.1081(2)	70(1)	0.37(1)	5.1
Cu	PF_6	0.1044(2)	74(2)	0.29(2)	5.2
Cu	AsF_6	0.1043(3)	78(2)	0.31(3)	4.9
Cu	SbF_6	0.1047(2)	64(1)	0.30(1)	5.0
Cu	BF_4	0.1042(1)	76(1)	0.26(1)	26
Cu	ClO_4	0.1087(1)	71(1)	0.37(1)	25
Cu	SbF_6	0.1080(3)	59(1)	0.26(1)	30
Cu	NbF_6	0.1039(4)	69(3)	0.32(3)	32
Cu	TaF_6	0.1039(2)	78(2)	0.26(3)	32
Ni	SbF_6	0.1068(4)	60(1)	0.38(1)	19
Ni	PF_6	0.1063(5)	66(2)	0.40(1)	8.4

This interaction is dominated by the F- μ coupling and, for our fitting, the observed muon-fluorine dipole-dipole oscillations were found to be well described by a single F μ interaction damped by a phenomenological relaxation factor. For such F μ entanglement, the time evolution of the polarization is described by

$$D_z(t) = \frac{1}{6} \left[1 + \sum_{j=1}^3 u_j \cos(\omega_j t) \right], \quad (12)$$

where $u_1 = 2$, $u_2 = 1$, and $u_3 = 2$. The frequencies $\omega_j = j\omega_d/2$, where $\omega_d = \mu_0\gamma_\mu\gamma_F\hbar/4\pi r^3$, in which $\gamma_F = 2\pi \times 2.518 \times 10^8 \text{ MHz T}^{-1}$ is the gyromagnetic ratio of a ^{19}F nucleus³⁴ and r is the muon-fluorine separation. These three frequencies arise from the three transitions between the three energy levels present in a system of two entangled $S = \frac{1}{2}$ particles (see inset to Fig. 7). The fact that the relaxation function is similar in all materials in the series, including $[\text{Cu}(\text{HF}_2)(\text{pyz})_2]\text{ClO}_4$, which is the only compound studied without fluorine in its anion (the only difference being a slight lengthening of the μ -F bond, and with no significant change in oscillating fraction), suggests that the muon site giving rise to the F μ oscillations in all systems is near the HF_2 bridging ligand.

The temperature evolution of the F μ signal was studied for $T \leq 300 \text{ K}$ in $[\text{Cu}(\text{HF}_2)(\text{pyz})_2]\text{BF}_4$ and $[\text{Cu}(\text{HF}_2)(\text{pyz})_2]\text{ClO}_4$. In both cases, the dipole-dipole oscillations disappear gradually in a temperature range $150 \lesssim T \lesssim 250 \text{ K}$, with oscillations totally absent in the center of this range, followed by reappearing as temperature is increased further. Plots of $A(t)$ spectra at a variety of temperatures are shown in Figs. 8(a) and 8(d). The data were initially fitted to Eq. (11), with all parameters left free to vary. The temperature-evolution of the muon-fluorine bond length, $r_{\text{F}-\mu}$, can be seen in Figs. 8(b) and 8(e). The spectra were also fitted with

$$A(t) = A_0(p_1 e^{-\lambda_0 t} + p_2 e^{-\sigma^2 t^2}) + A_{\text{bg}} e^{-\lambda_{\text{bg}} t}, \quad (13)$$

a sum of an exponential and a Gaussian relaxation, which might be expected to describe the data in the region where the oscillations vanish. Both this relaxation and that extracted from Eq. (11) are plotted in Figs. 8(c) and 8(f), labeled λ_0 and $\lambda_{\text{F}-\mu}$, respectively.

This bond length appears to grow and then shrink by nearly 20% over the 100 K range where the oscillations fade from the spectra and reappear. This variation is significantly larger than any variation in crystal lattice parameters which would be expected. Since the oscillations visibly disappear from the measured spectra, results from fitting with an oscillatory relaxation function are artifacts of the fitting procedure: since the frequencies scale with $1/r^3$, increasing bond length together with the associated relaxation rate fits the data with a suppressed oscillatory signal. This can be approximately quantified by examining the ratio $Q = 2\pi\lambda_{\text{F}-\mu}/\omega_d$, where a large value indicates that the function relaxes significantly before a single F μ oscillation is completed. The shaded regions in Fig. 8 show where $Q > 2$, which acts as an approximate bound on where the parametrization in Eq. (11) would be expected to fail. In the low- T region where $Q < 2$, the bond lengths appear to scale roughly as T^2 , which has previously been observed in

fluoropolymers.³² Parameters extracted from fitting to

$$r_{\text{F}-\mu} = aT^2 + r_0 \quad (14)$$

are shown in Table III.

The observation in these two samples of F μ oscillations which disappear and then reappear is puzzling. While we have not identified a definitive mechanism, we can probably rule out an electronically mediated effect since, for $T \gg T_N$, the Cu moment fluctuations will be outside the muon time window. An explanation could involve nearby nuclear moments, possibly influenced by a thermally driven structural distortion or instability.

A similar study of $[\text{Cu}(\text{HF}_2)(\text{pyz})_2]\text{SbF}_6$ is shown in Figs. 8(g), 8(h), and 8(i). In this material, the oscillations appear not to vanish over the temperature range studied, though we cannot rule out a brief disappearance at $T \approx 200 \text{ K}$. Instead, the oscillations show an apparently monotonic increase in damping with temperature, and the fitted bond length does not follow Eq. (14). The shaded region in Figs. 8(h) and 8(i) has no upper bound, though we cannot rule out a constraint at $T > 250 \text{ K}$. The pure relaxation λ_0 is omitted because there is no region where the F μ oscillations are sufficiently damped for Eq. (13) to be a good parametrization.

E. Muon site determination

Combining the data measured above and below the transition in these materials allows us to attempt to construct a self-consistent picture of possible muon sites. The observed dipole-dipole observations above T_N suggest that at least one muon stopping site is near a fluorine ion. We consider three classes of probable muon sites: Class I sites near the fluorine ions in the HF_2 groups, Class II sites near the pyrazine rings, and Class III sites near the anions at the center of the pseudocubic pores. Comparison of Tables I and II show that the dominant amplitude component for $T > T_N$ arises from dipole-dipole oscillatory component $p_1 e^{-\lambda t} D_z(t)$ and from the fast-relaxing component $p_3 e^{-\lambda_3 t}$ for $T < T_N$, and that these are comparable in amplitude. It is plausible, therefore, to suggest that these two signals correspond to contributions from the same Class I muon sites near the HF_2 groups. Moreover, the analysis of the $T > T_N$ spectra in the previous section implies that this site lies $r_{\mu-\text{F}} \approx 0.11 \text{ nm}$ from an F in the HF_2 groups. The remainder of the signal (the oscillating fraction below T_N and the Gaussian relaxation above) can also be identified, suggesting that the sites uncoupled from fluorine nuclei (Classes II and/or III) result in the magnetic oscillations observed for $T < T_N$.

We note further that the evidence from F μ oscillations makes the occurrence of Class III muon sites unlikely. The fact that spectra observed for $T > T_N$ in the $X^- = \text{ClO}_4^-$ material are nearly identical to those in all other compounds, in which X contains fluorine, suggests that the muons do not stop near the anions. Moreover, as discussed in Secs. IV and V below, we observe no F μ oscillations in $[\text{Cu}(\text{pyz})_2(\text{pyo})_2]X_2$ ($Y^- = \text{BF}_4^-$, PF_6^-) or $[\text{Cu}(\text{pyo})_6](\text{BF}_4)_2$, suggesting that muons do not stop preferentially near these fluorine-rich anions either. We therefore rule out the existence of Class III muon sites and propose that the magnetic oscillations measured for $T < T_N$ most probably arise due to Class II sites found near the pyrazine ligands.

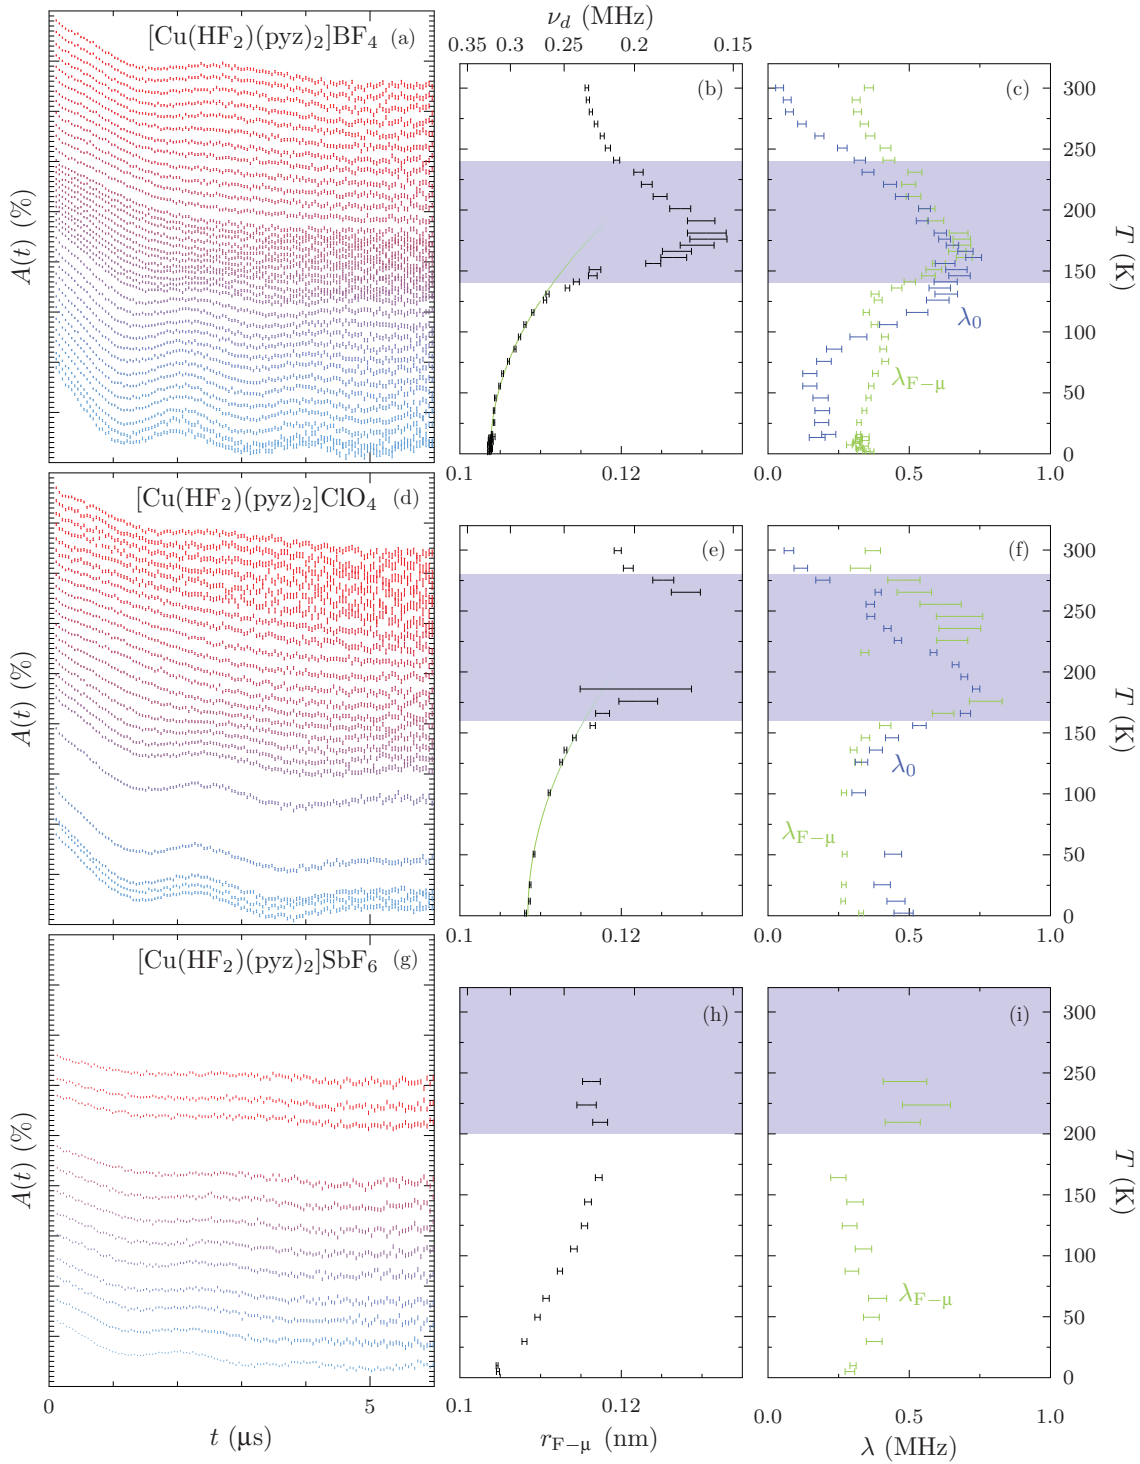


FIG. 8. (Color online) (a) Muon-fluorine dipole-dipole oscillations in $[\text{Cu}(\text{HF}_2)(\text{pyz})_2]\text{BF}_4$ over a temperature range $2 \leq T \leq 300$ K. Asymmetry spectra are displaced vertically so as to approximately align with the temperature scale on plots (b) and (c). Ticks on the y axis of (a) denote 1% asymmetry. Plot (b) shows the fitted value for $r_{\text{F}-\mu}$ as a function of temperature. The line shown is a fit to the low- T points with a T^2 scaling law, Eq. (14). The upper x axis shows values of the dipole frequency, ν_d , which correspond to the lower x-axis values of $r_{\text{F}-\mu}$. Plot (c) shows fitted relaxation rates $\lambda_{\text{F}-\mu}$ and λ_0 , referring to the relaxation of the $\text{F}\mu$ function $D_z(t)$ in Eq. (11), and the pure relaxation in Eq. (13). Shaded regions indicate temperatures where $Q = 2\pi\lambda_{\text{F}-\mu}/\omega_d > 2$, roughly parametrizing the disappearance of the oscillations. (d), (e), and (f) follow (a), (b), and (c), but show data for $[\text{Cu}(\text{HF}_2)(\text{pyz})_2]\text{ClO}_4$. (g), (h), and (i) similarly, but for $[\text{Cu}(\text{HF}_2)(\text{pyz})_2]\text{SbF}_6$ over the range $5 \leq T \leq 250$ K. The 5 K $A(t)$ plot is omitted because the background is raised substantially by approach to the transition to LRO.

TABLE III. Fitted values obtained by fitting muon-fluorine bond lengths with a T^2 scaling law, as Eq. (14).

Material	r_0 (nm)	a (10^{-7} nm K $^{-2}$)
[Cu(HF $_2$)(pyz) $_2$]BF $_4$	0.10376(3)	3.96(6)
[Cu(HF $_2$)(pyz) $_2$]ClO $_4$	0.10842	2.7212
PVDF (Ref. 32)	0.10914	1.9488

Below T_N , the measured muon precession frequencies allow us to determine the magnetic field at these Class II muon sites via $\nu = \gamma_\mu B/2\pi$. Simulating the magnetic field inside the crystal therefore allows us to compare these B fields with those predicted for likely magnetic structures and may permit us to constrain the ordered moment. For the case of our ZF measurements in the antiferromagnetic state, the local magnetic field at the muon site $\mathbf{B}_{\text{local}}$ is given by

$$\mathbf{B}_{\text{local}} = \mathbf{B}_{\text{dipole}} + \mathbf{B}_{\text{hyperfine}}, \quad (15)$$

where $\mathbf{B}_{\text{dipole}}$ is the dipolar field from magnetic ions located within a large sphere centered on the muon site and $\mathbf{B}_{\text{hyperfine}}$ the contact hyperfine field caused by any spin density overlapping with the muon wave function. This spin density is difficult to estimate accurately, particularly in complex molecular systems, but it is probable for insulating materials such as these that the spin density on the copper ion is well localized and so we ignore the hyperfine contribution in our analysis. The dipole field $\mathbf{B}_{\text{dipole}}$ is a function of the coordinate of the muon site \mathbf{r}_μ , and comprises a vector sum of the fields from each of the magnetic ions in the crystal approximated as a point dipole, so that

$$\mathbf{B}_{\text{dipole}}(\mathbf{r}_\mu) = \mu \sum_i \frac{\mu_0}{4\pi r_i^3} [3(\hat{\boldsymbol{\mu}}_i \cdot \hat{\mathbf{r}})\hat{\mathbf{r}} - \hat{\boldsymbol{\mu}}_i], \quad (16)$$

where $\mathbf{r} = \mathbf{r}_i - \mathbf{r}_\mu$ is the relative position of the muon and the i th ion with magnetic moment $\boldsymbol{\mu}_i = \mu \hat{\boldsymbol{\mu}}_i$, and i is an index implying summation over all of the ions which make up the crystal.

Although these materials are known to be antiferromagnetic from their negative Curie-Weiss temperatures and zero spontaneous magnetization at low temperatures,^{14,35} their magnetic structures are unknown. Dipole field simulations were therefore performed for a variety of trial magnetic structures with $\mu = \mu_B$. We analyze the results of these calculations using a probabilistic method. We begin by allowing the possibility that the magnetic precession signal could arise from any of the possible classes of muon sites identified above. Random positions in the unit cell were generated and dipole fields calculated at these. To prevent candidate sites lying too close to atoms we constrain all sites such that $r_{\mu-A} > 0.1$ nm where A is any atom. Possible Class I muon sites were identified with $r_{\mu-F} = r_0 \pm 0.01$ nm (where r_0 is the muon-fluorine distance established from $F\mu$ oscillations) and possible Class II sites were selected with the constraint that $0.10 \leq r_{\mu-C,N} \leq 0.12$ nm. The predicted probability density function (pdf) of muon precession frequencies (resulting from the magnitudes of the calculated fields) is plotted in Fig. 9, with the observed frequencies superimposed. Results are shown for a trial magnetic structure comprising copper spins lying in the plane of the pyrazine layers and at 45° to the directions of the pyrazine chains, and

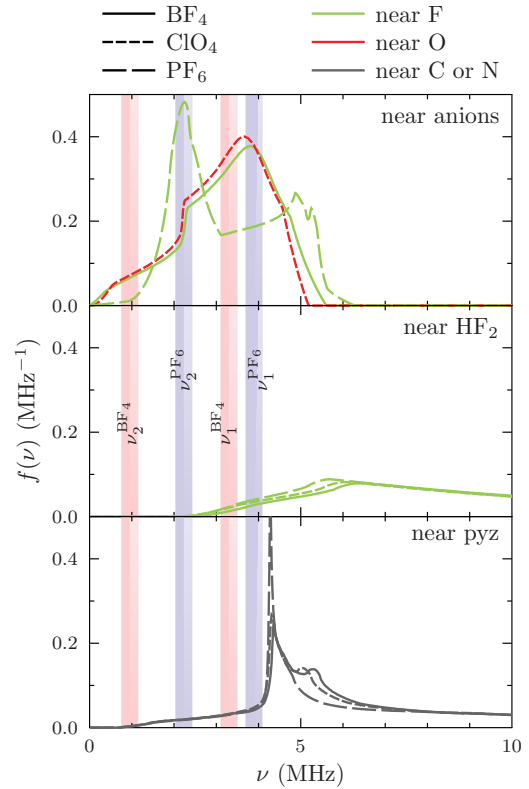


FIG. 9. (Color online) Probability density functions of muon precession frequencies at positions close to likely muon stopping sites in [Cu(HF $_2$)(pyz) $_2$]X with Cu $^{2+}$ moments $\mu = \mu_B$. The graphs show dipole fields near the fluorine or oxygen atoms in the negative anions; near the fluorine atoms in the bifluoride ligands; and near the carbon and nitrogen atoms, as a proxy for proximity to the pyrazine ring. The type of line indicates the compound for which the calculation was performed. The muon site is constrained to be close to particular atoms, indicated by line color. The shaded areas indicate ranges of fitted frequencies as $T \rightarrow 0$; two frequencies $\nu_{1,2}^{\text{BF}_4}$ represent those observed where $X^- = \text{BF}_4^-$, and $\nu_{1,2}^{\text{PF}_6}$ those observed in the $X^- = \text{PF}_6^-$ analog.

with spins arranged antiferromagnetically both along those chains and along the HF $_2$ groups. This candidate structure is motivated by analogy with [Cu(pyz) $_2$](ClO $_4$) $_2$, which also comprises Cu $^{2+}$ ions in layers of 2D pyrazine lattices,³⁶ and with the parent phases of the cuprate superconductors,³⁰ which are also two-dimensional Heisenberg systems of $S = \frac{1}{2}$ Cu $^{2+}$ ions. Other magnetic structures investigated give qualitatively similar results. From Fig. 9 it is clear that the only sites with significant probability density near to the observed frequencies are those lying near the anions (i.e., Class III sites) which we have argued are not compatible with our data. The more plausible muon sites correspond to higher frequencies than those observed. Our conclusion is that it is likely that the Cu $^{2+}$ moments are rather smaller than the μ_B assumed in the initial calculation.

If we accept that the muon sites giving rise to magnetic precession are near the pyrazine groups then we may use this calculation to constrain the size of the copper moment. Since ν is obtained from experiment, what we would like to know is $g(\mu|\nu)$, the pdf of copper moment μ given the observed

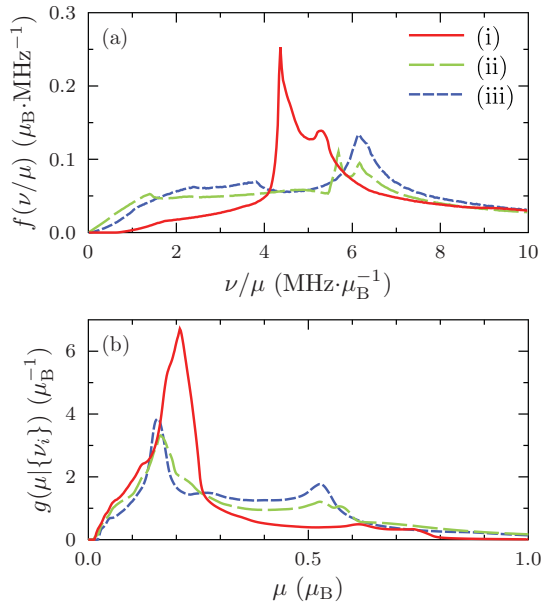


FIG. 10. (Color online) Probability density functions for muons in the putative oscillating sites near the pyrazine rings in $[\text{Cu}(\text{HF}_2)(\text{pyz})_2]\text{BF}_4$ (a) for muon precession frequency ν assuming that the moment on the copper site $\mu = \mu_B$, created from a histogram of dipole fields evaluated using Eq. (16) at points satisfying the constraints detailed in the text; and (b) for moment on the copper sites given the frequencies actually observed, evaluated using the pdfs in (a) and Eq. (18). Lines represent trial magnetic structures. All exhibit antiferromagnetic coupling through both the bifluoride and pyrazine exchange paths, while (i) has copper moments pointing at 45° to the pyrazine grid, (ii) has moments along one of the pyrazine grid directions (**a** or **b**), and (iii) has copper moments pointing along the bifluoride axis (**c**).

ν . This can be obtained from our calculated $f(\nu/\mu)$ using Bayes's theorem,³⁷ which yields

$$g(\mu|\nu) = \frac{\frac{1}{\mu} f(\nu/\mu)}{\int_0^{\mu_{\max}} \frac{1}{\mu'} f(\nu/\mu') d\mu'}, \quad (17)$$

where we have assumed a prior probability for the copper moment that is uniform between zero and μ_{\max} . We take $\mu_{\max} = 2\mu_B$, although our results are insensitive to the precise value of μ_{\max} as long as it is reasonably large. When multiple frequencies $\{\nu_i\}$ are present in the spectra, it is necessary to multiply their probabilities of observation in order to obtain the chance of their simultaneous observation, so we evaluate

$$g(\mu|\{\nu_i\}) \propto \prod_i \int_{\nu_i - \Delta\nu_i}^{\nu_i + \Delta\nu_i} f(\nu_i/\mu) d\nu_i, \quad (18)$$

where $\Delta\nu_i$ is the error on the fitted frequency. Results are shown in Fig. 10, along with the dipole field pdfs which gave rise to them. By inspection of the pdfs, the copper moment is likely to be $\mu \lesssim 0.5\mu_B$. The dipole field simulations results also lend weight to our contention that the oscillatory signal cannot arise from the sites that also lead to the $F\mu$ component above T_N . If this were the case then the most likely moment on the copper would be $\mu_{\text{Cu}} \lesssim 0.2\mu_B$, which seems unreasonably small. We note that moment sizes of

$\mu \lesssim 0.5\mu_B$ were also observed for the 2DSLQHA system La_2CuO_4 (a recent estimate³⁸ from neutron diffraction gave $[0.42 \pm 0.01]\mu_B$), despite the predictions of $0.6\mu_B$ from spin wave theory and quantum Monte Carlo.³⁹ It was suggested in that case³⁹ that disorder might play a role in reducing the moment sizes; an additional possible mechanism for this suppression is ring exchange.^{40,41}

One limitation of this analysis is that the mechanism for magnetic coupling of copper ions through the pyrazine rings is postulated to be via spin exchange, in which small magnetic polarizations are induced on intervening atoms.⁴² Density functional theory calculations estimate that these are small, with the nitrogen and carbon moments estimated at $\mu_C \approx 0.01\mu_B$ and $\mu_N \approx 0.07\mu_B$, respectively.⁴³ However, their effect may be nonnegligible: They may be significantly closer to the muon site than a copper moment, and dipole fields fall off rapidly, as $1/r^3$. Further, since much of the electron density in a pyrazine ring is delocalized in π orbitals, the moments may not be pointlike, as assumed in our dipole field calculations. Further, this may lead to overlap of spin density at the muon site and result in a nonzero hyperfine field.

IV. $[\text{Cu}(\text{pyz})_2(\text{pyo})_2]\text{Y}_2$

In this section, we report the magnetic behavior of another family of molecular systems which shows quasi-2D magnetism, but for which the interlayer groups are very different and arranged in a completely different structure, resulting in a 2D coordination polymer. This system is $[\text{Cu}(\text{pyz})_2(\text{pyo})_2]\text{Y}_2$, where $\text{Y}^- = \text{BF}_4^-, \text{PF}_6^-$. As with the previous case, $S = \frac{1}{2}$. Cu^{2+} ions are bound in a 2D square lattice of $[\text{Cu}(\text{pyz})_2]^{2+}$ sheets lying in the ab plane. Pyridine-*N*-oxide (pyo) ligands [shown in Fig. 1(b)] protrude from the copper ions along the c direction, perpendicular to the ab plane in the $\text{Y}^- = \text{PF}_6^-$ material, but making an angle $\beta - 90^\circ \approx 29^\circ$ with the normal in $\text{Y}^- = \text{BF}_4^-$. The anions then fill the pores remaining in the structure. The structure of $[\text{Cu}(\text{pyz})_2(\text{pyo})_2](\text{BF}_4)_2$ is shown in Fig. 11.

In a typical synthesis, an aqueous solution of CuY_2 hydrate ($\text{Y}^- = \text{BF}_4^-$ or PF_6^-) was combined with an ethanol solution that contained a mixture of pyrazine and pyridine-*N*-oxide or 4-phenylpyridine-*N*-oxide. Deep blue-green solutions were obtained in each case, and when allowed to slowly evaporate at room temperature for a few weeks; dark green plates were recovered in high yield. Crystal quality could be improved by sequential dilution and collection of multiple batches of crystals from the original mother liquor. The relative amounts of pyz and pyo were optimized in order to prevent formation of compounds such as $\text{CuY}_2(\text{pyz})_2$ or $[\text{Cu}(\text{pyo})_6]\text{Y}_2$.

Samples were measured in the LTF apparatus at $S\mu\text{S}$. Example data measured on $[\text{Cu}(\text{pyz})_2(\text{pyo})_2]\text{Y}_2$ are shown in Fig. 12, where we observe oscillations in $A(t)$ at a single frequency below T_N . Data were fitted to a relaxation function

$$A(t) = A_0(p_1 \cos(2\pi\nu_1 t)e^{-\lambda_1 t} + p_2 e^{-\lambda_2 t} + p_3 e^{-\lambda_3 t}) + A_{\text{bg}}. \quad (19)$$

The small amplitude fraction $p_1 < 10\%$ for both samples refers to muons stopping in a site or set of sites with a narrow distribution of quasistatic local magnetic fields, giving rise to the oscillations; $p_2 \approx 50\%$ is the fraction of muons stopping

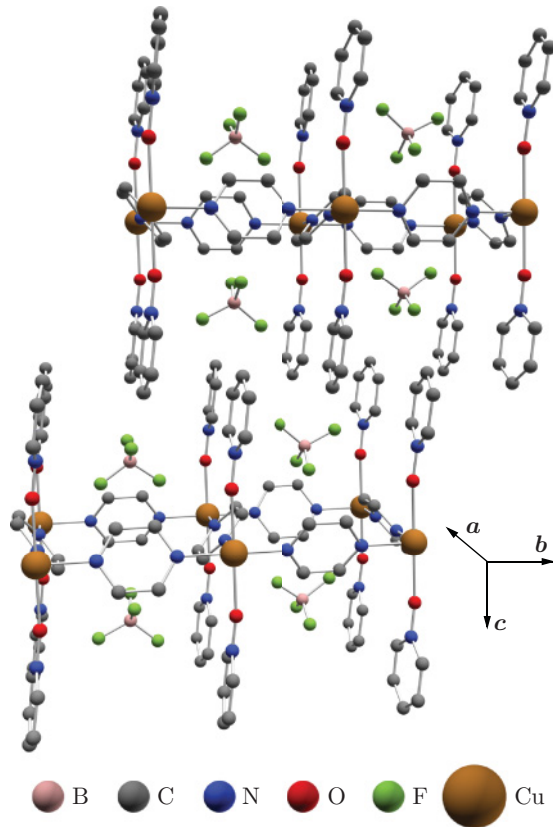


FIG. 11. (Color online) Structure of $[\text{Cu}(\text{pyz})_2(\text{pyo})_2](\text{BF}_4)_2$. Copper ions lie in 2D square layers, bound by pyrazine rings. Pyridine-*N*-oxide ligands protrude from the coppers in a direction approximately perpendicular to these layers. Tetrafluoroborate ions fill the pores remaining in the structure. Ion sizes are schematic; copper ions are shown twice as large for emphasis, and hydrogens have been omitted for clarity.

in a class of sites giving rise to a large relaxation rate $30 \lesssim \lambda \lesssim 60$ MHz, and $p_3 \approx 50\%$ represents the fraction of muons stopping in sites with a small relaxation rate $\lambda_3 \approx 1$ MHz. The data from these compounds fit best with $\phi = 0$, and they are thus omitted from this expression. Frequencies obtained from fitting the data to Eq. (19) were then modeled with Eq. (4). The results of these fits are shown in Fig. 12, and Table IV.

Our results show that $[\text{Cu}(\text{pyz})_2(\text{pyo})_2](\text{BF}_4)_2$ has a transition temperature $T_N = 1.5 \pm 0.1$ K and a quasistatic magnetic field at the muon site $\nu_1(T = 0) = 1.4 \pm 0.1$ MHz. No quantities other than ν_1 show a significant trend in the temperature region $0.1 \leq T \leq 1.6$ K. Above the transition, purely relaxing spectra are observed, displaying no $F\mu$ oscillations. As suggested above, this makes the existence of muon sites near the anions unlikely. We find a critical exponent of $\beta = 0.25 \pm 0.10$, where the large uncertainty results in part from the difficulty in fitting the $A(t)$ data in the critical region.

Our results for $[\text{Cu}(\text{pyz})_2(\text{pyo})_2](\text{PF}_6)_2$ show that the transition temperature is slightly higher at $T_N = 1.72 \pm 0.02$ K and the oscillations occur at a lower frequency of $\nu_1(T = 0) = 1.07 \pm 0.03$ MHz. The relaxation rates λ_2 and λ_3 also decrease in magnitude as temperature is increased, settling on roughly constant values $\lambda_2 \approx 0.6$ MHz and $\lambda_3 \approx 15$ MHz for $T > T_N$. No other quantities show a significant trend in the

temperature region $0.2 \leq T \leq 1.7$ K. Above the transition, relaxing spectra devoid of $F\mu$ oscillations are again observed. The critical exponent $\beta = 0.22 \pm 0.02$.

The small amplitude of the oscillations, common to both samples, might be explained in a number of ways. The materials may undergo long-range ordering but there may be an increased likelihood of stopping in sites where the magnetic field nearly precisely cancels. Alternatively, a range of similar muon sites may be present with a large distribution of frequencies, or alternatively the presence of dynamics, washing out any clear oscillations in large fractions of the spectra and instead resulting in a relaxation. Finally, we cannot exclude the possibility that only a small volume of the sample undergoes a magnetic transition; this may indicate the presence of a small impurity phase, possibly located at either grain boundaries or, given that this is a powder sample, near the crystallites' surfaces. We note also that the behavior of fitted parameters in these materials is qualitatively similar to that reported in $\text{CuCl}_2(\text{pyz})$, where there is also a relatively small precessing fraction of muons and little variation in relaxation rates as T_N is approached from below.²¹

V. $[\text{Cu}(\text{pyo})_6]\text{Z}_2$

The next example is not a coordination polymer, but instead forms a three-dimensional structure of packed molecular groups. The molecular magnet $[\text{Cu}(\text{pyo})_6]\text{Z}_2$, where $Z^- = \text{BF}_4^-, \text{ClO}_3^-, \text{PF}_6^-$, comprises Cu^{2+} ions on a slightly distorted cubic lattice, located in $[\text{Cu}(\text{pyo})_6]^{2+}$ complexes, and surrounded by octahedra of oxygen atoms.⁴⁴ The structure is shown in Fig. 13. This approximately cubic structure, which arises from the molecules' packing, might suggest that a three-dimensional model of magnetism would be appropriate. In fact, although the observed bulk properties of $[M(\text{pyo})_6]\text{X}_2$, where $M^{2+} = \text{Co}^{2+}, \text{Ni}^{2+},$ or Fe^{2+} , are largely isotropic, but the copper analogues display quasi-low-dimensional, $S = \frac{1}{2}$ Heisenberg antiferromagnetism.⁴⁴ Weakening of superexchange in certain directions, and thus the lowering of the systems' effective dimensionality, is attributed to lengthening of the superexchange pathways resulting from Jahn-Teller distortion of the Cu-O octahedra, which is observed in structural and EPR measurements.^{45,46} At high temperatures ($T \gtrsim 100$ K), these distortions are expected to be dynamic but, as T is reduced (to ≈ 50 K), they freeze out. The anion Z^- determines the nature of the static Jahn-Teller elongation. The $Z^- = \text{BF}_4^-$ material displays ferrodistorive ordering which, in combination with the antiferromagnetic exchange, gives rise to 2D Heisenberg antiferromagnetic behavior.^{44,47} By contrast, $Z^- = \text{ClO}_4^-, \text{NO}_3^-$ (neither of which is investigated here) display antiferrodistorive ordering,⁴⁶ which gives rise to quasi-1D Heisenberg antiferromagnetism.⁴⁴ All of the samples investigated were measured in the LTF spectrometer at $S\mu\text{S}$.

In the $Z^- = \text{BF}_4^-$ compound, below a temperature T_N , a single oscillating frequency is observed, indicating a transition to a state of long-range magnetic order. Example data above and below the transition, along with fits, are shown in Fig. 14(a). Data were fitted to Eq. (19), and the frequencies extracted from the procedure fitted as a function of temperature to Eq. (4), as shown in Fig. 14(b). This procedure identifies a transition temperature

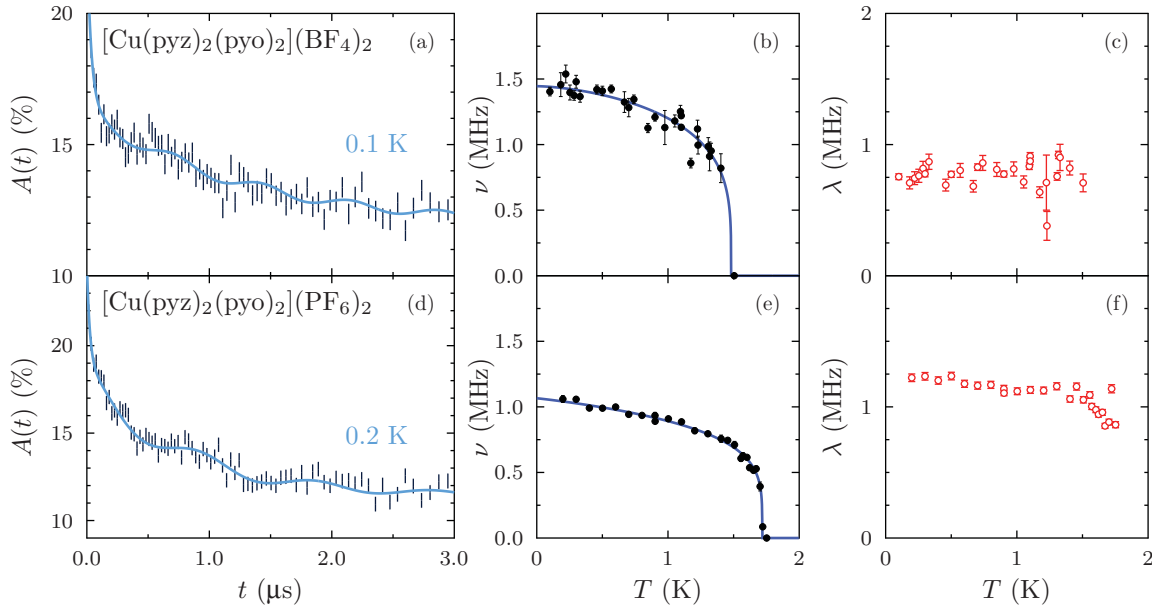


FIG. 12. (Color online) Example data and fits for $[\text{Cu}(\text{pyz})_2(\text{pyo})_2]\text{Y}_2$. From left to right: (a) and (d) show sample asymmetry spectra $A(t)$ for $T < T_N$ along with a fit to Eq. (19); (b) and (e) show the frequency ν as a function of temperature; and (c) and (f) show relaxation rates λ_i as a function of temperature. The relaxation rates λ_1 , associated with the oscillation, and λ_3 , the fast-relaxing initial component, do not vary significantly with T and are not shown. Only a slight trend in λ_2 in the $\text{Y}^- = \text{PF}_6^-$ material [graph (f)] is observed.

$T_N = 0.649 \pm 0.005$ K. The only other parameter found to vary significantly in the range $20\text{mK} \leq T \leq T_N$ was λ_2 , shown in Fig. 14(c). The fitted parameters are shown in Table IV. We may compare this with the result of an earlier low-temperature specific-heat study⁴⁴ which found a very small λ -point anomaly at $T_N = 0.62 \pm 0.01$ K, slightly lower than our result. Fitting the magnetic component of the heat capacity with the predictions from a two-dimensional Heisenberg antiferromagnet gives $J/k_B = -1.10 \pm 0.02$ K, and similar analysis of the magnetic susceptibility⁴⁴ yields $J/k_B = -1.08 \pm 0.03$ K. Using these values, together with the muon estimate of T_N and Eq. (6), allows us to estimate the interplane coupling, $J_\perp/J = 0.26 \pm 0.01$. (Using the value of T_N from heat capacity results in an estimate $J_\perp/J = 0.21 \pm 0.02$.)

For temperatures $T_N < T \leq 1$ K, the spectra are well described by a relaxation function

$$A(t) = A_0(p_1 e^{-\lambda t} + p_2 e^{-\sigma^2 t^2}) + A_{\text{bg}}, \quad (20)$$

comprising an initial fast-relaxing component with $\lambda \approx 20$ MHz, and a Gaussian relaxation with $\sigma \approx 0.4$ MHz corresponding to the slow depolarization of muon spins due to randomly orientated nuclear moments.

The $\text{Z}^- = \text{ClO}_3^-$ material also shows evidence for a magnetic transition, although in this case we do not observe oscillations in the muon asymmetry. Instead we measure a discontinuous change in the relaxation which seems to point toward an ordering transition. Example asymmetry spectra are shown in Fig. 15(a), and data at all measured temperatures are well described with the relaxation function

$$A(t) = A_0 e^{-\lambda t} + A_{\text{bg}}. \quad (21)$$

Evidence for a magnetic transition comes from the temperature evolution of λ [Fig. 15(b)], where we see that the relaxation

decreases with increasing temperature until it settles at $T \approx 0.3$ K, on a value $\lambda \approx 0.5$ MHz. It is likely that this tracks the internal magnetic field inside the material, and is suggestive of $T_N = 0.30 \pm 0.01$ K.

The final member of this family studied, $\text{Z}^- = \text{PF}_6^-$, shows no evidence for a magnetic transition over the range of temperatures studied, $0.02 \text{ K} \leq T \leq 1$ K. An example spectrum is shown in Fig. 16. The data resemble the above transition data measured in the BF_4 and ClO_3 compounds and it therefore seems likely that the paramagnetic state persists to the lowest temperature measured.

VI. $\text{Ag}(\text{pyz})_2(\text{S}_2\text{O}_8)$

The examples so far have used Cu^{2+} ($3d^9$) as the magnetic species. An alternative strategy is to employ Ag^{2+} ($4d^9$) which also carries an $S = \frac{1}{2}$ moment. This idea has led to the synthesis of $\text{Ag}(\text{pyz})_2(\text{S}_2\text{O}_8)$, which comprises square sheets of $[\text{Ag}(\text{pyz})_2]^{2+}$ units spaced with $\text{S}_2\text{O}_8^{2-}$ anions.⁴⁸ Each silver ion lies at the center of an elongated (AgN_4O_2) octahedron, where the Ag-N bonds are significantly shorter than the Ag-O. Preparation details can be found in Ref. 49.

Measurements were made using the GPS instrument at $S\mu\text{S}$. Example muon data, along with fits to various parameters, are shown in Fig. 17. Asymmetry oscillations are visible in spectra taken below a transition temperature T_N . The data were fitted with a relaxation function

$$A(t) = A_0(p_1 \cos(2\pi \nu_1 t + \phi_1) e^{-\lambda_1 t} + p_2 e^{-\lambda_2 t}) + A_{\text{bg}}, \quad (22)$$

comprising a single damped oscillatory component, a slow-relaxing component, and a static background signal. The onset of increased relaxation λ_1 as the transition is approached from below leads to large statistical errors on fitted values,

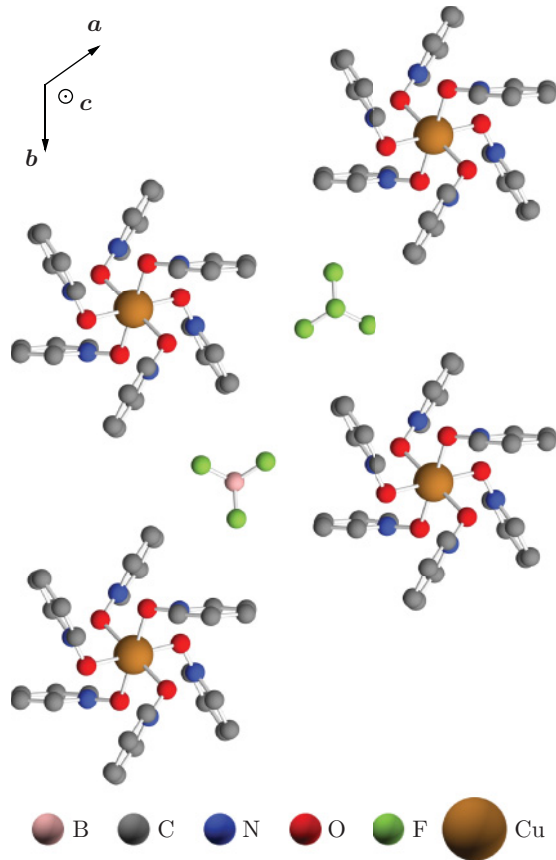


FIG. 13. (Color online) Structure of $[\text{Cu}(\text{pyO})_6](\text{BF}_4)_2$, viewed along the threefold (c) axis, after Ref. 45. Copper ions are surrounded by octahedra of six oxygens, each part of a pyridine- N -oxide ligand; $[\text{Cu}(\text{pyO})_6]^{2+}$ complexes space-pack with BF_4^- stabilizing the structure. Ion sizes are schematic; copper ions are shown twice as large for emphasis, and hydrogens have been omitted for clarity. As indicated in the top left, the a and b directions lie in the plane of the paper, separated by $\gamma = 120^\circ$, while the c direction is out of the page.

as is evident in Fig. 17(c). The relaxation λ_2 decreases with increasing temperature. Fitting to Eq. (4) allows the critical parameters $\beta = 0.19 \pm 0.02$ and $T_N = 7.8 \pm 0.3$ K to be determined. Fitted values are shown in Table IV.

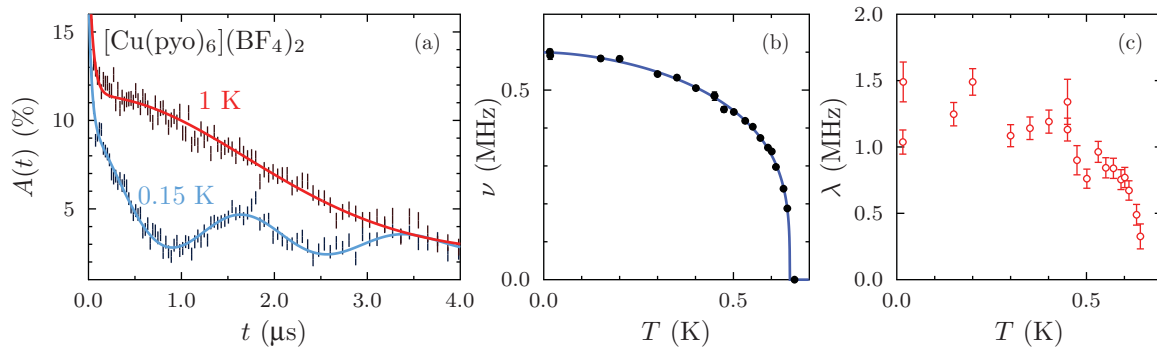


FIG. 14. (Color online) Example data and fits for $[\text{Cu}(\text{pyO})_6](\text{BF}_4)_2$. From left to right: (a) shows sample asymmetry spectra $A(t)$ for $T < T_N$ and $T > T_N$, along with fits to Eqs. (19) and (20), respectively; (b) shows frequency as a function of temperature; and (c) shows relaxation rate λ_2 as a function of temperature; λ_1 was held fixed during the fitting procedure, and λ_3 persists for $T > T_N$. In the $\nu(T)$ plot, error bars are included on the points but in most cases they are smaller than the marker being used.

The in-plane exchange J is too large to be determined with pulsed fields⁴⁸: $M(B)$ does not saturate in fields up to 64 T. However, fitting $\chi(T)$ data allows an estimate of the exchange $J/k_B \approx 53$ K (and thus, in conjunction with g measured by EPR, the saturation field B_c is estimated to be 160 T). Thus, $k_B T_N/J = 0.148 \pm 0.006$. Estimation of the exchange anisotropy with Eq. (6) yields $|J_\perp/J| \sim 10^{-6}$, but this very small ratio of ordering temperature to exchange strength is outside the range in which the equation is known to yield accurate results. The alternative method of parametrizing the low dimensionality in terms of correlation length at the Néel temperature (see Sec. III B) yields $\xi(T_N)/a = 1000 \pm 300$.

VII. $[\text{Ni}(\text{HF}_2)(\text{pyz})_2]X$

In order to investigate the influence of a different spin state on the magnetic cation in the $[\text{M}(\text{HF}_2)(\text{pyz})_2]X$ architecture the $[\text{Ni}(\text{HF}_2)(\text{pyz})_2]X$ ($X^- = \text{PF}_6^-, \text{SbF}_6^-$) system has been synthesised.¹⁶ These materials are isostructural with the copper family discussed in Sec. III, but contain $S = 1$ Ni^{2+} cations.

Data were taken using the GPS spectrometer at PSI. Example data are shown in Fig. 18. We observe oscillations at two frequencies below the materials' respective ordering temperatures. Data were fitted with a relaxation function

$$A(t) = A_0[p_1 e^{-\lambda_1 t} \cos(2\pi \nu_1 t) + p_2 e^{-\lambda_2 t} \cos(2\pi P_2 \nu_1 t) + p_3 e^{-\lambda_3 t}] + A_{\text{bg}} e^{-\lambda_{\text{bg}} t}. \quad (23)$$

Of those muons which stop in the sample, $p_1 \approx 25\%$ indicates the fraction of the signal corresponding to the low-frequency oscillating state with $\nu_1(T=0) \approx 12.3$ MHz; $p_2 \approx 10\%$ corresponds to muons stopping in the high-frequency oscillating state with $\nu_2(T=0) \approx 9.0$ MHz; and $p_3 \approx 65\%$ represents muons stopping in a site with a large relaxation rate $\lambda_3(T=0) \approx 70$ MHz. The frequencies were observed to scale with one another, and consequently the second frequency was held in fixed proportion $\nu_2 = P_2 \nu_1$ during the fitting procedure. The only other parameter which changes significantly in value below T_N is λ_3 , which decreases with a trend qualitatively similar to that of the frequencies. Fitting the extracted frequencies to Eq. (4) allows the transition

TABLE IV. Fitted parameters for molecular magnets in the family $[\text{Cu}(\text{pyz})_2(\text{pyo})_2]\text{Y}_2$, $[\text{Cu}(\text{pyo})_6](\text{BF}_4)_2$ and $\text{Ag}(\text{pyz})_2(\text{S}_2\text{O}_8)$. The first parameters shown relate to fits to Eq. (19) (for the first three rows) or Eq. (22) [for $\text{Ag}(\text{pyz})_2(\text{S}_2\text{O}_8)$]. This allows us to derive frequencies at $T = 0$, ν_i ; and probabilities of stopping in the various classes of stopping site, p_i , in percent. Then, the temperature dependence of ν_i is fitted with Eq. (4), extracting values for the Néel temperature T_N , critical exponent β , and parameter α . Finally, the quoted J/k_B is obtained from pulsed-field experiments (Ref. 7). The asterisk (*) indicates the value of J was obtained using $g_{ab} = 2.04(1)$ in conjunction with single-crystal pulsed-field data. The dagger (†) indicates that the value of J is extracted from heat capacity and susceptibility from Ref. 44. The ratio of inter-to in-plane coupling, J_\perp/J , is obtained by combining T_N and J with formulas extracted from quantum Monte Carlo simulations (see Sec. III B and Ref. 7). The dash in the p_3 column for $\text{Ag}(\text{pyz})_2(\text{S}_2\text{O}_8)$ reflects the fact that there is no third component in Eq. (22). Dashes in the J/k_B and J_\perp/J columns for $[\text{Cu}(\text{pyz})_2(\text{pyo})_2](\text{BF}_4)_2$ indicate a lack of pulsed-field data for this material.

Material	ν_1 (MHz)	p_1	p_2	p_3	T_N (K)	β	α	J/k_B (K)	$ J_\perp/J $
$[\text{Cu}(\text{pyz})_2(\text{pyo})_2](\text{BF}_4)_2$	1.4(1)	<10	50	50	1.5(1)	0.25(10)	1.6(3)	–	–
$[\text{Cu}(\text{pyz})_2(\text{pyo})_2](\text{PF}_6)_2$	0.64(1)	<10	50	50	1.72(2)	0.22(2)	1.1(3)	8.1(3)*	2×10^{-4}
$[\text{Cu}(\text{pyo})_6](\text{BF}_4)_2$	0.599(5)	15	30	55	0.649(5)	0.29(1)	1.7(1)	1.09(2)†	0.23(2)
$\text{Ag}(\text{pyz})_2(\text{S}_2\text{O}_8)$	2.45(4)	30	70	–	7.8(3)	0.19(2)	3(2)	52.7(3)	$\sim 10^{-6}$

temperature $T_N = 12.25 \pm 0.03$ K and critical exponent $\beta = 0.34 \pm 0.04$ to be extracted. In contrast to the copper family studied in Sec. III, the relation $\lambda \propto \nu^2$ holds true, suggesting that a field distribution whose width diminishes with increasing temperature is responsible for the variation in λ , and that dynamics are relatively unimportant in determining the muon response. This is shown graphically in the inset to Fig. 18(f), where a plot of frequency against relaxation rate lies on top of a line representing a $\lambda = \nu^2$ relationship. The phase ϕ required in previous fits [e.g. Eq. (3)] is not necessary in fitting these spectra, and is set to zero. Fitted parameters are shown in Table V.

Data for the $X^- = \text{PF}_6^-$ compound were subject to similar analysis, fitting spectra below T_N to Eq. (23), this time with $p_1 \approx 15\%$, $\nu_1(T = 0) \approx 12.0$ MHz; $p_2 \approx 10\%$, $\nu_2(T = 0) \approx 9.3$ MHz; and $p_3 \approx 75\%$, $\lambda_3(T = 0) \approx 100$ MHz. The phase ϕ again proved unnecessary. These spectra do not show as sharp a transition as the $X^- = \text{SbF}_6^-$ compound, with the oscillating fraction of the signal decaying rather before the appearance of spectra whose different character indicates clearly that the sample is above T_N . The available data do not allow reliable extraction of critical parameters, but we estimate $5.5 \text{ K} \leq T_N \leq 6.2 \text{ K}$ and $0.15 \leq \beta \leq 0.4$. Fitted values are shown in Table V.

Another method to locate the transition is to observe a transition in the amplitude of the muon spectra at late times

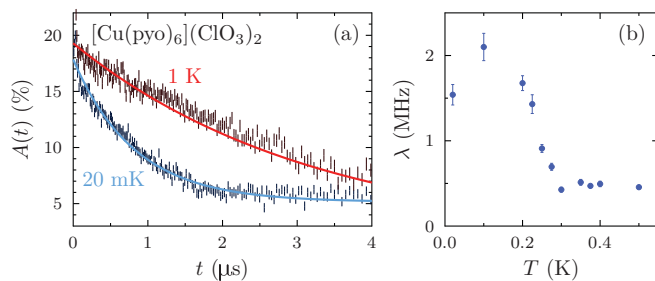


FIG. 15. (Color online) Example data and fits for $[\text{Cu}(\text{pyo})_6](\text{ClO}_3)_2$. Representative $A(t)$ spectra for $T < T_N$ and $T > T_N$, along with fits to Eq. (21), are shown in (a), while the value of the relaxation rate, λ , as a function of temperature is shown in (b).

to observe the transition as a function of temperature from zero in the unordered state to the “ $\frac{1}{3}$ tail” characteristic of LRO, described in Sec. II. Spectra were fitted with the simple relaxation function $A(t > 5 \mu\text{s}) = A_{\text{bg}} e^{-\lambda_{\text{bg}} t}$, and then the amplitudes obtained fitted with a Fermi-like step function

$$A(t > 5 \mu\text{s}, T) = A_2 + \frac{A_1 - A_2}{e^{(T - T_{\text{mid}})/w} + 1}, \quad (24)$$

which provides a method of modeling a smooth transition between $A_1 = A(T < T_N)$ and $A_2 = A(T > T_N)$. The fitted amplitudes and Fermi function are shown in Fig. 19(c). The fitted midpoint $T_{\text{mid}} = 6.4 \pm 0.1$ K, and width $w = 0.3 \pm 0.1$ K. Spin relaxation peaks just above T_N , and so one would expect that T_N lies at the lower end of this transition. Thus, the μ^+ SR analysis suggests $T_N = 6.1 \pm 0.3$ K (i.e., $T_{\text{mid}} - w \pm w$). This is consistent with the estimate from $\nu_i(T)$ and the value $T_N = 6.2$ K obtained from heat capacity.¹⁶

Members of the $M = \text{Ni}$ family exhibit $F\mu$ oscillations rather like their copper counterparts, with a similar fraction of the muons in sites giving rise to dipole-dipole interactions. The results of these fits are shown along with those from Cu compounds in Table II. Because the nickel data were measured at temperatures different from those of the copper compounds and, as described in Sec. III D, the muon-fluorine

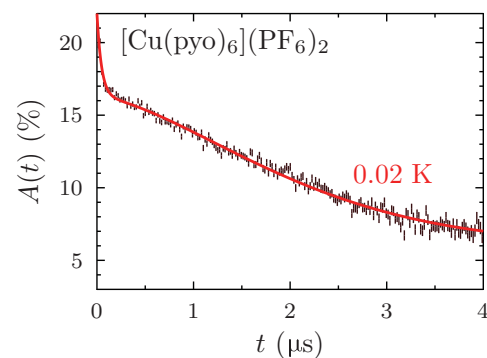


FIG. 16. (Color online) Sample asymmetry spectrum for $[\text{Cu}(\text{pyo})_6](\text{PF}_6)_2$ measured at $T = 0.02$ K. The spectra remain indistinguishable from this across the range of temperatures examined, $0.02 \text{ K} \leq T \leq 1 \text{ K}$.

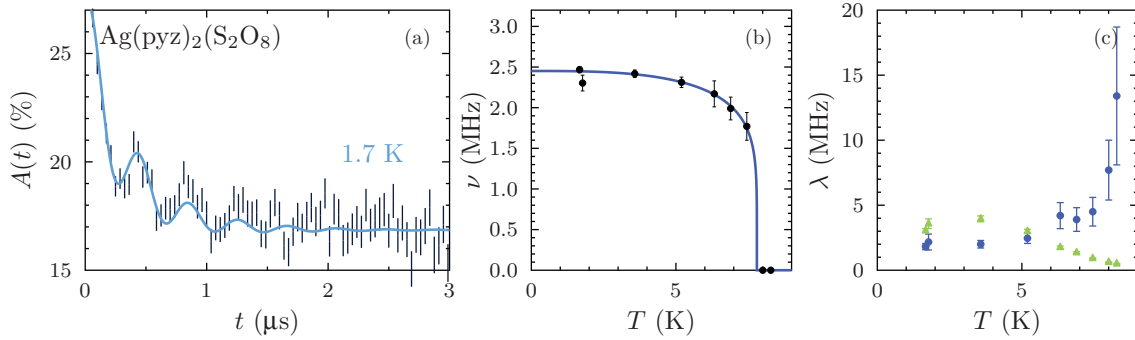


FIG. 17. (Color online) Example data and fits for $\text{Ag}(\text{pyz})_2(\text{S}_2\text{O}_8)$. From left to right: (a) shows sample asymmetry spectra $A(t)$ for $T < T_N$ along with a fit to Eq. (22); (b) shows the frequency as a function of temperature; and (c) shows relaxation rates λ_i as a function of temperature. Filled circles show the relaxation rate λ_1 , which relaxes the oscillation. The filled triangles correspond to the relaxation λ_2 .

bond length in the compound is sensitive to changes in temperature, care must be taken when comparing these values to those of the Cu family. Linearly interpolating the bond lengths for $[\text{Cu}(\text{HF}_2)(\text{pyz})_2]\text{SbF}_6$ at 9 K and 29 K to find an approximate value of the bond length at 19 K yields $r_{\mu-F}(T = 19 \text{ K}) = 0.1062 \pm 0.0002$ nm (where the error represents a combination of the statistical errors on the fits and variation recorded in thermometry, and is thus a lower bound), very similar to that measured for $[\text{Ni}(\text{HF}_2)(\text{pyz})_2]\text{SbF}_6$, $r_{\mu-F}(T = 19 \text{ K}) = 0.1068 \pm 0.0004$ nm.

In spite of being isostructural to the $[\text{Cu}(\text{HF}_2)(\text{pyz})_2]X$ systems, the dimensionality of these Ni variants is ambiguous. Susceptibility data fit acceptably to a number of models, and *ab initio* theoretical calculations are suggestive of one-dimensional behavior, dominated by the exchange along the bifluoride bridges. This is discussed more fully in Ref. 16.

VIII. DISCUSSION

Figure 20 collects the results from this paper and shows how isolation between two-dimensional layers varies over a variety of systems: those presented in this paper, molecular materials studied elsewhere, and inorganic materials. The primary axis is the experimental ratio T_N/J . Also shown are the ratios of the in-plane and inter-plane exchange interactions, J_{\perp}/J , and the correlation length at the transition, $\xi(T_N)/a$, extracted from fits to quantum Monte Carlo simulations. Of the materials in this paper, the least anisotropic is $[\text{Cu}(\text{pyo})_6](\text{BF}_4)_2$, whose low transition temperature is caused by a small exchange constant rather than particularly high exchange anisotropy. The members of the $[\text{Cu}(\text{HF}_2)(\text{pyz})_2]X$ family with octahedral anions have $k_B T_N/J \approx 0.33$, rather more than the $k_B T_N/J \approx 0.25$ shown by their counterparts with tetrahedral anions (as has been noted previously⁷). This

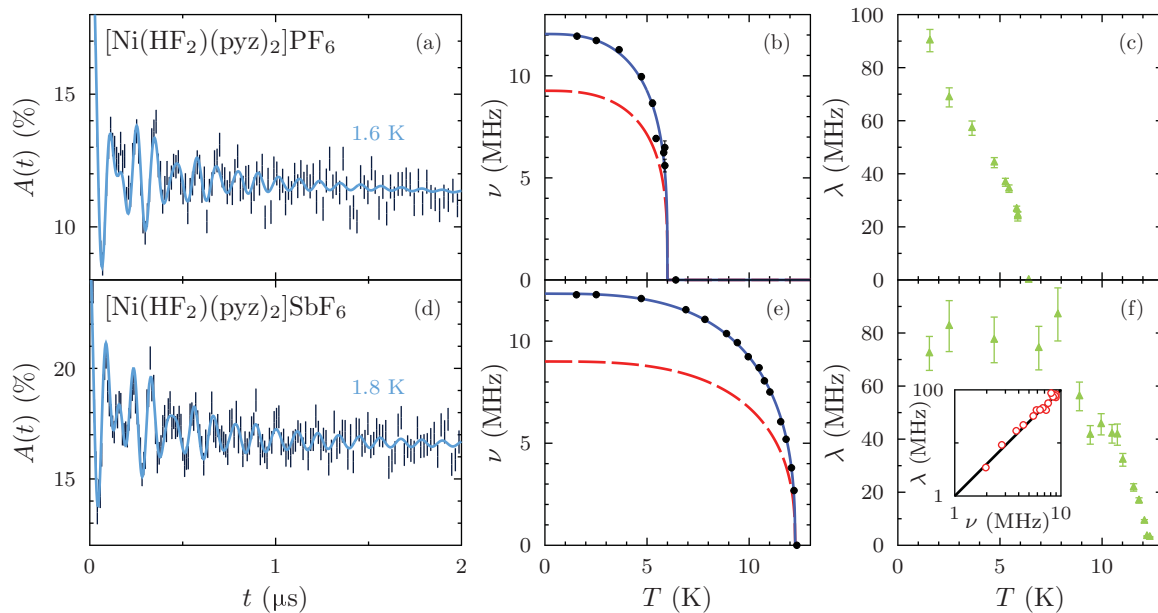


FIG. 18. (Color online) Example data and fits for $M = \text{Ni}$ magnets. From left to right: (a) and (d) show sample asymmetry spectra $A(t)$ for $T < T_N$ along with a fit to Eq. (3); (b) and (e) show frequencies as a function of temperature [no data points are shown for the second line because this frequency ν_2 was held in fixed proportion to the first, ν_1 (see text)]; and (c) and (f) show relaxation rate λ_3 as a function of temperature. In the $\nu(T)$ plot, error bars are included on the points but in most cases they are smaller than the marker being used. The inset in (f) shows $\nu_2 \equiv \nu$ plotted against $\lambda_3 \equiv \lambda$ on a log-log scale. The black line shows $\lambda = \nu^2$.

TABLE V. Fitted parameters for $M = \text{Ni}$ magnets. Errors shown are statistical uncertainties on fitting and thus represent lower bounds. Errors on $\text{Ni}\dots\text{PF}_6$ could not be estimated due to the fitting procedure (see text).

X	T_N (K)	ν_1 (MHz)	ν_2 (MHz)	λ_3 (MHz)	p_1	p_2	p_3	β	α
PF_6	6.0(4)	12.0	9.3	90	15	10	75	0.25(10)	2.8(2)
SbF_6	12.26(1)	12.3(1)	8.98(1)	80	25	10	65	0.34(4)	3.1(1)

makes the latter comparable to highly 2D molecular systems $[\text{Cu}(\text{pyz})_2](\text{ClO}_4)_2$ and $\text{CuF}_2(\text{H}_2\text{O})_2(\text{pyz})$, and the cuprate parent compound La_2CuO_4 . Below this, $[\text{Cu}(\text{pyo})_2(\text{pyz})_2](\text{PF}_6)_2$ exhibits a ratio $k_B T_N/J = 0.21(1)$. The prototypical inorganic 2D system $\text{Sr}_2\text{CuO}_2\text{Cl}_2$ exhibits $k_B T_N/J = 0.177 \pm 0.009$, and thus $\xi(T_N)/a = 280 \pm 90$. The most 2D material investigated in this paper, $\text{Ag}(\text{pyz})_2(\text{S}_2\text{O}_8)$, has $k_B T_N/J = 0.148 \pm 0.006$, implying $\xi(T_N)/a = 1000 \pm 300$, with the added benefit that the magnetic field required to probe its interactions is far closer to the range of fields achievable in the laboratory. By these measures, molecular magnets provide some excellent realizations of the 2DSLQHA, with $\text{Ag}(\text{pyz})_2(\text{S}_2\text{O}_8)$ being the best realization found to date.

Another method of examining the dimensionality of these systems is to consider their behavior in the critical region. The critical exponent β is a quantity frequently extracted in studies of magnetic materials, and it is often used to make inferences about the dimensionality of the system under study. In the critical region near a magnetic transition, an order parameter Φ , identical to the (staggered) magnetization, would be expected to vary as

$$\Phi(T) = \Phi_0 \left(1 - \frac{T}{T_N}\right)^\beta. \quad (25)$$

In simple, isotropic cases, the value of β depends on the dimensionality of the system, d , and that of the order parameter, D . For example, in the 3D Heisenberg model ($d = 3$, $D = 3$), $\beta = 0.367$, while in the 2D Ising model

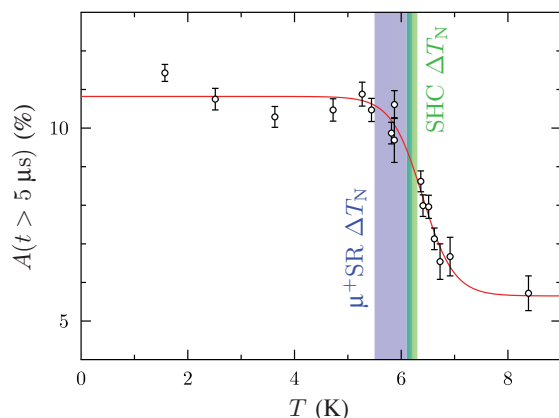


FIG. 19. (Color online) The asymmetry at late times $A(t > 5 \mu\text{s})$ measured in $\text{Ni}(\text{HF}_2)(\text{pyz})_2\text{PF}_6$ along with a fit to Eq. (24). Overlaid are regions corresponding to the range of values found by fitting the frequency of oscillations as a function of temperature with Eq. (4) ($5.5 \text{ K} \leq T_N \leq 6.2 \text{ K}$), and the value of the λ -like anomaly in specific-heat capacity (SHC) measurements with a representative error of 0.1 K ($6.1 \text{ K} \leq T_N \leq 6.3 \text{ K}$). The darker area represents the overlap between these regions.

($d = 2$, $D = 1$), $\beta = \frac{1}{8}$. Since the muon precession frequency is proportional to the local field, it is also proportional to the

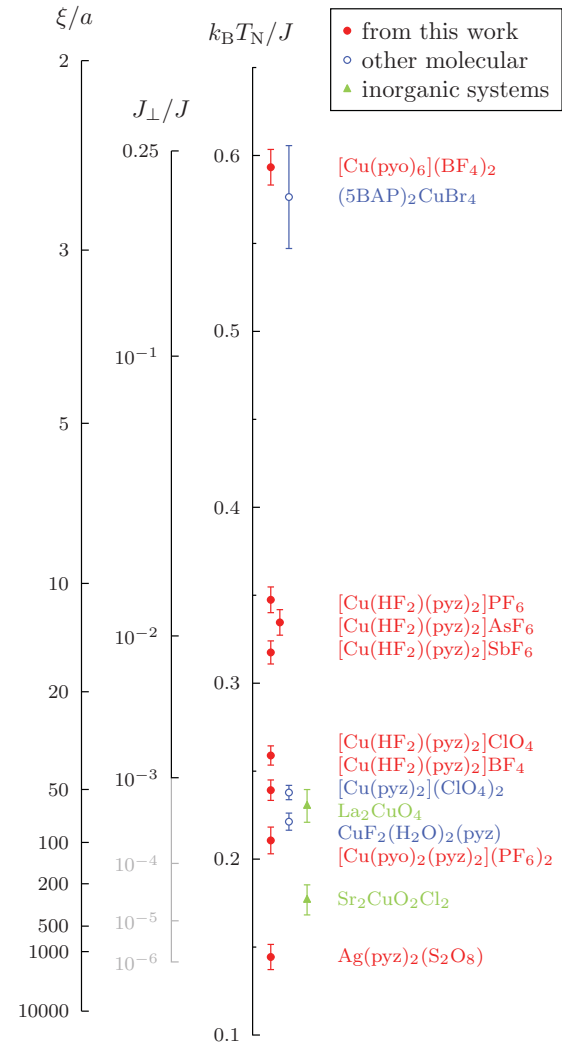


FIG. 20. (Color online) Quantification of the two-dimensionality of the materials in this paper and comparison with other notable 2DSLQHA systems. Filled circles show materials investigated in this paper; open circles show other molecular materials; and filled triangles show inorganic systems. The low dimensionality is parametrized first with the directly experimental ratio T_N/J , and then with predictions from quantum Monte Carlo simulations for both the exchange anisotropy, J_\perp/J [Eq. (6)], and the correlation length of an ideal 2D Heisenberg antiferromagnet with the measured J at a temperature T_N [Eq. (7)]. The grayed-out of the axis for J_\perp/J indicates where Eq. (6) is extrapolated beyond the range for which it was originally derived (Ref. 27). Values of T_N/J for the other materials were evaluated from Refs. 50–52.

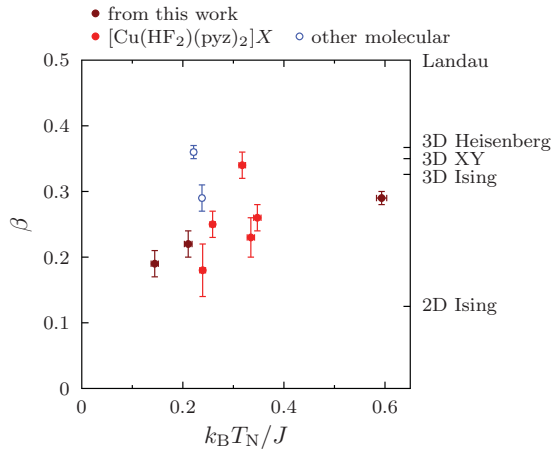


FIG. 21. (Color online) Critical exponent β , as commonly extracted from Eq. (4), plotted against the experimental ratio $k_B T_N / J$, indicative of exchange anisotropy. Bright filled circles indicate $[\text{Cu}(\text{HF}_2)(\text{pyz})_2]\text{X}$ materials examined in Sec. III, while darker circles indicate other materials studied in this work: $[\text{Cu}(\text{pyz})_2(\text{pyo})_2]\text{BF}_4$ (Sec. IV); $[\text{Cu}(\text{pyo})_6](\text{BF}_4)_2$ (Sec. V); $\text{Ag}(\text{pyz})_2(\text{S}_2\text{O}_8)$ (Sec. VI). Open circles indicate other molecular materials: $\text{CuF}_2(\text{H}_2\text{O})_2(\text{pyz})$ (Ref. 54); $[\text{Cu}(\text{pyz})_2](\text{ClO}_4)_2$ (Ref. 8).

moment on the magnetic ions in a crystal, and can be used as an effective order parameter. However, Eq. (25) would only be expected to hold true in the critical region. The extent of the critical region (defined as that region where simple mean-field theory does not apply) can be parametrized by the Ginzburg temperature T_G , which is related to the transition temperature T_c by⁵³

$$\frac{|T_G - T_c|}{T_c} = \left[\left(\frac{\xi}{a} \right)^d \left(\frac{\Delta C}{k_B} \right) \right]^{2/(d-4)}, \quad (26)$$

where d is the dimensionality, ξ is the correlation length, and ΔC is the discontinuity in the heat capacity. Quantum Monte Carlo simulations suggest⁵ that $\Delta C / k_B \approx J_\perp / J$. It follows that for $d = 3$, where $\Delta C / k_B \approx 1$, we have $|T_G - T_c| / T_c \approx (\xi/a)^{-6}$, giving rise to a narrow critical region. In two dimensions, we have $|T_G - T_c| / T_c \approx (\xi/a)^{-2} (\Delta C / k_B)^{-1}$. Anisotropic materials with small J_\perp / J only show a small heat capacity discontinuity, while ξ/a grows according to Eq. (7). This leads to a $|T_G - T_c| / T_c$ of order 1 for our materials, that is, a larger critical region for 2D (as compared to 3D) systems.

The large critical region in these materials allows meaningful critical parameters to be extracted from muon data. The simplest method of doing so is to fit the data to Eq. (4), as we have throughout this study; alternatively, critical scaling plots can be used (e.g., Ref. 18), which we have performed, finding the results are unchanged within error. Since β might be expected to give an indication of the dimensionality of the hydrodynamical fluctuations in these materials, a comparison between extracted β and exchange anisotropy parametrized by $k_B T_N / J$ is shown in Fig. 21. Members of the $[\text{Cu}(\text{HF}_2)(\text{pyz})_2]\text{X}$ family show some correlation between the critical exponent and the effective dimensionality but overall, the relationship is weak. This is probably because β , which is not a Hamiltonian parameter, is not simply a function of the dimensionality of the interactions, but probes the nature of the critical dynamics

(including propagating and diffusive modes) which could differ substantially between systems.

IX. CONCLUSIONS

We have presented a systematic study of muon-spin relaxation measurements on several families of quasi two-dimensional molecular antiferromagnets, comprising ligands of pyrazine, bifluoride, and pyridine-*N*-oxide; and the magnetic metal cations Cu^{2+} , Ag^{2+} , and Ni^{2+} . In each case $\mu^+\text{SR}$ has been shown to be sensitive to the transition temperature T_N , which is often difficult to unambiguously identify with specific-heat and magnetic-susceptibility measurements. We have combined these measurements with predictions of quantum Monte Carlo calculations to identify the extent to which each is a good realization of the 2DSLQHA model. The critical parameters derived from following the temperature evolution of the $\mu^+\text{SR}$ precession frequencies do not show a strong correlation with the degree of isolation of the 2D magnetic layers.

The analysis of magnetic ordering in zero applied field in terms of interlayer coupling J_\perp presented here does not take into account the effect of single-ion-type anisotropy on the magnetic order. This has been suggested to be important close to T_N in several examples of 2D molecular magnets¹¹ where it causes a crossover to XY-like behavior. In fact, its influence is confirmed in the nonmonotonic B - T phase diagram seen in $[\text{Cu}(\text{HF}_2)(\text{pyz})_2]\text{BF}_4$. It is likely that this is one factor that determines the ordering temperature of a system, although, as shown in Ref. 11, it is a smaller effect than the interlayer coupling parametrized by J_\perp . The future synthesis of single-crystal samples of these materials will allow the measurement of the single-ion anisotropies for the materials studied here.

The presence of muon-fluorine dipole-dipole oscillations allows the determination of some muon sites in these materials, although it appears from our results that these are not those that lead to magnetic oscillations. However, the $\text{F}\mu$ signal has been shown to be useful in identifying transitions at temperatures well above the magnetic ordering transition, which appear to have a structural origin. The fluorine oscillations hamper the study of dynamic fluctuations above T_N , which often appear as a residual relaxation on top of the dominant nuclear relaxation. It may be possible in future to use rf radiation to decouple the influence of the fluorine from the muon ensemble to allow muons to probe the dynamics.

The muon-spin precession signal, upon which much of the analysis presented here is based, is seen most strongly in the materials containing Cu^{2+} and is more heavily relaxed in the Ni^{2+} materials. This is likely due to the larger spin value in the Ni-containing materials. This is borne out by measurements on pyz-based materials containing Mn and Fe ions,⁵⁵ where no oscillations are observed, despite the presence of magnetic order shown unambiguously by other techniques. In the case of Mn-containing materials magnetic order is found with $\mu^+\text{SR}$ through a change in relative amplitudes of relaxing signals due to a difference in the nature of the relaxation on either side of the transition. It is likely, therefore, that muon studies of molecular magnetic materials containing ions with small spin quantum numbers will be most fruitful in the future.

Finally, the temperature dependence of the relaxation rates in these materials has been shown to be quite complex, reflecting the variety of muon sites in these systems. In

favorable cases these data could be used to probe critical behavior, such as critical slowing down, although the unambiguous identification of such behavior may be problematic.

Despite these limitations on the use of μ^+ SR in examining molecular magnetic systems of the type studied here, it is worth stressing that the technique still appears uniquely powerful in providing insights into the magnetic behavior of these materials and will certainly be useful in the future as a wealth of new systems are synthesized and the goal of microscopically engineering such materials is approached.

ACKNOWLEDGMENTS

This work was partly supported by the Engineering and Physical Sciences Research Council, UK. Experiments at the ISIS Pulsed Neutron and Muon Source were supported by

a beam-time allocation from the Science and Technology Facilities Council. Further experiments were performed at the Swiss Muon Source, Paul Scherrer Institute, Villigen, Switzerland. This research project has been supported by the European Commission under the 7th Framework Programme through the “Research Infrastructures” action of the “Capacities” Programme, Contract No. CP-CSA-INFRA-2008-1.1.1 Number 226507-NMI3. The work at EWU was supported by the National Science Foundation under Grant No. DMR-1005825. Work supported by UChicago Argonne, LLC, Operator of Argonne National Laboratory (“Argonne”). Argonne, a US Department of Energy Office of Science laboratory, is operated under Contract No. DE-AC02-06CH11357. The authors would like to thank Paul Goddard, Ross McDonald, William Hayes, and Johannes Möller for useful discussions.

¹E. Manousakis, *Rev. Mod. Phys.* **63**, 1 (1991).

²Note that in this model, the exchange energy in a bond between two parallel spins is $2J$. The sums are therefore over unconstrained values of i and j . They include an implicit factor of $\frac{1}{2}$ to prevent double-counting, leading to the form in Eq. (1).

³N. D. Mermin and H. Wagner, *Phys. Rev. Lett.* **17**, 1133 (1966).

⁴V. L. Berezinskii, *Sov. Phys. JETP* **32**, 493 (1971).

⁵P. Sengupta, A. W. Sandvik, and R. R. P. Singh, *Phys. Rev. B* **68**, 094423 (2003).

⁶S. J. Blundell, T. Lancaster, F. L. Pratt, P. J. Baker, M. L. Brooks, C. Baines, J. L. Manson, and C. P. Landee, *J. Phys. Chem. Solids* **68**, 2039 (2007).

⁷P. A. Goddard, J. Singleton, P. Sengupta, R. D. McDonald, T. Lancaster, S. J. Blundell, F. L. Pratt, S. Cox, N. Harrison, J. L. Manson, H. I. Southerland, and J. A. Schlueter, *New J. Phys.* **10**, 083025 (2008).

⁸T. Lancaster, S. J. Blundell, M. L. Brooks, P. J. Baker, F. L. Pratt, J. L. Manson, M. M. Conner, F. Xiao, C. P. Landee, F. A. Chaves, S. Soriano, M. A. Novak, T. P. Papageorgiou, A. D. Bianchi, T. Herrmannsdorfer, J. Wosnitza, and J. A. Schlueter, *Phys. Rev. B* **75**, 094421 (2007).

⁹T. Lancaster, S. J. Blundell, M. L. Brooks, P. J. Baker, F. L. Pratt, J. L. Manson, C. P. Landee, and C. Baines, *Phys. Rev. B* **73**, 020410 (2006).

¹⁰S. J. Blundell and F. L. Pratt, *J. Phys. Condens. Matter* **16**, R771 (2004).

¹¹F. Xiao, F. M. Woodward, C. P. Landee, M. M. Turnbull, C. Mielke, N. Harrison, T. Lancaster, S. J. Blundell, P. J. Baker, P. Babkevich, and F. L. Pratt, *Phys. Rev. B* **79**, 134412 (2009).

¹²P. Sengupta, C. D. Batista, R. D. McDonald, S. Cox, J. Singleton, L. Huang, T. P. Papageorgiou, O. Ignatchik, T. Herrmannsdorfer, J. L. Manson, J. A. Schlueter, K. A. Funk, and J. Wosnitza, *Phys. Rev. B* **79**, 060409 (2009).

¹³S. J. Blundell, *Contemp. Phys.* **40**, 175 (1999).

¹⁴J. L. Manson, M. M. Conner, J. A. Schlueter, T. Lancaster, S. J. Blundell, M. L. Brooks, F. L. Pratt, T. Papageorgiou, A. D. Bianchi, J. Wosnitza, and M.-H. Whangbo, *Chem. Commun.* 4894 (2006).

¹⁵J. L. Manson, J. A. Schlueter, K. A. Funk, H. I. Southerland, B. Twamley, T. Lancaster, S. J. Blundell, P. J. Baker, F. L. Pratt, J. Singleton, R. D. McDonald, P. A. Goddard, P. Sengupta,

C. D. Batista, L. Ding, C. Lee, M.-H. Whangbo, I. Franke, S. Cox, C. Baines, and D. Trial, *J. Am. Chem. Soc.* **131**, 6733 (2009).

¹⁶J. L. Manson, S. H. Lapidus, P. W. Stephens, P. K. Peterson, K. E. Carreiro, H. I. Southerland, T. Lancaster, S. J. Blundell, A. J. Steele, P. A. Goddard, F. L. Pratt, J. Singleton, Y. Kohama, R. D. McDonald, R. E. D. Sesto, N. A. Smith, J. Bendix, S. A. Zvyagin, J. Kang, C. Lee, M.-H. Whangbo, V. S. Zapf, and A. Plonczak, *Inorg. Chem.* **50**, 5990 (2011).

¹⁷R. S. Hayano, Y. J. Uemura, J. Imazato, N. Nishida, T. Yamazaki, and R. Kubo, *Phys. Rev. B* **20**, 850 (1979).

¹⁸F. L. Pratt, P. J. Baker, S. J. Blundell, T. Lancaster, M. A. Green, and M. Kurmoo, *Phys. Rev. Lett.* **99**, 017202 (2007).

¹⁹T. Lancaster, S. J. Blundell, D. Andreica, M. Janoschek, B. Roessli, S. N. Gvasaliya, K. Conder, E. Pomjakushina, M. L. Brooks, P. J. Baker, D. Prabhakaran, W. Hayes, and F. L. Pratt, *Phys. Rev. Lett.* **98**, 197203 (2007).

²⁰T. Lancaster, S. J. Blundell, F. L. Pratt, C. H. Gardiner, W. Hayes, and A. T. Boothroyd, *J. Phys. Condens. Matter* **15**, 8407 (2003).

²¹T. Lancaster, S. J. Blundell, F. L. Pratt, M. L. Brooks, J. L. Manson, E. K. Brechin, C. Cadiou, D. Low, E. J. L. McInnes, and R. E. P. Winpenny, *J. Phys. Condens. Matter* **16**, S4563 (2004).

²²T. Lancaster, S. J. Blundell, M. L. Brooks, P. J. Baker, F. L. Pratt, J. L. Manson, and C. Baines, *Phys. Rev. B* **73**, 172403 (2006).

²³J. Major, J. Mundy, M. Schmolz, A. Seeger, K. Döring, K. Fürderer, M. Gladisch, D. Herlach, and G. Majer, *Hyperfine Interact.* **31**, 259 (1986).

²⁴A. Amato, *Rev. Mod. Phys.* **69**, 1119 (1997).

²⁵J. Sugiyama, M. Månsson, Y. Ikeda, T. Goko, K. Mukai, D. Andreica, A. Amato, K. Ariyoshi, and T. Ohzuku, *Phys. Rev. B* **79**, 184411 (2009).

²⁶S. J. Blundell, *Magnetism in Condensed Matter* (Oxford University Press, Oxford, UK, 2001).

²⁷C. Yasuda, S. Todo, K. Hukushima, F. Alet, M. Keller, M. Troyer, and H. Takayama, *Phys. Rev. Lett.* **94**, 217201 (2005).

²⁸P. Hasenfratz and F. Niedermayer, *Phys. Lett. B* **268**, 231 (1991).

²⁹B. B. Beard, R. J. Birgeneau, M. Greven, and U.-J. Wiese, *Phys. Rev. Lett.* **80**, 1742 (1998).

³⁰M. A. Kastner, R. J. Birgeneau, G. Shirane, and Y. Endoh, *Rev. Mod. Phys.* **70**, 897 (1998).

- ³¹T. Lancaster, S. J. Blundell, P. J. Baker, M. L. Brooks, W. Hayes, F. L. Pratt, J. L. Manson, M. M. Conner, and J. A. Schlueter, *Phys. Rev. Lett.* **99**, 267601 (2007).
- ³²T. Lancaster, F. L. Pratt, S. J. Blundell, I. McKenzie, and H. E. Assender, *J. Phys. Condens. Matter* **21**, 346004 (2009).
- ³³J. H. Brewer, S. R. Kreitzman, D. R. Noakes, E. J. Ansaldo, D. R. Harshman, and R. Keitel, *Phys. Rev. B* **33**, 7813 (1986).
- ³⁴D. M. Grant and R. K. Harris (eds.), *Encyclopedia of Nuclear Magnetic Resonance*, Advances in NMR, Vol. 9 (Wiley, Chichester, UK, 2002).
- ³⁵J. L. Manson, J. A. Schlueter, K. A. Funk, H. I. Southerland, B. Twamley, T. Lancaster, S. J. Blundell, P. J. Baker, F. L. Pratt, J. Singleton, R. D. McDonald, P. A. Goddard, P. Sengupta, C. D. Batista, L. Ding, C. Lee, M.-H. Whangbo, I. Franke, S. Cox, C. Baines, and D. Trial, *J. Am. Chem. Soc.* **131**, 6733 (2009).
- ³⁶N. Tsyrlin, F. Xiao, A. Schneidewind, P. Link, H. M. Ronnow, J. Gavilano, C. P. Landee, M. M. Turnbull, and M. Kenzelmann, *Phys. Rev. B* **81**, 134409 (2010).
- ³⁷D. Sivia and J. Skilling, *Data Analysis: A Bayesian Tutorial*, 2nd ed. (Oxford University Press, Oxford, UK, 2006).
- ³⁸M. Reehuis, C. Ulrich, K. Prokes, A. Gozar, G. Blumberg, S. Komiya, Y. Ando, P. Pattison, and B. Keimer, *Phys. Rev. B* **73**, 144513 (2006).
- ³⁹S. Chakravarty, B. I. Halperin, and D. R. Nelson, *Phys. Rev. B* **39**, 2344 (1989).
- ⁴⁰O. I. Motrunich, *Phys. Rev. B* **72**, 045105 (2005).
- ⁴¹A. A. Katanin and A. P. Kampf, *Phys. Rev. B* **66**, 100403 (2002).
- ⁴²F. Lloret, G. De Munno, M. Julve, J. Cano, R. Ruiz, and A. Caneschi, *Angew. Chem. Int. Ed.* **37**, 135 (1998).
- ⁴³D. S. Middlemiss, L. M. Lawton, C. A. Morrison, and C. C. Wilson, *Chem. Phys. Lett.* **459**, 119 (2008).
- ⁴⁴H. A. Algra, L. J. de Jongh, and R. L. Carlin, *Physica B & C* **93**, 24 (1978).
- ⁴⁵D. Reinen and S. Krause, *Solid State Commun.* **29**, 691 (1979).
- ⁴⁶J. S. Wood, C. P. Keijzers, E. De Boer, and A. Buttafava, *Inorg. Chem.* **19**, 2213 (1980).
- ⁴⁷R. Burriel, A. Lambrecht, and R. L. Carlin, *J. Appl. Phys.* **67**, 5853 (1990).
- ⁴⁸J. L. Manson, K. H. Stone, H. I. Southerland, T. Lancaster, A. J. Steele, S. J. Blundell, F. L. Pratt, P. J. Baker, R. D. McDonald, P. Sengupta, J. Singleton, P. A. Goddard, C. Lee, M.-H. Whangbo, M. M. Warter, C. H. Mielke, and P. W. Stephens, *J. Am. Chem. Soc.* **131**, 4590 (2009).
- ⁴⁹R. A. Walton and R. W. Matthews, *Inorg. Chem.* **10**, 1433 (1971).
- ⁵⁰F. M. Woodward, C. P. Landee, J. Giantsidis, M. M. Turnbull, and C. Richardson, *Inorg. Chim. Acta* **324**, 324 (2001).
- ⁵¹M. Greven, R. J. Birgeneau, Y. Endoh, M. A. Kastner, M. Matsuda, and G. Shirane, *Z. Phys. B* **96**, 465 (1995).
- ⁵²G. Aeppli, S. M. Hayden, H. A. Mook, Z. Fisk, S.-W. Cheong, D. Rytz, J. P. Remeika, G. P. Espinosa, and A. S. Cooper, *Phys. Rev. Lett.* **62**, 2052 (1989).
- ⁵³P. M. Chaikin and T. C. Lubensky, *Principles of Condensed Matter Physics* (Cambridge University Press, Cambridge, UK, 1995).
- ⁵⁴J. L. Manson, M. M. Conner, J. A. Schlueter, A. C. McConnell, H. I. Southerland, I. Malfant, T. Lancaster, S. J. Blundell, M. L. Brooks, F. L. Pratt, J. Singleton, R. D. McDonald, C. Lee, and M.-H. Whangbo, *Chem. Mater.* **20**, 7408 (2008).
- ⁵⁵T. Lancaster, S. J. Blundell, M. L. Brooks, F. L. Pratt, and J. L. Manson, *Physica B* **374-375**, 118 (2006).