

Anisotropy in BaFe_2Se_3 single crystals with double chains of FeSe tetrahedra

Hechang Lei (雷和畅),¹ Hyejin Ryu (류혜진),^{1,2} Anatoly I. Frenkel,³ and C. Petrovic^{1,2}

¹*Condensed Matter Physics and Materials Science Department, Brookhaven National Laboratory, Upton, New York 11973, USA*

²*Department of Physics and Astronomy, Stony Brook University, Stony Brook, New York 11794-3800, USA*

³*Physics Department, Yeshiva University, 245 Lexington Avenue, New York, New York 10016, USA*

(Received 13 October 2011; revised manuscript received 15 November 2011; published 7 December 2011)

We studied the anisotropy in physical properties of $\text{Ba}_{1.00(4)}\text{Fe}_{1.9(1)}\text{Se}_{3.1(1)}$ single crystals. BaFe_2Se_3 is a semiconductor below 300 K. Magnetization measurements show that there is a crossover from short-range antiferromagnetic (AFM) correlations at room temperature to a long-range AFM order with $T_N = 255$ K. The anisotropy of magnetization is consistent with the previous neutron results. This crossover is supported by the heat-capacity measurement, where the phase-transition peak is absent at 255 K. The superconducting transition at about 10 K is likely due to the small amount of β -FeSe impurities.

DOI: [10.1103/PhysRevB.84.214511](https://doi.org/10.1103/PhysRevB.84.214511)

PACS number(s): 75.50.Ee, 75.10.Pq, 75.30.Gw, 75.47.Np

I. INTRODUCTION

Since the discovery of iron-based superconductors,¹ iron pnictide and chalcogenide materials have stimulated great interest. All iron-based superconductors show some structural similarity. From the initially discovered $\text{LaFeAsO}_{1-x}\text{F}_x$ to very recently reported $\text{K}_x\text{Fe}_{2-y}\text{Se}_2$ two-dimensional (2D) FePn or FeCh (Pn = pnictogens, Ch = chalcogens) tetrahedron layers are the common structural ingredient probably related to high-temperature superconductivity.^{1–5} However, the mechanism of superconductivity and its relation to the crystal structure motifs in these systems is still under debate. In order to fully understand the nature of the superconductivity, study of materials containing similar building blocks related to these systems is of significant interest.

On the other hand, the dimensionality of magnetic interactions and electronic transport is another important factor which will influence Fermi surface topology and magnetic ground state. For example, CaFe_4As_3 is a compound which is closely related to iron-based superconductors, but has a different dimensionality and spatial arrangement of similar FePn(Ch) local structural units. It contains an open three-dimensional (3D) channel-like network of shared FeAs tetrahedra with Ca atoms in the channels that run along the b axis of the orthorhombic cell.⁶ CaFe_4As_3 exhibits Fermi-liquid behavior with enhanced electron-electron correlations and antiferromagnetic (AFM) long-range order without superconductivity above 1.8 K.^{6,7} Another structurally related material is BaFe_2Se_3 , which contains one-dimensional (1D) double chains of edge-shared Fe-Se tetrahedra along the b axis.⁸ Studies of magnetic properties indicate that there is a crossover from short-range AFM correlation to long-range AFM order at around 250 K. However, the existence of a superconducting transition at the low temperature is still controversial.^{9,10}

In this paper, we report the detailed characterization of anisotropic physical properties and local crystal structure of $\text{Ba}_{1.00(4)}\text{Fe}_{1.9(1)}\text{Se}_{3.1(1)}$ single crystals. We show that this material is a semiconductor with long-range antiferromagnetic (AFM) order below $T_N = 255$ K.

II. EXPERIMENT

Single crystals of BaFe_2Se_3 were grown by the self-flux method with nominal composition Ba : Fe : Se = 1 : 2 : 3. Ba

pieces, Fe powder, and Se shot were mixed and put into the carbon crucible, then sealed into the quartz tube with partial pressure of argon. The quartz tube was annealed at 1150 °C for 24 h for homogenization, and then the ampoule was slowly cooled down to 750 °C with about 6 °C/h. Finally, the furnace was shut down and the ampoule was cooled down to room temperature naturally. Single crystals with typical size $5 \times 2 \times 1 \text{ mm}^3$ can be grown. The powder x-ray-diffraction (XRD) spectra were taken with Cu K_α radiation $\lambda = 1.5418 \text{ \AA}$ using a Rigaku miniflex x-ray machine. The orientation of crystal is determined using Bruker SMART APEX II single-crystal x-ray diffractometer. The average stoichiometry was determined by examination of multiple points using an energy-dispersive x-ray spectroscopy (EDX) in a JEOL JSM-6500 scanning electron microscope. The x-ray-absorption spectra of the Fe and Se K edges were taken in transmission mode on powder samples of BaFe_2Se_3 at the X18A beamline of the National Synchrotron Light Source. Standard procedure was used to extract the x-ray absorption near edge structure (XANES) and extended x-ray-absorption fine structure (EXAFS) from the absorption spectrum.¹¹ Standard Fe and Se metal foils and FeO, Fe_2O_3 , and Fe_3O_4 oxide powders were used for energy calibration and also for evaluating the valence states of Fe and Se ions. Electrical transport measurements were performed using a four-probe configuration. Thin Pt wires were attached to electrical contacts made of silver paste. Electrical transport, heat capacity, and magnetization measurements were carried out in Quantum Design PPMS-9 and MPMS-XL5.

III. RESULTS AND DISCUSSION

Powder XRD result and structural refinements of BaFe_2Se_3 using Rietica¹² [Fig. 1(a)] indicate that all reflections can be indexed in the $Pnma$ space group. The refined lattice parameters are $a = 11.940(2) \text{ \AA}$, $b = 5.444(1) \text{ \AA}$, and $c = 9.174(1) \text{ \AA}$, consistent with the values reported in literature.^{9,10} The crystal structure of BaFe_2Se_3 [Fig. 1(b)] can be depicted as alternate stacking of Fe-Se layers and Ba cations along the crystallographic a axis, similar to $\text{K}_x\text{Fe}_{2-y}\text{Se}_2$.⁵ However, in the Fe-Se plane, Fe-Se tetrahedra do not connect each other along two planar directions to form a two-dimensional (2D) infinite layer. Instead, they are broken along the c axis periodically and only one-dimensional (1D) double chains of edge-shared Fe-Se tetrahedra propagate along the b axis. The

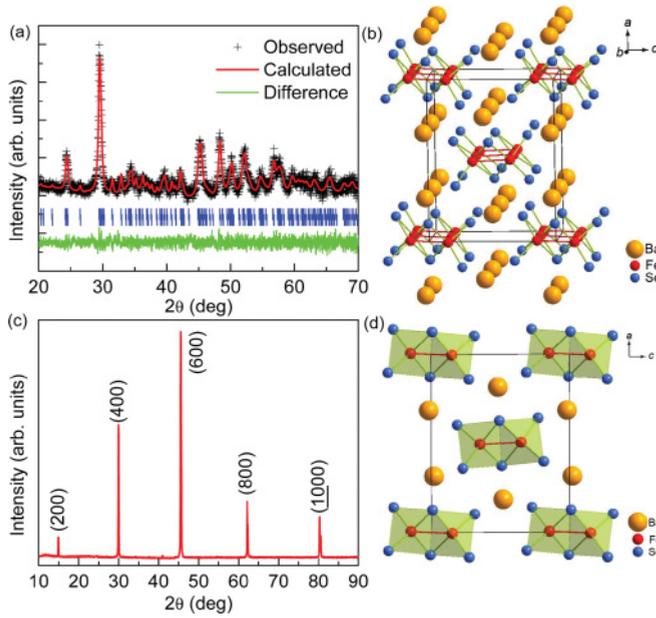


FIG. 1. (Color online) (a) Powder XRD patterns of BaFe_2Se_3 . (b) Crystal structure of BaFe_2Se_3 . The big orange, small red, and medium blue balls represent Ba, Fe, and Se ions. (c) Single crystal XRD of BaFe_2Se_3 . (d) The arrangement of double chains of edge-sharing Fe-Se tetrahedra along the b axis.

double chains are separated by Ba^{2+} ions and are slightly tilted off the bc plane. The tilting directions are opposite between the two neighboring layers as shown in Fig. 1(d). The shape of the BaFe_2Se_3 crystal is long plate like. The XRD pattern of a BaFe_2Se_3 crystal [Fig. 1(c)] reveals that the crystal surface is normal to the a axis with the plate-shaped surface parallel to the bc plane. Moreover, the b axis is along the long direction of crystal in the bc plane. The EDX spectrum of a single crystal confirms the presence of Ba, Fe, and Se. The average atomic ratios determined from EDX are Ba : Fe : Se = 1.00(4) : 1.9(1) : 3.1(1), close to the expected stoichiometric BaFe_2Se_3 ratio. Hence there are no vacancies on either Ba or Fe sites, which is different from $\text{K}_x\text{Fe}_{2-y}\text{Se}_2$.^{5,13}

The features of Fe K -edge XANES spectrum of BaFe_2Se_3 [Fig. 2(a)] are similar to FeSe_x .¹⁴ The prepeak A (~ 7112.5 eV) is due to either dipole or quadrupole $1s \rightarrow 3d$ transitions. The shoulder B with maximum absorption jump at ~ 7118.4 eV can be ascribed to the $1s \rightarrow 4p$ transition. When compared to the spectrum of FeO, the shoulder B is located at the lower energy side, suggesting that the valence of Fe is slightly smaller than $2+$. The valence of Fe is evaluated by linear interpolation of the energy of BaFe_2Se_3 with those of standards [Fe foil (metallic Fe), FeO (Fe^{2+}), and Fe_2O_3 (Fe^{3+})]. From the peak of first-derivative spectra corresponding to the maximum absorption jump, we obtain $\sim 1.87+$ for Fe valence, which is close to the value for FeSe_x .¹⁴ On the other hand, there are two features for Se K -edge XANES spectrum of BaFe_2Se_3 [Fig. 2(b)]. The feature C is mainly due to the $1s \rightarrow 4p$ dipole transition and the broad hump D should be a multiple scattering of the photoelectron with the near neighbors.¹⁵ By extrapolating the maximum absorption jumps of Se (~ 12659.2 eV) and SeO_2 (~ 12662 eV),¹⁴ we estimate

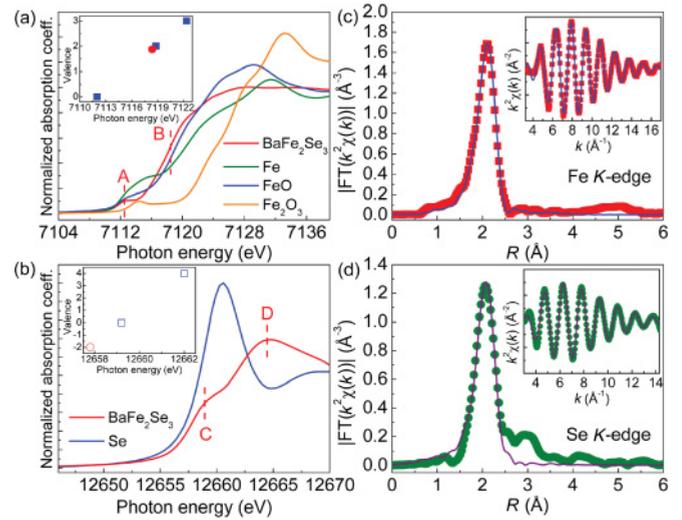


FIG. 2. (Color online) (a) Fe k -edge XANES spectra of BaFe_2Se_3 , Fe, FeO, and Fe_2O_3 measured at 300 K. The inset shows the valence states of Fe calculated from the first derivative of the XANES spectra. FT magnitudes of the EXAFS oscillations (symbols) for Fe k edge (c) and Se k edge (d). The model fits are shown as solid lines. The FTs are not corrected for the phase shifts and represent raw experimental data. Insets of (c) and (d) filtered EXAFS (symbols) with k -space model fits (solid line).

~ -1.98 for the Se valence, consistent with the formal value of Se ion ($2-$). For the Fe site, the nearest neighbors are four Se atoms [$1 \times \text{Se(I)}$, $2 \times \text{Se(II)}$, and $1 \times \text{Se(III)}$] with four different distances close to ~ 2.418 Å and the next nearest neighbors are three Fe atoms with almost the same distance (~ 2.723 Å).⁸ From the joint analysis of Fe and Se edges, EXAFS data using a single bond distance for Fe-Se and Fe-Fe, and by fitting the k range 3.2 – 18.4 Å⁻¹ for Fe K edge and 2 – 14 Å⁻¹ for Se K edge [main panels and insets of Figs. 2(c) and 2(d)], the fitted average Fe-Se and Fe-Fe bond lengths are $d_{\text{Fe-Se}} = 2.428(5)$ Å and $d_{\text{Fe-Fe}} = 2.71(5)$ Å. This is consistent with the reported values.⁸

Temperature dependence of the resistivity $\rho(T)$ of BaFe_2Se_3 crystal for $\mu_0 H = 0$ and 9 T indicates that this material is a semiconductor in the measured temperature region (Fig. 3). The room-temperature value $\rho(300$ K) is about 17 Ω cm, which is much larger than in BaFe_2S_3 (~ 0.35 Ω cm).¹⁶ Fits of the $\rho(T)$ at high temperature using the thermal activation model $\rho = \rho_0 \exp(E_a/k_B T)$, where ρ_0 is a prefactor, E_a is thermal activated energy, and k_B is Boltzmann's constant, gives $E_a = 0.178(1)$ eV in the temperature range above 170 K (inset in Fig. 3), which is also much larger than in BaFe_2S_3 .^{16,17} The larger room-temperature resistivity and E_a can be ascribed to the increase of structural distortion which might localize the carriers and increase the band gap when compared to BaFe_2S_3 .⁸ For BaFe_2S_3 , bond lengths are almost identical for all four Fe-S bonds, in contrast to very different bond lengths for BaFe_2Se_3 . Moreover, the Fe-Fe bond distances in a single chain are identical for BaFe_2S_3 , whereas they are different for BaFe_2Se_3 , where the longer and shorter bonds alternately connect along the b axis. All structural features imply that in the former compound the coordination polyhedron is more symmetric than in the latter.

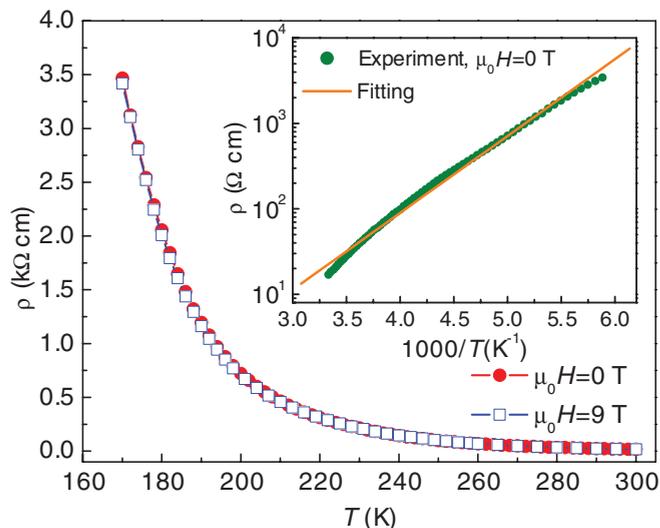


FIG. 3. (Color online) Temperature dependence of the resistivity $\rho(T)$ of the BaFe₂Se₃ crystal with $\mu_0 H = 0$ (closed red circle) and 9 T (open blue square, $H \parallel c$). Inset: Fitting result of $\rho(T)$ at zero field using the thermal activation model, where the red line is the fitting curve.

It should be noted that the shorter Fe-Fe bond in BaFe₂Se₃ may also have some contribution to higher conductivity. On the other hand, when compared to BaFe₂S₃, which exhibits negative magnetoresistance (MR) below 25 K,¹⁶ there is no obvious MR in BaFe₂Se₃ as shown in Fig. 3.

Temperature dependence of dc magnetic susceptibility $\chi(T)$ of BaFe₂Se₃ single crystal [Figs. 4(a), 4(b), and 4(c)] cannot be fitted using Curie-Weiss law up to 390 K. It decreases

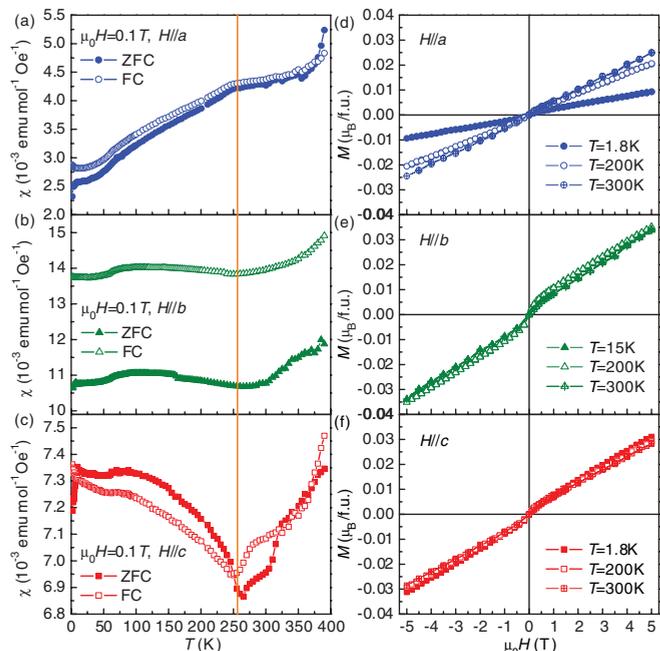


FIG. 4. (Color online) (a) Temperature dependence of dc magnetic susceptibility $\chi(T)$ below 300 K under ZFC and FC modes with the applied field $\mu_0 H = 0.1$ T along (a) a , (b) b , and (c) c axis. Isothermal magnetization hysteresis loops $M(H)$ for (d) $H \parallel a$, (e) $H \parallel b$, and (f) $H \parallel c$ at various temperatures.

with decreasing temperature for all field directions ($H \parallel a$, b , and c). It suggests that there is AFM interaction up to 390 K, in agreement with neutron results that found short-range correlations (SRC).^{9,10} Another characteristic in $\chi(T)$ curves is a transition appearing at about 255 K for all three field directions, which is ascribed to a crossover from short-range AFM correlation to long-range AFM order.^{9,10} It should be noted that the absolute $\chi_a(T)$ is much smaller than $\chi_b(T)$ and $\chi_c(T)$. Nevertheless, similar to $H \parallel b$, a Curie-like upturn in susceptibility is seen below 255 K for $H \parallel c$, while a faster drop is seen below 255 K for $H \parallel a$. It suggests that the easy axis of magnetization direction is a axis. According to mean-field theory for the collinear antiferromagnet, magnetic susceptibility along the easy-axis direction goes to zero for $T \rightarrow 0$, whereas perpendicular to the easy-axis magnetization direction is nearly constant below T_N . This is consistent with the neutron results.^{9,10} The small positive value of $\chi_a(T \rightarrow 0)$ is probably due to the presence of a van Vleck paramagnetism. A large diversity of susceptibilities between $H \parallel a$, $H \parallel b$, and $H \parallel c$ persisting up to 390 K suggests that there may be an intriguing anisotropy of SRC in the system. On the other hand, when the magnetic field was applied along the c axis, there is no obvious hysteresis between zero-field-cooled (ZFC) and field-cooled (FC) measurements. The lack of hysteresis suggests that the ferromagnetic component of magnetic interactions between the Fe chains along the c axis is very weak. This can be ascribed to the large Fe-Fe (or ferromagnetic Fe4 plaquette) interchain distance ($d_{\text{Fe-Fe}}^{\text{interchain}} \sim 6.441 \text{ \AA}$).⁸ In contrast, for $H \parallel b$, the ZFC

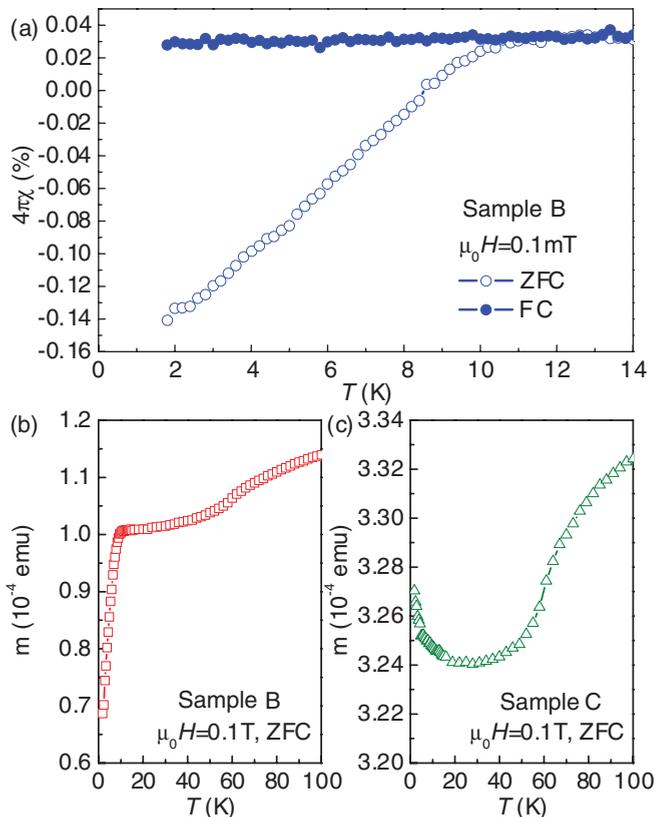


FIG. 5. (Color online) (a) $\chi(T)$ of sample B below 15 K under ZFC and FC modes with $\mu_0 H = 0.1$ mT. $\chi(T)$ below 100 K under ZFC mode with $\mu_0 H = 0.1$ T for (b) sample B and (c) sample C.

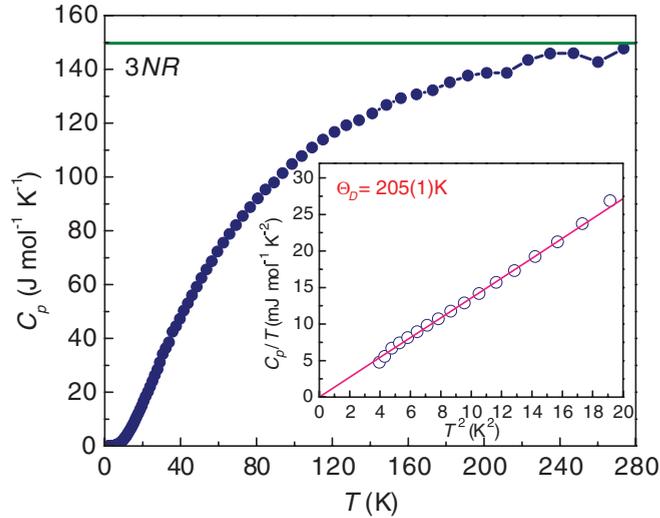


FIG. 6. (Color online) Temperature dependence of heat capacity for BaFe_2Se_3 crystal. The green solid line represents the classical value according to Dulong-Petit law at high temperature. Inset: the low-temperature specific-heat data in the plot of C_p/T vs T^2 . The red solid line is the fitting curve using formula $C_p/T = \beta T^2$.

and FC measurements exhibit significant hysteresis due to the fact of short Fe-Fe (or ferromagnetic Fe4 plaquette) intrachain distance ($d_{\text{Fe-Fe}}^{\text{intrachain}} \sim 2.720$ and 2.727 Å),⁸ resulting in strong magnetic interaction. The hysteresis between the ZFC and FC curves extends up to 390 K, suggesting that this intrachain interaction exists at temperatures above the long-range order.

Isothermal $M(H)$ for $H \parallel a$, $H \parallel b$, and $H \parallel c$ [Figs. 4(d), 4(e), and 4(f)] at various temperatures show that there is no hysteresis for all three field directions, which confirms the AFM order in the system and excludes the ferromagnetic impurities. For $H \parallel a$, the slopes of $M(H)$ increase with increasing temperature, but for the other two directions, $M(H)$ curves are almost unchanged, consistent with the $M(T)$ results. Moreover, the slopes of $M(H)$ are $H \parallel b > H \parallel c > H \parallel a$ for all of measured temperatures, corresponding to the increase of paramagnetic moment when magnetic field is rotated from a toward c and then toward the b axis, as shown Figs. 4(a), 4(b), and 4(c).

On the other hand, there is a small drop at about 10 K. This is also observed in a previous paper and might correspond to the superconducting transition.⁹ In order to clarify whether this transition is extrinsic or intrinsic, we measured the other two samples from the same batch. As shown in Figs. 5(a) and 5(b), sample B exhibits a similar drop at about 10 K for $\mu_0 H = 0.1$ mT and 0.1 T, but the superconducting volume fraction is only about 0.15% at 1.8 K for $\mu_0 H = 0.1$ mT. On the other hand, sample C does not show any drop below 15 K for $\mu_0 H = 0.1$ T. These results imply that this superconducting transition should be extrinsic and coming

from residual β -FeSe in the melt. Moreover, the transition temperature (~ 10 K) is close to the T_c of β -FeSe (~ 8.5 K and up to ~ 36.7 K at 8.9 GPa).¹⁸ Thus a small drop at about 10 K might be ascribed to the residual amount of β -FeSe impurities.

The heat capacity C_p of the BaFe_2Se_3 crystal approaches the classic value of $3NR$ at 300 K, where N is the atomic number in the chemical formula ($N = 6$) and R is the gas constant ($R = 8.314$ J mol⁻¹ K⁻¹), consistent with the Dulong-Petit law (Fig. 6). At the low temperature, $C_p(T)$ curve can be fitted solely by a cubic term βT^3 (inset of Fig. 6). From the fitted value of $\beta = 1.357(6)$ mJ mol⁻¹ K⁻⁴, the Debye temperature is estimated to be $\Theta_D = 205(1)$ K using the formula $\Theta_D = (12\pi^4 NR/5\beta)^{1/3}$. This is slightly smaller than Θ_D of $\text{K}_x\text{Fe}_{2-y}\text{Se}_2$, which might be due to the larger atomic mass of Ba than K.¹⁹ On the other hand, there is no λ -type anomaly for BaFe_2Se_3 at the temperature of magnetic transitions ($T_N = 255$ K). This can be ascribed to the overwhelming release of magnetic entropy due to existence of SRC above the long-range order at T_N .¹⁰ This is also consistent with the absence of Curie-Weiss law in $M(T)$ [Figs. 4(a), 4(b), and 4(c)].

IV. CONCLUSION

In summary, we studied the physical properties of $\text{Ba}_{1.00(4)}\text{Fe}_{1.9(1)}\text{Se}_{3.1(1)}$ single crystals with 1D double chains of edge-shared Fe-Se tetrahedra parallel to the b axis. Composition analysis indicates that all crystallographic sites are fully occupied. XANES result shows that the valence of Fe is about 1.87+. Taken together with transport, magnetic, and thermodynamic properties, this indicates that the BaFe_2Se_3 is a semiconductor with a short-range AFM correlation at room temperature and a long-range AFM order below 255 K. The anisotropy of magnetization is consistent with magnetic structure determined from neutron results previously. This is rather similar to parent materials of Fe-based superconductors; however, the absence of appreciable conductivity coincides with the absence of connected infinite 2D Fe-Se planar tetrahedra.

ACKNOWLEDGMENTS

We are grateful to Kefeng Wang for helpful discussions. We thank John Warren for help with scanning electron microscopy measurements and Qi Wang for help with XAFS measurements. Work at Brookhaven is supported by the US DOE under Contract No. DE-AC02-98CH10886 and in part by the Center for Emergent Superconductivity, an Energy Frontier Research Center funded by the US DOE, Office for Basic Energy Science. A.I.F. acknowledges support by US Department of Energy Grant No. DE-FG02-03ER15476. Beamline X18A at the NSLS is supported in part by the US Department of Energy Grant No. DE-FG02-05ER15688.

¹Y. Kamihara, T. Watanabe, M. Hirano, and H. Hosono, *J. Am. Chem. Soc.* **130**, 3296 (2008).

²M. Rotter, M. Tegel, and D. Johrendt, *Phys. Rev. Lett.* **101**, 107006 (2008).

³X. C. Wang, Q. Q. Liu, Y. X. Lv, W. B. Gao, L. X. Yang, R. C. Yu, F. Y. Li, and C. Q. Jin, *Solid State Commun.* **148**, 538 (2008).

⁴F. C. Hsu, J. Y. Luo, K. W. Yeh, T. K. Chen, T. W. Huang, P. M. Wu, Y. C. Lee, Y. L. Huang, Y. Y. Chu, D. C. Yan,

- and M. K. Wu, *Proc. Natl. Acad. Sci. USA* **105**, 14262 (2008).
- ⁵J. Guo, S. Jin, G. Wang, S. Wang, K. Zhu, T. Zhou, M. He, and X. Chen, *Phys. Rev. B* **82**, 180520(R) (2010).
- ⁶I. Todorov, D. Y. Chung, C. D. Malliakas, Q. Li, T. Bakas, A. Douvalis, G. Trimarchi, K. Gray, J. F. Mitchell, A. J. Freeman, and M. G. Kanatzidis, *J. Am. Chem. Soc.* **131**, 5405 (2009).
- ⁷L. L. Zhao, T. H. Yi, J. C. Fettinger, S. M. Kauzlarich, and E. Morosan, *Phys. Rev. B* **80**, 020404(R) (2009).
- ⁸H. Y. Hong and H. Steinfink, *J. Solid State Chem.* **5**, 93 (1972).
- ⁹A. Krzton-Maziopa, E. Pomjakushina, V. Pomjakushin, D. Sheptyakov, D. Chernyshov, V. Svitlyk, and K. Conder, *J. Phys. Condens. Matter* **23**, 402201 (2011).
- ¹⁰J. M. Caron, J. R. Neilson, D. C. Miller, A. Llobet, and T. M. McQueen, *Phys. Rev. B* **84**, 180409(R) (2011).
- ¹¹R. Prins and D. Koningsberger, *X-ray Absorption: Principles, Applications, Techniques of EXAFS, SEXAFS, XANES* (Wiley, New York, 1988).
- ¹²B. Hunter, “Rietica—A visual Rietveld program.” International Union of Crystallography Commission on Powder Diffraction Newsletter No. 20 (Summer 1998) [<http://www.rietica.org>].
- ¹³H. C. Lei and C. Petrovic, *Phys. Rev. B* **83**, 184504 (2011).
- ¹⁴C. L. Chen, S. M. Rao, C. L. Dong, J. L. Chen, T. W. Huang, B. H. Mok, M. C. Ling, W. C. Wang, C. L. Chang, T. S. Chan, J. F. Lee, J.-H. Guo, and M. K. Wu, *Europhys. Lett.* **93**, 47003 (2011).
- ¹⁵B. Joseph, A. Iadecola, L. Simonelli, Y. Mizuguchi, Y. Takano, T. Mizokawa, and N. L. Saini, *J. Phys. Condens. Matter* **22**, 485702 (2010).
- ¹⁶Z. S. Gönen, P. Fournier, V. Smolyaninova, R. Greene, F. M. Araujo-Moreira, and B. Eichhorn, *Chem. Mater.* **12**, 3331 (2000).
- ¹⁷W. M. Reiff, I. E. Grey, A. Fan, Z. Eliezer, and H. Steinfink, *J. Solid State Chem.* **13**, 32 (1975).
- ¹⁸S. Medvedev, T. M. McQueen, I. A. Troyan, T. Palasyuk, M. I. Erements, R. J. Cava, S. Naghavi, F. Casper, V. Ksenofontov, G. Wortmann, and C. Felser, *Nat. Mater.* **8**, 630 (2009).
- ¹⁹B. Zeng, B. Shen, G. F. Chen, J. B. He, D. M. Wang, C. H. Li, and H. H. Wen, *Phys. Rev. B* **83**, 144511 (2011).