

Possible triplet superconductivity in the quasi-one-dimensional conductor $\text{Li}_{0.9}\text{Mo}_6\text{O}_{17}$

A. G. Lebed* and O. Sepper

Department of Physics, University of Arizona, 1118 East 4th Street, Tucson, Arizona 85721, USA

(Received 23 October 2012; published 27 March 2013)

We consider a theoretical problem of the upper critical magnetic field parallel to a conducting axis of a quasi-one-dimensional layered superconductor. We show that the orbital effects against superconductivity in a magnetic field are capable of destroying the superconducting phase at low temperatures if the interplane distance is less than the corresponding coherence length. Applications of our results to recent experiments, performed in the superconductor $\text{Li}_{0.9}\text{Mo}_6\text{O}_{17}$ [J.-F. Mercure *et al.*, *Phys. Rev. Lett.* **108**, 187003 (2012)], provide strong arguments in favor of a triplet superconducting pairing in this quasi-one-dimensional layered conductor.

DOI: [10.1103/PhysRevB.87.100511](https://doi.org/10.1103/PhysRevB.87.100511)

PACS number(s): 74.78.-w, 74.20.-z, 74.25.Ha, 74.70.Kn

Quasi-one-dimensional (Q1D) superconductors have been intensively studied since the discovery of superconductivity in the organic superconductor $(\text{TMTSF})_2\text{PF}_6$.^{1,2} Early experiments,²⁻⁵ performed on the Q1D superconductors $(\text{TMTSF})_2X$ ($X = \text{PF}_6$ and ClO_4), provided hints of their unconventional nature. In addition to possible triplet pairing,⁶⁻¹⁰ it was proposed that Q1D superconductors can demonstrate such unusual phenomena as reentrant superconductivity,⁷⁻¹⁰ the Larkin-Ovchinnikov-Fulde-Ferrell (LOFF) phase,^{2,7-15} and hidden reentrant superconductivity.¹⁵ Although triplet superconducting pairing was considered as the most probable mechanism for many years, more recent experiments^{12,16} and theories^{15,17} are in favor of a d -wave-like superconducting pairing in the $(\text{TMTSF})_2\text{ClO}_4$ conductor. As for the $(\text{TMTSF})_2\text{PF}_6$ conductor, the question of possible triplet superconducting pairing^{6,7,10,18-20} is still not completely resolved. Triplet superconductivity is a rather unusual phenomenon. In our opinion, it has been firmly established in the heavy fermion superconductor UPt_3 (Ref. 21) and most likely exists in the Sr_2RuO_4 (Refs. 22 and 23) and ferromagnetic superconductors.²⁴

In this intriguing situation, it is important that a novel, strong candidate for triplet superconductivity—the Q1D layered superconductor $\text{Li}_{0.9}\text{Mo}_6\text{O}_{17}$ —has been very recently suggested.²⁵ As shown in experiments,²⁵ the upper critical magnetic field, parallel to a conducting axis of this superconductor, is five times larger than the so-called Clogston-Chandrasekhar paramagnetic limit for singlet superconductivity.²⁶ A distinctive feature of the measurements in Ref. 25 is that the paramagnetic limit for the superconductor $\text{Li}_{0.9}\text{Mo}_6\text{O}_{17}$, $H_p = 3.1$ T, has been extracted from direct measurements of the Pauli susceptibility and specific heat jump (see also Refs. 27 and 28). Therefore, it does not depend on the details of a theoretical model. As also shown in Ref. 25, the above-mentioned superconductor is in the clean limit and, thus, the spin-orbital scattering cannot be responsible for the extremely large experimental value of the upper critical magnetic field along the conducting axis, $H_{c2}^x \simeq 15$ T. These facts would posit strong arguments in favor of the existence of a triplet superconducting phase in the $\text{Li}_{0.9}\text{Mo}_6\text{O}_{17}$, making it insensitive to decoupling Pauli paramagnetic effects. However, as mentioned in Ref. 25, orbital destructive effects are minimized when the magnetic field is parallel to a conducting axis of a Q1D superconductor. Therefore, it is stressed in Ref. 25 that the experimentally

observed destruction of superconductivity at $H > H_{c2}^x \simeq 15$ T can only be ascribed to Pauli paramagnetic effects, which is not in favor of the above-mentioned triplet scenario of superconductivity.

The goal of our Rapid Communication is to show theoretically the following nontrivial fact: The orbital effects can destroy superconductivity at low temperatures even for a magnetic field, applied parallel to a conducting axis of a Q1D layered superconductor, provided that the interplane distance is less than the corresponding coherence length. By extracting electronic band and superconducting phase parameters from measurements in Ref. 25, we show that the above condition holds for the Q1D layered superconductor $\text{Li}_{0.9}\text{Mo}_6\text{O}_{17}$. We consider our results as a step in establishing triplet superconductivity in the above-discussed superconductor.

Let us consider a tight-binding model for the electron spectrum of a Q1D layered conductor,

$$\epsilon(\mathbf{p}) = -2t_x \cos(p_x a_x) - 2t_y \cos(p_y a_y) - 2t_z \cos(p_z a_z), \quad (1)$$

where $t_x \gg t_y \gg t_z$ are overlap integrals of the electron wave functions along the \mathbf{x} , \mathbf{y} , and \mathbf{z} crystallographic axes, respectively. In a magnetic field,

$$\mathbf{H} = (H, 0, 0), \quad \mathbf{A} = (0, 0, H_y), \quad (2)$$

parallel to the conducting chains of the Q1D layered conductor (1), it is convenient to write the electron wave function with a definite energy and momentum component p_x in the following way:

$$\psi_{\epsilon, p_x}^{\pm}(x, y, z) = \exp(\pm i p_x x) \exp[\pm i p_y^{\pm}(p_x) y] \phi_{\epsilon, p_x}^{\pm}(y, z). \quad (3)$$

Note that, in Eq. (3), $+$ ($-$) corresponds to the left (right) sheet of the Q1D Fermi surface (FS), and the functions $p_y^{\pm}(p_x)$ are defined by the following equations:

$$v_F(p_x \mp p_F) \mp 2t_y \cos[p_y^{\pm}(p_x) a_y] = 0, \quad (4)$$

where v_F and p_F are the Fermi velocity and Fermi momentum, respectively. In this case, we can linearize Eq. (1) near two sheets of a Q1D FS in the following way:

$$\delta\epsilon^{\pm}(\mathbf{p}) = \pm 2t_y a_y [p_y - p_y^{\pm}(p_x)] \sin[p_y^{\pm}(p_x) a_y] - 2t_z \cos(p_z a_z), \quad (5)$$

where electron energy, $\delta\epsilon = \epsilon - \epsilon_F$, is counted from the Fermi energy ϵ_F .

In a magnetic field, we use the Peierls substitution method for Eq. (5), $p_y - p_y^{\pm}(p_x) \rightarrow -id/dy$, $p_z a_z \rightarrow p_z a_z - \omega_z y/v_F$,

where $\omega_z = eHv_F a_z/c$, e is the electron charge, and c is the velocity of light. As a result, we obtain the following Schrödinger-like equation for the electron wave functions in the mixed (y, p_z) representation:

$$\left\{ \mp i v_y [p_y^\pm(p_x)] \frac{d}{dy} - 2t_z \cos\left(p_z a_z - \frac{\omega_z}{v_F} y\right) - 2\mu_B s H \right\} \phi_{\epsilon, p_x}^\pm(y, p_z) = \delta\epsilon \phi_{\epsilon, p_x}^\pm(y, p_z), \quad (6)$$

with s being the projection of an electron spin on the \mathbf{x} axis; μ_B is the Bohr magneton, $v_y [p_y^\pm(p_x)] = 2t_y a_y \sin[p_y^\pm(p_x) a_y]$. Note that Eq. (6) can be solved exactly:

$$\begin{aligned} \phi_{\epsilon, p_x}^\pm(y, p_z) &= \exp\left\{ \frac{\pm i \delta\epsilon y}{v_y [p_y^\pm(p_x)]} \right\} \exp\left\{ \frac{\pm 2i \mu_B s H y}{v_y [p_y^\pm(p_x)]} \right\} \\ &\times \exp\left\{ \pm i \frac{2t_z}{v_y [p_y^\pm(p_x)]} \int_0^y \cos\left(p_z a_z - \frac{\omega_z}{v_F} u\right) du \right\}. \quad (7) \end{aligned}$$

It is important that the finite temperature Green's functions for the wave functions (7) and (3) can be determined by the standard equation²⁹

$$\begin{aligned} g_{i\omega_n}^\pm(x, x_1; y, y_1; p_z) &= \int_{-\infty}^{+\infty} d(\delta\epsilon) [\psi_{\epsilon, p_x}^\pm(x_1, y_1, p_z)]^* \\ &\times \psi_{\epsilon, p_x}^\pm(x, y, p_z) / (i\omega_n - \delta\epsilon), \quad (8) \end{aligned}$$

where ω_n is the so-called Matsubara frequency.

In this Rapid Communication, we consider the simplest triplet scenario of superconductivity in the $\text{Li}_{0.9}\text{Mo}_6\text{O}_{17}$, where superconducting pairing is not sensitive to Pauli paramagnetic effects.⁷

$$\hat{\Delta}(p_x, y) = \hat{I} \text{sgn}(p_x) \Delta(y), \quad (9)$$

where \hat{I} is a unit matrix in spin space, $\text{sgn}(p_x)$ changes the sign of a triplet superconducting order parameter on two slightly corrugated sheets of the Q1D FS, and $\Delta(y)$ takes into account the orbital destructive effects against superconductivity in a magnetic field. It is important that the triplet order parameter (9) corresponds to a fully gapped Q1D FS (4), which is in qualitative agreement with the experimentally observed large specific heat jump in the $\text{Li}_{0.9}\text{Mo}_6\text{O}_{17}$ superconductor (see Ref. 27). To derive the gap equation for the superconducting order parameter $\Delta(y)$, we use Gor'kov's equations for unconventional superconductivity.^{30–32} As a result of the calculations, we obtain

$$\begin{aligned} \Delta(y) &= g \left\langle \int_{|y-y_1| > \frac{|v_y(p_y)|}{\Omega}} \frac{2\pi T dy_1}{v_y(p_y) \sinh\left[\frac{2\pi T |y-y_1|}{v_y(p_y)}\right]} \Delta(y_1) \right. \\ &\times J_0 \left\{ \frac{8t_z v_F}{\omega_z v_y(p_y)} \sin\left[\frac{\omega_z(y-y_1)}{2v_F}\right] \right. \\ &\left. \left. \times \sin\left[\frac{\omega_z(y+y_1)}{2v_F}\right] \right\} \right\rangle_{p_y}, \quad (10) \end{aligned}$$

where $\langle \dots \rangle_{p_y}$ stands for the averaging procedure over momentum p_y , g is the electron coupling constant, and Ω is the cutoff energy. [We pay attention that Eq. (10) is completely different from the main equation of Ref. 7, since the former

describes destruction of superconductivity in a magnetic field, parallel (not perpendicular) to a conducting axis. As a result, it contains an extra integration with respect to the electron momentum component p_y .]

Note that Eq. (10) is very general. For instance, at high magnetic fields and/or low temperatures, it describes the exotic reentrant superconducting phase, introduced for a different direction of the magnetic field in Ref. 7. Analysis of Eq. (10) shows that we can disregard the reentrant superconductivity effects at high enough temperatures,

$$T \geq T^*(H) \simeq \frac{\omega_z(H) v_y^0}{2\pi^2 v_F}, \quad (11)$$

and low enough magnetic fields,

$$\omega_z(H) \ll \frac{8t_z v_F}{v_y^0}, \quad (12)$$

where $v_y^0 = 2t_y a_y$. It is possible to show that Eq. (10) can be rewritten under the conditions (11) and (12) in the following way:

$$\begin{aligned} \Delta(y) &= g \left\langle \int_{|y-y_1| > \frac{|v_y(p_y)|}{\Omega}} \frac{2\pi T dy_1}{v_y(p_y) \sinh\left[\frac{2\pi T |y-y_1|}{v_y(p_y)}\right]} \right. \\ &\times J_0 \left\{ \frac{4t_z(y-y_1)}{v_y(p_y)} \sin\left[\frac{\omega_z(y+y_1)}{2v_F}\right] \right\} \Delta(y_1) \left. \right\rangle_{p_y}. \quad (13) \end{aligned}$$

It is important that Eq. (13) is still rather general. In fact, it describes both the so-called Lawrence-Doniach (LD) model^{33,34} and anisotropic three-dimensional (3D) superconductivity. As mentioned in Ref. 25, the LD model condition, $\xi_z \ll a_z/\sqrt{2}$, is not obeyed in the superconductor $\text{Li}_{0.9}\text{Mo}_6\text{O}_{17}$ and, as we show below, it is possible to simplify Eq. (13) to describe anisotropic 3D superconductivity:

$$\begin{aligned} \Delta(y) &= g \left\langle \int_{|y-y_1| > \frac{|v_y(p_y)|}{\Omega}} \frac{2\pi T dy_1}{v_y(p_y) \sinh\left[\frac{2\pi T |y-y_1|}{v_y(p_y)}\right]} \right. \\ &\times J_0 \left[\frac{2t_z \omega_z (y^2 - y_1^2)}{v_y(p_y) v_F} \right] \Delta(y_1) \left. \right\rangle_{p_y}. \quad (14) \end{aligned}$$

[Note that, in a physically different situation (i.e., for a quasi-two-dimensional case), the transition from the most general quantum gap equation—in our case, Eq. (10)—to a simplified quasiclassical gap equation—in our case, Eq. (14)—was made in Ref. 35 and partially discussed in Ref. 36.] In Eq. (14), it is convenient to perform the following transformation of the variable y_1 : $y_1 - y = z v_y(p_y)/v_F$. As a result, Eq. (14) can be rewritten as

$$\begin{aligned} \Delta(y) &= g \left\langle \int_{|z| > \frac{v_F}{\Omega}} \frac{2\pi T dz}{v_F \sinh\left[\frac{2\pi T z}{v_F}\right]} \Delta\left[y + \frac{v_y(p_y)}{v_F} z\right] \right. \\ &\times J_0 \left\{ \frac{2t_z \omega_z}{v_F^2} z \left[2y + \frac{v_y(p_y)}{v_F} z \right] \right\} \left. \right\rangle_{p_y}. \quad (15) \end{aligned}$$

It is possible to show that in the vicinity of the superconducting transition temperature, $(T_c - T) \ll T_c$, Eq. (15) leads to the

TABLE I. Electron spectrum and superconducting parameters.

$\text{Li}_{0.9}\text{Mo}_6\text{O}_{17}$	\hat{x}	\hat{y}	\hat{z}
a_i (Å)	5.53	12.73	9.51
ξ_i (Å)	426	77	20
t_i (K)		41	14
v_i (cm/s) $\times 10^6$	$v_F = 5.3$	1.4	0.25

Ginzburg-Landau (GL) formula for the upper critical field,

$$H_{c2}^x(T) = \frac{4\pi^2 c \hbar T_c^2}{7\zeta(3) e t_y t_z a_y a_z} \left(\frac{T_c - T}{T_c} \right), \quad (16)$$

where $\zeta(x)$ is the Riemann zeta function. We note that the GL slopes for the magnetic field applied perpendicular to the conducting axis of a Q1D layered superconductor were derived in Refs. 37 and 38. Using the results of Ref. 38, we can write

$$H_{c2}^y(T) = \frac{4\sqrt{2}\pi^2 c T_c^2}{7\zeta(3) e v_F t_z a_z} \left(\frac{T_c - T}{T_c} \right), \quad (17)$$

$$H_{c2}^z(T) = \frac{4\sqrt{2}\pi^2 c T_c^2}{7\zeta(3) e v_F t_y a_y} \left(\frac{T_c - T}{T_c} \right), \quad (18)$$

where the GL coherence lengths along the x , y , and z crystallographical axes are

$$\xi_x^2 = \frac{7\zeta(3) v_F^2 \hbar^2}{16(\pi T_c)^2}, \quad \xi_y^2 = \frac{7\zeta(3) t_y^2 a_y^2}{8(\pi T_c)^2}, \quad \xi_z^2 = \frac{7\zeta(3) t_z^2 a_z^2}{8(\pi T_c)^2}. \quad (19)$$

From Eqs. (16)–(19) and experimental data,²⁵ $H_{c2}^x(0) \simeq 22$ T, $H_{c2}^y(0) \simeq 4$ T, $H_{c2}^z(0) \simeq 1$ T, it is possible to estimate the parameters of the Q1D layered electron spectrum (1), (4), (5), and the coherence lengths (19). They are summarized in Table I.

We note that the above-mentioned parameters, deduced from the experimental low temperature behavior of the $H_{c2}^x(T)$, are similar but a little bit different from those deduced in Ref. 25 from the slopes of the upper critical fields near the superconducting transition temperature, $T_c \simeq 2.2$ K.

By using data from Table I and Eqs. (11) and (12), we can estimate the region of temperatures and magnetic fields where Eq. (13) is valid. As a result, we obtain $T \geq T^* \simeq 0.06$ K and $H \ll 300$ T, conditions which are well satisfied in experiment.²⁵ As already mentioned in Ref. 25 and as seen from Table I, in the $\text{Li}_{0.9}\text{Mo}_6\text{O}_{17}$ superconductor, $\xi_z \simeq 20$ Å $> a_z/\sqrt{2} = 6.7$ Å. Thus, the LD model is not applicable and we can use Eqs. (14) and (15) for anisotropic 3D superconductivity. We note that Eqs. (14) and (15) are qualitatively different from the gap equations for a 3D isotropic case,^{39,40} since the former take into account Q1D topology of the FS (4) and (5). In particular, a typical solution of Eq. (15) at low temperatures, $T \ll T_c \simeq 2.2$ K, changes its sign with changing coordinate y , in contrast to the 3D isotropic case, as shown in Fig. 1. We solve Eq. (15) numerically in the range of temperatures $T_c \geq T \gg T^*$ and compare the obtained temperature dependence of the upper critical magnetic field $H_{c2}^x(T)$ with the experimental data²⁵ in Fig. 2. As seen from Fig. 2, the calculated dependence of $H_{c2}^x(T)$ is in good

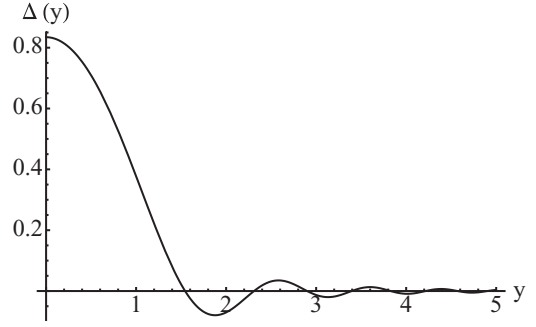


FIG. 1. Solution of Eq. (15) at $T = 0.1$ K is an oscillatory function of the coordinate y . The solution is normalized by the following condition: $\int_{-\infty}^{+\infty} \Delta^2(y) dy = 1$.

qualitative and quantitative agreement with the experimental results.

To summarize, we have explained theoretically the observed destruction of superconductivity in the Q1D layered superconductor $\text{Li}_{0.9}\text{Mo}_6\text{O}_{17}$ in a magnetic field parallel to its conducting axis,²⁵ in the framework of a triplet superconductivity scenario. We have also suggested the most probable triplet order parameter [see Eq. (9)]. It corresponds to the absence of Pauli paramagnetic destructive effects against superconductivity and is qualitatively consistent with a large value of the experimentally observed specific heat jump at the superconducting transition at $H = 0$.²⁷ (Note that from the microscopic point of view, the triplet phase can be stabilized in a Q1D superconductor as a result of repulsive interchain electron-electron interactions.^{41–43}) We also recall that the Clogston-Chandrasekhar paramagnetic limiting field, $H_p \simeq 3$ T, was deduced in Ref. 25 without using any concrete theoretical model and thus was firmly established. Therefore, it is not realistic to expect that a singlet superconductivity scenario with the possible LOFF phase formation can explain the experimentally observed result that exceeds by five times the paramagnetic limit in $\text{Li}_{0.9}\text{Mo}_6\text{O}_{17}$. Moreover, the calculations,¹³ performed for a presumably singlet superconductor $(\text{TMTSF})_2\text{ClO}_4$ in a similar experimental geometry, show a less than two times increase of H_p due to the LOFF phase formation.

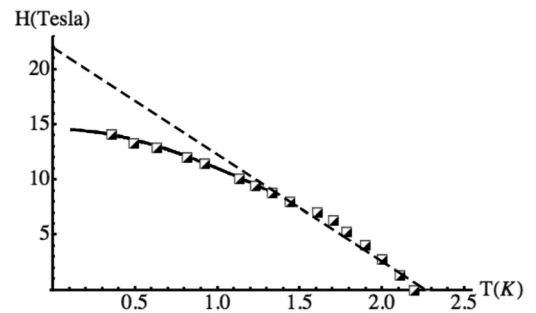


FIG. 2. Temperature dependence of the upper critical magnetic field $H_{c2}^x(T)$, numerically calculated from Eq. (15) at low enough temperatures, is shown by a solid line. The Ginzburg-Landau linear dependence (16), which is valid at $T_c - T \ll T_c$, is shown by a dashed line. Rectangles represent the experimental data (Ref. 25).

Below, we would like to discuss the applicability of the Fermi liquid (FL) approach we have used in the Rapid Communication to describe the superconducting phase transition in $\text{Li}_{0.9}\text{Mo}_6\text{O}_{17}$. First, we note that at high enough temperatures, the Luttinger liquid effects are observed^{44–46} in the $\text{Li}_{0.9}\text{Mo}_6\text{O}_{17}$ conductor. This naturally reflects the Q1D nature of its electron spectrum (4) and (5) and is not crucial for our analysis, since we consider the low temperature region, $T < T_c = 2.2$ K. In this context, it is important that from a theoretical point of view, the FL picture is restored at temperatures lower than $t_z, t_y \simeq 10\text{--}45$ K. Another point of concern is the experimentally observed increase of resistivity at $T \leq T_{\min} \simeq 15\text{--}30$ K. So far, its nature has not been clearly understood. At present, there exist two most popular competing points of view

on this resistivity increase phenomenon: localization effects,⁴⁷ and the possible partial charge-density-wave instability or the corresponding fluctuations.^{48,49} Nevertheless, we stress that there are two experimental features²⁵ which are important for the validity of our analysis. The first one is based on the fact that the noted increase in resistivity is of the order of $\delta\rho/\rho \simeq 0.25$ (Ref. 25) and is thus small. The second feature is that the magnetoresistance at $T \simeq 4$ K, as shown in Ref. 25, demonstrates quadratic behavior, $\delta\rho(H)/\rho(0) \sim H^2$, which is a direct test of the FL theory.

One of us (A.G.L.) is thankful to N. N. Bagmet and N. E. Hussey for useful discussions. This work was supported by the NSF under Grant No. DMR-1104512.

*Also at L. D. Landau Institute for Theoretical Physics, RAS, 2 Kosyгина Street, Moscow 117334, Russia.

¹D. Jerome, A. Mazaud, M. Ribault, and K. Bechgaard, *J. Phys. (Paris) Lett.* **41**, L95 (1980).

²*The Physics of Organic Superconductors and Conductors*, edited by A. G. Lebed (Springer, Berlin, 2008).

³M. Y. Choi, P. M. Chaikin, S. Z. Huang, P. Haen, E. M. Engler, and R. L. Greene, *Phys. Rev. B* **25**, 6208 (1982).

⁴S. Bouffard, M. Ribault, R. Brussetti *et al.*, *J. Phys. C* **15**, 2651 (1982).

⁵M. Takigawa, H. Yasuoka, and G. Saito, *J. Phys. Soc. Jpn.* **56**, 873 (1987).

⁶A. A. Abrikosov, *J. Low Temp. Phys.* **53**, 359 (1983).

⁷A. G. Lebed, *JETP Lett.* **44**, 114 (1986) [*Pis'ma Zh. Eksp. Teor. Fiz.* **44**, 89 (1986)].

⁸N. Dupuis, G. Montambaux, and C. A. R. Sa de Melo, *Phys. Rev. Lett.* **70**, 2613 (1993).

⁹I. J. Lee, M. J. Naughton, G. M. Danner, and P. M. Chaikin, *Phys. Rev. Lett.* **78**, 3555 (1997).

¹⁰A. G. Lebed, *Phys. Rev. B* **59**, R721 (1999); A. G. Lebed, K. Machida, and M. Ozaki, *ibid.* **62**, R795 (2000).

¹¹A. I. Buzdin and V. V. Tugushev, *Zh. Eksp. Teor. Phys.* **85**, 735 (1983) [*Sov. Phys. JETP* **58**, 428 (1983)].

¹²S. Yonezawa, S. Kusaba, Y. Maeno, P. Auban-Senzier, C. Pasquier, K. Bechgaard, and D. Jérôme, *Phys. Rev. Lett.* **100**, 117002 (2008).

¹³A. G. Lebed and S. Wu, *Phys. Rev. B* **82**, 172504 (2010).

¹⁴M. D. Croitoru, M. Houzet, and A. I. Buzdin, *Phys. Rev. Lett.* **108**, 207005 (2012).

¹⁵A. G. Lebed, *Phys. Rev. Lett.* **107**, 087004 (2011); *Physica B* **407**, 1803 (2012); *JETP Lett.* **94**, 382 (2011).

¹⁶J. Shinagawa, Y. Kurosaki, F. Zhang, C. Parker, S. E. Brown, D. Jérôme, J. B. Christensen, and K. Bechgaard, *Phys. Rev. Lett.* **98**, 147002 (2007).

¹⁷C. Bourbonnais and A. Sedeki, *Phys. Rev. B* **80**, 085105 (2009).

¹⁸I. J. Lee, S. E. Brown, W. G. Clark, M. J. Strouse, M. J. Naughton, W. Kang, and P. M. Chaikin, *Phys. Rev. Lett.* **88**, 017004 (2001).

¹⁹I. J. Lee, P. M. Chaikin, and M. J. Naughton, *Phys. Rev. B* **62**, R14669 (2000).

²⁰N. Belmehri, G. Abramovici, and M. Heritier, *Europhys. Lett.* **82**, 47009 (2008).

²¹H. Tou, Y. Kitaoka, K. Ishida, K. Asayama, N. Kimura, Y. Onuki, E. Yamamoto, Y. Haga, and K. Maezawa, *Phys. Rev. Lett.* **80**, 3129 (1998).

²²T. M. Rice and M. Sigrist, *J. Phys.: Condens. Matter* **7**, L643 (1995).

²³A. P. Mackenzie and Y. Maeno, *Rev. Mod. Phys.* **75**, 657 (2003).

²⁴K. Machida and T. Ohmi, *Phys. Rev. Lett.* **86**, 850 (2001); K. V. Samokhin and M. B. Walker, *Phys. Rev. B* **66**, 174501 (2002).

²⁵J.-F. Mercure, A. F. Bangura, Xiaofeng Xu, N. Wakeham, A. Carrington, P. Walmsley, M. Greenblatt, and N. E. Hussey, *Phys. Rev. Lett.* **108**, 187003 (2012).

²⁶A. M. Clogston, *Phys. Rev. Lett.* **9**, 266 (1962); B. S. Chandrasekhar, *Appl. Phys. Lett.* **1**, 7 (1962).

²⁷See Supplemental Material for Ref. 25 at <http://link.aps.org/supplemental/10.1103/PhysRevLett.108.187003> for details.

²⁸F. Zuo, J. S. Brooks, R. H. McKenzie, J. A. Schlueter, and J. M. Williams, *Phys. Rev. B* **61**, 750 (2000).

²⁹A. A. Abrikosov, L. P. Gor'kov, and I. E. Dzyaloshinski, *Methods of Quantum Field Theory in Statistical Physics* (Dover, New York, 1975).

³⁰V. P. Mineev and K. V. Samokhin, *Introduction to Unconventional Superconductivity* (Gordon and Breach, Amsterdam, 1999).

³¹M. Sigrist and K. Ueda, *Rev. Mod. Phys.* **63**, 239 (1991).

³²A. G. Lebed and K. Yamaji, *Phys. Rev. Lett.* **80**, 2697 (1998).

³³L. N. Bulaevskii, *Sov. Phys. JETP* **38**, 634 (1974).

³⁴R. A. Klemm, A. Luther, and M. R. Beasley, *Phys. Rev. B* **12**, 877 (1975).

³⁵A. G. Lebed and N. Hayashi, *Physica C* **341–348**, 1677 (2000).

³⁶V. P. Mineev, *J. Phys. Soc. Jpn.* **69**, 3371 (2000).

³⁷L. P. Gor'kov and D. Jerome, *J. Phys. (Paris) Lett.* **46**, L643 (1985).

³⁸A. G. Lebed, *JETP Lett.* **94**, 689 (2011).

³⁹L. P. Gor'kov, *Zh. Eksp. Teor. Fiz.* **37**, 833 (1959) [*Sov. Phys. JETP* **10**, 593 (1960)].

⁴⁰N. R. Werthamer, E. Helfand, and P. C. Hohenberg, *Phys. Rev.* **147**, 295 (1966).

⁴¹J. C. Nickel, R. Duprat, C. Bourbonnais, and N. Dupuis, *Phys. Rev. Lett.* **95**, 247001 (2005).

⁴²K. Kuroki, R. Arita, and H. Aoki, *Phys. Rev. B* **63**, 094509 (2001).

⁴³Y. Fuseya and Y. Suzumura, *J. Phys. Soc. Jpn.* **74**, 1263 (2005).

⁴⁴F. Wang, J. V. Alvarez, S.-K. Mo, J. W. Allen, G.-H. Gweon, J. He, R. Jin, D. Mandrus, and H. Hochst, *Phys. Rev. Lett.* **96**, 196403 (2006).

- ⁴⁵C. A. M. dos Santos, B. D. White, Y.-K. Yu, J. J. Neumeier, and J. A. Souza, *Phys. Rev. Lett.* **98**, 266405 (2007).
- ⁴⁶N. Wakeham, A. F. Bangura, X. Xu, J.-F. Mercure, M. Greenblatt, and N. E. Hussey, *Nat. Commun.* **2**, 396 (2011).
- ⁴⁷M. Sato, Y. Matsuda, and H. Fukuyama, *J. Phys. C* **20**, L137 (1987).
- ⁴⁸X. Xu, A. F. Bangura, J. G. Analytis, J. D. Fletcher, M. M. J. French, N. Shannon, J. He, S. Zhang, D. Mandrus, R. Jin, and N. E. Hussey, *Phys. Rev. Lett.* **102**, 206602 (2009).
- ⁴⁹Note that, in a quarter-filled Q1D conductor, a charge-density-wave phase can coexist with a spin-density-wave one, as shown in S. Mazumdar, S. Ramasesha, R. T. Clay, and D. K. Campbell, *Phys. Rev. Lett.* **82**, 1522 (1999).