

Nonequilibrium theory of tunneling into a localized state in a superconductor

Ivar Martin¹ and Dmitry Mozyrsky²

¹*Materials Science Division, Argonne National Laboratory, Argonne, Illinois 60439, USA*

²*Theoretical Division, Los Alamos National Laboratory, Los Alamos, New Mexico 87545, USA*

(Received 5 February 2014; revised manuscript received 28 August 2014; published 25 September 2014)

A single static magnetic impurity in a fully gapped superconductor leads to the formation of an intragap quasiparticle bound state. At temperatures much below the superconducting transition, the energy relaxation and spin dephasing of the state are expected to be exponentially suppressed. The presence of such a state can be detected in electron tunneling experiments as a pair of conductance peaks at positive and negative biases. Here we show that, for an arbitrarily weak tunneling strength, the peaks have to be symmetric with respect to the applied bias. This is in contrast to the standard result in which the tunneling conductance is proportional to the local (in general, particle-hole asymmetric) density of states. The asymmetry can be recovered if one allows for either a finite density of impurity states, or if impurities are coupled to another, nonsuperconducting, equilibrium bath.

DOI: [10.1103/PhysRevB.90.100508](https://doi.org/10.1103/PhysRevB.90.100508)

PACS number(s): 05.60.Gg, 03.67.Lx, 73.50.Td, 74.50.+r

Introduction. Conventional *s*-wave superconductors are remarkably robust with respect to nonmagnetic disorder [1]: The potential scattering of electrons does not significantly affect either the superconducting gap or the transition temperature. On the other hand, even weak magnetic impurities have been found to be strongly Cooper pair breaking, leading to a rapid suppression of superconductivity [2].

An exact treatment of a quantum magnetic impurity in a superconductor is a complex problem [3]. However, in the case when the magnetic moment can be treated as static (approximately the case for atoms with large spin *S* or when conduction electrons only couple to one of the components of the spin), within the BCS approximation, the problem is easily solvable. The key result is the appearance of a localized, so-called Yu-Shiba-Rusinov (YSR) quasiparticle state [4–6]. For a finite density of impurities, these states fill the superconducting gap, eventually destroying superconductivity.

The presence of YSR-like states in superconductors has been confirmed by tunneling experiments [7,8] [see Fig. 1(a)]. The metal-insulator-superconductor junction experiment of Ref. [7] on Mn doped Pb revealed a $\sigma(V) = dI/dV$ that is symmetric with respect to the reversal of applied bias (particle-hole symmetry), with a clearly visible intragap peak whose energy and width remained approximately constant but the intensity grew with increasing Mn concentration. Remarkably, the normal-tip scanning tunneling microscopy (STM) experiment of Ref. [8], which allows for focusing on individual magnetic ions of Mn or Gd on the surface of superconducting Nb, showed particle-hole asymmetric $\sigma(V)$. The asymmetry was attributed to the asymmetry in the particle and the hole content of the Bogoliubov quasiparticle associated with the YSR state. This, however, raises a question of why no such asymmetry had been observed in the earlier tunnel junction experiment [7].

It is interesting to note that individual YSR states bear a strong resemblance to the localized impurity, e.g., donor, states in semiconductors. Each donor or acceptor state in a semiconductor can be populated by at most two electrons (including spin). Consequently, if one were to perform a tunneling experiment in a semiconductor, as long as the bias is insufficient to inject carries into the conduction or valence band, the dc current will remain zero, e.g., after the tunneling

electrons populate the initially unoccupied localized states, the current has to stop. What makes the YSR states different? Just as in a semiconductor, the individual YSR states are infinitely sharp resonances, since there are no continuum states that they could hybridize with. Therefore, it would seem that continuous tunneling into YSR states should be impossible, in conflict with the experimental observations. That YSR assumes classical impurity cannot be the issue, since even for a quantum impurity, the spectrum has only one bound quasiparticle state associated with every impurity [3]. The reason that the intragap tunneling through the localized states in a superconductor is possible lies in the ability of a superconductor to violate the particle conservation law: While it is impossible to introduce a single electron with subgap energy into the bulk of a superconductor, *two* injected electrons with zero total energy can be absorbed by the condensate [9].

This problem can be analyzed by means of a nonequilibrium Green's function formalism for superconductors [10]. However, here we will follow a more physically transparent approach, valid in the case of singlet superconductors: By applying a partial particle-hole transformation, we convert the problem of tunneling from a metallic tip to a YSR state into the problem of tunneling between two nonsuperconducting spinless reservoirs through a single resonant level [Fig. 1(b)]. Each transfer of a spinless particle between the reservoirs in the equivalent model corresponds to the transfer of a pair of electrons between the metallic tip and the superconductor. This mapping allows us to see immediately that for a single impurity $\sigma(V)$ has to be symmetric, regardless of the local particle-hole content of the YSR state. The origin of this surprising result is that since in the absence of coupling to the tip the YSR state has zero energy width, any arbitrarily weak perturbation can drive it out of equilibrium. The height of the peaks in $\sigma(V)$ is of the order of conductance quantum, $G_0 = 2e^2/h$. In contrast, the standard approach for calculating the tunneling conductance assumes that the YSR remains in equilibrium with the superconductor, leading to the erroneous conclusion that for a single magnetic impurity the tunneling conductance is simply proportional to the tunneling density of states [11].

Why do some experiments show a symmetric tunneling density of states [7], and others do not [8]? The reason for the observed asymmetry in Ref. [8] most likely lies in

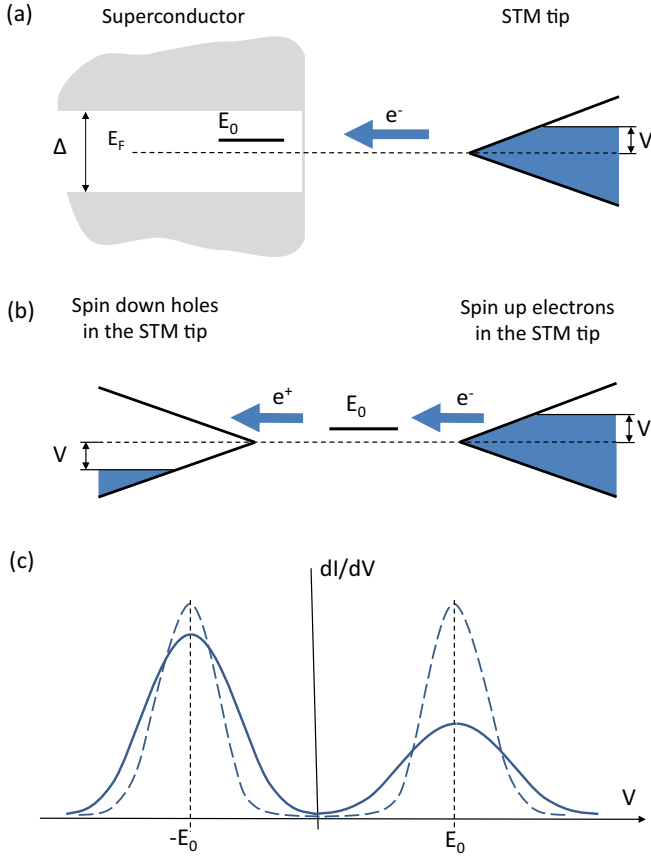


FIG. 1. (Color online) (a) Schematic representation of the problem: Electrons from an STM tip tunnel into a superconductor containing a single YSR state. (b) Effective representation after the particle-hole transformation on the spin-down tip electrons is performed. (c) Differential conductance of the system. The punctured line is the conductance of an “ideal” system, i.e., when the broadening is caused by the coupling to the STM tip only. The solid line accounts for the “extrinsic” broadening by an extra bath (other impurities or additional normal reservoir).

the broadening of the resonant level due to the presence of other nearby magnetic impurities, which allows electrons to tunnel into multiple YSR states simultaneously, or due to an additional relaxation channel for YSR states. The latter can be modeled as a metallic reservoir that remains in equilibrium with the superconductor and thus can easily absorb quasiparticles injected into the YSR state. We will explicitly model this possibility here.

Model. The Hamiltonian for an s -wave superconductor with a magnetic impurity is [5]

$$H = H_{\text{BCS}} + H_{\text{imp}}, \quad (1)$$

$$H_{\text{BCS}} = \int dr \left[\sum_{\alpha} \psi_{\alpha}(r)^{\dagger} \left(-\frac{\nabla^2}{2m} - \mu \right) \psi_{\alpha}(r) + \Delta_0 \psi_{\uparrow}(r)^{\dagger} \psi_{\downarrow}(r)^{\dagger} + \Delta_0 \psi_{\downarrow}(r) \psi_{\uparrow}(r) \right], \quad (2)$$

$$H_{\text{imp}} = JS[\psi_{\uparrow}(0)^{\dagger} \psi_{\uparrow}(0) - \psi_{\downarrow}(0)^{\dagger} \psi_{\downarrow}(0)]. \quad (3)$$

Here, $\psi_{\alpha}(r)$ is the annihilation operator for an electron with spin α at location r , m is the mass of the electron, and Δ_0 is the unperturbed value of the superconducting order parameter (assumed real and positive for concreteness). For the impurity we assume a classical moment of size S polarized in the positive z direction (in the continuum limit the value of the coupling constant J is related to the atomic value by the factor of the unit cell volume a^3). This Hamiltonian can be diagonalized by the Bogoliubov quasiparticles [12] γ_n , which satisfy $[H, \gamma_n^{\dagger}] = E_n \gamma_n^{\dagger}$ and can be expressed in terms of the electronic operators as

$$\gamma_n = \int dr [u_n(r) \psi_{\uparrow}(r) + v_n(r) \psi_{\downarrow}^{\dagger}(r)]. \quad (4)$$

The solution of the Bogoliubov equations for $u(r)$ and $v(r)$ reveals that a static magnetic impurity leads to the formation of a localized state inside the superconducting gap [6], with the energy

$$E_0 = -\Delta_0 \operatorname{sgn}(J) \frac{1 - (\pi N_0 J)^2}{1 + (\pi N_0 J)^2}, \quad (5)$$

and (u, v) that oscillate with the Fermi wave vector and decay in space as $\exp(-r/\tilde{\xi})/r$. The exponential decay is governed by the length $\tilde{\xi} = v_F / \sqrt{\Delta_0^2 - E_0^2}$. Here v_F is the Fermi velocity and N_0 is the normal-state density of states in the superconductor. In general, $u(r) \neq v(r)$.

In addition to the localized states, there is a continuum of Bogoliubov’s quasiparticles both for $E_n > \Delta_0$ and $E_n < -\Delta_0$. The fermion operators can be expanded in terms of all Bogoliubov quasiparticles as $\psi_{\uparrow}(r) = \sum_n u_n(r) \gamma_n$ and $\psi_{\downarrow}^{\dagger}(r) = \sum_n v_n(r) \gamma_n$. Hence, the local density of electronic states is $N_{\uparrow}(\omega) = \sum_n u_n^2(r) \delta(\omega - E_n)$ and $N_{\downarrow}(\omega) = \sum_n v_n^2(r) \delta(\omega + E_n)$. Note, that a *single* YSR level contributes *two* delta functions at energies $\pm E_0$ with weights u_0^2 and v_0^2 that correspond to spin-up and spin-down states, respectively.

According to the standard theory of electron tunneling from a metallic contact [11], at zero temperature the differential tunneling conductance $\sigma(V)$ is proportional to the density of states in the sample at $E = V$, which in the case of YSR states would correspond to, in general, asymmetric delta function peaks. However, as we discussed above, such treatment neglects the possibility of having a nonequilibrium distribution function, which, in fact, leads to a qualitatively different result.

The tunneling between an atomically sharp tip and the sample can be described by the tunneling Hamiltonian,

$$H' = H_{\text{tip}} + t[d_{\sigma}^{\dagger}(r_0) \psi_{\sigma}(r_0) + \psi_{\sigma}^{\dagger}(r_0) d_{\sigma}(r_0)], \quad (6)$$

where r_0 corresponds to the location where the tip and sample wave functions overlap, with the matrix element t , and $H_{\text{tip}} = \sum_{k\sigma} (\epsilon_k^t - \mu^t) d_{k\sigma}^{\dagger} d_{k\sigma}$ is the Hamiltonian of the tip, with modes d_k . The tunneling part of the Hamiltonian can be conveniently expressed in terms of the Bogoliubov quasiparticles. Since we are interested in the subgap conductance due to the YSR state, out of the full expansion we only need to keep terms related to it, $\psi_{\uparrow}(r_0) \rightarrow u_0(r_0) \gamma_0$ and $\psi_{\downarrow}^{\dagger}(r_0) \rightarrow v_0(r_0) \gamma_0$. In the spin-down channel this leads to terms of the form $d_{\downarrow}^{\dagger} \gamma_0^{\dagger}$, which do not conserve the number of particles. A significant simplification

occurs if one performs a particle-hole transformation of spin-down electrons in the tip, $\tilde{d}_\downarrow = d_\downarrow^\dagger$. For the spin-down holes, $\epsilon_k^t \rightarrow -\epsilon_k^t$, $\mu^t \rightarrow -\mu^t$ (relative to the chemical potential of the superconductor), and the state occupation numbers $n_k \rightarrow 1 - n_k$. In the new basis, the tunneling Hamiltonian becomes

$$tu(r_0)d_\uparrow^\dagger(r_0)\gamma_0 - tv(r_0)\tilde{d}_\downarrow^\dagger(r_0)\gamma_0 + \text{H.c.}$$

The fully transformed Hamiltonian, which includes the superconductor, the tip, and the tunneling between them, now conveniently conserves the number of particles. It corresponds to the problem of tunneling of spinless particles between two reservoirs through a resonant level. The couplings to the two reservoirs are in general different due to the factors $u(r_0), v(r_0)$. Schematically, the equivalent representation is illustrated in Fig. 1(b). The right reservoir corresponds to spin-up electrons, and the left reservoir to spin-down holes. Notice that the process in which a particle is transferred from the right reservoir to the left one, in terms of the original electrons, corresponds to transferring two electrons (with spin up and spin down) into the superconductor, with the help of the YSR state. The initial and final energy of the spinless particle is the same; in the original language this corresponds to selecting two electrons with a total energy equal to zero (relative to the superconductor's μ).

The problem of tunneling through a resonant level is very well known [13]. The key quantities that enter are the tunneling rates between the level and the reservoirs, $\Gamma_1 = \pi N^t u_0^2(r_0)t^2$ and $\Gamma_2 = \pi N^t v_0^2(r_0)t^2$. The sum of these two rates determines the resonant level broadening. Interestingly, even when $\Gamma_1 \neq \Gamma_2$, the particle current through the resonant level does not depend on the direction of bias, reaching the maximum value of $(2e/\hbar)[2\Gamma_1\Gamma_2/(\Gamma_1 + \Gamma_2)]$ for large bias. The ratio of the current to the level width, measured in voltage units, gives, up to a constant, the differential conductance. Since the magnitude of the current does not depend on the direction of bias, subgap $\sigma(V)$ is symmetric with respect to the sign of V . With the numerical prefactors included, we find

$$\sigma(\pm E_0) = \frac{2e^2}{h} \frac{4\Gamma_1\Gamma_2}{(\Gamma_1 + \Gamma_2)^2} = G_0 \frac{4u_0^2v_0^2}{(u_0^2 + v_0^2)^2}. \quad (7)$$

Thus the maximum value of conductance, which is achieved at the spatial locations r where $u_0(r) = v_0(r)$ is equal to one quantum of conductance, and the spatial map of $\sigma(\pm E_0)$ can be used to determine the spatial dependence of the quasiparticle particle-hole content, $u_0(r)/v_0(r)$.

Extra bath. We now turn to the case when the magnetic impurity is not fully isolated within the superconductor. To allow for additional relaxation, we introduce a gapless bath, whose chemical potential is pinned to the chemical potential of the superconductor, into which the YSR state can decay with rate Γ_0 . Such a bath can originate from a finite electronic density of states inside the superconducting gap, possibly forming other nearby magnetic impurities or metallic contacts. It is naturally present in unconventional superconductors which have a gapless spectrum, e.g., superconducting cuprates [14–16]. If the rate Γ_0 is much faster than $\Gamma_{1,2}$, the YSR state will remain in equilibrium with the superconductor, and we expect to recover the “standard” result where $\sigma(V)$ is proportional to the density of states in the superconductor.

We study this problem within the normal-state nonequilibrium Green's function formalism. The current through the system is fully determined by the resonant level Green's function [17], which in this case is

$$G^>(\omega) = -2i \frac{\sum_{i=0,1,2} \Gamma_i [1 - n_i(\omega)]}{(\omega - E_0)^2 + (\Gamma_0 + \Gamma_1 + \Gamma_2)^2}, \quad (8)$$

$$G^<(\omega) = 2i \frac{\sum_{i=0,1,2} \Gamma_i n_i(\omega)}{(\omega - E_0)^2 + (\Gamma_0 + \Gamma_1 + \Gamma_2)^2}, \quad (9)$$

with $n_{1(2)}(\omega)$ being the Fermi distribution functions for the reservoirs of spin-up electrons and spin-down holes, e.g., Fig. 1(b), $n_{1(2)}(\omega) = \{1 + \exp[(\omega \pm V)/T]\}^{-1}$, and n_0 is the distribution function for the bulk of the superconductor, $n_0(\omega) = [1 + \exp(\omega/T)]^{-1}$. The retarded (advanced) components are $G^{R(A)} = [\omega - E_0 \pm i(\Gamma_1 + \Gamma_2 + \Gamma_0)]^{-1}$. The current through the YSR level is given by

$$I(V) = \frac{ie}{\hbar} \int \frac{d\omega}{2\pi} \{(\Gamma_1 - \Gamma_2)G^<(\omega) + [\Gamma_1 n_1(\omega) - \Gamma_2 n_2(\omega)][G^R(\omega) - G^A(\omega)]\}, \quad (10)$$

which is twice that of the case of a conventional resonant level [13]. The corresponding differential conductance $\sigma(V) = dI/dV$ at zero temperature has a simple two-Lorentzian form,

$$\sigma = 2G_0 \left[\frac{2\Gamma_1\Gamma_2 + \Gamma_0\Gamma_1}{(V - E_0)^2 + \Gamma_T^2} + \frac{2\Gamma_1\Gamma_2 + \Gamma_0\Gamma_2}{(V + E_0)^2 + \Gamma_T^2} \right], \quad (11)$$

with $\Gamma_T = \Gamma_0 + \Gamma_1 + \Gamma_2$. If $\Gamma_0 \gg \Gamma_{1,2}$, the heights of the Lorentzian peaks at $\pm E_0$ are proportional to u^2 and v^2 , respectively, which is the standard density of states result [see Fig. 1(c), solid line]. Only when $\Gamma_0 \ll \Gamma_{1,2}$ is the symmetric $\sigma(V)$ recovered, e.g., Eq. (7). Finite temperature does not change this conclusion.

In view of this result, we conclude that in the STM experiment of Ref. [8], the impurity states cannot be considered as isolated. A likely reason is that the density of the surface coverage by magnetic atoms was rather high and led to line broadening, larger than the YSR broadening due to coupling to the metallic tip. On the other hand, the planar tunnel junction experiment of Ref. [7] showed YSR peaks whose width was independent of the Mn concentration, up to 250 ppm. This is a strong indication that the linewidth was dominated by the coupling to the metallic lead. Indeed, symmetric $\sigma(V)$ was observed in this case, consistent with the dilute limit (no extra bath), in which tunneling current drives YSR states out of equilibrium. We note here that since the crossover from asymmetric to symmetric $\sigma(V)$ occurs when $\Gamma_0 \sim \Gamma_{1,2}$, varying $\Gamma_{1,2}$ in STM experiments by means of changing the tunneling distance and lateral tip location can be used to determine the broadening Γ_0 . In the context of unconventional superconductors, this technique can be applied to extract information about the local electronic environment of magnetic atoms, in a way similar to NMR [18].

Measurement of impurity spin. Spin-polarized tunneling into the YSR state can be used to measure the impurity spin orientation. Upon impurity spin reversal, the Bogoliubov quasiparticles transform as $E_n \rightarrow -E_n$ and $(u_n, v_n) \rightarrow (v_n, -u_n)$. A spin-polarized STM tip can be modeled by assuming different densities of states for up and down electrons,

$N_{\uparrow}^t \neq N_{\downarrow}^t$. If the impurity spin is up, then $\Gamma_{1\uparrow} = \pi t^2 u_0^2(r_0) N_{\uparrow}^t$ and $\Gamma_{2\uparrow} = \pi t^2 v_0^2(r_0) N_{\downarrow}^t$; for an impurity spin down, $\Gamma_{1\downarrow} = \pi t^2 v_0^2(r_0) N_{\uparrow}^t$ and $\Gamma_{2\downarrow} = \pi t^2 u_0^2(r_0) N_{\downarrow}^t$. Since $\Gamma_{i\uparrow} \neq \Gamma_{i\downarrow}$ for $|u(r)| \neq |v(r)|$, the value of the current for the two impurity states will be different, and hence can be used to determine the spin orientation.

Thus, the presence of the YSR state enables the measurement of the local moment orientation. However, as we will now show, it also leads to dephasing of the local moment. From the Hamiltonian (1), the effective magnetic field acting on the local moment is

$$h_z = J[\psi_{\uparrow}^{\dagger}(0)\psi_{\uparrow}(0) - \psi_{\downarrow}^{\dagger}(0)\psi_{\downarrow}(0)], \quad (12)$$

with the main contribution to the fluctuation of h_z deriving from the YSR state; the delocalized Bogoliubov quasiparticles can be neglected at low temperatures, as we will show below. That leaves

$$h_z = J[u_0^2(0)^2 + v_0^2(0)]\gamma_0^{\dagger}\gamma_0 - Jv_0^2(0). \quad (13)$$

[Notably, within the YSR approximation, the transverse field components are zero since they involve operator combinations $\gamma_0^2 = (\gamma_0^{\dagger})^2$.] The spin dephasing time T_2 is related to the fluctuations of this field as

$$\frac{1}{T_2} \sim S^2 \int_{-\infty}^{\infty} dt [\langle h_z(t) - \langle h_z \rangle] [h_z(0) - \langle h_z \rangle],$$

i.e., its determination reduces to an evaluation of the zero-frequency correlation function of the YSR level occupation number. The zero-frequency fluctuations of occupancy reach maximum in the sequential tunneling regime. These fluctuations can be easily determined from the classical rate equations to be $\Gamma_1\Gamma_2/(\Gamma_1 + \Gamma_2)^3$, which for the dephasing rate yields

$$\frac{1}{T_2 \text{ seq}} \sim \frac{J^2 S^2}{\Gamma} \left(\frac{a}{\xi_0} \right)^6$$

(we assumed here that $\Gamma_1 \sim \Gamma_2 \equiv \Gamma$). For instance, in the case of Nb, the ratio of the coherence length to the lattice constant $\xi_0/a \sim 100$. Taking $J \sim 1$ eV, and tunneling rate $\Gamma \sim 10^{10} \text{ s}^{-1}$, which corresponds to the tunnel current of about 0.1 nA, the dephasing time is 10^{-8} s.

In the low-bias regime, such that $|E_0| \gg (T, V) \gg \Gamma$, the fluctuations can be found using the same Green's function formalism as we used to determine the current. In this regime,

$$\frac{1}{T_2 \text{ l.b.}} \sim \frac{\Gamma^3 \max(T, V)}{E_0^4} \frac{1}{T_2 \text{ seq}},$$

which, for the same tunneling rate and E_0 of the order of $\Delta_0 \sim 1$ meV, gives $T_{2 \text{ l.b.}} \sim 10^{-4}$ s. In this regime, the dephasing rate is proportional to Γ^2 . We can see that the contribution of the delocalized states in the superconductor to spin dephasing can be neglected, as can be seen from the following qualitative argument. Let us consider each delocalized state in the same way as we did the YSR state. Since these states are delocalized, their broadening will scale as $u^2(0), v^2(0) \sim 1/V$. The number of these states is proportional to the sample volume V , and hence their overall contribution to dephasing will scale as $1/V$, vanishing for nonmicroscopic samples. Moving the tip away from the sample, one can recover the dephasing and relaxation rates that are governed by thermal excitations, whose density is $\sim e^{-\Delta_0/T}$. This long dephasing rate makes localized spin states in superconductors an appealing framework for various quantum computing applications, including those based on Majorana fermions [19,20].

The results obtained here apply not only to YSR states, but to any other localized intragap states in superconductors, e.g., states in the vortex cores [21]. The importance of YSR states has also been discussed in the related context of tunneling through quantum dots, when a Coulomb blockade enforces odd occupancy [10,22–25]. Outside the strongly correlated Kondo regime and in the limit of weak coupling to the metallic lead, an approximately symmetric differential conductance is commonly observed [22]. The tunability of quantum dot systems provides an opportunity to study the crossover from the weakly correlated YSR regime to the strongly correlated Kondo regime. We thus expect that future experiments will be able to test the range of validity of our theory.

Experimentally it has been found that using a superconducting tip provides a way to enhance the features associated with tunneling through the YSR state [25,26]. Theoretically, this problem can also be mapped onto tunneling of spinless particles between two reservoirs with energy dependent densities of states. Unlike in the normal tip case, however, the peaks that appear due to YSR states at $\pm(|\Delta_{\text{tip}}| + |E_0|)$ are in general no longer symmetric [27], even in the absence of an additional bath. This is consistent with experimental findings [26].

Acknowledgments. We would like to thank E. Demler, J. Sau, A. Yazdani, A. Shnirman, A. Koshelev, and K. McElroy for useful discussions. Work performed at Argonne National Laboratory (I.M.) was supported by the U.S. Department of Energy, Office of Science, Materials Sciences and Engineering Division. Work at Los Alamos National Laboratory (D.M.) was carried out under the auspices of the NNSA of the U.S. Department of Energy under Contract No. DE-AC52-06NA25396.

[1] P. W. Anderson, *J. Phys. Chem. Solids* **11**, 26 (1959).
 [2] A. A. Abrikosov and L. P. Gorkov, *Zh. Eksp. Teor. Fiz.* **39**, 1781 (1960) [*Sov. Phys. JETP* **12**, 1243 (1961)].
 [3] O. Sakai, Y. Shimizu, H. Shiba, and K. Satori, *J. Phys. Soc. Jpn.* **62**, 3181 (1993); W. Chung and M. Jarrell, *Phys. Rev. Lett.* **77**, 3621 (1996).
 [4] L. Yu, *Acta Phys. Sin.* **21**, 75 (1965).
 [5] H. Shiba, *Prog. Theor. Phys.* **40**, 435 (1968).

[6] A. I. Rusinov, *Zh. Eksp. Teor. Fiz.* **56**, 2047 (1969) [*Sov. Phys. JETP* **29**, 1101 (1969)].
 [7] W. Bauriedl, P. Ziemann, and W. Buckel, *Phys. Rev. Lett.* **47**, 1163 (1981).
 [8] A. Yazdani, B. A. Jones, C. P. Lutz, M. F. Crommie, and D. M. Eigler, *Science* **275**, 1767 (1997).
 [9] A. F. Andreev, *Zh. Eksp. Teor. Fiz.* **46**, 1823 (1964) [*Sov. Phys. JETP* **19**, 1228 (1964)].

- [10] V. Koerting, B. M. Andersen, K. Flensberg, and J. Paaske, *Phys. Rev. B* **82**, 245108 (2010).
- [11] G. D. Mahan, *Many-Particle Physics* (Springer, Berlin, 2000).
- [12] P. de Gennes, *Superconductivity of Metals and Alloys* (Westview, Boulder, CO, 1999).
- [13] Y. Meir and N. S. Wingreen, *Phys. Rev. Lett.* **68**, 2512 (1992); A.-P. Jauho, N. S. Wingreen, and Y. Meir, *Phys. Rev. B* **50**, 5528 (1994).
- [14] A. V. Balatsky, I. Vekhter, and J.-X. Zhu, *Rev. Mod. Phys.* **78**, 373 (2006).
- [15] S. H. Pan, E. W. Hudson, K. M. Lang, H. Eisaki, S. Uchida, and J. C. Davis, *Nature (London)* **403**, 746 (2000); E. W. Hudson, K. M. Lang, V. Madhavan, S. H. Pan, H. Eisaki, S. Uchida, and J. C. Davis, *ibid.* **411**, 920 (2001).
- [16] In unconventional superconductors, Γ_0 can be identified with the impurity level broadening due to the finite density of states inside the gap, e.g., $\Gamma_0 \sim \Delta_0 [N_0(U \pm J) \ln^2 |8N_0(U \pm J)|]^{-1}$ in the case of *d*-wave superconductors with gap amplitude Δ_0 . U here is the potential part of the impurity potential. Note that in unconventional superconductors even nonmagnetic impurities can generate (broadened) intragap states.
- [17] D. Mozyrsky, I. Martin, and M. B. Hastings, *Phys. Rev. Lett.* **92**, 018303 (2004).
- [18] N. J. Curro, T. Imai, C. P. Slichter, and B. Dabrowski, *Phys. Rev. B* **56**, 877 (1997).
- [19] S. Nadj-Perge, I. K. Drozdov, B. A. Bernevig, and A. Yazdani, *Phys. Rev. B* **88**, 020407(R) (2013).
- [20] N. Y. Yao, L. I. Glazman, E. A. Demler, M. D. Lukin, and J. D. Sau, [arXiv:1309.2633](https://arxiv.org/abs/1309.2633).
- [21] C. Caroli, P. G. de Gennes, and J. Matricon, *Phys. Lett.* **9**, 307 (1964).
- [22] M. R. Gräber, T. Nussbaumer, W. Belzig, and C. Schönenberger, *Nanotechnology* **15**, S479 (2004); R. S. Deacon, Y. Tanaka, A. Oiwa, R. Sakano, K. Yoshida, K. Shibata, K. Hirakawa, and S. Tarucha, *Phys. Rev. Lett.* **104**, 076805 (2010); *Phys. Rev. B* **81**, 121308(R) (2010); E. J. H. Lee *et al.*, *Nat. Nanotechnol.* **9**, 79 (2014).
- [23] R. Fazio and R. Raimondi, *Phys. Rev. Lett.* **80**, 2913 (1998).
- [24] Y. Tanaka, N. Kawakami, and A. Oguri, *J. Phys. Soc. Jpn.* **76**, 074701 (2007).
- [25] E. J. H. Lee, X. Jiang, R. Aguado, G. Katsaros, C. M. Lieber, and S. De Franceschi, *Phys. Rev. Lett.* **109**, 186802 (2012).
- [26] S.-H. Ji, T. Zhang, Y.-S. Fu, X. Chen, X.-C. Ma, J. Li, W.-H. Duan, J.-F. Jia, and Q.-K. Xue, *Phys. Rev. Lett.* **100**, 226801 (2008).
- [27] I. Martin and D. Mozyrsky (unpublished).