

Interplay of spin-orbit and entropic effects in cerium

Nicola Lanatà,^{1,*} Yong-Xin Yao,^{2,†} Cai-Zhuang Wang,² Kai-Ming Ho,² and Gabriel Kotliar¹¹*Department of Physics and Astronomy, Rutgers University, Piscataway, New Jersey 08856-8019, USA*²*Ames Laboratory-U.S. DOE and Department of Physics and Astronomy, Iowa State University, Ames, Iowa 50011, USA*

(Received 12 August 2014; revised manuscript received 2 October 2014; published 21 October 2014)

We perform first-principles calculations of elemental cerium and compute its pressure-temperature phase diagram, finding good quantitative agreement with the experiments. Our calculations indicate that, while a signature of the volume-collapse transition appears in the free energy already at low temperatures, at higher temperatures this signature is enhanced because of the entropic effects, and originates an actual thermodynamical instability. Furthermore, we find that the catalyst determining this feature is—in all temperature regimes—a pressure-induced effective reduction of the f -level degeneracy due to the spin-orbit coupling. Our analysis suggests also that the lattice vibrations might be crucial in order to capture the behavior of the pressure-temperature transition line at large temperatures.

DOI: [10.1103/PhysRevB.90.161104](https://doi.org/10.1103/PhysRevB.90.161104)

PACS number(s): 71.30.+h, 71.27.+a

At ambient temperature elemental cerium undergoes a pressure-induced first-order isostructural transition, which is accompanied by a volume collapse of about 14%. The critical pressure where this transition occurs increases linearly with the temperature, and the corresponding transition line in the pressure-temperature phase diagram ends at a critical temperature $T_c \simeq 500$ K. Since 1949, when the γ - α transition was discovered, it has stimulated a lot of experimental and theoretical work, but a complete theoretical description of this phenomenon is still lacking. In particular, two theoretical pictures are still nowadays under debate: (i) the Kondo volume collapse model (KVC) that was proposed by Allen and Martin [1] and independently by Lavagna, Lacroix, and Cyrot [2], and (ii) the orbital-selective Mott transition that was proposed by Johansson [3]. The main difference between these two models is that, while the KVC attributes the γ - α transition of cerium to a rapid change of the degree of hybridization between the f electrons and the spd conduction bands (and consequently of the Kondo temperature), within the Mott transition the key quantity whose rapid variation is responsible for the transition is the kinetic energy of the f electrons, while the itinerant electrons are inert spectators of the transition. Consistently with both the Mott picture and the KVC, photoemission experiments [4–6] have demonstrated that the f electrons are correlated both in the γ phase and in the α phase. On the other hand, calculations of the optical spectrum [7] have enabled one to interpret the experiments [8] in favor of the KVC.

In our view, there are few fundamental questions that have to be answered in order fully understand the physics underlying the γ - α transition of cerium. (1) Why does T_K vary rapidly only within a narrow window of volumes rather than varying smoothly? (2) How does the rapid variation of T_K affect the free energy and, in particular, generate the γ - α isostructural transition? (3) Is the fact that the γ - α isostructural transition ends at $T_c \simeq 500$ K purely due to electronic effects or does it require one to take into account the temperature-induced lattice vibrations [9–11]?

Recent first-principles calculations of cerium [12] within the Gutzwiller approximation in combination with the local density approximation (LDA + GA) [13] have suggested a possible solution to the first of the questions listed above. In fact, these calculations have shown that a clear signature of the γ - α isostructural transition of cerium can be observed at zero temperature if (and only if) the spin-orbit coupling is taken into account. Furthermore, they have shown that the reason underlying this result is that the spin-orbit coupling effectively reduces the f -level degeneracy from 14 to 6 when the hybridization strength is reduced by increasing the volume, thus causing a crossover in the evolution of T_K . On the contrary, if the spin-orbit coupling is not taken into account, T_K evolves smoothly as a function of the volume. This point of view has been further clarified in a following work [14] making use of the “principle of maximum entanglement entropy.” The importance of the spin-orbit coupling for the determination of the thermodynamical properties of cerium has been finally confirmed also within the framework of LDA in combination with dynamical mean-field theory (LDA + DMFT) [15] (see Ref. [16]), where the spin-orbit coupling was neglected because of the great computational complexity of the problem. In fact, the LDA + DMFT low-temperature pressure-volume phase diagram—that is in very good quantitative agreement with the LDA + GA calculations of Ref. [12]—does not display any signature of the transition at low temperatures. Furthermore, it was shown that, if the spin-orbit coupling is neglected, not even the entropy is sufficient to induce a thermodynamical instability, but only a softening of the bulk modulus.

The second of the questions listed above is particularly challenging, as a rapid variation of T_K affects differently the internal energy E and the entropy S of the system. In fact, at small volumes (where $T_K \gg T$) the Kondo-stabilization effect decreases the internal energy [17,18], while the entropy is small; on the contrary, at large volumes (where $T_K \ll T$) the entropy of the system is large, thus decreasing considerably the free energy and stabilizing the γ phase. Because of these reasons, it is rather complicated to predict quantitatively the behavior of the free energy $F = E - TS$ in concomitance with a rapid variation of T_K , and accurate first-principles calculations are essential in order to study this problem.

*Corresponding author: lanata@physics.rutgers.edu

†Corresponding author: ykent@iastate.edu

Since the spin-orbit coupling and the entropic effects are both important at finite temperatures, it is clear that in order to fully understand the γ - α transition at finite temperatures (and in particular to answer the second and the third questions listed above) it is essential to perform first-principles calculations that are able to take into account both of these physical effects. In this Rapid Communication, besides taking into account the spin-orbit coupling, we describe the entropic effects at finite temperatures by employing a charge self-consistent combination of LDA with the rotationally invariant slave-boson (SB) mean-field theory [19] that we have implemented following Ref. [20]. Note that this method is equivalent to LDA + GA at zero temperature [21] and, although it is not as accurate as LDA + DMFT, it has the advantage of being much less computationally demanding. For completeness, in the Supplemental Material [22] we give a brief introduction to the LDA + SB method.

As in Ref. [12], we employ the “standard” prescription for the double-counting functional and the general (rotationally invariant) Slater-Condon parametrization [23] of the on-site interaction, assuming that the Hund’s coupling constant is $J = 0.7$ eV and that the value of the interaction strength is $U = 6$ eV.

The upper panel of Fig. 1 shows the evolution of the free energy $F = E - TS$ at different temperatures T . While at small volumes F is not very sensitive to T , at larger volumes it is considerably reduced by the temperature. Because of this effect, at $T \gtrsim 300$ K the γ phase is stable at zero pressure, while at lower temperatures the γ phase is stable only at negative pressures. In other words, consistently with the experiments, our calculations indicate that at $T \gtrsim 300$ K the volume-collapse transition occurs at positive pressures. The boundaries of the transition have been evaluated within the common-tangent construction, and are indicated by the dots in the inset of the upper panel of Fig. 1.

The pressure-volume curves that are calculated from the free energy F using $P = -dF/dV$ are shown in the middle panel of Fig. 1 in comparison with the room-temperature experimental data of Refs. [24–26]. The critical pressures (at different temperatures) are identified here by the equal-area construction, and are indicated by horizontal lines. The volumes V_c where dP/dV reaches the maximum value are indicated by vertical lines. Remarkably, our finite-temperature calculations are in very good agreement with the room-temperature experimental pressure-volume phase diagram. In particular, note that the entropic effects improve the comparison with the experiments at large volumes, which confirms that they are very important to describe the thermodynamical properties of cerium, especially in the γ phase.

The lower panel of Fig. 1 shows the evolution as a function of the volume of the Gutzwiller quasiparticle renormalization weights of the $7/2$ and $5/2$ f electrons. Interestingly, the overall qualitative behavior of the quasiparticle weights is similar for all temperatures: Both $Z_{5/2}$ and $Z_{7/2}$ are significantly smaller than 1 already at high pressures, and in this regime they monotonically decrease as a function of the volume; on the contrary, at volumes larger than a temperature-dependent crossover volume V_c we observe that $Z_{7/2}$ increases while $Z_{5/2}$ rapidly decreases. This behavior was already discussed in the zero-temperature calculations of Ref. [12], and reflects the

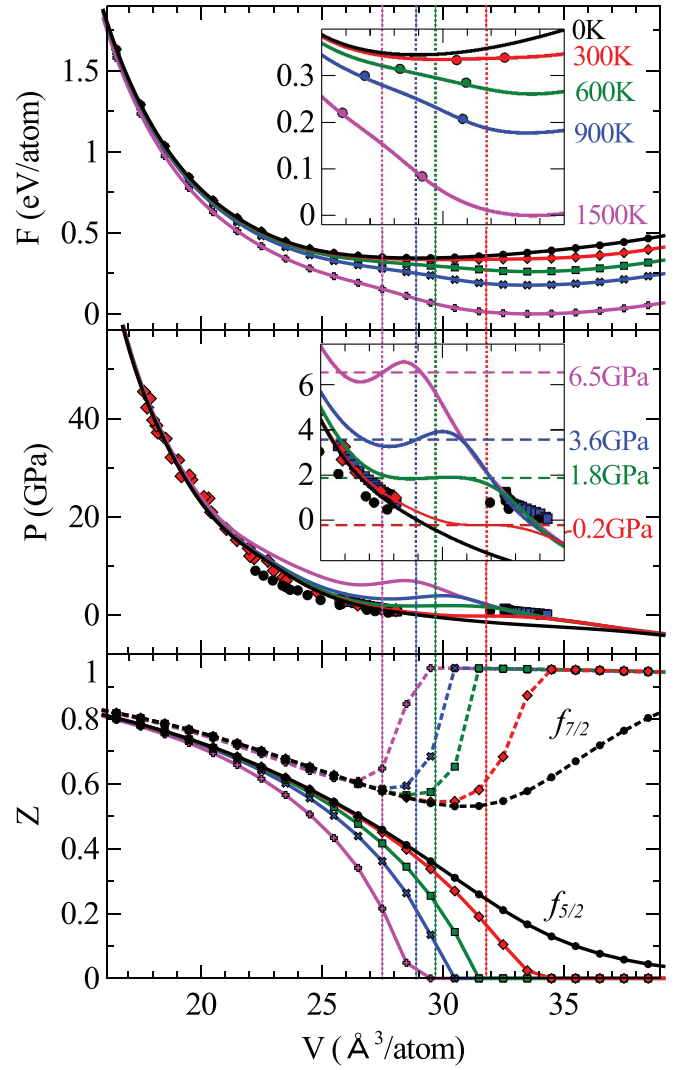


FIG. 1. (Color online) Evolution of the free energy (upper panel), pressure (middle panel), and Gutzwiller quasiparticle weights (lower panel) as a function of the volume at different temperatures. The vertical lines indicate the crossover volumes V_c where the pressure dP/dV achieves its maximum (positive) value. The dots in the inset of the upper panel indicate the boundaries of the volume-collapse transition according to the common-tangent construction. The dots in the middle panel represent the room-temperature experimental data of Refs. [24] (black circles), [25] (red diamonds), and [26] (blue squares).

above-mentioned effective reduction of the f -level degeneracy from 14 to 6 due to the spin-orbit coupling. Remarkably, here we find that the crossover of the Z 's takes place for all temperatures at the same volume V_c where dP/dV reaches its maximum value. This finding indicates that, also at finite temperatures, the γ - α volume-collapse transition is induced by the rapid reduction of the Kondo temperature, which occurs because the spin-orbit coupling effectively reduces the f -level degeneracy from 14 to 6 at $V \simeq V_c$.

Note that, while at zero temperature we find that $Z > 0$ even at large volumes, at $T > 0$ we find that $Z_{5/2} = 0$ for all volumes larger than a critical value $V_M > V_c$, which approaches V_c when the temperature is increased. This

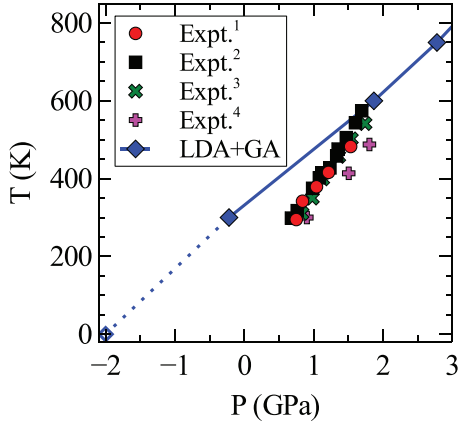


FIG. 2. (Color online) Theoretical pressure-temperature phase diagram in comparison with the experimental data of Refs. [26,28–30]. The open square at $T = 0$ and negative pressures indicates the signature of the transition identified by a maximum (but negative) value of dP/dV , while the other points indicate actual thermodynamical instabilities identified by a positive value of dP/dV .

observation is suggestive with respect to the considerations of Ref. [27], which partially reconcile the Mott and the KVC pictures at finite temperatures. On the other hand, we believe that the second-order selective Mott transition found in our calculations does not reflect an actual physical effect, but is an artifact of the SB approximation scheme. More precisely, we do not expect that in cerium a transition should be observed as a function of the volume, but only as a function of the pressure. In any case, we point out that the thermodynamical properties of cerium are determined exclusively by the free energy, which does not display any singular behavior at V_M in our calculations.

In Fig. 2 the theoretical pressure-temperature phase diagram extrapolated from the free-energy curves of Fig. 1 is shown in comparison with the experimental data. Note that at zero temperature no transition is observed in our calculations with $U = 6$ eV, but only a signature identified by a maximum (but negative) value of dP/dV (see Ref. [12]). The open square at $T = 0$ and negative pressures indicates this signature. Remarkably, the behavior of the transition line in the pressure-temperature phase diagram is in good agreement with the experiments (see Fig. 2). In particular, note that the critical pressure P_c increases as a function of the temperature, and it is positive for $T \gtrsim 300$ K. On the other hand, our calculations do not reproduce the experimental behavior of the transition line at high temperatures. In fact, while experimentally the transition line ends at $T_c \simeq 500$ K, our calculations indicate that the transition line continues far beyond the range of temperatures displayed in Fig. 2, as a volume-collapse transition is observed even at $T = 1500$ K.

Figure 3 shows the thermodynamical potentials $G = E - TS + P_c V$ as a function of the volume, which are evaluated at different T by fixing the corresponding critical pressures $P_c(T)$. Consistently with the definition of the common-tangent construction, G displays a double-minima structure, indicating that the system is unstable at $P = P_c$. Interestingly, the energy barrier Δ between the α and γ phases is smaller than 4 meV for all of the temperatures considered, and it increases

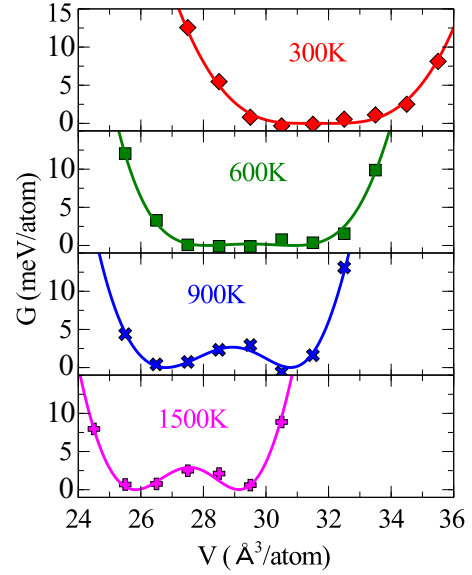


FIG. 3. (Color online) Thermodynamical potentials $G = E - TS + P_c V$ as a function of the volume evaluated at different temperatures T by fixing the corresponding critical pressures $P_c(T)$ of Fig. 2. The continuous curves are obtained by fitting the free-energy data of Fig. 1 over the entire range of volumes using a one-dimensional smoothing spline fit with order 4 and smoothing factor 5×10^{-2} meV, as implemented in the PYTHON class “scipy.interpolate.UnivariateSpline.”

monotonically with T . Note also that Δ increases rapidly only at low temperatures, while it remains almost unchanged between $T = 900$ and 1500 K.

We point out that, within the Born-Oppenheimer approximation, the function $G = E - TS + PV$ represents the effective potential experienced by the cerium atoms at fixed temperature T and pressure P . This observation suggests that the lattice vibrations—which were not taken into account in our calculations—might be the actual reason why the transition line ends at the finite temperature $T_c \simeq 500$ K. In fact, since the energy barrier Δ is very small even at high temperatures, it might be possible that, because of the temperature-induced lattice vibrations, the atom configurations “sample” simultaneously both the α and the γ phase not only at the critical pressure P_c defined above, but also within a small interval of pressures $P \simeq P_c$, thus transforming the volume-collapse transition in a crossover when the temperature is sufficiently high.

In conclusion, we have calculated from first principles the phase diagram of fcc cerium, finding good agreement with the experiments. Our analysis suggests that the isostructural pressure-induced γ - α transition is induced by a rapid variation of the Kondo temperature, which occurs because of the interplay between the spin-orbit coupling and the f -electron correlations. While a signature of the volume-collapse transition appears in the free energy already at low temperatures, at higher temperatures this signature is enhanced because of the entropic effects, and originates an actual thermodynamical instability. The behavior of the theoretical thermodynamical potential at constant pressure indicates that the γ and α phases are separated by a very small energy barrier at all

temperatures. This observation suggests an appealing possible explanation of why the pressure-temperature transition line ends at $T_c \simeq 500$ K: At $T > T_c$ the atom configurations might be able to overcome the above-mentioned barrier and sample simultaneously the γ and α phases even slightly before the critical pressure, thus transforming the γ - α transition in a crossover. In order to clarify this point, and thus answer the third of the questions listed in the introduction of this Rapid Communication, it would be interesting to perform molecular dynamics simulations [31,32], e.g., using effective atomistic potentials extrapolated from the free-energy curves of this work. Alternatively, this issue could be investigated by performing direct Monte Carlo simulations (iterating LDA + SB calculations of cerium with a large unit cell).

Note added in proof. Ming-Feng Tian *et al.* have recently performed LDA+GA calculations of cerium, see Ref. [33], which are in good agreement with our results.

We thank Xi Dai, Kristjan Haule, Michele Fabrizio, and XiaoYu Deng for useful discussions. N.L. and G.K. were supported by US DOE Office of Basic Energy Sciences under Grant No. DE-FG02-99ER45761. Research at Ames Laboratory is supported by the US Department of Energy, Office of Basic Energy Sciences, Division of Materials Sciences and Engineering. Ames Laboratory is operated for the US Department of Energy by Iowa State University under Contract No. DE-AC02-07CH11358.

-
- [1] J. W. Allen and R. M. Martin, *Phys. Rev. Lett.* **49**, 1106 (1982).
 - [2] M. Lavagna, C. Lacroix, and M. Cyrot, *Phys. Lett. A* **90**, 210 (1982).
 - [3] B. Johansson, *Philos. Mag.* **30**, 469 (1974).
 - [4] D. M. Wieliczka, C. G. Olson, and D. W. Lynch, *Phys. Rev. Lett.* **52**, 2180 (1984).
 - [5] E. Weschke, C. Laubschat, T. Simmons, M. Domke, O. Strebel, and G. Kaindl, *Phys. Rev. B* **44**, 8304 (1991).
 - [6] F. Patthey, B. Delley, W. D. Schneider, and Y. Baer, *Phys. Rev. Lett.* **55**, 1518 (1985).
 - [7] K. Haule, V. Oudovenko, S. Y. Savrasov, and G. Kotliar, *Phys. Rev. Lett.* **94**, 036401 (2005).
 - [8] J. W. van der Eb, A. B. Kuz'menko, and D. van der Marel, *Phys. Rev. Lett.* **86**, 3407 (2001).
 - [9] T. Jarlborg, E. G. Moroni, and G. Grimvall, *Phys. Rev. B* **55**, 1288 (1997).
 - [10] B. Johansson, I. A. Abrikosov, M. Aldén, A. V. Ruban, and H. L. Skriver, *Phys. Rev. Lett.* **74**, 2335 (1995).
 - [11] T. Jarlborg, *Phys. Rev. B* **89**, 184426 (2014).
 - [12] N. Lanatà, Y.-X. Yao, C.-Z. Wang, K.-M. Ho, J. Schmalian, K. Haule, and G. Kotliar, *Phys. Rev. Lett.* **111**, 196801 (2013).
 - [13] X. Deng, L. Wang, X. Dai, and Z. Fang, *Phys. Rev. B* **79**, 075114 (2009).
 - [14] N. Lanatà, H. U. R. Strand, Y.-X. Yao, and G. Kotliar, *Phys. Rev. Lett.* **113**, 036402 (2014).
 - [15] G. Kotliar, S. Y. Savrasov, K. Haule, V. S. Oudovenko, O. Parcollet, and C. A. Marianetti, *Rev. Mod. Phys.* **78**, 865 (2006).
 - [16] J. Bieder and B. Amadon, *Phys. Rev. B* **89**, 195132 (2014).
 - [17] A. K. McMahan, K. Held, and R. T. Scalettar, *Phys. Rev. B* **67**, 075108 (2003).
 - [18] B. Amadon, S. Biermann, A. Georges, and F. Aryasetiawan, *Phys. Rev. Lett.* **96**, 066402 (2006).
 - [19] F. Lechermann, A. Georges, G. Kotliar, and O. Parcollet, *Phys. Rev. B* **76**, 155102 (2007).
 - [20] N. Lanatà, Y. X. Yao, C. Z. Wang, K. M. Ho, and G. Kotliar, *arXiv:1405.6934*.
 - [21] J. Bünenmann and F. Gebhard, *Phys. Rev. B* **76**, 193104 (2007).
 - [22] See Supplemental Material at <http://link.aps.org/supplemental/10.1103/PhysRevB.90.161104> for Brief introduction to the LDA+SB method at finite temperature.
 - [23] V. I. Anisimov, F. Aryasetiawan, and A. Lichtenstein, *J. Phys.: Condens. Matter* **9**, 767 (1997).
 - [24] W. H. Zachariasen and F. H. Ellinger, *Acta Crystallogr., Sect. A* **33**, 155 (1977).
 - [25] J. Olsen, L. Gerward, U. Benedict, and J.-P. Itié, *Physica B + C* **133**, 129 (1985).
 - [26] M. J. Lipp, D. Jackson, H. Cynn, C. Aracne, W. J. Evans, and A. K. McMahan, *Phys. Rev. Lett.* **101**, 165703 (2008).
 - [27] K. Held, C. Huscroft, R. T. Scalettar, and A. K. McMahan, *Phys. Rev. Lett.* **85**, 373 (2000).
 - [28] R. Beecroft and C. Swenson, *J. Phys. Chem. Solids* **15**, 234 (1960).
 - [29] A. Jayaraman, *Phys. Rev.* **137**, A179 (1965).
 - [30] A. Schiwek, F. Porsch, and W. B. Holzapfel, *High Pressure Res.* **22**, 407 (2002).
 - [31] M. Parrinello and A. Rahman, *J. Appl. Phys.* **52**, 7182 (1981).
 - [32] Z. P. Yin, X. Deng, K. Basu, Q. Yin, and G. Kotliar, *Philos. Mag. Lett.* **94**, 620 (2014).
 - [33] M.-F. Tian, H.-F. Song, H.-F. Liu, C. Wang, Z. Fang, and X. Dai, *arXiv:1408.2382*.