

Near-complete violation of detailed balance in thermal radiation

Linxiao Zhu

Department of Applied Physics, Stanford University, Stanford, California 94305, USA

Shanhui Fan*

Department of Electrical Engineering, Ginzton Laboratory, Stanford University, Stanford, California 94305, USA

(Received 5 July 2014; revised manuscript received 15 November 2014; published 1 December 2014)

We introduce general principles for achieving maximal violation of detailed balance in thermal radiation. We validate these principles by direct numerical calculations, based on fluctuational electrodynamics, on thermal emitters constructed from magneto-optical photonic crystals. Such a capability to maximally violate the detailed balance provides different opportunities for the design of thermal absorbers and emitters.

DOI: [10.1103/PhysRevB.90.220301](https://doi.org/10.1103/PhysRevB.90.220301)

PACS number(s): 44.40.+a, 42.79.Ek, 78.20.Ls, 78.67.Pt

For thermal radiation, the principle of detailed balance leads to the general form of the Kirchhoff's law [1–4], which states that

$$e(\omega, \theta, \phi) = \alpha(\omega, \theta, \phi), \quad (1)$$

where e is the directional spectral emissivity, α is the directional spectral absorptivity, ω is the frequency, and θ and ϕ specify a direction. Seeking to violate detailed balance is fundamentally important, because the principle of detailed balance implies the existence of an intrinsic loss mechanism that limits the efficiency of many energy conversion processes. For example, a solar absorber absorbs light from the sun. The detailed balance then dictates that the solar absorber must therefore radiate back to the sun. Such a radiation back to the sun is an intrinsic loss mechanism that can only be eliminated by maximal violation of detailed balance. The ability to significantly violate detailed balance therefore points to a pathway for the fundamental improvement of a wide variety of energy conversion processes, including solar energy harvesting and thermal radiation energy conversion.

Microscopically, Eq. (1) can be proven using the fluctuation-dissipation theorem, but only for emitters consisting of materials satisfying Lorentz reciprocity [5,6]. It has been noted theoretically that nonreciprocal materials, such as magneto-optical materials, may not obey detailed balance [7] and hence may not satisfy Eq. (1), without violating the second law of thermodynamics [8]. However, direct experimental measurements or theoretical designs of actual physical structures that violate detailed balance are still lacking.

In recent years, significant efforts have been devoted to the use of engineered photonic structures, including photonic crystals [9–26], optical antennas [27–29], and metamaterials [30–32], for the control of thermal radiation properties. Photonic structures can exhibit thermal radiation properties that are significantly different from naturally occurring materials. Notable examples include the creation of thermal emitters with a narrow spectrum [12,15,25] or enhanced coherence [11,17]. Previous works on the thermal radiation properties of photonic structures, however, consider only reciprocal materials. In this Rapid Communication, using the formalism of fluctuational electrodynamics [33–37], we present a direct

numerical calculation of thermal emission from nonreciprocal photonic structures, and introduce the theoretical conditions for such structures to maximally violate detailed balance, i.e., to achieve a unity difference between directional spectral emissivity and absorptivity.

Nonreciprocal photonic structures represent an important emerging direction for control of thermal radiation. From a fundamental point of view, significant numbers of theoretical approaches for the calculations of far-field thermal radiation use the Kirchhoff's law of Eq. (1) by computing the absorption properties [15–19,21,22,24]. Such an approach is no longer applicable for nonreciprocal thermal emitters, and direct calculations using the formalism of fluctuational electrodynamics become essential. From a practical point of view, creating nonreciprocal thermal emitters can have important implications for the enhancement of the efficiency for solar cells [38,39] and thermophotovoltaic systems [40].

We start by reviewing the general thermodynamic constraints on nonreciprocal thermal emitters. Consider an emitter that undergoes radiative exchange through two radiation channels, A and B , with two separate blackbodies also labeled A and B , respectively. Part of the emission from either blackbody A or blackbody B towards the emitter is absorbed, as described by absorptivities α_A and α_B , respectively. The emitter also emits towards the blackbodies, as described by emissivities e_A and e_B , respectively. We consider the equilibrium situation where the emitter, and the blackbodies, are at the same temperature T . The second law of thermodynamics then requires that there is no net energy flow in or out of the emitter, independent of whether or not the emitter is reciprocal. In the reciprocal case [Fig. 1(a)], $\alpha_{A,B} = e_{A,B}$, and as a result the second law of thermodynamics is satisfied. In the nonreciprocal case [Fig. 1(b)], considering the emission from blackbody A , through channel A , we assume that the part of the emission that is not absorbed by the emitter is reflected through channel B to blackbody B , with a reflectivity $r_{A \rightarrow B}$. As a result, we have

$$\alpha_A + r_{A \rightarrow B} = 1. \quad (2)$$

On the other hand, blackbody A receives emission from both the emitter and the part of emission from blackbody B that is not absorbed by the emitter, i.e.,

$$e_A + r_{B \rightarrow A} = 1. \quad (3)$$

*shanhui@stanford.edu

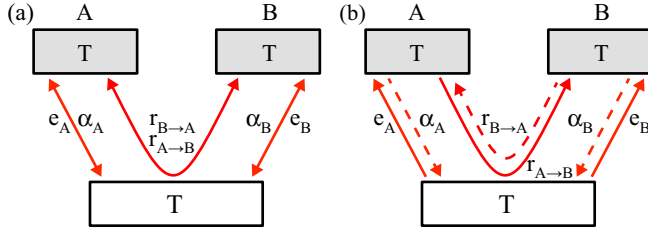


FIG. 1. (Color online) Energy flow diagrams in the cases of (a) a reciprocal emitter and (b) a nonreciprocal emitter. The emitter undergoes radiative exchange with two separate blackbodies labeled A and B, respectively. The emitter and the blackbodies are at the same temperature T .

Combining Eqs. (2) and (3) and similarly considering the energy balance of the blackbody B, we have

$$e_A - \alpha_A = r_{A \rightarrow B} - r_{B \rightarrow A} = \alpha_B - e_B. \quad (4)$$

For nonreciprocal systems, $r_{A \rightarrow B} \neq r_{B \rightarrow A}$ [41–43]. As a result, $e_{A,B} \neq \alpha_{A,B}$, and the detailed balance is violated. On the other hand, from Eq. (4) there is no net energy flow in and out of the emitter as well as bodies A and B, as required by the second law. Thus, for the nonreciprocal structure considered here, the second law in fact dictates the violation of detailed balance. The argument here is equivalent to Ref. [7], which uses bidirectional reflectance distribution functions, but simplified and generalized so that the argument can be directly applied to the physical system that has only specular reflection which we will consider in this Rapid Communication.

As a main contribution of this Rapid Communication, we next introduce the general conditions in order to achieve *maximum* violation of detailed balance in a physical structure. As the emitter, we consider a photonic crystal emitter structure that is periodic in the x direction, emitting to free space on top of the structure, with a mirror at the back side (Fig. 2). For simplicity we consider only a two-dimensional case where both the fields and the structure are assumed uniform along the z direction. The principle described here, however, is generalizable to three dimensions. For such a structure, its

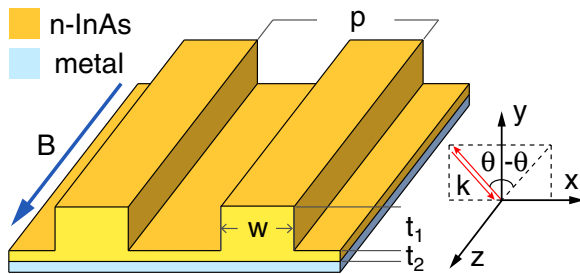


FIG. 2. (Color online) A schematic of a photonic crystal structure for maximal violation of detailed balance. The structure consists of an n -InAs grating structure atop a uniform metal layer. The structure is periodic in the x direction, and has the following geometry parameters: $p = 7.24 \mu\text{m}$, $w = 3.2 \mu\text{m}$, $t_1 = 1.981 \mu\text{m}$, and $t_2 = 0.485 \mu\text{m}$. An external magnetic field is applied in the z direction. TM polarization with an electric field in the x - y plane is considered.

electromagnetic properties are characterized by a photonic band structure $\omega(k_x)$, where ω is the frequency and k_x is the parallel wave vector.

Corresponding to the scenario as described in Fig. 1, we study the directional spectral emissivity and absorptivity $e(\omega, \pm\theta)$ and $\alpha(\omega, \pm\theta)$, respectively, where $\pm\theta$ are the angles of incidence for the two channels. Consider light incident with an angle of incidence θ having a parallel wave vector $k_x = \omega/c \sin \theta$. With a proper choice of periodicity that is sufficiently small, by momentum conservation, light can only be reflected into the $-\theta$ channel (Fig. 2). Moreover, if the ω and k_x of the incident light satisfy the photonic band structure $\omega(k_x)$ of the emitter, a mode inside the emitter will be resonantly excited, and as a result, typically there will be strong absorption, with part of the resonant excitation contributing to the reflected wave in the $-\theta$ channel. Similarly, the reflection and absorption properties for light incident with an angle of incidence of $-\theta$ will be controlled by the photonic band structure at $\omega(-k_x)$.

For an emitter constructed from a reciprocal material, its photonic band structure is symmetric in the k_x space [44], i.e., $\omega(k_x) = \omega(-k_x)$. The resonance frequencies for lights incident with an incidence angle of either θ or $-\theta$ are the same, and $r_{\theta \rightarrow -\theta} = r_{-\theta \rightarrow \theta}$. As a result, from Eq. (4) we have $e(\omega, \pm\theta) = \alpha(\omega, \pm\theta)$, and thus detailed balance is satisfied. On the other hand, with the breaking of reciprocity, for example, by the use of magneto-optical material, one can achieve an asymmetry of the photonic band structure in k_x space [41,45–48], i.e., $\omega(k_x) \neq \omega(-k_x)$. In such a case, the resonance conditions for the two channels are no longer the same, hence $r_{\theta \rightarrow -\theta} \neq r_{-\theta \rightarrow \theta}$, and as a result detailed balance can be violated.

In order to achieve maximum violation of detailed balance, from Eq. (4), one needs to have $r_{\theta \rightarrow -\theta} \approx 1$ and $r_{-\theta \rightarrow \theta} \approx 0$. Using coupled mode theory (CMT) [49], when the frequency of the incident light is near resonant, one can show that

$$r(\omega)_{\theta \rightarrow -\theta} = \frac{[\omega - \omega(k_x)]^2 + (\gamma_i - \gamma_e)^2}{[\omega - \omega(k_x)]^2 + (\gamma_i + \gamma_e)^2} \quad (5)$$

and

$$r(\omega)_{-\theta \rightarrow \theta} = \frac{[\omega - \omega(-k_x)]^2 + (\gamma_i - \gamma_e)^2}{[\omega - \omega(-k_x)]^2 + (\gamma_i + \gamma_e)^2}, \quad (6)$$

where for simplicity we have assumed that the two resonances at $\omega(k_x)$ and $\omega(-k_x)$ have the same intrinsic material loss rate γ_i and external leakage rate γ_e . Therefore, to achieve maximum violation of detailed balance, the structure needs to provide critical coupling for light incident with an angle of θ , i.e.,

$$\gamma_i = \gamma_e, \quad (7)$$

and also needs to be sufficiently off resonance for light incident with an angle of $-\theta$, i.e.,

$$|\omega(k_x) - \omega(-k_x)| \gg \gamma_i. \quad (8)$$

We provide a brief comment on some of the assumptions for Eqs. (5) and (6). The coupled mode theory is valid for resonance systems having a relatively high quality factor [49] and therefore it applies to our system. Also, when compared

with the underlying reciprocal structure, the introduction of nonreciprocal effects typically shifts the resonance frequency by a substantial amount, without significantly influencing the intrinsic material loss rate and external leakage rate of the resonance.

We implement the general consideration above with a photonic crystal structure as shown in Fig. 2. The photonic crystal structure consists of an n -InAs grating structure with $7.24 \mu\text{m}$ periodicity, on top of a uniform metal layer acting

$$\bar{\epsilon} = \begin{bmatrix} \epsilon_\infty - \frac{\omega_p^2(\omega+i\Gamma)}{\omega[(\omega+i\Gamma)^2-\omega_c^2]} & \frac{i\omega_p^2\omega_c}{\omega[(\omega+i\Gamma)^2-\omega_c^2]} & 0 \\ -\frac{i\omega_p^2\omega_c}{\omega[(\omega+i\Gamma)^2-\omega_c^2]} & \epsilon_\infty - \frac{\omega_p^2(\omega+i\Gamma)}{\omega[(\omega+i\Gamma)^2-\omega_c^2]} & 0 \\ 0 & 0 & \epsilon_\infty - \frac{\omega_p^2}{\omega(\omega+i\Gamma)} \end{bmatrix},$$

where $\epsilon_\infty = 12.37$ [53] is the high-frequency permittivity, Γ is the relaxation rate, $\omega_p = \sqrt{n_e e^2 / (m^* \epsilon_0)}$ is the plasma frequency, and $\omega_c = eB/m^*$ is the cyclotron frequency. Here n_e is the electron carrier density, m^* is effective electron mass, and B is the external magnetic field. We assume a doping concentration $n_e = 7.8 \times 10^{17} \text{ cm}^{-3}$. For the given doping level, the effective electron mass is $m^* = 0.033m_e$ [53] (m_e is the electron mass), and the relaxation rate Γ is calculated from $A = 4\pi/\lambda \text{ Im}[\sqrt{\epsilon_\infty - \frac{\omega_p^2}{\omega(\omega+i\Gamma)}}]$, where experimental absorbance $A = 0.0382\lambda^3$ (with λ in μm , and A in cm^{-1}) is extracted from Ref. [53]. We consider an experimentally achievable external magnetic field $B = 3 \text{ T}$. As our structure operates at $T \geq 300 \text{ K}$, where the thermal energy is larger than the Landau splitting energy $\hbar\omega_c$, Landau quantization is ignored.

The band structure of the photonic crystal can be understood by first considering a uniform slab of n -InAs with a thickness of $1.361 \mu\text{m}$, atop a PEC mirror. This uniform slab contains the same amount of n -InAs per unit area as the structure in Fig. 2. Its dispersion relation $\omega(k_x)$ can be calculated from

$$\tan(k_y t) = \frac{\epsilon_\perp k_y \alpha_y}{\epsilon_\perp (\omega/c)^2 - k_x^2 - \eta k_x \alpha_y}, \quad (9)$$

where $\epsilon_\perp = \text{Re}(\epsilon_{xx}) = \text{Re}(\epsilon_{yy})$, gyration $\eta = \text{Im}(\epsilon_{xy}) = -\text{Im}(\epsilon_{yx})$, t is the thickness of the uniform slab, $k_y = \sqrt{(\omega/c)^2 (\epsilon_\perp - \eta^2/\epsilon_\perp) - k_x^2}$ is the y -component wave vector of the guided mode inside the uniform slab, and $\alpha_y = \sqrt{k_x^2 - (\omega/c)^2}$ describes the exponential decay of the fields in vacuum. When $\eta \neq 0$, as will occur when the magnetic field is applied, we have $\omega(k_x) \neq \omega(-k_x)$.

To determine the dispersion relation of the photonic crystal, we compute the directional spectral absorptivity as shown in Fig. 3. We calculate absorptivity by a Fourier modal method adapted for nonreciprocal structures [54]. The location of the absorption peak in the ω - k_x space, which corresponds to the band structure of the photonic crystal, compares quite well with the folded band structure of the uniform slab. The effect of periodicity results in part of the band structure being folded above the light line, creating guided resonances which then

manifest as absorption resonances. In Fig. 3, we observe $\omega(k_x) \neq \omega(-k_x)$ in the band structure of the photonic crystal. In connection to the theory as shown earlier, we show the reflection spectra $r_{\theta \rightarrow -\theta}$, and $r_{-\theta \rightarrow \theta}$ in Fig. 4. In our system, the periodicity is chosen to be small enough such that only specular reflection occurs. For a reciprocal system, these spectra should be the same. In the presence of B , we see a difference between $r_{\theta \rightarrow -\theta}$ and $r_{-\theta \rightarrow \theta}$. The reflection spectra agree very well with coupled mode theory fitting using Eqs. (5) and (6), as shown in Fig. 4, with the parameters of the theoretical fit included in the caption of Fig. 4. The resonances are close to the critical coupling condition, as can be seen either by noting that peak absorption approaches 100%, or by examining the relevant internal absorption and external leakage rates in Fig. 4. The resonance frequency separation $|\omega(k_x) - \omega(-k_x)|$ is much larger than the decay rates, and satisfies the requirement of Eq. (8).

The calculation above, on the absorption properties of the photonic crystal, shows that such a photonic crystal satisfies all the theoretical conditions for maximum violation of detailed

balance as a mirror. For most of the calculations in this Rapid Communication, we assume the mirror to be a perfect electric conductor (PEC). The effect of using a lossy aluminum mirror will be discussed later. We consider the TM polarization with electric fields in the x - y plane. To break reciprocity, we use a Voigt geometry, where an external magnetic field is applied along the translation-invariant z direction. The relative permittivity tensor of n -InAs in the presence of the B field is [50–52]

manifest as absorption resonances. In Fig. 3, we observe $\omega(k_x) \neq \omega(-k_x)$ in the band structure of the photonic crystal. In connection to the theory as shown earlier, we show the reflection spectra $r_{\theta \rightarrow -\theta}$, and $r_{-\theta \rightarrow \theta}$ in Fig. 4. In our system, the periodicity is chosen to be small enough such that only specular reflection occurs. For a reciprocal system, these spectra should be the same. In the presence of B , we see a difference between $r_{\theta \rightarrow -\theta}$ and $r_{-\theta \rightarrow \theta}$. The reflection spectra agree very well with coupled mode theory fitting using Eqs. (5) and (6), as shown in Fig. 4, with the parameters of the theoretical fit included in the caption of Fig. 4. The resonances are close to the critical coupling condition, as can be seen either by noting that peak absorption approaches 100%, or by examining the relevant internal absorption and external leakage rates in Fig. 4. The resonance frequency separation $|\omega(k_x) - \omega(-k_x)|$ is much larger than the decay rates, and satisfies the requirement of Eq. (8).

The calculation above, on the absorption properties of the photonic crystal, shows that such a photonic crystal satisfies all the theoretical conditions for maximum violation of detailed

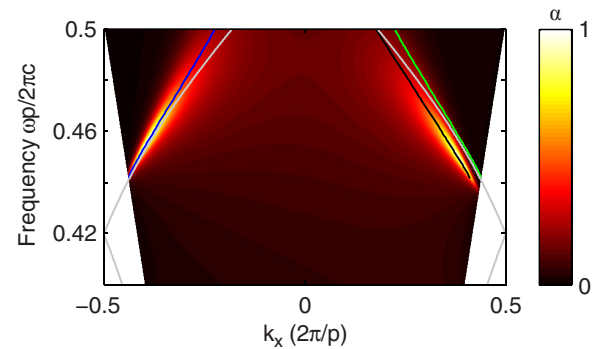


FIG. 3. (Color online) Absorptivity for different parallel wave vectors and frequencies, for the structure in Fig. 2 with PEC as a mirror, at $B = 3 \text{ T}$. The black and blue solid curves denote the peaks of absorptivities at positive and negative parallel wave vectors, respectively. The green solid curve is the mirror reflection of the blue solid curve. The gray solid curves denote the folded band structure for a $1.361\text{-}\mu\text{m}$ -thick uniform n -InAs atop a PEC mirror without an external B field.

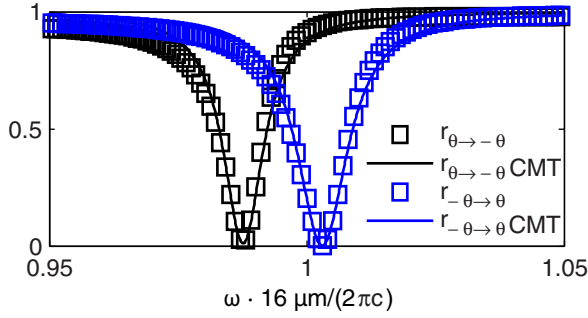


FIG. 4. (Color online) Reflectivity spectra of $r_{\theta \rightarrow -\theta}$ and $r_{-\theta \rightarrow \theta}$, for the structure in Fig. 2 with a PEC mirror, at $B = 3$ T and $\theta = 61.28^\circ$. The parameters for the coupled mode theory (CMT) fitting using Eqs. (5) and (6) are $\omega(k_x) = 456.6 \times 10^{11}$ rad/s, $\omega(-k_x) = 463.7 \times 10^{11}$ rad/s, $\gamma_{i,k_x} = 1.22 \times 10^{11}$ rad/s, $\gamma_{e,k_x} = 9.78 \times 10^{10}$ rad/s, $\gamma_{i,-k_x} = 1.33 \times 10^{11}$ rad/s, and $\gamma_{e,-k_x} = 1.42 \times 10^{11}$ rad/s.

balance. As a direct check of the theoretical concept, we now proceed to compute the directional spectral emissivity and compare that with the corresponding directional spectral absorptivity. Obviously, since our goal is to demonstrate violation of detailed balance, we cannot use an absorptivity calculation to infer about emissivity, as was commonly done in the literature on thermal radiation calculations [15–19,21,22,24]. Instead, to compute emissivity, we provide a direct calculation based on fluctuational electrodynamics. In this approach, the thermal emission is generated by fluctuating random current $j(\mathbf{r}, t)$ inside the material. The magnitude of the fluctuation is related to the imaginary part of the dielectric tensor,

$$\langle j_k(\mathbf{r}, \omega) j_l^*(\mathbf{r}', \omega') \rangle = 4\pi\omega\Theta(\omega, T)\delta(\mathbf{r} - \mathbf{r}')\delta(\omega - \omega') \times [\epsilon_{kl}(\mathbf{r}, \omega) - \epsilon_{lk}^*(\mathbf{r}, \omega)] / (2i), \quad (10)$$

where $\Theta(\omega, T) = \hbar\omega / [\exp(\hbar\omega/k_B/T) - 1]$. This form of the fluctuation-dissipation theorem is appropriate for magneto-optical materials [37]. We assume the structure is in local thermal equilibrium with a uniform temperature T . To compute the resulting energy flux from such sources, we use a Fourier modal method, where the fluctuating random current $j(\mathbf{r}, t)$, the dielectric constant profile in each patterned layer, and the electromagnetic fields are all expanded in Fourier space. We use a numerically stable scattering matrix formalism [54] to relate Fourier modal amplitudes between layers. The magnitude of the fluctuation is determined from Eq. (10).

In Figs. 5(a) and 5(b), we show the emissivity spectra, for the structure atop a PEC mirror (Fig. 2), at $\theta = 61.28^\circ$, compared to the absorptivity spectra at the same angle. Figure 5(a) shows the calculation result when $B = 0$. The absorptivity and emissivity spectra perfectly overlap, and detailed balance is satisfied in this case, as expected. We emphasize that our computation method itself does not use reciprocity. Thus the agreement between two separate calculations on absorptivity and emissivity provides a direct check of our numerical approach. With $B = 3$ T [Fig. 5(b)], the absorptivity and emissivity no longer overlap, indicating the violation of detailed balance. The contrast in directional

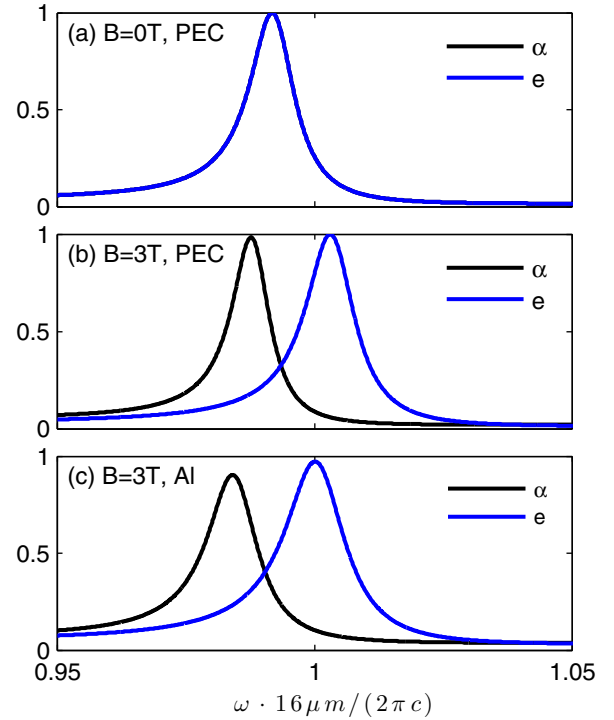


FIG. 5. (Color online) Absorptivity (α) and emissivity (e) spectra, for the structure atop a PEC mirror (Fig. 2), at $\theta = 61.28^\circ$, and (a) $B = 0$ T or (b) $B = 3$ T. (c) Absorptivity and emissivity spectra, for the structure atop an aluminum (Al) mirror (Fig. 2), at $\theta = 61.28^\circ$ and $B = 3$ T.

spectral absorptivity and emissivity can be as large as 12.7 dB at a wavelength of $15.92 \mu\text{m}$. Thus, our structure indeed provides near-maximum violation of detailed balance. The results here provide a numerical validation of the theoretical condition.

Figure 5(c) shows the calculation results for the absorptivity and emissivity, when we replace the PEC mirror with a more realistic aluminum mirror. The effect of near-maximum violation of detailed balance persists. The contrast ratio between the directional spectral emissivity and absorptivity is as large as 10.2 dB at a wavelength of $15.96 \mu\text{m}$, with $\theta = 61.28^\circ$.

The capability to achieve significant violation of detailed balance may provide different opportunities for the design of thermal absorbers and emitters. By violating detailed balance, the thermal radiation from the absorber does not need to be sent to the source, but instead can be reused to boost the energy conversion efficiency [38,39]. Our design for an thermal emitter that maximally violates detailed balance therefore points to opportunities to exploit nonreciprocal photonics to enhance the efficiency of renewable energy systems.

This work was supported by the DOE Light-Material Interactions in Energy Conversion Energy Frontier Research Center under Grant No. DE-SC0001293. S.F. acknowledges discussions with E. Yablonovitch.

- [1] G. Kirchhoff, *Ann. Phys.* **185**, 275 (1860).
- [2] M. Planck, *The Theory of Heat Radiation* (Forgotten Books, London, 2013).
- [3] R. Siegel and J. Howell, *Thermal Radiation Heat Transfer*, 4th ed. (Taylor & Francis, London, 2001), p. 49.
- [4] T. Bergman, A. Lavine, F. Incropera, and D. DeWitt, *Fundamentals of Heat and Mass Transfer*, 7th ed. (Wiley, Hoboken NJ, 2011), p. 811.
- [5] M. Krüger, G. Bimonte, T. Emig, and M. Kardar, *Phys. Rev. B* **86**, 115423 (2012).
- [6] S. E. Han, *Phys. Rev. B* **80**, 155108 (2009).
- [7] W. C. Snyder, Z. Wan, and X. Li, *Appl. Opt.* **37**, 3464 (1998).
- [8] L. Rayleigh, *Nature (London)* **64**, 577 (1901).
- [9] S. Y. Lin, J. G. Fleming, E. Chow, J. Bur, K. K. Choi, and A. Goldberg, *Phys. Rev. B* **62**, R2243 (2000).
- [10] S. Maruyama, T. Kashiwa, H. Yugami, and M. Esashi, *Appl. Phys. Lett.* **79**, 1393 (2001).
- [11] J.-J. Greffet, R. Carminati, K. Joulain, J.-P. Mulet, S. Mainguy, and Y. Chen, *Nature (London)* **416**, 61 (2002).
- [12] S. Y. Lin, J. Moreno, and J. G. Fleming, *Appl. Phys. Lett.* **83**, 380 (2003).
- [13] A. Narayanaswamy and G. Chen, *Phys. Rev. B* **70**, 125101 (2004).
- [14] C. Luo, A. Narayanaswamy, G. Chen, and J. D. Joannopoulos, *Phys. Rev. Lett.* **93**, 213905 (2004).
- [15] I. Celanovic, D. Perreault, and J. Kassakian, *Phys. Rev. B* **72**, 075127 (2005).
- [16] M. Florescu, H. Lee, A. J. Stimpson, and J. Dowling, *Phys. Rev. A* **72**, 033821 (2005).
- [17] M. Laroche, R. Carminati, and J.-J. Greffet, *Phys. Rev. Lett.* **96**, 123903 (2006).
- [18] D. L. C. Chan, M. Soljačić, and J. D. Joannopoulos, *Phys. Rev. E* **74**, 016609 (2006).
- [19] D. L. C. Chan, M. Soljačić, and J. D. Joannopoulos, *Opt. Express* **14**, 8785 (2006).
- [20] D. L. C. Chan, M. Soljačić, and J. D. Joannopoulos, *Phys. Rev. E* **74**, 036615 (2006).
- [21] S. E. Han, A. Stein, and D. J. Norris, *Phys. Rev. Lett.* **99**, 053906 (2007).
- [22] B. J. Lee and Z. M. Zhang, *J. Heat Transfer* **129**, 17 (2007).
- [23] M. Florescu, K. Busch, and J. P. Dowling, *Phys. Rev. B* **75**, 201101 (2007).
- [24] P. Bermel, M. Ghebrebrhan, W. Chan, Y. X. Yeng, M. Araghchini, R. Hamam, C. H. Marton, K. F. Jensen, M. Soljačić, J. D. Joannopoulos, S. G. Johnson, and I. Celanovic, *Opt. Express* **18**, A314 (2010).
- [25] M. D. Zoysa, T. Asano, K. Mochizuki, A. Oskooi, T. Inoue, and S. Noda, *Nat. Photonics* **6**, 535 (2012).
- [26] K. A. Arpin, M. D. Losego, A. N. Cloud, H. Ning, J. Mallek, N. P. Sergeant, L. Zhu, Z. Yu, B. Kalanyan, G. N. Parsons, G. S. Girolami, J. R. Abelson, S. Fan, and P. V. Braun, *Nat. Commun.* **4**, 2630 (2013).
- [27] J. A. Schuller, T. Taubner, and M. L. Brongersma, *Nat. Photonics* **3**, 658 (2009).
- [28] X. Liu, T. Tyler, T. Starr, A. F. Starr, N. M. Jokerst, and W. J. Padilla, *Phys. Rev. Lett.* **107**, 045901 (2011).
- [29] L. Zhu, S. Sandhu, C. Otey, S. Fan, M. B. Sinclair, and T. Shan Luk, *Appl. Phys. Lett.* **102**, 103104 (2013).
- [30] N. Dahan, Y. Gorodetski, K. Frischwasser, V. Kleiner, and E. Hasman, *Phys. Rev. Lett.* **105**, 136402 (2010).
- [31] S. Molesky, C. J. Dewalt, and Z. Jacob, *Opt. Express* **21**, A96 (2013).
- [32] M. A. Kats, R. Blanchard, S. Zhang, P. Genevet, C. Ko, S. Ramanathan, and F. Capasso, *Phys. Rev. X* **3**, 041004 (2013).
- [33] S. Rytov, Y. A. Kravtsov, and V. Tatarskii, *Principles of Statistical Radiophysics* (Springer, Berlin 1989).
- [34] H. B. Callen and T. A. Welton, *Phys. Rev.* **83**, 34 (1951).
- [35] R. Kubo, *Rep. Prog. Phys.* **29**, 255 (1966).
- [36] G. S. Agarwal, *Phys. Rev. A* **11**, 230 (1975).
- [37] L. Landau, E. Lifshitz, and L. Pitaevskii, *Course of Theoretical Physics* (Pergamon, New York, 1980), Vol. 9, Part 2, Chap. VIII, p. 319.
- [38] M. Green, *Nano Lett.* **12**, 5985 (2012).
- [39] H. Ries, *Appl. Phys. B* **32**, 153 (1983).
- [40] A. Lenert, D. M. Bierman, Y. Nam, W. R. Chan, I. Celanović, M. Soljačić, and E. N. Wang, *Nat. Nanotechnol.* **9**, 126 (2014).
- [41] Z. Yu, Z. Wang, and S. Fan, *Appl. Phys. Lett.* **90**, 121133 (2007).
- [42] D. E. Brown, T. Dumelow, T. J. Parker, K. Abraha, and D. R. Tilley, *Phys. Rev. B* **49**, 12266 (1994).
- [43] T. Dumelow and R. E. Camley, *Phys. Rev. B* **54**, 12232 (1996).
- [44] J. D. Joannopoulos, S. G. Johnson, J. N. Winn, and R. D. Meade, *Photonic Crystals: Molding the Flow of Light*, 2nd ed. (Princeton University Press, Princeton, NJ, 2011).
- [45] M. J. Steel, M. Levy, and R. M. Osgood, *IEEE Photonics Technol. Lett.* **12**, 1171 (2000).
- [46] I. Bitá and E. Thomas, *J. Opt. Soc. Am. B* **22**, 1199 (2005).
- [47] M. Vanwolleghem, X. Checoury, W. Śmigaj, B. Gralak, L. Magdenko, K. Postava, B. Dagens, P. Beauvillain, and J.-M. Lourtioz, *Phys. Rev. B* **80**, 121102 (2009).
- [48] A. B. Khanikaev, A. V. Baryshev, M. Inoue, and Y. S. Kivshar, *Appl. Phys. Lett.* **95**, 011101 (2009).
- [49] H. Haus, *Waves and Fields in Optoelectronics* (Prentice Hall, Upper Saddle River, NJ, 1984).
- [50] K. Seeger, *Semiconductor Physics: An Introduction* (US Government Printing Office, Washington, DC, 2004).
- [51] V. I. Pipa, A. I. Liptuga, and V. Morozhenko, *J. Opt.* **15**, 075104 (2013).
- [52] S. Law, D. C. Adams, A. M. Taylor, and D. Wasserman, *Opt. Express* **20**, 12155 (2012).
- [53] O. Madelung, *Semiconductors: Data Handbook*, 3rd ed. (Springer, Berlin, 2004).
- [54] D. M. Whittaker and I. S. Culshaw, *Phys. Rev. B* **60**, 2610 (1999).