

Pressure dependence of the magnetic order in CrAs: A neutron diffraction investigation

L. Keller,^{1,*} J. S. White,¹ M. Frontzek,¹ P. Babkevich,² M. A. Susner,³ Z. C. Sims,³ A. S. Sefat,³
H. M. Rønnow,^{2,4} and Ch. Rüegg^{1,5}

¹Laboratory for Neutron Scattering and Imaging, Paul Scherrer Institut, CH-5232 Villigen PSI, Switzerland

²Laboratory for Quantum Magnetism, École Polytechnique Fédérale de Lausanne, CH-1015 Lausanne, Switzerland

³Materials Science and Technology Division, Oak Ridge National Laboratory, Oak Ridge, Tennessee 37831-6114, USA

⁴RIKEN Centre for Emergent Matter Science (CEMS), Waki 351-0198, Japan

⁵Department of Quantum Matter Physics, University of Geneva, CH-1211 Geneva, Switzerland

(Received 19 September 2014; revised manuscript received 24 November 2014; published 29 January 2015)

The suppression of magnetic order with pressure concomitant with the appearance of pressure-induced superconductivity was recently discovered in CrAs. Here we present a neutron diffraction study of the pressure evolution of the helimagnetic ground state towards and in the vicinity of the superconducting phase. Neutron diffraction on polycrystalline CrAs was employed from zero pressure to 0.65 GPa and at various temperatures. The helimagnetic long-range order is sustained under pressure and the magnetic propagation vector does not show any considerable change. The average ordered magnetic moment is reduced from 1.73(2) μ_B at ambient pressure to 0.4(1) μ_B close to the critical pressure $P_c \approx 0.7$ GPa, at which magnetic order is completely suppressed. The width of the magnetic Bragg peaks strongly depends on temperature and pressure, showing a maximum in the region of the onset of superconductivity. We interpret this as associated with competing ground states in the vicinity of the superconducting phase.

DOI: [10.1103/PhysRevB.91.020409](https://doi.org/10.1103/PhysRevB.91.020409)

PACS number(s): 61.05.fg, 74.70.-b, 75.25.-j

The magnetic structure of chromium monoarsenide was first investigated more than four decades ago [1–3]. At $T_N \approx 265$ K and ambient pressure, CrAs undergoes a first-order phase transition to a helimagnetic state. The magnetic propagation vector \mathbf{k} is found to be parallel to the c axis and the magnetic moments lie in the ab plane. The magnetic structure can be seen as a set of four magnetic spirals along c , one for each Cr in the crystallographic unit cell, with well-defined magnetic phase angles between the magnetic spirals. This first-order magnetic phase transition is accompanied by abrupt changes of the lattice parameters, most prominently seen by a sudden expansion of b below T_N [3]. Nevertheless, the orthorhombic MnP-type crystal structure with the space group $Pnma$ is preserved in the full temperature range.

The discontinuous onset of magnetic order has been related to a transition between collective and localized electronic states, with the abrupt change of b as an important feature of this transition [3]. Such a system with coupled structural, magnetic, and electronic properties is expected to be sensitive to pressure or doping, which motivated the investigation of the CrAs system under pressure. First pressure studies on CrAs reported that T_N shifts to lower values with pressure and vanishes completely at 0.45 GPa [4]. Very recently, the pressure-temperature phase diagram of CrAs has been independently investigated by Wu *et al.* [5] and Kotegawa *et al.* [6] using resistivity measurements under pressure. These studies each confirm that the magnetic ordering temperature T_N drastically decreases with pressure and that the magnetic order is completely suppressed above a critical pressure $P_c \approx 0.7$ GPa. Remarkably, superconductivity was discovered to appear on suppression of the magnetic phase, displaying a maximum superconducting transition temperature $T_c \approx 2.2$ K at about 1 GPa [5,6]. Increasing the pressure further decreases

T_c , and the superconducting phase adopts a domelike shape. This pressure-temperature phase diagram with the gradual suppression of the magnetic state and the superconducting dome resembles that of many superconducting systems where unconventional superconductivity is induced by pressure or chemical doping [7,8].

Wu *et al.* reported the onset of superconductivity already at ~ 0.3 GPa and a gradual increase of the superconducting volume fraction up to P_c , i.e., there is a region of coexistence of the magnetic and superconducting states. A very recent nuclear quadrupole resonance study under pressure [9] on CrAs reported that the internal field in the helimagnetic state only decreases slowly with increasing pressure, but maintains a large value close to P_c . This indicates that the pressure-induced suppression of the magnetic order is of the first order. Therefore, even though substantial fluctuations are present in the paramagnetic state, the system is not close to quantum criticality [9].

An incommensurate structure as found in CrAs at ambient pressure may be the result of competing exchange interactions or nesting. Such a structure is expected to be sensitive to distortions introduced by additional electronic or magnetic processes. A region of coexistence of magnetism and superconductivity is also a region of competing ground states and the magnetic structure might be distorted. Features of the magnetic structure close to or in the region of coexistence may therefore act as a sensitive local probe. Neutron scattering is a direct and bulk microscopic probe of magnetic order and domains, which have not yet been studied in CrAs in the vicinity of the pressure-induced superconducting phase. Here we report neutron powder diffraction experiments on the magnetic ground state of CrAs towards and in the vicinity of the superconducting phase.

The polycrystalline sample of CrAs was synthesized as previously described [10]. The neutron powder diffraction measurements were carried out using the cold neutron powder

*lukas.keller@psi.ch

TABLE I. Refined structural and magnetic parameters of CrAs at $T = 1.5, 80,$ and 300 K at ambient pressure; $a-c$: lattice parameters; x, z : atomic coordinates at site $4c$ in $Pnma$; B : temperature factor; μ : ordered magnetic moment; ϕ : magnetic phase angle; k_c : component of magnetic propagation vector.

	1.5 K	80 K	300 K
a (Å)	5.6049(3)	5.6068(3)	5.6472(3)
b (Å)	3.5852(2)	3.5846(2)	3.4727(2)
c (Å)	6.1301(5)	6.1304(4)	6.2017(6)
x/Cr (Å)	0.0068(12)	0.0064(12)	0.0060(10)
z/Cr (Å)	0.2034(10)	0.2026(8)	0.2022(10)
B/Cr (Å ²)	0.20(8)	0.32(7)	0.62(8)
x/As (Å)	0.2011(10)	0.2033(14)	0.2021(13)
z/As (Å)	0.5802(12)	0.5792(12)	0.5758(10)
B/As (Å ²)	0.12(5)	0.26(7)	0.51(7)
μ (μ_B)	1.73(2)	1.71(2)	
ϕ (°)	-110(4)	-108(4)	
k_c	0.3562(2)	0.3590(2)	
R_p	5.92	5.83	5.89

diffractometer DMC at the Swiss Spallation Neutron Source SINQ, Paul Scherrer Institute, Switzerland. The wavelength of the neutron beam was 3.804 Å. For the reference measurement at ambient pressure, CrAs powder was enclosed in a V container and measured at $1.5, 80,$ and 300 K. The clamp pressure cell was mounted in a He cryostat, covering a pressure range from ambient pressure up to 0.65 GPa at temperatures between 1.2 and 300 K. Within the pressure cell, the powder sample was enclosed in a lead capsule and a fluorocarbon-based fluid was used as the pressure-transmitting medium. The applied pressure was determined by measuring the change of lattice parameters of NaCl mixed with the sample. Profile refinements of the powder diffraction patterns were performed using the Rietveld software package FULLPROF SUITE [11].

As a reference for the experiments under pressure, we performed neutron powder diffraction measurements on CrAs (mixed with NaCl as a pressure calibrant) at ambient pressure in the paramagnetic state at $T = 300$ K and in the magnetically ordered state at $T = 80$ K and 1.5 K (see Table I). The ambient pressure diffraction pattern of CrAs at 1.5 K is presented in Fig. 1. Also shown are the calculated patterns from the refined structural and magnetic models and the difference of observed and calculated pattern, showing the excellent agreement of experimental data and model calculation. The three refined phases are the crystal and helimagnetic structures of CrAs and the crystal structure of NaCl. The analysis of the data is consistent with the type of magnetic structure found in the literature [2,3], i.e., incommensurate helical magnetic order. The magnetic propagation vector \mathbf{k} is of the form $\mathbf{k} = (0, 0, k_c)$ and the ordered moments lie in the ab plane (Fig. 2). The refined ordered magnetic moment per Cr is $1.73(2) \mu_B$, the nonzero component of the magnetic propagation vector $k_c = 0.3562(2)$, and the magnetic phase angle $\phi = -110(4)^\circ$. ϕ is defined as the angle between the moments of Cr atoms 1 and 2 (see Fig. 2), or between Cr atoms 3 and 4, respectively. ϕ deviates from previously published values, which cannot reproduce our data. In the earlier studies,

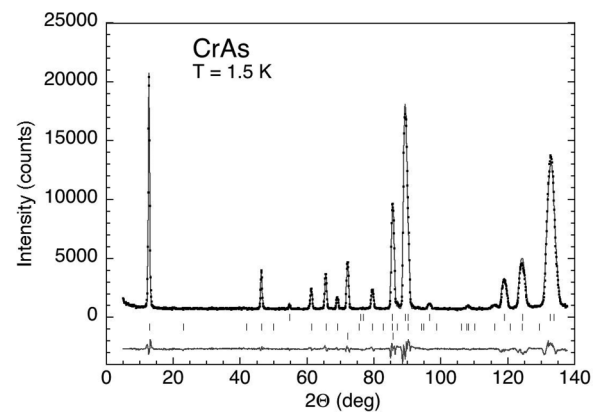


FIG. 1. Refinement of the neutron powder diffraction pattern of CrAs at $T = 1.5$ K and ambient pressure. The three phases used for the refinement are the crystal structure of CrAs, the magnetic structure of CrAs, and the crystal structure of NaCl, with neutron wavelength 3.804 Å.

the strongest magnetic peak ($00k_c$) was dominated by a large background at low angles, which flawed the determination of its integrated intensity. In our experiment, we avoided

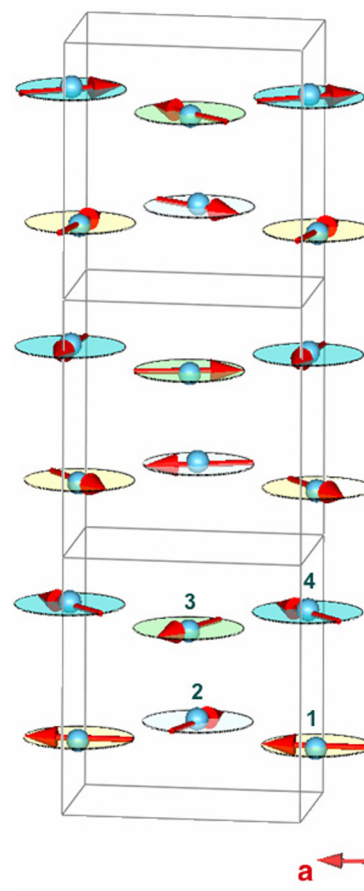


FIG. 2. (Color online) Incommensurate helical magnetic structure of CrAs. The evolution of the moments is shown for three unit cells along c ; the four spirals are marked in individual colors. ϕ is defined as the angle between the moments of Cr atoms 1 and 2 (or 3 and 4).

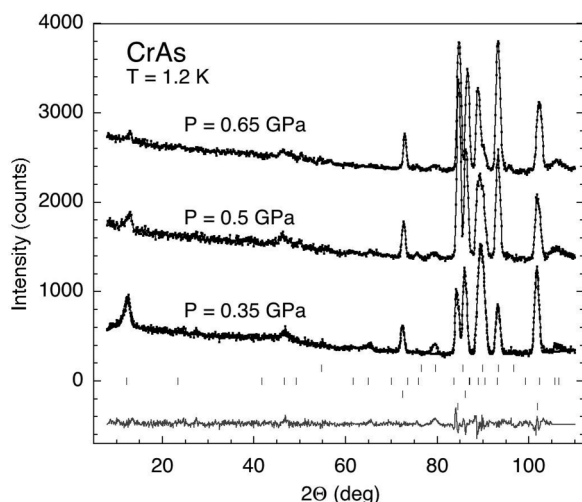


FIG. 3. Pressure dependence of the neutron diffraction patterns at $T = 1.2$ K for the pressures $P = 0.35, 0.5,$ and 0.65 GPa. The intensity axis relates to the 0.35 GPa data; other data sets have been shifted for clarity. Also shown is the refinement of the neutron powder diffraction pattern at $P = 0.35$ GPa, including the crystallographic phase of CrAs, the helimagnetic phase of CrAs, NaCl as the pressure calibrant, and Pb used for the sample capsule in the pressure cell; neutron wavelength is 3.804 \AA .

this problem by an experimental setup with long neutron wavelength of 3.804 \AA .

The pressure dependence of the neutron diffraction patterns at base temperature of 1.2 K, measured at $0.35, 0.5,$ and 0.65 GPa, is shown in Fig. 3. Analysis of the data revealed that no crystallographic or magnetic phase transition occurred and that the symmetries of the crystal and magnetic lattices are preserved. The observed peak shifts are due to shrinking of the lattice with pressure. The limited number of measured peaks does not allow for a full crystallographic refinement and the atomic positions were kept fixed in the analysis. A correction for preferred orientation introduced by applying pressure was included in the refinement. The data did not show a change of relative magnetic intensities or appearance of new magnetic peaks, which would give evidence for a reorientation of the magnetic moments. This is in agreement with recent nuclear magnetic resonance (NMR) and nuclear quadrupole resonance (NQR) measurements [9]. Therefore, for the refinement of the magnetic structure, the zero-pressure helimagnetic model was assumed, with the ordered moment and the propagation vector as refinable parameters. The profile refinement of the diffraction data at $T = 1.2$ K and $P = 0.35$ GPa is shown in Fig. 3, including the crystallographic phase of CrAs, the helimagnetic phase of CrAs, NaCl as the pressure calibrant, and Pb used for the sample capsule in the pressure cell. The magnetic intensities decrease with pressure, as also seen in Fig. 4, which indicates a reduction of the average ordered moment. The magnetic peaks of CrAs show a clear change in width and shape [Fig. 4 for $(0,0, \pm k_c)$], which is not seen for either the crystallographic CrAs peaks or the NaCl peaks. Therefore, an inhomogeneity induced by the pressure-transmitting medium at low temperature can be ruled

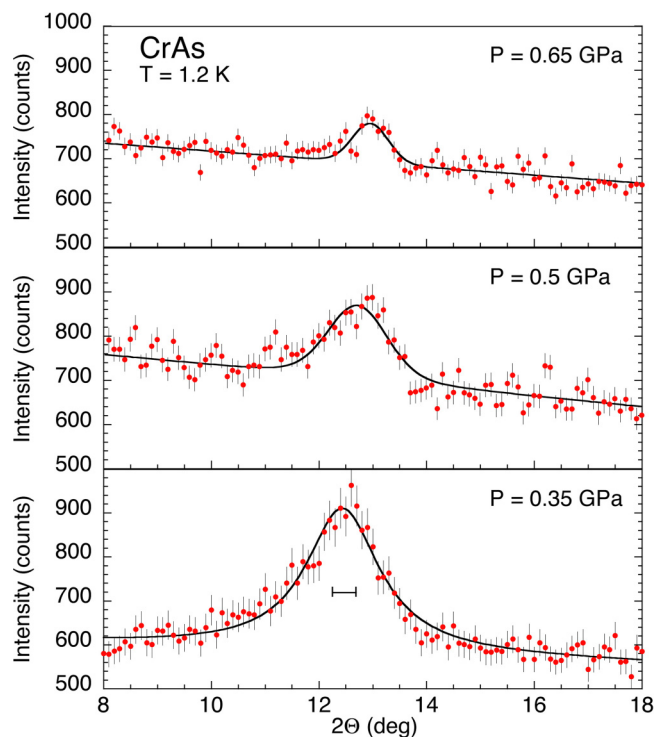


FIG. 4. (Color online) Pressure dependence of the first magnetic satellite $(00 \pm k_c)$ for the pressures $P = 0.35, 0.5,$ and 0.65 GPa. A convolution of Lorentzian and Gaussian peak shape functions was used for the profile fits.

out. Peak widths are sensitive probes for distortions to the magnetic structure; this will be discussed below.

The results of the magnetic refinements are summarized in Figs. 5(a) and 5(b). Figure 5(a) shows the pressure dependence of the average ordered Cr moment for the helimagnetic structure model. The average moment decreases with pressure to $0.42(10) \mu_B$ at 0.65 GPa, close to the critical pressure $P_c = 0.7$ GPa for total suppression of magnetic order. A recent NMR and NQR study [9] showed that the pressure dependence of the internal field H_{int} in CrAs shows a first-order transition to the paramagnetic state at P_c . This behavior as well as the suppression of magnetic fluctuations at low temperatures [9] suggest that the suppression of magnetic order as a function of pressure does not end in a magnetic quantum critical point at P_c . The moment deduced from H_{int} [Fig. 5(a)] shows only a moderate decrease with pressure as compared to the neutron results. Neutron diffraction measures the whole sample, while NMR probes the magnetic domains only. Therefore, the ordered moment deduced from neutron diffraction is averaged over the whole sample. The observed discrepancy can be explained with a reduced magnetic volume fraction and the refined size of the ordered moments with the sample under pressure should be regarded as a lower bound. Together with the observation by Wu *et al.* of a gradual increase of the superconducting volume fraction with increasing pressure [5], our diffraction results point towards a large coexistence region of magnetic order and superconductivity in CrAs.

Independent of the magnetic volume fraction, the magnetic propagation vector shows only a marginal pressure dependence within the error of the fit [Fig. 5(b)], i.e., the periodicity or

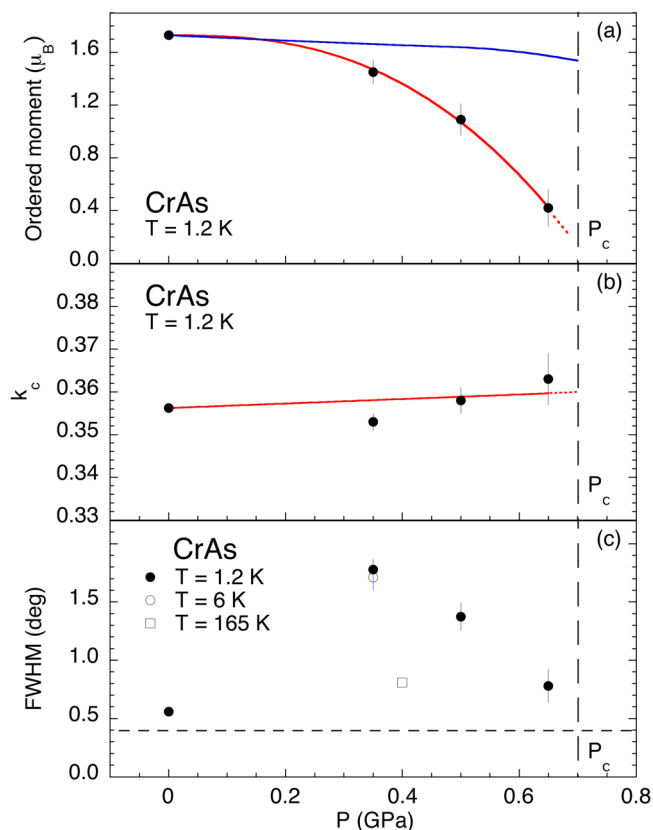


FIG. 5. (Color online) Pressure dependence of magnetic and peak shape parameters for $P = 0, 0.35, 0.5,$ and 0.65 GPa at $T = 1.2$ K. (a) Average ordered magnetic moment for the helimagnetic model, assuming 100% magnetic volume fraction (red line) and deduced from H_{int} in Ref. [9] (blue line). (b) Nonzero component of the magnetic propagation vector. (c) Full width at half maximum (FWHM) for the magnetic satellite ($00 \pm k_c$); the horizontal dashed line denotes the instrumental peak width.

turning angle of the magnetic spirals remains stable with applied pressure. This is a remarkable behavior since the incommensurate magnetic structure in CrAs is regarded to be the result of competing exchange interactions [3] and one would expect some response to the changes in atomic distances and angles caused by applied pressure. On the other hand, \mathbf{k} is also very stable as a function of temperature at ambient pressure and the present magnetic order seems clearly favored.

The pressure dependence presented in Fig. 4 showed not only a reduction of intensity due to a reduced magnetic moment, but also a change in peak shape. Therefore, it is interesting to also investigate the temperature-dependent effects at a fixed pressure. The temperature dependence of the diffraction patterns at 0.35 GPa is shown in Fig. 6, and the temperature evolution of the magnetic ($00 \pm k_c$) peak is shown in Fig. 7. The refinement reveals that the ordered magnetic moments at 1.2 and 6 K are the same within the error. But as for the pressure dependence at 1.2 K (Fig. 4), the width and the shape of the magnetic ($00 \pm k_c$) peak shows drastic changes. The peak shape function used for the profile fits in Fig. 7 is a convolution of a Lorentzian and Gaussian function with the respective weights as a free parameter. For the magnetic peak shape at 1.2 K, we obtain a pure Lorentzian function; at 6 K,

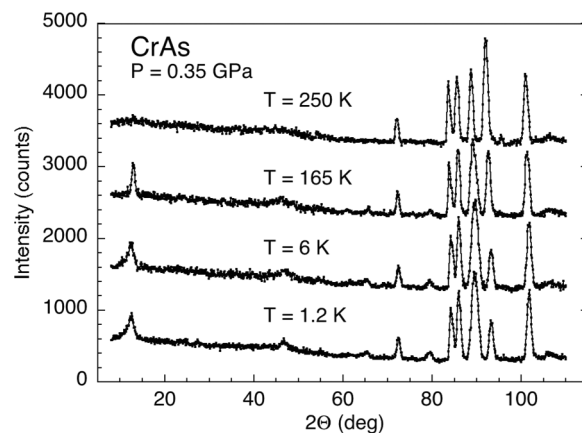


FIG. 6. Temperature dependence of the neutron diffraction patterns for $T = 1.2$ K (0.35 GPa), 6 K (0.35 GPa), 165 K (0.40 GPa), and 250 K (0.43 GPa). The intensity axis relates to the 1.2 K data; the other data sets have been shifted for clarity.

we obtain a mixed Lorentzian/Gaussian with equal weight; and at 165 K, we obtain an almost pure Gaussian function, which reflects the instrumental peak shape.

The pressure and temperature evolution of the full width at half maximum (FWHM) of the magnetic ($00 \pm k_c$) peak is plotted in Fig. 5(c). The FWHM shows a maximum at 1.2 K and 0.35 GPa, just in the region of coexistence of magnetism and superconductivity [5]. Increasing the pressure leads to a reduction of the FWHM and at 0.65 GPa it is

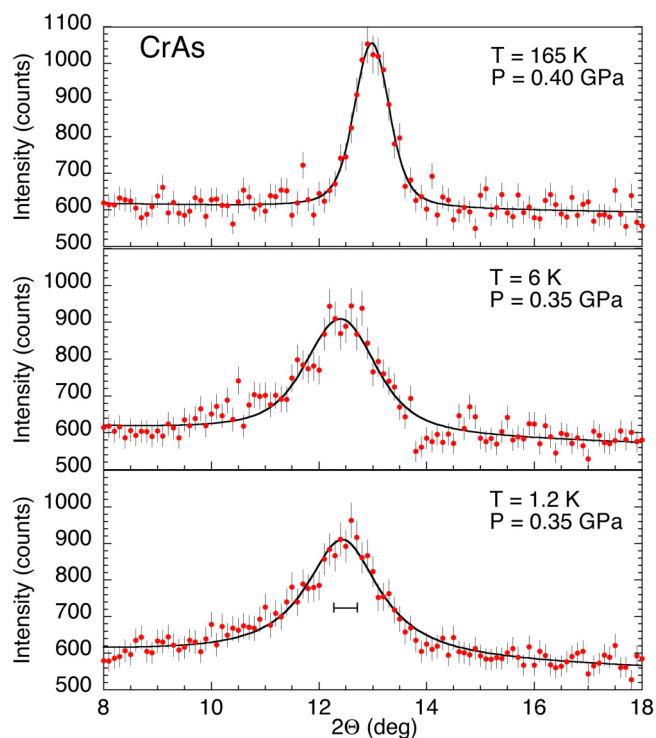


FIG. 7. (Color online) Temperature dependence of the first magnetic satellite ($00 \pm k_c$) for the temperatures $T = 1.2, 6,$ and 165 K. A convolution of Lorentzian and Gaussian peak shape functions was used for the profile fits.

close to the zero-pressure value. The same observation applies for increasing temperature at 0.35 GPa. The peak width is determined by instrumental parameters as well as by physical properties of the sample. The instrumental setup was not changed during the measurements and also an artifact due to freezing of the pressure-transmitting medium can be excluded as this would not only affect the magnetic peaks. Therefore, the observed magnetic peak broadening is an intrinsic property. The peak width of magnetic peaks reflects the magnetic correlation length or domain size. While the exact origin of the peculiar behavior of the FWHM cannot be determined from our experiments, it is worth noting that the maximum width is seen in the region of the onset of superconductivity as determined by Wu *et al.* [5].

The transition to the magnetic state in CrAs is interesting since it is first order and changes the system from a Pauli paramagnet to an incommensurate antiferromagnet [4] with an equal moment spiral. Additionally, the incommensurate wave vector does not display a significant pressure or temperature dependence. CrAs is set aside from other recently discovered superconductors, since its superconducting state emerges from a metallic antiferromagnet and not from a spin/charge density wave. Though the exchange mechanism to stabilize the magnetic spiral order remains quantitatively unresolved [12], it can be qualitatively argued, and with consideration of the closeness of the propagation vector to $1/3$, that the helical state might be stabilized by ferromagnetic third-nearest-neighbor exchange interaction [13], while the exchange interaction between the four spirals might be a weak indirect exchange interaction through the polarization of the conduction electrons, basically the Ruderman-Kittel-Kasuya-Yosida (RKKY) type. While we do not want to speculate on the pairing mechanism in CrAs, the properties in the region of coexisting antiferromagnetism and superconductivity indicate an explicit dependence on the electron density of states for both ordering phenomena. The expected change of the Fermi surface under pressure ultimately promotes paramagnetic fluctuations, which in a weak-coupling theory then can lead to an unconventional pairing formalism [14]. In the case of CrAs, the onset of the superconducting phase marks the beginning of competition, where the electrons either contribute in the

magnetic exchange or the Cooper pair formation through paramagnetic fluctuations. At this point, one can expect an energy equilibrium between both states, leading to pronounced fluctuations between these two possibilities. In our experiment, this manifests as strong broadening of the magnetic peaks. On driving the system further into the superconducting state by increasing the pressure, the superconducting state becomes the system's ground state and an energy gap separates the magnetic and superconducting state. Consequently, we speculate that this gapping leads to the suppression of the fluctuations and therefore to the counterintuitive reduction of the magnetic peak half widths observed in our experiments on the approach to P_c . The same argument can be used to explain the decrease of the magnetic half widths with increasing temperature. However, in this case, the electronic system has no second state to occupy and therefore no broadening due to fluctuations is observed.

In summary, we have investigated the pressure and temperature evolution of the helimagnetic order in CrAs. The magnetic periodicity shows only marginal changes with pressure up to 0.65 GPa. The ordered magnetic moment averaged over the whole sample is reduced from $1.73(2) \mu_B$ at ambient pressure to $0.42(10) \mu_B$ close to the critical pressure P_c , indicating a reduction of the magnetic volume fraction and a large coexistence region of magnetic order and superconductivity. An unusual behavior of the magnetic peak width and peak shape has been measured. We propose that its distinct pressure dependence can be interpreted as a fingerprint of underlying fluctuations between magnetic and superconducting ground states.

Part of this work was performed at the Swiss Spallation Neutron Source SINQ, Paul Scherrer Institut, Villigen, Switzerland. The work in Switzerland was supported by the Swiss National Science Foundation, its Sinergia network MPBH, and the European Research Council project CONQUEST. The work at Oak Ridge National Laboratory was supported by the U.S. Department of Energy, Office of Science Basic Energy Sciences, Materials Science and Engineering Division (Z.C.S. and A.S.); also partially by the LDRD program (M.A.S.). The authors thank R. Khasanov and H. Luetkens for helpful discussions.

-
- [1] H. Watanabe, N. Kazama, Y. Yamaguchi, and M. Ohashi, *J. Appl. Phys.* **40**, 1128 (1969).
 - [2] K. Selte, A. Kjekshus, W. E. Jamison, A. F. Andresen, and J. E. Engbretnsen, *Acta Chem. Scand.* **25**, 1703 (1971).
 - [3] H. Boller and A. Kallel, *Solid State Commun.* **9**, 1699 (1971).
 - [4] E. A. Zavadskii and I. A. Sibarova, *Zh. Eksp. Teor. Fiz.* **78**, 1076 (1980) [*Sov. Phys. JETP* **51**, 542 (1980)].
 - [5] W. Wu, J. Cheng, K. Matsubayashi, P. Kong, F. Lin, C. Jin, N. Wang, Y. Uwatoko, and J. Luo, *Nat. Commun.* **5**, 5508 (2014).
 - [6] H. Kotegawa, S. Nakahara, H. Tou, and H. Sugawara, *J. Phys. Soc. Jpn.* **83**, 093702 (2014).
 - [7] K. Jin, N. P. Butch, K. Kirshenbaum, J. Paglione, and R. L. Greene, *Nature (London)* **476**, 73 (2011).
 - [8] J. Paglione and R. L. Greene, *Nat. Phys.* **6**, 645 (2010).
 - [9] H. Kotegawa, H. Tou, H. Sugawara, and H. Harima, [arXiv:1408.3185](https://arxiv.org/abs/1408.3185).
 - [10] B. Saparov, J. E. Mitchell, and A. S. Sefat, *Supercond. Sci. Technol.* **25**, 084016 (2012).
 - [11] J. Rodriguez-Carvajal, *Physica B* **192**, 55 (1993).
 - [12] R. Wöhl, H. Berg, and K. Bärner, *Phys. Status Solidi A* **57**, 179 (1980).
 - [13] J. Rogan and M. Kiwi, *Phys. Rev. B* **55**, 14397 (1997).
 - [14] P. Monthoux, A. V. Balatsky, and D. Pines, *Phys. Rev. B* **46**, 14803 (1992).