

Europium mixed-valence, long-range magnetic order, and dynamic magnetic response in $\text{EuCu}_2(\text{Si}_x\text{Ge}_{1-x})_2$

K. S. Nemkovski,^{1,*} D. P. Kozlenko,² P. A. Alekseev,^{3,4} J.-M. Mignot,⁵ A. P. Menushenkov,⁴ A. A. Yaroslavl'tsev,^{4,6} E. S. Clementyev,^{7,8} A. S. Ivanov,⁹ S. Rols,⁹ B. Klobes,¹⁰ R. P. Hermann,¹¹ and A. V. Gribanov¹²

¹Jülich Centre for Neutron Science JCNS at Heinz Maier-Leibnitz Zentrum MLZ, Forschungszentrum Jülich GmbH, Lichtenbergstraße 1, 85747 Garching, Germany

²Frank Laboratory of Neutron Physics, 141980 JINR, Joliot-Curie 6, Dubna, Moscow Region, Russia

³National Research Centre "Kurchatov Institute," Kurchatov sq. 1, 123182 Moscow, Russia

⁴National Research Nuclear University MEPhI (Moscow Engineering Physics Institute), Kashirskoe shosse 31, 115409, Moscow, Russia

⁵Laboratoire Léon Brillouin-UMR12 CNRS-CEA, CEA Saclay, 91191 Gif-sur-Yvette, France

⁶European XFEL GmbH, Holzkoppel 4, 22869 Schenefeld, Germany

⁷REC "Functional Nanomaterial", I. Kant Baltic Federal University, Nevskogo Str., 14A, 236041 Kaliningrad, Russia

⁸Institute for Nuclear Research RAS, 117312 Moscow, Russia

⁹Institut Laue-Langevin, BP 156, 38042 Grenoble Cedex 9, France

¹⁰Jülich Centre for Neutron Science JCNS and Peter Grünberg Institute PGI, JARA-FIT, Forschungszentrum Jülich GmbH, 52425 Jülich, Germany

¹¹Materials Science & Technology Division, Oak Ridge National Laboratory, P.O. Box 2008, Tennessee 37831-6064, Oak Ridge, USA

¹²Chemistry Department of the Moscow State University, Leninskie Gory, GSP-1, 119991 Moscow, Russia

(Received 30 May 2016; revised manuscript received 15 August 2016; published 1 November 2016)

In mixed-valence or heavy-fermion systems, the hybridization between local f orbitals and conduction band states can cause the suppression of long-range magnetic order, which competes with strong spin fluctuations. Ce- and Yb-based systems have been found to exhibit fascinating physical properties (heavy-fermion superconductivity, non-Fermi-liquid states, etc.) when tuned to the vicinity of magnetic quantum critical points by use of various external control parameters (temperature, magnetic field, chemical composition). Recently, similar effects (mixed-valence, Kondo fluctuations, heavy Fermi liquid) have been reported to exist in some Eu-based compounds. Unlike Ce (Yb), Eu has a multiple electron (hole) occupancy of its $4f$ shell, and the magnetic Eu^{2+} state ($4f^7$) has no orbital component in the usual LS coupling scheme, which can lead to a quite different and interesting physics. In the $\text{EuCu}_2(\text{Si}_x\text{Ge}_{1-x})_2$ series, where the valence can be tuned by varying the Si/Ge ratio, it has been reported that a significant valence fluctuation can exist even in the magnetic order regime. This paper presents a detailed study of the latter material using different microscopic probes (XANES, Mössbauer spectroscopy, elastic and inelastic neutron scattering), in which the composition dependence of the magnetic order and dynamics across the series is traced back to the change in the Eu valence state. In particular, the results support the persistence of valence fluctuations into the antiferromagnetic state over a sizable composition range below the critical Si concentration $x_c \approx 0.65$. The sequence of magnetic ground states in the series is shown to reflect the evolution of the magnetic spectral response.

DOI: [10.1103/PhysRevB.94.195101](https://doi.org/10.1103/PhysRevB.94.195101)

I. INTRODUCTION

Rare-earth intermetallic compounds provide unique opportunities for furthering our understanding of magnetism in solids. Systems containing rare-earth elements (Ce, Sm, Eu, Tm, Yb) with unstable $4f$ shells exhibit challenging physical phenomena, such as Kondo effect, electron mass enhancement, valence fluctuations, unconventional (magnetically driven) superconductivity, non-Fermi-liquid state, or critical fluctuations in the vicinity of a quantum critical point [1–10]. The possibility for lanthanide-ion magnetism to depart from the canonical Russell-Saunders+spin-orbit+crystal-field ionic coupling scheme has been extensively documented since the discovery of so-called “unstable-valence” materials (SmB_6 , SmS) back in the 1960s [11–17]. Considerable experimental and theoretical effort has been devoted to those materials over the last decades. Our current understanding of their properties

is based, to a large extent, on the so-called “periodic Anderson model,” consisting of a narrow band of localized $4f$ electrons subject to strong Coulomb correlations, hybridized with a broad conduction band of itinerant sd electrons. Depending on the hybridization strength, band structure, or electronic configuration, a large variety of situations is predicted, which may account for some of the aforementioned experimental properties. Non-Fermi-liquid behaviors usually occur in the region of parameter space where magnetic long-range order (LRO) becomes destabilized by spin fluctuations or alternative “local quantum critical” phenomena [9,10,18,19].

Most studies in that field have focused on Ce- and Yb-based heavy-fermion (HF) compounds. In particular, the RT_2X_2 type (T : $3d$ or $4d$ transition metal, X : Si, Ge), and $\text{CeCu}_{6-x}\text{Au}_x$ families, provide numerous examples of the interplay between long-range magnetic order and Kondo fluctuations considered in Doniach’s seminal work on Kondo lattices [20], leading to the discovery of novel quantum critical phenomena. In such systems, nearly trivalent lanthanide ions have single-electron (or -hole) occupancy of their $4f$ shells. As the hybridization

*k.nemkovskiy@fz-juelich.de

becomes stronger, and the $4f$ level approaches the Fermi energy, charge instability sets in, and the average rare-earth valence significantly deviates from $+3$. The electronic state can then be described as a quantum superposition of the $4f^n$ and $4f^{n-1} + [5d-6s]^1$ configurations [1]. In that regime, long-range magnetic order at low temperature is normally hindered by short-lived fluctuations, and a strongly damped dynamical magnetic response results as seen, e.g., in CePd_3 (Ref. [21]) or YbAl_3 [22].

Valence instability has also been found to occur in rare-earth elements with multiple $4f$ -shell occupancies, such as Sm, Eu, Tm, and possibly Pr. A limited number of examples are known, among which archetypal Kondo insulators, such as SmB_6 or YbB_{12} . Recently, the existence of a HF state in Eu-based compounds has attracted renewed interest [23–28]. This behavior has been clearly evidenced, in particular for the MV compound EuNi_2P_2 ($v = 2.45\text{--}2.55$), from thermodynamic and transport [25] as well as spectroscopic measurements [24,27]. Hossain *et al.* [23] have also reported the observation of Kondo effect with a HF behavior in the $\text{EuCu}_2(\text{Si}_x\text{Ge}_{1-x})_2$ series. Those experimental results raise very interesting questions regarding the applicability to Eu systems of interpretations originally devised for Ce or Yb. The materials studied belong to the same structural class of so-called “1-2-2” rare-earth intermetallics as the above-mentioned RT_2X_2 systems (R : Ce, Yb). Eu-based 1-2-2 compounds have actually been found to exhibit a variety of unconventional behaviors: hybridization gap formation in EuNi_2P_2 [24], reentrant superconductivity under pressure, competing with long-range Eu magnetic order, in EuFe_2As_2 [29], along with a valence instability of Eu [30].

In the $\text{EuCu}_2(\text{Si}_x\text{Ge}_{1-x})_2$ series, Eu occurs in a composition-dependent mixed-valence (MV) state. The ground-state multiplets of the two parent ionic configurations are 7F_0 (nonmagnetic, $J = 0$) for Eu^{3+} , and $^8S_{7/2}$ (spin-only, $J = \frac{7}{2}$) for Eu^{2+} . In pure EuCu_2Ge_2 and the solid solutions with $0 \leq x \leq 0.6$, transport and thermodynamics measurements [23] evidence a phase transition around 15 K, which is ascribed to magnetic ordering with a magnetic moment estimated [31] to approach the theoretical value for Eu^{2+} . Pure EuCu_2Si_2 , on the other hand, can be described as an intermediate-valence Van Vleck paramagnet. The suppression of magnetic order and the transition to a Fermi-liquid, HF regime takes place in a concentration range, near $x_c \sim 0.65$, where the Eu valence was reported [23,32] to deviate strongly from an integer value. In the Si-rich compounds ($x = 0.9, 1.0$), inelastic neutron scattering (INS) spectra [33] are characterized by a renormalized Eu^{3+} -like intermultiplet (spin-orbit) transition, together with an extra magnetic peak at lower energy, which has been interpreted as an excitonlike “resonance,” related to the formation of a spin gap of 20–30 meV below $T \sim 100$ K.

In this work, we address the question of how the competing Kondo and magnetic ordering phenomena reported in Ref. [23] compare to those studied previously in Ce or Yb compounds. The key issue of a possible coexistence of long-range magnetic order with a MV state, as suggested in previous work [23,32], is addressed by means of different microscopic probes [XANES, Mössbauer spectroscopy, neutron powder diffraction (NPD)]. Evidence is reported for an unconventional coexistence of long-range magnetic order and a homogeneous MV state

with spin fluctuations in $\text{EuCu}_2(\text{Si}_x\text{Ge}_{1-x})_2$, occurring over a significant range of Si concentrations x below the critical value $x_c \approx 0.65$. This behavior is at variance with the general trend observed in other unstable-valence compounds.

The evolution of the magnetic spectral response across the $\text{EuCu}_2(\text{Si}_x\text{Ge}_{1-x})_2$ series was studied in a wide temperature range using INS experiments. In particular, high-resolution time-of-flight measurements on the Ge-rich compounds reveal the existence of narrow, concentration-dependent, quasielastic (QE) signal. On decreasing the Si concentration, the gradual change in the magnetic relaxation rate, indicated by the narrowing of this spectral component, together with the strong renormalization to lower energies of the Eu^{3+} spectral contribution, is found to play a key role in the formation of the unconventional magnetic and HF states in the vicinity of x_c .

II. EXPERIMENTAL DETAILS

A. Sample preparation

The $\text{EuCu}_2(\text{Si}_x\text{Ge}_{1-x})_2$ samples used in this work were prepared by arc melting from high-purity materials Si, Ge, Cu ($>99.99\%$) and Eu (99.9%). All of them were annealed at $T_{\text{ann}} = 0.8T_{\text{melt}}$ (melting temperature) during ~ 200 h. Further characterization by x-ray powder diffraction showed that all samples crystallized in the body-centered tetragonal ThCr_2Si_2 -type structure ($I4/mmm$ space group, #139). No impurity phase was detected within the sensitivity of the method.

B. X-ray absorption and Mössbauer spectroscopy

The valence state of the $\text{EuCu}_2(\text{Si}_x\text{Ge}_{1-x})_2$ compounds ($0 \leq x \leq 0.9$) was determined by x-ray absorption near-edge structure (XANES) spectroscopy at the Eu L_3 edge, and by Mössbauer spectroscopy. These methods are known to probe interconfigurational valence fluctuations on very different time scales: about 10^{-8} s for Mössbauer spectroscopy, as compared to $\sim 10^{-15}$ s for XANES. The XANES measurements were performed on the A1 beamline of the DORIS-III storage ring (DESY Photon Science, Hamburg) and at the *mySpot* beamline of BESSY-II (HZB, Berlin) in transmission geometry. In the data treatment, the f^6 and f^7 components were described by Lorentzian profiles at their respective center positions, whereas photoelectron excitations to the continuous spectrum could be represented by an arctangent function. To simulate experimental broadening, the overall function was convoluted with a Gaussian distribution. The experimental temperature range was $7 \text{ K} \leq T \leq 300 \text{ K}$.

^{151}Eu Mössbauer spectra were collected at the Forschungszentrum Jülich on a constant-acceleration spectrometer using a 30 mCi $^{151}\text{SmF}_3$ source. The velocity calibration was performed with $\alpha\text{-Fe}$ at room temperature (RT), using a $^{57}\text{Co/Rh}$ source. All Mössbauer spectra discussed here were obtained at RT on powder samples, and the isomer shifts (IS) are derived with reference to EuF_3 .

C. Neutron powder diffraction

Three $\text{EuCu}_2(\text{Si}_x\text{Ge}_{1-x})_2$ powder samples with compositions $x = 0.0, 0.40$, and 0.60 , corresponding to the part of magnetic phase diagram where magnetic order is expected

to occur, were measured on the hot-neutron diffractometer 7C2 at LLB-Orphée in Saclay. The sample masses were 0.66, 0.52, and 0.69 g for the three above compositions, respectively. Neutron scattering experiments on compounds containing natural Eu are challenging because of the very large absorption cross section of Eu ($\sigma_{\text{abs}} = 4530$ b for 2200 m/s neutrons). However, this problem can be circumvented by using incoming neutrons with a relatively short wavelength, $\lambda = 1.121$ Å, from a Ge(111) monochromator. The samples were prepared in a slab geometry, with an area of 12×45 mm² and a thickness of approximately 0.3 mm, corresponding to 0.15 mm of bulk material. Sample powder was packed in flat-shaped thin-foil Al sachets, whose surface was oriented perpendicular to the incoming monochromatic neutron beam. The scattering angle range in which intense peaks are observed was $3.3^\circ < 2\Theta < 40^\circ$, which corresponds to a momentum transfer range $0.3 < Q < 3.8$ Å⁻¹. Under those conditions, a nearly constant level of the transmission could be achieved, varying from 75% to 72% in the entire scattering angle range of interest. For all samples, diffraction patterns have been recorded at temperatures comprised between 4 and 50 K using an ILL-type Orange cryostat. The data analysis was performed using the Rietveld refinement program FULLPROF [34,35].

A fourth sample, with $x = 0.75$, was not measured on 7C2 for lack of experimental beam time, but the absence of magnetic Bragg peaks for this composition was deduced from the analysis of the elastic signal in the time-of-flight measurements on IN4C (see Sec. III).

D. Neutron spectroscopy

INS experiments were carried out on the thermal-neutron time-of-flight spectrometer IN4C at the ILL in Grenoble, with a resolution of 1.65 meV (FWHM at zero energy transfer, from the width of the vanadium elastic line). The measurements were performed using incident neutrons at energy $E_i = 36.3$ meV ($\lambda = 1.5$ Å), from a PG(004) monochromator. For that energy, a transmission factor of about 50% was achieved using thin samples (~ 0.3 mm of powder). With about 0.8 g of material in the beam, the typical measuring time for one spectrum was about 10 h.

III. RESULTS

A. XANES and Mössbauer spectra

XANES measurements at the Eu L_3 edge between 7 and 300 K have been performed on $\text{EuCu}_2(\text{Si}_x\text{Ge}_{1-x})_2$ for $x = 0, 0.6, 0.75, 0.9$, and 1.0. The spectra for the three solid solutions are shown in Fig. 1(a). In the Si-rich samples, the main peak from the Eu^{3+} electronic configuration exhibits a shoulder at lower energy indicating a sizable Eu^{2+} contribution. With decreasing Si concentration, the contribution of this Eu^{2+} component gradually increases to the expense of the Eu^{3+} component, and becomes dominant for $x < 0.6$. The Eu valence for each composition was derived from the relative spectral weights by fitting the spectra as explained in Sec. II B). This procedure is based on the assumption that final-state (“shakeup”) effects can be neglected, which has been questioned in previous studies of Eu intermetallics [36,37]. This

point is discussed in more detail hereafter (Sec. IV). The obtained composition dependence of the Eu valence at $T = 7$ and 300 K, plotted in Fig. 1(c), is quite consistent with the previous data of Fukuda *et al.* [32].

The ^{151}Eu Mössbauer spectra at RT are characterized, for all studied concentrations ($x = 0, 0.4, 0.6, 0.75$, and 0.9) by a single absorption line, as illustrated in Fig. 1(b) for $x = 0.4$ and 0.9. The position of this line (Mössbauer IS) is clearly intermediate between those expected for pure Eu^{2+} and Eu^{3+} electronic configurations (denoted by arrows in the plot). Its line shape is well described by a single Lorentzian function, which implies that the Eu^{2+} - Eu^{3+} valence mixing state is *homogeneous* on the characteristic time scale of the measurement ($\sim 10^{-8}$ s).

From the composition dependence of the IS, it is clear that the average valence at RT steadily increases with increasing Si content. To get a quantitative estimate, one needs to know precisely the positions expected for pure Eu^{2+} and Eu^{3+} valence states, which actually depend on the unit-cell volume, and therefore vary slightly from one family of compounds to another [39,40]. Here, we limited ourselves to checking the consistency of the composition dependence of the Eu valence derived from the IS, by normalizing the values obtained for $x = 0.6$ and 0.9 to those derived from XANES (2.28 and 2.52). The resulting agreement between the two methods in the entire composition range, shown in Fig. 1(c), is satisfactory.

B. Long-range magnetic order

For the three measured concentrations $x = 0, 0.4, 0.6$, the diffraction patterns collected at $T_{\text{min}} \approx 4$ K show clear evidence of magnetic superstructure reflections, which vanish in the paramagnetic phase (Fig. 2). These satellites demonstrate that long-range magnetic order occurs between EuCu_2Ge_2 and $\text{EuCu}_2\text{Si}_{1.2}\text{Ge}_{0.8}$. For $x = 0.75$, on the other hand, careful analysis of the elastic signal in our time-of-flight measurements on IN4C (Sec. II D) revealed no Bragg satellites indicative of magnetic order, whereas such satellites are clearly seen in $\text{EuCu}_2\text{Si}_{1.2}\text{Ge}_{0.8}$ under the same experimental conditions. The present results thus agree perfectly with those obtained previously from thermodynamic and transport measurements [23], where the critical concentration of the long-range magnetic order suppression was estimated to be $x_c = 0.65$.

For the three compositions showing magnetic order, the superstructure peaks can be indexed using a single, commensurate, magnetic wave vector $\mathbf{k} = (\frac{1}{3}, 0, 0)$. The data refinement points to the formation of a spin spiral antiferromagnetic (AFM) structure, in which the Eu magnetic moments located at the $2a$ Wyckoff positions $(0, 0, 0)$ and $(\frac{1}{2}, \frac{1}{2}, \frac{1}{2})$ in the tetragonal unit cell of the $I4/mmm$ space group, are antiparallel. The refined ordered magnetic moment is smaller in the two diluted systems ($5.3\mu_B$) than in pure EuCu_2Ge_2 ($6.7\mu_B$). In a recent NPD study of undoped EuCu_2Ge_2 , Rowan-Weetaluktuk *et al.* [41] have reported a magnetically inhomogeneous ground state consisting of two incommensurate AFM phases. The reason for this discrepancy is not known but it might be suggested that even a small amount (below the limit of detection of NPD) of strongly dispersed EuO impurity phase, with a very large Eu^{2+} magnetic moment, could significantly affect the ordered magnetic state.

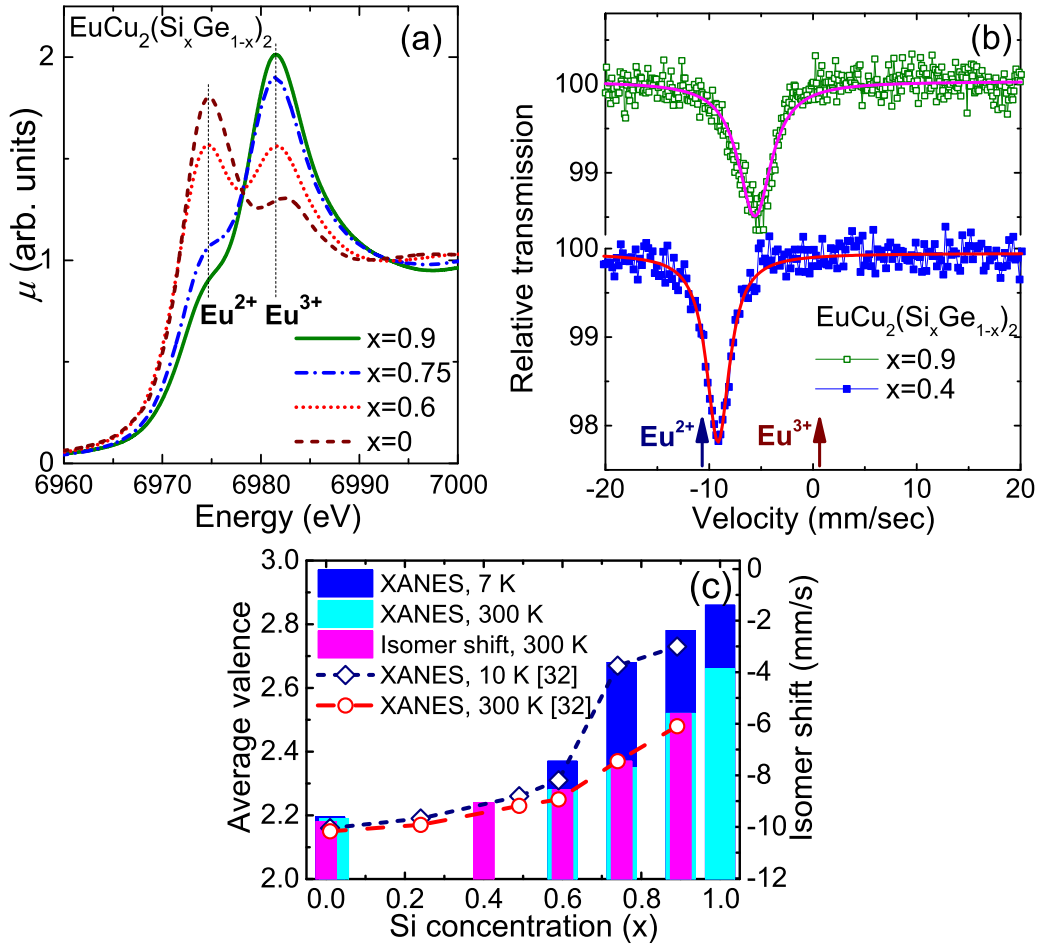


FIG. 1. (a) XANES transmission spectra in $\text{EuCu}_2(\text{Si}_x\text{Ge}_{1-x})_2$ for $x = 0, 0.6, 0.75$, and 0.9 at $T = 7$ K. (b) ^{151}Eu Mössbauer absorption spectra for $x = 0.6$ and 0.9 at RT, fitted to a single Lorentzian profile; arrows indicate the positions expected for the pure Eu^{2+} and Eu^{3+} electronic configurations, derived from measurements on the isostructural compounds $\text{Eu}^{2+}\text{Pd}_2\text{Ge}_2$ (-10.6 mm/s) and $\text{Eu}^{3+}\text{Ru}_2\text{Si}_2$ ($+0.6$ mm/s) [38]. (c) Bar chart showing the average Eu valence as a function of the Si concentration derived from the present XANES data for $T = 7$ K (blue) and 300 K (cyan), as well as from the Mössbauer IS at $T = 300$ K (pink). The dashed lines with symbols show the values determined by Fukuda *et al.* [32] from XANES at $T = 10$ K (short-dashed dark-blue line with diamonds) and 300 K (red dashed line with circles).

C. Neutron scattering spectra

In this section, we present the results of the time-of-flight INS experiments performed on IN4C. The magnetic contribution to the inelastic scattering was obtained experimentally as the difference between the data measured on the $\text{EuCu}_2(\text{Si}_x\text{Ge}_{1-x})_2$ samples and on the nonmagnetic reference compound $\text{LaCu}_2\text{Si}_{1.2}\text{Ge}_{0.8}$. An example of the spectra for $T = 3$ K is shown in Fig. 3. One sees that the magnetic signal can be determined reliably even for the composition $\text{EuCu}_2\text{Si}_{0.8}\text{Ge}_{1.2}$ ($x = 0.4$) at which its intensity is the weakest.

The magnetic spectra of $\text{EuCu}_2\text{Si}_{1.5}\text{Ge}_{0.5}$ ($x = 0.75$), measured at $T = 3$ K, and of $\text{EuCu}_2\text{Si}_{1.2}\text{Ge}_{0.8}$ ($x = 0.6$), measured at $T = 3$ and 50 K, are shown in Fig. 4 in combination with data previously collected on MARI at ISIS [33]. With an incident neutron energy of $E_0 = 36.3$ meV, the resolution at zero-energy transfer was $\Gamma = 1.65$ meV, FWHM, giving access to the low-energy part of the magnetic response, which is the main focus of this study and was not addressed in earlier experiments [33]. All spectra have been reduced to $Q = 0$ according to the magnetic form factor for the $^7F_0 \rightarrow ^7F_1$ spin-orbit transition of Eu^{3+} .

The sample with the higher Si content ($x = 0.75$) is located above the critical concentration $x_c = 0.65$ in the phase diagram [23], and thus does not order magnetically. At the base temperature [Fig. 4(a)], its magnetic response contains both inelastic and quasielastic (QE) components. The former consists of two peaks, reminiscent of those observed previously in pure EuCu_2Si_2 (Ref. [42]) and $\text{EuCu}_2\text{Si}_{1.8}\text{Ge}_{0.2}$ (Ref. [33]), but strongly damped, as is commonly observed in the HF regime [43–45], to which this compound is thought to belong. The magnetic QE signal has a Lorentzian line shape with a full width at half maximum (FWHM) Γ of about 1.5 meV. Its existence contrasts with the spin-gap response observed [33,42] below 100 – 150 K for compositions $x > 0.75$, and reflects a qualitative change in the energy spectrum of spin fluctuations. With increasing temperature, the QE linewidth gradually increases to exceed 3 meV at 100 K. This broadening, however, remains limited in comparison with the linewidths of 10 meV or more observed above 150 K in the Si-rich compounds [33,42] [Fig. 5(a)].

At lower Si concentrations ($x = 0.6 < x_c$), one enters the long-range magnetic order region of the phase diagram. At

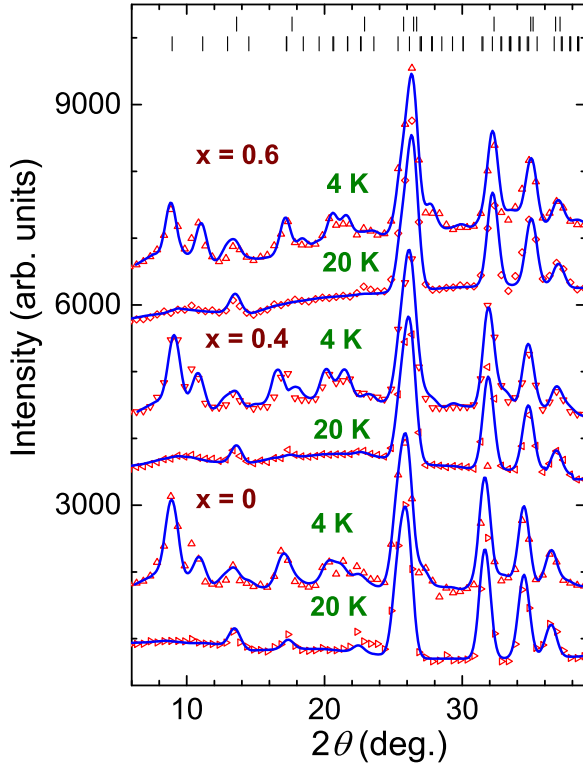


FIG. 2. Neutron diffraction patterns of $\text{EuCu}_2(\text{Si}_x\text{Ge}_{1-x})_2$ ($x = 0, 0.4, 0.6$) measured at $T = 20$ and 4 K and refined using the Rietveld method. The ticks at the top of the frame represent the calculated positions of the nuclear reflections corresponding to the tetragonal $I4/mmm$ crystal structure (upper row) and the magnetic reflections corresponding to the propagation vector $\mathbf{k} = (\frac{1}{3}, 0, 0)$ (lower row).

$T = 3$ K [Fig. 4(b)], no evidence remains for the two broad excitations previously observed above 10 meV, and the main component of the magnetic response now consists of a rather narrow QE signal ($\Gamma \approx 0.3$ meV). The asymmetry visible on the experimental spectrum is due to the detailed-balance factor.

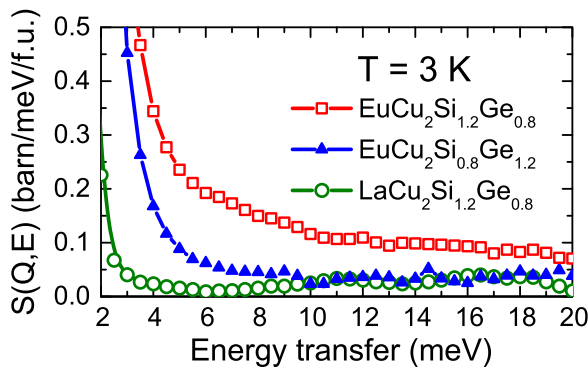


FIG. 3. Time-of-flight INS spectra of $\text{EuCu}_2(\text{Si}_x\text{Ge}_{1-x})_2$ at $T = 3$ K, measured on IN4C with incident neutron energy $E_0 = 36.3$ meV (resolution at zero energy transfer $\Gamma = 1.65$ meV, FWHM). Intensities have been averaged over the scattering angle range 13° – 32° . Data for $x = 0.6$ (red squares) and 0.4 (blue triangles) are displayed, together with those (black circles) obtained for $\text{LaCu}_2\text{Si}_{1.2}\text{Ge}_{0.8}$, which serve as an estimate of the nuclear background contribution.

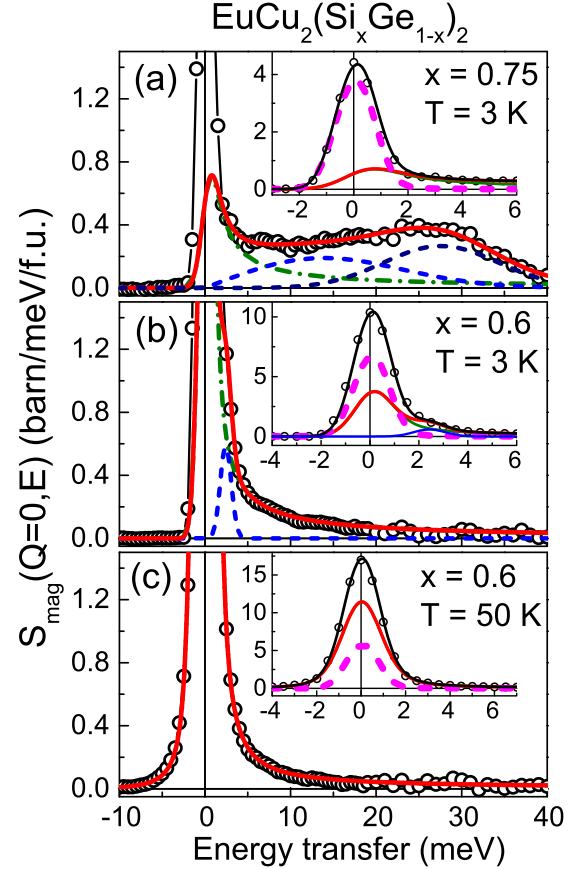


FIG. 4. Magnetic neutron scattering spectra of $\text{EuCu}_2\text{Si}_{1.5}\text{Ge}_{0.5}$ ($x = 0.75$) at $T = 3$ K (a), and of $\text{EuCu}_2\text{Si}_{1.2}\text{Ge}_{0.8}$ ($x = 0.6$) at $T = 3$ K (b) and 50 K (c), combined from those measured in present experiment on IN4C at $E_0 = 36.3$ meV ($-10 \leq E \leq 20$ meV) and previous study on MARI at ISIS [33] at $E_0 = 100$ meV ($20 \leq E \leq 40$ meV). Black circles: experimental values after vanadium normalization, background correction, and subtraction of the nuclear (incoherent elastic and phonon) scattering, estimated from measurements of nonmagnetic $\text{LaCu}_2\text{Si}_{1.2}\text{Ge}_{0.8}$. Lines: (solid red) total magnetic signal; (dashed-dotted green) quasielastic line fitted to a Lorentzian line shape (temperature factor included), convoluted with a Gaussian resolution function [in frame (c), the red and green traces are superimposed]; (dashed blue and dark blue) inelastic response. Insets: same data on a larger intensity scale, further showing the elastic peak with a vanadium line shape (in magenta, dashed). This residual nuclear scattering signal results from the fact that the large nuclear incoherent scattering cannot be determined with sufficient accuracy from the La reference compound. Nonetheless, the value obtained is consistent between the different samples.

On heating, the linewidth increases to $\Gamma = 0.8$ meV at 50 K and 1.3 meV at 100 K. An extra peak near 2.4 meV, observed only in the ordered magnetic state below $T_N \approx 17$ K, likely reflects the existence of a magnon branch with a gap at the ordering wave vector \mathbf{q}_{AF} . This signal is rather weak and narrow, and merges into the magnetic excitation continuum for $T \geq T_N$. For $\text{EuCu}_2\text{Si}_{0.8}\text{Ge}_{1.2}$ ($x = 0.4$, not presented in Fig. 4) the spectra are quite similar to those for $x = 0.6$, apart from a further reduction of the QE linewidth at low temperature, estimated to be less than 0.25 meV.

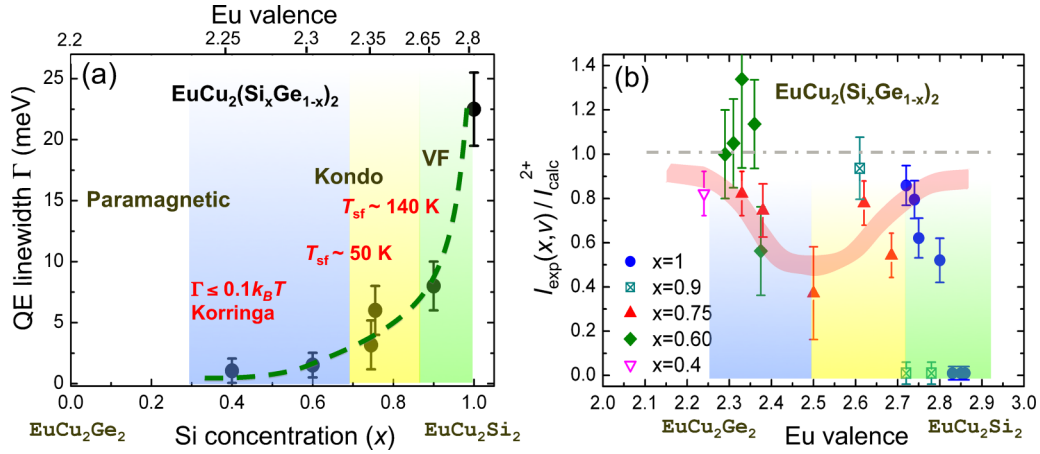


FIG. 5. (a) Concentration dependence of the magnetic quasielastic linewidth (FWHM) at $T = 100\text{--}200$ K (see text) in the $\text{EuCu}_2(\text{Si}_x\text{Ge}_{1-x})_2$ series. An approximate valence scale, derived from the XANES and Mössbauer results (see Fig. 1 and Ref. [33]), as discussed in Sec. IV A, is indicated on the upper horizontal axis. (b) Integrated intensity of the quasielastic signal as a function of the average Eu valence derived from XANES; the values have been normalized, for each temperature and composition, to the scattering intensity expected from the estimated Eu^{2+} fraction. The pink shaded trace emphasizes the general trend in the high-temperature limit (see text for details). In (a) and (b) the colored regions represent the different regimes occurring at low temperature; from right to left: (i) spin-gap, (ii) HF, (iii) long-range magnetic order (with a high-temperature paramagnetic regime characterized by normal Korringa-type thermal relaxation).

It is interesting to follow the evolution of the QE *linewidth* as the Eu valence increases with increasing Si content. To avoid complications due to the spin-gap formation in the Si-rich compounds at low temperature, we focus on the QE response in the temperature region $100 \leq T \leq 200$ K. The values of Γ derived from the present data are plotted in Fig. 5(a), together with those obtained previously [33] for EuCu_2Si_2 and $\text{EuCu}_2\text{Si}_{1.8}\text{Ge}_{0.2}$, as a function of the Si concentration x . For $x = 0.4$, the linewidth is too small to be measured precisely within instrumental resolution. It remains low, of the order of 1.5 meV, in the concentration range $0.4 \leq x \leq 0.6$, then increases to 5 meV on entering the Kondo/HF regime ($x = 0.75$). Finally, a dramatic rise, by a factor of 5, takes place in the narrow interval $0.9 \leq x \leq 1$, leading to a value of about 22 meV in EuCu_2Si_2 . This highly nonlinear dependence reflects the dependence of the average Eu valence on the Si concentration plotted in Fig. 1(c), supporting the idea that the parameter controlling the evolution of the spin dynamics across the series is the Eu valence state. At low temperature, where the QE signal exists, its width never exceeds 2–3 meV but, in the HF regime ($x = 0.75$), this relatively narrow signal coexists with quite broad inelastic peaks (linewidths of the order of 10 meV) at energies comprised between 10 and 20 meV.

The *integrated intensity* of the QE signal for all measured Si concentrations and temperatures is summarized in Fig. 5(b) as a function of the Eu valence. As implied by Fig. 1(c), lower valence values for a given composition correspond to higher temperatures. For the Si-rich compounds ($x = 0.9$ and 1.0), data points (shown as shaded symbols) corresponding to spectra measured in, or close to, the spin-gap regime are affected by the transfer of spectral weight from the QE to the inelastic component and therefore irrelevant to the present argument. In the spin-fluctuation regime, the general trend is tentatively represented by the pink trace. It appears that, on both ends of the plot, the measured intensity is close

to that expected from the cross section calculated for the Eu^{2+} fraction, whereas some reduction seems to occur in the intermediate region, where the valence is strongly mixed (HF regime).

IV. DISCUSSION

A. Eu mixed valence

The results presented in Sec. III A confirm the pronounced composition and temperature variation of the Eu valence in this series of compounds, as was emphasized in previous studies [23,32]. However, quantitative determinations using different experimental techniques have remained controversial. Therefore, before discussing the dependence of the magnetic properties on the degree of valence mixing, one needs to consider possible problems in the interpretation of XANES and Mössbauer data.

One striking point in the XANES spectra is the existence of a sizable Eu^{3+} -like component for *all* compositions, including pure EuCu_2Ge_2 , in which the implied deviation from divalency is far beyond the uncertainty of the method. This result, however, seems to contradict the overall “ Eu^{2+} -like” behavior observed in bulk properties (entropy, magnetization). This discrepancy was already noted in the paper by Fukuda *et al.* [32], but no explanation was proposed. It has been argued, in earlier x-ray absorption studies of other Eu intermetallics such as EuPd_2P_2 (Ref. [36]) or Eu 1-1-1 noble-metal pnictides [37], that *final-state* effects can produce an artifact peak, simulating a Eu^{3+} contribution, in the XANES spectra of purely divalent compounds. In such a process, one electron from the $4f^7$ shell is partially promoted (“shakeup”) into one of the ligand orbitals, following the creation of a $2p$ core hole by the incoming photon. This is more likely to occur in systems with a higher degree of covalency, as may be the case close to a valence instability, where $4f$ states hybridize with ligand orbitals [46]. However, there is no consensus so

far on the possible magnitude of such effects in one given material. On the other hand, it is known that some divalent 1-2-2 Eu compounds (EuFe₂As₂, Refs. [30,47], or EuCo₂As₂, Ref. [48]) exhibit a single Eu²⁺ peak under normal conditions, while they develop a two-peak XANES structure when a MV state is produced by means of hydrostatic or chemical pressure. The role of final-state effects in that class of systems has been questioned by Röhler [49] and remains partly unsettled.

Quantitatively, one can note that all deviations from divalency ascribed to final-state effects in Ref. [36] (fractional Eu³⁺ intensity of approximately 15% in EuPd₂P₂), Ref. [37] (apparent valence comprised between 2.12 and 2.22 in 1-1-1 compounds), and Ref. [46] (deviation of 0.09 to 0.12 in the EuPd_{2-x}Au_xSi₂ series) are weak in comparison with those observed in the EuCu₂(Si_xGe_{1-x})₂ compounds, especially for $x \geq 0.4$. Furthermore, for $x = 0.75$ and, notably, for $x = 0.6 < x_c$, the temperature dependence of the valence determined from XANES (also observed by Fukuda *et al.* [32] for the same composition, and even faintly for $x = 0.5$) supports a true valence-mixing effect.

In Sec. III A, the Mössbauer results were used primarily to demonstrate the homogeneous character of the MV state. Valence determination based on the IS, on the other hand, is problematic. The main problem comes from the lack of reliable divalent or trivalent reference system. In this work, for $x \leq 0.75$ we found IS comprised between -9.8 and -7.5 mm/s, with IS = -8.6 mm/s for $x = 0.6$. Michels *et al.* [37], have reported isomer shifts near -10.7 mm/s or below for divalent EuAuP and EuCuPt, although they mention relative velocities covering a wide range between -12 and -8 mm/s for Eu²⁺ in other metallic compounds. The values found here are systematically larger than the average estimate for divalent Eu, though still in a range compatible with a pure Eu²⁺ state.

Based on the literature data for the compressibility of EuCu₂Si₂ [50], the expansion of the lattice due to the substitution of Ge for Si [23], and the typical pressure dependence of the Eu isomer shift of 10^{-2} mm s⁻¹ kbar⁻¹ (Ref. [51]), we have estimated the possible change in the Eu isomer shift due to the difference in lattice parameters within the EuCu₂(Si_xGe_{1-x})₂ series. We have found that the expected change in the isomer shift for EuCu₂Si_{0.8}Ge_{1.2} and EuCu₂Si_{1.2}Ge_{0.8} with respect to EuCu₂Ge₂ is about 0.35 and 0.45 mm/s, respectively, whereas the values obtained experimentally are 0.7 and 1.2 mm/s, respectively, are at least twice higher. Therefore, even if EuCu₂Ge₂ is assumed to be divalent, this suggests that other compositions are mixed valent. Although this difference cannot be regarded as a conclusive proof, it lends support to our assumptions, at least for $x \geq 0.6$.

In summary, we believe that the present XANES and IS data consistently point to the existence of a MV state of Eu in EuCu₂(Si_xGe_{1-x})₂ for $x = 0.6$ and above, in particular in the region of interest, near $x = x_c$, where competing Kondo, HF, and long-range-order phenomena have been reported to occur [23]. The large trivalent contribution in the XANES spectra, as well as its significant temperature dependence, are unlikely to result from shakeup effects. This regime probably extends to the Ge-rich range up to $1 - x = 0.6$. For even higher Ge contents, as well as in pure EuCu₂Ge₂, it is difficult to decide whether the residual (but significant) trivalent character

indicated by the present, as well as Fukuda's [32] earlier XANES results, is entirely due to experimental artifacts. This point is not critical to our discussion of magnetic properties, and remains open for future studies. In the following, we will not attempt to correct the valence values obtained in Sec. III A and use the correspondence between valence and composition as displayed in Fig. 1.

B. Dynamic magnetic response

Starting from pure EuCu₂Ge₂, the substitution of Si causes a reduction of the ordered Eu magnetic moment, as shown by the neutron diffraction results. This moment reduction can be ascribed to the approach of the strong spin-fluctuation regime ($x > 0.6$), which gradually suppresses Eu long-range magnetism and correlates with the increase in the average Eu valence evidenced from XANES experiments.

Key features of the spin fluctuations dynamics developing in the MV state are revealed by neutron spectroscopy. In a wide composition range ($0.4 < x < 0.75$), a pronounced QE peak is observed in the magnetic spectral function, in contrast with the spin-gap behavior ($\Delta \approx 20$ – 30 meV) developing at low temperature in pure EuCu₂Si₂ ($x = 1$) and EuCu₂Si_{1.8}Ge_{0.2} ($x = 0.9$). In Refs. [33,42], the latter compounds were shown to exhibit an inelastic response at $T = 5$ K consisting of two excitations, which were ascribed to a renormalized Eu³⁺ spin-orbit excitation $^7F_0 \rightarrow ^7F_1$ and a resonancelike magnetic mode, respectively.

Above the temperature of the spin-gap suppression (on the order of 100 K), a very high spin-fluctuation rate was observed, as already noted above. With increasing Ge content (x decreasing from 1 to 0.75), the inelastic signal broadens and shifts to lower energies. In the region of maximum valence mixing (average Eu valence $v \sim 2.5$ at $T = 10$ K near $x = 0.65$), a QE signal coexists, at low temperature, with overdamped inelastic peaks [see Fig. 4(a) for $x = 0.75$]. For $x = 0.6$ and below, only the QE response exists [apart from a magnonlike component below T_N seen in Fig. 4(b) for $x = 0.6$]. We stress that no (Eu³⁺)-type inelastic peak was observed here in the spectra for $x = 0.6$ (near 45 meV) and $x = 0.4$ (up to 30 meV).

From these results and the discussion given in the previous section, one is led to the important conclusion that the long-range order developing below x_c , e.g., for $x = 0.6$ in EuCu₂Si_{1.2}Ge_{0.8}, cannot be based on the magnetism of the Eu²⁺ ionic component alone, but represents a genuine property of the MV state, whose character gradually changes, with decreasing x , from a nonmagnetic singlet to a degenerate spin-fluctuation state. In view of gradual evolution observed, as a function of composition, in the AFM region, the same possibly applies to lower Si concentrations as well. Obviously, the MV state does not preclude the occurrence of long-range order, and might even provide additional coupling channels whereby this order can develop.

The results are mapped out on the magnetic phase diagram for the entire EuCu₂(Si_xGe_{1-x})₂ series (Fig. 6). The Néel temperatures obtained from neutron diffraction, represented by triangles, agree perfectly with those reported in the previous work [23], and the observation of magnetic superstructure peaks further confirms the long-range character of the order.

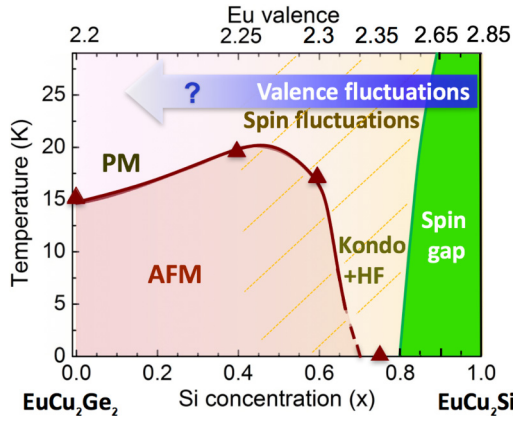


FIG. 6. Magnetic phase diagram for $\text{EuCu}_2(\text{Si}_x\text{Ge}_{1-x})_2$ based on the original data of Ref. [23] (solid brown line showing the phase boundary between the AFM and paramagnetic states) and those obtained in this work. Triangles indicate values obtained from our NPD experiments and correspond to samples composition used in this work. The yellow-colored area, extending to $x = 0.4$ and encroaching upon the AFM region, corresponds to the spin-fluctuation regime in which a QE response is observed, and the green-colored area to the spin-gap regime. The valence values indicated on the upper scale are those derived from the XANES data at $T = 7$ K of this work and of Ref. [33].

In particular, we note the unexpected robustness of the AFM ordered state, characterized by an initial increase in the Néel temperature from 15 to 19 K between $x = 0$ and ~ 0.4 , followed by a moderate decrease to 17 K at $x = 0.6$, despite the reduction of the Eu magnetic moment likely due to the enhancement of spin fluctuations [Fig. 5(a)]. The order observed at the composition $x = 0.6$ is of particular interest because it corresponds to a regime in which a Kondo behavior has been clearly established [23], with a Kondo temperature ($T_K \sim 10$ K) comparable to the Néel temperature. The absence of long-range order in the IN4C data for $x = 0.75$ agrees with the value of $x_c = 0.65$ reported in Ref. [23], and confirms that the drop of T_N to zero occurs precipitously in a narrow concentration interval, just above $x = 0.6$.

The green-colored area shown in Fig. 6 for Si concentrations above $x \sim 0.8$ corresponds to the formation of the spin gap in the excitation spectra at low temperature. The yellow-colored area denotes the existence of a detectable QE magnetic signal in the INS spectra. The gradual evolution of the dynamic response as x decreases provides further insight into the formation of the spin fluctuations state near x_c . Above $x = 0.8$, the low-temperature behavior is dominated by the suppression of the low-energy spectral weight in the spin-gap range ($E < 30$ meV) below ~ 150 K, associated with the formation of a Eu singlet ground state [33]. As x decreases, the inelastic components renormalize to low energies, as shown in Ref. [33], eventually leading to a pure QE response at $T = 50$ K $> T_N$ for $x < 0.6$. The gradual appearance of the QE signal around $x = 0.6$ – 0.75 reflects the recovery of magnetic moments in the ground state (instead of the singlet ground state with a spin gap for $x \geq 0.8$). This can be viewed as the necessary condition for both the enhancement of spin fluctuations and the tendency to form the long-range-ordered

magnetic state. Around $x = 0.75$, the decrease (in comparison with higher x) of the spin-fluctuation energy to the range of a few millielectronvolts allows the HF state to be formed, leading to the first known case of a HF behavior occurring in a strongly MV material (around $v \sim 2.5$ – 2.6 , according to XANES).

The competition between, and/or coexistence of, long-range magnetic order and strong spin fluctuations has been extensively studied in Ce- or Yb-based intermetallic compounds, a number of which [43–45] belong to the same 1-2-2 family as $\text{EuCu}_2(\text{Si}_x\text{Ge}_{1-x})_2$. In such compounds, the lanthanide ion occurs in a nearly trivalent HF state, with a magnetic (degenerate) ground state defined by the crystal-field splitting, and the properties are well understood in terms of the competition between the Kondo effect and RKKY exchange interactions, as suggested in Doniach’s [20] and subsequent models. Strongly MV Ce compounds, on the other hand, do not exhibit magnetic order. The latter scenario is in strong contrast with the present situation, where the AFM order extends far into the MV regime, and its suppression occurs close to one-to-one mixing of the Eu^{2+} and Eu^{3+} states.

A clue to clarifying the similarities and differences between “classical” CeT_2X_2 systems and MV $\text{EuCu}_2(\text{Si}_x\text{Ge}_{1-x})_2$ may be given by the magnetic spectral response observed in the present INS study. It is important to note that, both in the case of Ce and Yb, one of the electronic configurations involved in the valence fluctuation is nonmagnetic not just as a result of Russel-Saunders and/or spin-orbit coupling, but because its $4f$ shell is either empty (Ce) or full (Yb). In Eu^{3+} , on the other hand, the ionic ground-state multiplet is indeed a singlet (7F_0) but, as revealed by the INS spectra, magnetic (spin-orbit) excited states exist at relatively low energies, less than 40 meV in pure EuCu_2Si_2 . As Ge is substituted for Si, this energy further decreases, while spectral weight is gradually transferred to the QE region. Meanwhile, the spin-fluctuation rate, evidenced by the linewidth of the QE signal at high temperature, decreases considerably. The emergence of a degenerate ground state due to the renormalization to low energies of the inelastic part of the Eu spectrum, as well as the slowing down of spin fluctuations, may restore the conditions for Kondo-type (s - f exchange) spin dynamics in competition with long-range magnetic order. This may also explain why, contrary to the Ce case, the strongly MV character does not preclude the emergence of the magnetic state.

That magnetic order can develop in the presence of strong valence fluctuations, provided magnetic degrees of freedom exist in both valence states, was well documented, back in the 1980s, for the rock-salt structure chalcogenide compound TmSe. Despite the Tm valence being strongly noninteger ($v \sim 2.58$, almost temperature independent), type-I AFM order was found to set in below $T_N = 3.45$ K for stoichiometric samples [52–54]. Thulium shares with europium the multiple electron occupancy of its $4f$ shell, unlike cerium and ytterbium, which have only one $4f$ electron (Ce) or hole (Yb) in their trivalent ionic states. On the other hand, the peculiar MV behavior of TmSe is generally ascribed to the fact that the ground-state multiplets of both Tm^{2+} ($4f^{13}$, ${}^2F_{7/2}$, $p_{\text{eff}} = 4.5\mu_B$) and Tm^{3+} ($4f^{12}$, 3H_6 , $p_{\text{eff}} = 7.5\mu_B$) configurations are magnetic (neglecting crystal-field effects [55], which are likely wiped out by the valence fluctuations). This ingredient is central

to several of the models [56–60] proposed to explain the properties of TmSe and, obviously, cannot be carried over to $\text{EuCu}_2(\text{Si}_x\text{Ge}_{1-x})_2$ where, as already noted, valence mixing involves one magnetic Eu^{2+} ($J = \frac{7}{2}$) and one nonmagnetic Eu^{3+} ($J = 0$) ionic configuration.

The magnetic spectral response of TmSe [56,60] also differs significantly from that observed in $\text{EuCu}_2(\text{Si}_x\text{Ge}_{1-x})_2$ below the critical concentration. Above $T = 100$ K, a rather broad ($\Gamma \sim 10$ meV [56,60] comparable to $\Gamma = 22$ meV in EuCu_2Si_2 in the same temperature range) temperature-independent QE response is observed, reflecting the existence of fast spin fluctuations but, upon cooling, the QE linewidth decreases with a crossover to a linear temperature dependence, $\Gamma/2 \sim 0.7k_B T$, for $T \rightarrow 0$. Simultaneously, an inelastic response appears, whose energy increases on cooling to reach about 10 meV at $T = 10$ K. The intensity of the latter mode exhibits a strong periodic Q dependence, with a maximum at the fcc zone-boundary X point. Below T_N , the QE scattering is suppressed.

In 1-2-2 intermetallics, electron states of different symmetries (s , d) can occur at the Fermi level [61,62]. In TmSe, on the other hand, the only electrons populating the conduction band are those provided by the hybridization with the $4f$ orbitals. As a result, TmSe is known to exhibit unique Kondo-insulator properties at low temperature [63], whereas the present compounds remain metallic. Accordingly, the suppression of the QE signal due to spin fluctuations in the AFM state below T_N [56] is at variance with the behavior observed here in $\text{EuCu}_2(\text{Si}_x\text{Ge}_{1-x})_2$, as well as in Ce-based HF compounds.

Theoretical attempts to specifically address the multiple occupancy of the $4f$ shell in MV systems are rather scarce. Apart from those applicable to TmSe, which rely on the existence of two magnetic valence states, and are therefore not directly relevant to the case of Eu, one can mention the work of Bulk and Nolting [64], developed in connection with early experimental results on Eu systems (elemental Eu, $\text{Eu}[\text{Pd}, \text{Au}]_2\text{Si}_2$). Their extended “ s - f model” considers, in addition to the hybridization V between the $4f$ and the conduction band states, an independent, non-Kondo, s - f exchange interaction J_{sf} assumed to be positive (i.e., ferromagnetic) in the case of Eu compounds. The AFM order is then ascribed to a direct exchange coupling J_1^{AB} between $4f$ magnetic moment at neighboring Eu sites. This model accounts for the possibility of developing AFM order inside the MV regime. It also predicts, for some parameter range, that the Néel temperature can increase with increasing V , as observed in the low- x region of the $\text{EuCu}_2(\text{Si}_x\text{Ge}_{1-x})_2$ phase diagram. However, the clear observation of a Kondo-type behavior in the electrical transport coefficients [23] seems to rule out the predominantly FM s - f coupling assumed in that model.

In a recent paper [28], Hotta has proposed an interesting theoretical basis to explain how the $4f^7$ state of Eu^{2+} can give rise to a Kondo phenomenology (including quantum criticality controlled by an external parameter) very similar to that found in nearly trivalent ($4f^1$) Ce compounds. The key argument is that, for realistic values of the spin-orbit coupling, a correct description of atomic $4f$ states cannot be achieved in terms of the standard Russel-Saunders scheme. The real situation is intermediate between LS and j - j couplings and,

even for a relatively weak spin-orbit interaction $\lambda_{so}/U \sim 0.1$ (U : Hund’s rule interaction), i.e., far from the pure j - j regime, this has to be taken into account. The main result reported for this regime is the observation of a “single- f -electron”-like behavior, due to 6 electrons being accommodated in a fully occupied $j = \frac{5}{2}$ sextet ($j = l - s$), while one single electron occupies the $j = \frac{7}{2}$ octet ($j = l + s$). The latter state can account for a $R \ln 2$ step in the entropy, a (Yb-like) Γ_6 - Γ_7 - Γ_8 crystal-field scheme, as well as for Kondo effect. The model has been applied [25,26] to the HF behavior reported in EuNi_2P_2 . The $\text{EuCu}_2(\text{Si}_x\text{Ge}_{1-x})_2$ series could provide a second useful benchmark for these ideas. To this end, Hotta’s approach should be extended to take proper account of the degenerate conduction bands (multichannel Kondo?), and the consideration of valence fluctuations affecting the Kondo regime. It has also been suggested that the treatment of MV in Eu should consider “intersite” Coulomb repulsion (as in the Falicov-Kimball model [65]) between local and conduction electrons, which is not included in the Anderson model.

The evolution of the spin dynamics observed in this study on approaching the critical concentration provides guidelines along which further theoretical work should be undertaken. A possible starting point is the previous description [33] of the magnetic response for pure EuCu_2Si_2 and the Si-rich solid solutions in terms of a renormalized spin-orbit excitation associated with the parent Eu^{3+} configuration, with an extra magnetic exciton mode below the spin-gap edge, as proposed in Ref. [66].

V. CONCLUSION

In summary, the $\text{EuCu}_2(\text{Si}_x\text{Ge}_{1-x})_2$ MV system exhibits an unusual ground state involving a coexistence of long-range antiferromagnetic order and spin fluctuations, observed over a significant concentration range. The critical value $x_c = 0.65$ corresponds to the suppression of the magnetic order and the appearance of a HF behavior. This observation is at variance with the typical behavior found in Ce- and Yb-based 1-2-2 HF systems, and requires further theoretical understanding. The analysis of the inelastic and QE magnetic contributions to the Eu magnetic spectral function provides clues as to the physical mechanism of the crossover from spin fluctuations to magnetic order, and the origin of the HF state in this unconventional situation. In particular, we emphasize the evolution of the magnetic response of MV Eu, as the Ge content increases, from the spin-gap spectrum found in pure EuCu_2Si_2 to a degenerate ground state with moderate spin fluctuations. This evolution takes place through a renormalization of the magnetic excitations to lower energies and the transfer of spectral weight to the quasielastic component. This spectral rearrangement favors the formation of a HF ground state in the corresponding intermediate region of the phase diagram. Below T_N , spin fluctuations extend into the long-range-order state. An important open question, in analogy with the Ce- and Yb-based 1-2-2 HF systems, is the possible existence of quantum criticality near the AFM onset. Addressing this question by means of neutron scattering would require a detailed single-crystals study of the Q dependence of the fluctuations.

ACKNOWLEDGMENTS

We are grateful to C. Geibel, I. P. Sadikov, V. N. Lazukov, A. V. Kuznetsov, I. Sergueev, and R. Gainov for helpful discussions, to B. Beuneu, C. Pantalei, and A. Orecchini for their support during the neutron scattering experiments, to J. de Groot and H. Nair for the help in the magnetic sample quality assessment, to I. Zizak and D. Wallacher for assistance in the XANES experiment at BESSY II, to DESY Photon Science and Helmholtz Zentrum Berlin for provid-

ing beamtime. Support from the Helmholtz Gemeinschaft Deutscher Forschungszentren for funding of the Helmholtz-University Young Investigator Group NG-407 (R.P.H.), and from the U.S. Department of Energy, Office of Science, Basic Energy Sciences, Materials Sciences and Engineering Division (R.P.H.) is acknowledged. The work was partly supported by the grants of RFBR Grants No. 14-22-01002 and No. 14-02-01096-a (neutron measurements) and Russian Science Foundation Grant No. 14-22-00098 (synchrotron radiation measurements).

-
- [1] J. M. Lawrence, P. S. Riseborough, and R. D. Parks, *Rep. Prog. Phys.* **44**, 1 (1981).
 - [2] P. Riseborough, *Adv. Phys.* **49**, 257 (2000).
 - [3] P. Aynajian, E. H. da Silva Neto, A. Gyenis, R. E. Baumbach, J. D. Thompson, Z. Fisk, E. D. Bauer, and A. Yazdani, *Nature (London)* **486**, 201 (2012).
 - [4] N. D. Mathur, F. M. Grosche, S. R. Julian, I. R. Walker, D. M. Freye, R. K. W. Haselwimmer, and G. G. Lonzarich, *Nature (London)* **394**, 39 (1998).
 - [5] P. Coleman, in *Handbook of Magnetism and Advanced Magnetic Materials*, edited by H. Kronmüller and S. Parkin (Wiley, New York, 2007), Vol. 1.
 - [6] O. Stockert, J. Arndt, E. Faulhaber, C. Geibel, H. S. Jeevan, S. Kirchner, M. Loewenhaupt, K. Schmalzl, W. Schmidt, Q. Si, and F. Steglich, *Nat. Phys.* **7**, 119 (2011).
 - [7] H. Jang, G. Friemel, J. Ollivier, A. V. Dukhnenko, N. Y. Shitsevalova, V. B. Filipov, B. Keimer, and D. S. Inosov, *Nat. Mater.* **13**, 682 (2014).
 - [8] P. J. W. Moll, B. Zeng, L. Balicas, S. Galeski, F. F. Balakirev, E. D. Bauer, and F. Ronning, *Nat. Commun.* **6**, 6663 (2015).
 - [9] T. Dahm, V. Hinkov, S. V. Borisenko, A. A. Kordyuk, V. B. Zabolotnyy, J. Fink, B. Büchner, D. J. Scalapino, W. Hanke, and B. Keimer, *Nat. Phys.* **5**, 217 (2009).
 - [10] G. Yu, Y. Li, E. M. Motoyama, and M. Greven, *Nat. Phys.* **5**, 873 (2009).
 - [11] E. E. Vainshtein, S. M. Blokhin, and Y. B. Paderno, *FTT* **6**, 2909 (1964) [*Sov. Phys.—Solid State* **6**, 2318 (1965)].
 - [12] Y. B. Paderno, S. Pokrzywnicki, and B. Staliński, *Phys. Status Solidi B* **24**, K73 (1967).
 - [13] A. Menth, E. Buehler, and T. H. Geballe, *Phys. Rev. Lett.* **22**, 295 (1969).
 - [14] J. C. Nickerson, R. M. White, K. N. Lee, R. Bachmann, T. H. Geballe, and G. W. Hull, *Phys. Rev. B* **3**, 2030 (1971).
 - [15] E. Bucher, V. Narayanamurti, and A. Jayaraman, *J. Appl. Phys.* **42**, 1741 (1971).
 - [16] E. Kaldis and P. Wachter, *Solid State Commun.* **11**, 907 (1972).
 - [17] L. J. Tao and F. Holtzberg, *Phys. Rev. B* **11**, 3842 (1975).
 - [18] A. Schröder, G. Aeppli, R. Coldea, M. Adams, O. Stockert, H. V. Löhneysen, E. Bucher, R. Ramazashvili, and P. Coleman, *Nature (London)* **407**, 351 (2000).
 - [19] P. Gegenwart, Q. Si, and F. Steglich, *Nat. Phys.* **4**, 186 (2008).
 - [20] S. Doniach, in *Valence Instabilities and Related Narrow-Band Phenomena*, edited by R. D. Parks (Plenum, New York, 1977), p. 169.
 - [21] E. Holland-Moritz, M. Loewenhaupt, W. Schmatz, and D. K. Wohlleben, *Phys. Rev. Lett.* **38**, 983 (1977).
 - [22] A. P. Murani, *Phys. Rev. Lett.* **54**, 1444 (1985).
 - [23] Z. Hossain, C. Geibel, N. Senthilkumaran, M. Deppe, M. Baenitz, F. Schiller, and S. L. Molodtsov, *Phys. Rev. B* **69**, 014422 (2004).
 - [24] S. Danzenbächer, D. V. Vyalikh, Y. Kucherenko, A. Kade, C. Laubschat, N. Caroca-Canales, C. Krellner, C. Geibel, A. V. Fedorov, D. S. Dessau, R. Follath, W. Eberhardt, and S. L. Molodtsov, *Phys. Rev. Lett.* **102**, 026403 (2009).
 - [25] Y. Hiranaka, A. Nakamura, M. Hedo, T. Takeuchi, A. Mori, Y. Hirose, K. Mitamura, K. Sugiyama, M. Hagiwara, T. Nakama, and Y. Onuki, *J. Phys. Soc. Jpn.* **82**, 083708 (2013).
 - [26] A. Mitsuda, *JPSJ News Comments* **10**, 14 (2013).
 - [27] V. Guritanu, S. Seiro, J. Sichelschmidt, N. Caroca-Canales, T. Iizuka, S. Kimura, C. Geibel, and F. Steglich, *Phys. Rev. Lett.* **109**, 247207 (2012).
 - [28] T. Hotta, *J. Phys. Soc. Jpn.* **84**, 114707 (2015).
 - [29] N. Kurita, M. Kimata, K. Kodama, A. Harada, M. Tomita, H. S. Suzuki, T. Matsumoto, K. Murata, S. Uji, and T. Terashima, *Phys. Rev. B* **83**, 214513 (2011).
 - [30] L. Sun, J. Guo, G. Chen, X. Chen, X. Dong, W. Lu, C. Zhang, Z. Jiang, Y. Zou, S. Zhang, Y. Huang, Q. Wu, X. Dai, Y. Li, J. Liu, and Z. Zhao, *Phys. Rev. B* **82**, 134509 (2010).
 - [31] P. A. Alekseev, K. S. Nemkovski, D. P. Kozlenko, A. P. Menushenkov, A. A. Yaroslavl'tsev, A. V. Gribanov, E. S. Clementyev, C. Pantalei, B. Klobes, and R. P. Hermann, *JETP Lett.* **99**, 164 (2014).
 - [32] S. Fukuda, Y. Nakanuma, J. Sakurai, A. Mitsuda, Y. Isikawa, F. Ishikawa, T. Goto, and T. Yamamoto, *J. Phys. Soc. Jpn.* **72**, 3189 (2003).
 - [33] P. A. Alekseev, K. S. Nemkovski, J.-M. Mignot, V. N. Lazukov, A. A. Nikonov, A. P. Menushenkov, A. A. Yaroslavl'tsev, R. I. Bewley, J. R. Stewart, and A. V. Gribanov, *J. Phys.: Condens. Matter* **24**, 375601 (2012).
 - [34] J. Rodriguez-Carvajal, *Phys. B (Amsterdam)* **192**, 55 (1993).
 - [35] J. Rodriguez-Carvajal, Commission on Powder Diffraction (IUCr) Newsletter **26**, 12 (2001).
 - [36] E. V. Sampathkumaran, G. Kaindl, W. Krone, B. Perscheid, and R. Vijayaraghavan, *Phys. Rev. Lett.* **54**, 1067 (1985).
 - [37] G. Michels, S. Junk, W. Schlabit, E. Holland-Moritz, M. M. Abd-Elmeguid, J. Dunner, and A. Mewis, *J. Phys.: Condens. Matter* **6**, 1769 (1994).
 - [38] E. V. Sampathkumaran, L. C. Gupta, R. Vijayaraghavan, K. V. Gopalakrishnan, R. G. Pillay, and H. G. Devare, *J. Phys. C: Solid State Phys.* **14**, L237 (1981).
 - [39] G. Wortmann, K. H. Frank, E. V. Sampathkumaran, B. Perscheid, G. Schmiester, and G. Kaindl, *J. Magn. Magn. Mater.* **49**, 325 (1985).

- [40] I. Nowik, I. Felner, and G. K. Wertheim, *Hyperfine Interact.* **33**, 145 (1987).
- [41] W. N. Rowan-Weetaluktuk, D. H. Ryan, P. Lemoine, and J. M. Cadogan, *J. Appl. Phys.* **115**, 17E101 (2014).
- [42] P. A. Alekseev, J.-M. Mignot, K. S. Nemkovski, V. N. Lazukov, E. V. Nefeodova, A. P. Menushenkov, A. V. Kuznetsov, R. I. Bewley, and A. V. Griбанov, *J. Exp. Theor. Phys.* **105**, 14 (2007).
- [43] G. Knopp, A. Loidl, K. Knorr, L. Pawlak, M. Duczmal, R. Caspary, U. Gottwick, H. Spille, F. Steglich, and A. P. Murani, *Z. Phys. B: Condens. Matter* **77**, 95 (1989).
- [44] A. Severing, E. Holland-Moritz, B. D. Rainford, S. R. Culverhouse, and B. Frick, *Phys. Rev. B* **39**, 2557 (1989).
- [45] A. Severing, E. Holland-Moritz, and B. Frick, *Phys. Rev. B* **39**, 4164 (1989).
- [46] G. Wortmann, B. Perscheid, and W. Krone, *J. Phys. Colloq.* **47**, C8-979 (1986).
- [47] K. Matsubayashi, K. Munakata, M. Isobe, N. Katayama, K. Ohgushi, Y. Ueda, N. Kawamura, M. Mizumaki, N. Ishimatsu, M. Hedo, I. Umehara, and Y. Uwatoko, *Phys. Rev. B* **84**, 024502 (2011).
- [48] X. Tan, G. Fabbris, D. Haskel, A. A. Yaroslavl'tsev, H. Cao, C. M. Thompson, K. Kovnir, A. P. Menushenkov, R. V. Chernikov, V. O. Garlea, and M. Shatruk, *J. Am. Chem. Soc.* **138**, 2724 (2016).
- [49] J. Röhler, in *Handbook on the Physics and Chemistry of Rare Earths*, Vol. 10, edited by K. Gschneidner, Jr, L. Eyring, and S. Hüfner (Elsevier, Amsterdam, 1987), Chap. 71, pp. 453–545, in particular, see p. 521 sqq.
- [50] G. Neumann, J. Langen, H. Zahel, D. Plümacher, Z. Kletowski, W. Schlabit, and D. Wohlleben, *Z. Phys. B: Condens. Matter* **59**, 133 (1985).
- [51] F. Grandjean and G. J. Long, Mössbauer spectroscopy of europium-containing compounds, in *Mössbauer Spectroscopy Applied to Inorganic Chemistry*, edited by G. J. Long and F. Grandjean (Springer, Boston, 1989), pp. 513–597.
- [52] E. Bucher, K. Andres, F. J. di Salvo, J. P. Maita, A. C. Gossard, A. S. Cooper, and G. W. Hull, *Phys. Rev. B* **11**, 500 (1975).
- [53] H. B. Möller, S. M. Shapiro, and R. J. Birgeneau, *Phys. Rev. Lett.* **39**, 1021 (1977).
- [54] H. Launois, M. Rawiso, E. Holland-Moritz, R. Pott, and D. Wohlleben, *Phys. Rev. Lett.* **44**, 1271 (1980).
- [55] A. Furrer, W. Bührer, and P. Wachter, *Solid State Commun.* **40**, 1011 (1981).
- [56] M. Loewenhaupt and E. Holland Moritz, *J. Appl. Phys.* **50**, 7456 (1979).
- [57] J. Mazzaferro, C. A. Balseiro, and B. Alascio, *Phys. Rev. Lett.* **47**, 274 (1981).
- [58] B. Alascio, A. A. Aligia, J. Mazzaferro, and C. Balseiro, in *Valence Instabilities*, edited by P. Wachter and H. Boppert (North Holland, Amsterdam, 1982), pp. 493–496.
- [59] P. Schlottmann and L. M. Falicov, *Phys. Rev. B* **23**, 5916 (1981).
- [60] E. Holland-Moritz, *J. Magn. Magn. Mater.* **38**, 253 (1983).
- [61] J. Sticht, N. d'Ambrumenil, and J. Kübler, *Z. Phys. B: Condens. Matter* **65**, 149 (1986).
- [62] T. Jarlborg, H. F. Braun, and M. Peter, *Z. Phys. B: Condens. Matter* **52**, 295 (1983).
- [63] P. Haen, F. Lapierre, J.-M. Mignot, R. Tournier, and F. Holtzberg, *Phys. Rev. Lett.* **43**, 304 (1979).
- [64] G. Bulk and W. Nolting, *Z. Phys. B: Condens. Matter* **70**, 473 (1988).
- [65] V. Zlatić and J. Freericks, *Acta Phys. Pol.*, B **34**, 931 (2003).
- [66] K. A. Kikoin and A. S. Mishchenko, *J. Phys.: Condens. Matter* **7**, 307 (1995).