

Inductive detection of fieldlike and dampinglike ac inverse spin-orbit torques in ferromagnet/normal-metal bilayers

Andrew J. Berger,¹ Eric R. J. Edwards,¹ Hans T. Nembach,¹ Alexy D. Karenowska,² Mathias Weiler,^{3,4} and Thomas J. Silva^{1,*}

¹*Quantum Electromagnetics Division, National Institute of Standards and Technology, Boulder, Colorado 80305, USA*

²*Department of Physics, University of Oxford, Oxford, United Kingdom*

³*Walther-Meißner-Institut, Bayerische Akademie der Wissenschaften, Garching, Germany*

⁴*Physik-Department, Technische Universität München, Garching, Germany*



(Received 30 October 2017; revised manuscript received 26 January 2018; published 7 March 2018; corrected 26 September 2018)

Functional spintronic devices rely on spin-charge interconversion effects, such as the reciprocal processes of electric field-driven spin torque and magnetization dynamics-driven spin and charge flow. Both dampinglike and fieldlike spin-orbit torques have been observed in the forward process of current-driven spin torque and dampinglike inverse spin-orbit torque has been well studied via spin pumping into heavy metal layers. Here, we demonstrate that established microwave transmission spectroscopy of ferromagnet/normal metal bilayers under ferromagnetic resonance can be used to inductively detect the ac charge currents driven by the inverse spin-charge conversion processes. This technique relies on vector network analyzer ferromagnetic resonance (VNA-FMR) measurements. We show that in addition to the commonly extracted spectroscopic information, VNA-FMR measurements can be used to quantify the magnitude and phase of all ac charge currents in the sample, including those due to spin pumping and spin-charge conversion. Our findings reveal that Ni₈₀Fe₂₀/Pt bilayers exhibit both dampinglike and fieldlike inverse spin-orbit torques. While the magnitudes of both the dampinglike and fieldlike inverse spin-orbit torque are of comparable scale to prior reported values for similar material systems, we observed a significant dependence of the dampinglike magnitude on the order of deposition. This suggests interface quality plays an important role in the overall strength of the dampinglike spin-to-charge conversion.

DOI: [10.1103/PhysRevB.97.094407](https://doi.org/10.1103/PhysRevB.97.094407)

I. INTRODUCTION

Spin-charge transduction effects for ferromagnet/nonmagnet (FM/NM) multilayers couple electric fields to magnetic torques in the forward process [so-called spin-orbit torque (SOT)], and they couple magnetization dynamics to currents in the inverse process (iSOT). In general, these torques can be phenomenologically separated into two components: dampinglike and fieldlike. Both are perpendicular to the FM magnetization, but the dampinglike torque is odd under time-reversal and dissipative, whereas the fieldlike torque is even under time-reversal and conservative [1]. A classic example of a fieldlike torque is the action of an Oersted field on an FM magnetization due to a charge current in an adjacent conducting layer. By Onsager reciprocity, the inverse process is captured by Faraday's law: magnetization dynamics in the FM generate charge currents in the NM. Recently, it has been found that spin-orbit coupling (SOC) in multilayers can give rise to both field- and dampinglike SOTs [2,3], but with substantially different scaling than that achieved with Oersted fields. Unlike the Oersted effect, these spin-orbitronic effects are short-range, making them highly advantageous for microelectronic applications that require device scaling to high densities such as nonvolatile memory and alternative state-variable logic [4,5].

Dampinglike torques due to the spin Hall effect (SHE) in heavy NM layers such as Pt and β -Ta are well-studied and understood, and have been investigated in both forward [4] and inverse configurations [6–8]. Substantial fieldlike torques have also been measured for FM/NM interfaces in the forward configuration [2,9–11]. However, an inverse measurement of the fieldlike torque in Ni₈₀Fe₂₀/Pt has not yet been unambiguously reported [12]. Here, we present simultaneous measurements of inverse fieldlike and dampinglike torques in Ni₈₀Fe₂₀/Pt bilayers via well-established coplanar waveguide (CPW) ferromagnetic resonance (FMR). Time-varying magnetic fields produced by a FM/NM sample under FMR excitation will inductively couple into the CPW, altering the total inductance of the microwave circuit. Such fields are produced by (1) the Py precessing magnetization, (2) Faraday effect induced ac currents in the Pt layer, and (3) spin-orbit ac currents due to dampinglike and (4) fieldlike processes. We show that through proper background normalization, combined with Onsager reciprocity for the specific phenomenology of these measurements, commonly-used vector network analyzer (VNA) FMR spectroscopy allows accurate identification of the processes that contribute to spin-charge conversion.

The paper is organized as follows. In Sec. II, by appealing to Onsager reciprocity, we provide the phenomenological background relating the forward and inverse processes that produce magnetic torques and charge flow in a ferromagnet/normal metal system under electrical bias or with excited magnetization dynamics. Section III describes the quantitative

*thomas.silva@nist.gov

VNA-FMR technique, and derives the expressions we use to calculate the sample's complex inductance. This section also introduces the effective conductivity $\bar{\sigma}_{\text{NM}}$ that quantifies the magnitude and symmetry of magnetic torques due to applied charge currents, and reciprocally, of the ac charge currents flowing in a sample in response to the driven magnetization dynamics. In Sec. IV, we present data acquired from Ni₈₀Fe₂₀/Pt bilayers and Ni₈₀Fe₂₀/Cu control samples. The magnitude of the phenomenological parameter $\bar{\sigma}_{\text{NM}}$ extracted from these data is well within the range of reported values, and it obeys the usual symmetry properties associated with the stacking order of the Ni₈₀Fe₂₀ and Pt layers. Finally, we discuss the results in Sec. V by comparing our extracted iSOT parameters to the microscopic spin-charge conversion parameters of spin Hall angle and Rashba parameter. In all cases, the magnitudes of the extracted spin Hall angle and Rashba parameter are in rough agreement with what has been reported in the literature, though this agreement is contingent on the assumption of typical values for the interfacial and bulk spin transport parameters. However, we find that the extracted spin Hall angle changes

by a factor of almost 4 depending on the growth order of the multilayer stacks, with a larger spin Hall angle when the Pt is grown on top of the Ni₈₀Fe₂₀. This suggests that the spin transport parameters are in actuality highly dependent on the stack growth order.

II. ONSAGER RELATIONS FOR SPIN-ORBIT TORQUE

Onsager reciprocity relations [13] are well known for certain pairs of forces and flows. For example, for thermoelectric effects, applied electric fields or thermal gradients can drive both charge and heat flow. In this section, we establish Onsager relations for charge current and magnetic torque as the flows that are driven by applied electric fields and magnetization dynamics in a FM/NM multilayer [1].

By analogy to Ohm's law, $\mathbf{J} = \sigma \mathbf{E}$, we can write a general matrix equation relating driving forces (magnetization dynamics $\partial \hat{m} / \partial t$ and electric field \mathbf{E}) to flows (magnetic torque density \mathbf{T} and charge current density \mathbf{J}) [1]:

$$\begin{bmatrix} \left(\frac{2e}{\hbar}\right) \left[\int_0^{+d_{\text{FM}}} \mathbf{T}(z) dz \right] \\ \left[\int_{-d_{\text{NM}}}^{+d_{\text{FM}}} \mathbf{J}(z) dz \right] \end{bmatrix} = \mathcal{G} \begin{bmatrix} G_{\text{mag}} & \text{sgn}(\hat{z} \cdot \hat{n})(-\sigma_e^{\text{F}} + \sigma_e^{\text{SOT}} - \sigma_o^{\text{SOT}}[\hat{m} \times]) \\ \text{sgn}(\hat{z} \cdot \hat{n})(-\sigma_e^{\text{F}} + \sigma_e^{\text{SOT}} - \sigma_o^{\text{SOT}}[\hat{m} \times]) & -\frac{1}{Z_{\text{eff}}} \end{bmatrix} \begin{bmatrix} \left(\frac{\hbar}{2e}\right) \frac{\partial \hat{m}}{\partial t} \\ \hat{z} \times \mathbf{E} \end{bmatrix}, \quad (1)$$

where \hat{m} is the magnetization unit vector, \hbar is Planck's constant divided by 2π , e is the electron charge, d_{FM} and d_{NM} are the FM and NM thicknesses. The terms in the 2×2 conductivity matrix are described below. The sign of the off-diagonal terms are determined by $\text{sgn}(\hat{z} \cdot \hat{n})$, where \hat{n} is an interface normal pointing into the FM. The coordinate unit vector \hat{z} is defined by the sample placement on the CPW, as shown in Fig. 1(a), and $z = 0$ is defined by the FM/NM interface. \mathcal{G} is a 2×2 matrix imposing geometrical constraints: (1) magnetic torques are orthogonal to \hat{m} and (2) charge currents can flow only in the x, y plane:

$$\mathcal{G} = \begin{bmatrix} [\hat{m} \times] & 0 \\ 0 & [\hat{z} \times] \end{bmatrix}. \quad (2)$$

The diagonal elements of the effective conductivity matrix describe the Gilbert damping of the FM and charge flow in the metallic bilayer in response to an applied electric field. That is,

$$\left(\frac{2e}{\hbar}\right) \left[\int_0^{+d_{\text{FM}}} \mathbf{T}(z) dz \right] = \left(\frac{\hbar}{2e}\right) G_{\text{mag}} \left(\hat{m} \times \frac{\partial \hat{m}}{\partial t} \right), \quad (3)$$

$$\left[\int_{-d_{\text{NM}}}^{+d_{\text{FM}}} \mathbf{J}(z) dz \right] = -\frac{1}{Z_{\text{eff}}} \hat{z} \times (\hat{z} \times \mathbf{E}), \quad (4)$$

where $G_{\text{mag}} \equiv -d_{\text{FM}}(2e/\hbar)^2(\alpha M_s/\gamma)$, α is the Gilbert damping parameter, and γ is the gyromagnetic ratio, such that Eq. (3) is the usual Gilbert damping term from the Landau-Lifshitz-Gilbert equation:

$$\frac{\partial \hat{m}}{\partial t} = -\gamma \mu_0 \hat{m} \times \mathbf{H} - \left(\frac{\gamma}{M_s d_{\text{FM}}} \right) \int_0^{+d_{\text{FM}}} \mathbf{T}(z) dz. \quad (5)$$

In Eq. (4), Z_{eff} is the effective frequency-dependent impedance of the bilayer. Equation (4) reduces to Ohm's law in the dc limit ($Z_{\text{eff}} \rightarrow R_{\square}$ as $f \rightarrow 0$).

The off-diagonal terms describe the electromagnetic reciprocity between Faraday's and Ampere's laws [14,15], as well as spin-orbit torques (SOT) and their inverse, using the effective conductivities σ_e^{F} , σ_e^{SOT} , and σ_o^{SOT} :

$$\begin{aligned} \left(\frac{2e}{\hbar}\right) \left[\int_0^{+d_{\text{FM}}} \mathbf{T}(z) dz \right] \\ = \text{sgn}(\hat{z} \cdot \hat{n}) \hat{m} \times [(-\sigma_e^{\text{F}} + \sigma_e^{\text{SOT}} - \sigma_o^{\text{SOT}}[\hat{m} \times]) (\hat{z} \times \mathbf{E})], \end{aligned} \quad (6)$$

$$\begin{aligned} \left[\int_{-d_{\text{NM}}}^{+d_{\text{FM}}} \mathbf{J}(z) dz \right] \\ = \text{sgn}(\hat{z} \cdot \hat{n}) \left(\frac{\hbar}{2e}\right) \hat{z} \times [(-\sigma_e^{\text{F}} + \sigma_e^{\text{SOT}} - \sigma_o^{\text{SOT}}[\hat{m} \times]) \frac{\partial \hat{m}}{\partial t}]. \end{aligned} \quad (7)$$

Here, the superscripts indicate the source of the torque or current as due to the Faraday effect or SOT. The subscripts indicate "even" or "odd" with respect to time-reversal, which determines the torque direction or phase of the corresponding current with respect to the driving electric field or magnetization dynamics. The signs of the effective conductivities are chosen to comply with the appropriate time-reversal symmetry of an Oersted torque (or Faraday's law of induction) for σ_e^{F} , and of fieldlike and dampinglike SOT (σ_e^{SOT} and σ_o^{SOT} , respectively). Furthermore, the sign of the fieldlike SOT terms are consistent with that used by Emori *et al.* [16] and Kim *et al.* [17], in which a positive, interfacial SOT field points

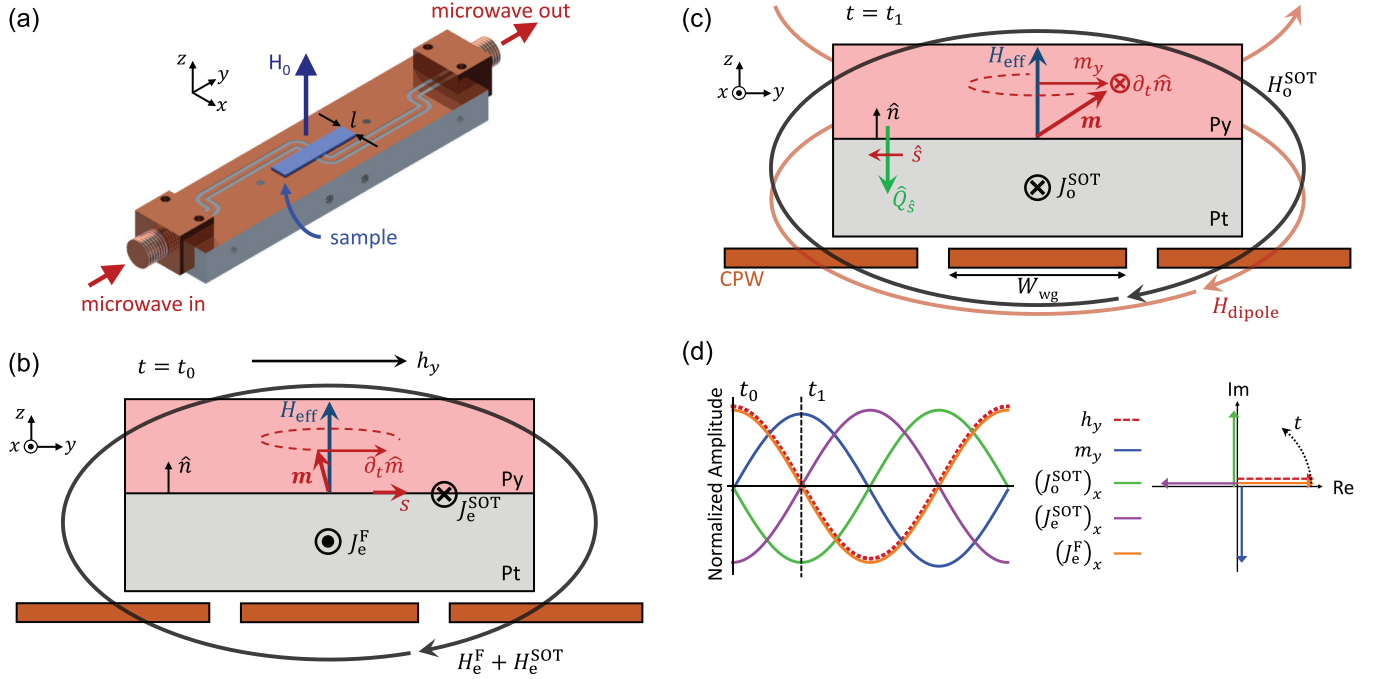


FIG. 1. (a) Sample on CPW, showing out-of-plane field H_0 and sample length l . The microwave driving field points primarily along \hat{y} at the sample. (b) Schematic of the bilayer, with precessing magnetization $\mathbf{m}(t)$ at time t_0 when $\mathbf{m} = \langle m_x, 0, m_z \rangle$. Bilayer is insulated from CPW using photoresist spacer layer (not shown). At this instant in time, J_e^F (due to the Faraday effect in the NM) and J_e^{SOT} (e.g., due to inverse Rashba-Edelstein effect) are maximal along $\pm \hat{x}$, and h_y is also at its maximum strength. The corresponding Oersted fields from J_e^F and J_e^{SOT} are superposed. The spin accumulation (with orientation \hat{s}) and J_e^{SOT} are produced at the FM/NM interface. Interface normal is given by \hat{n} . (c) Same as (b), except at time t_1 when $\mathbf{m} = \langle 0, m_y, m_z \rangle$. Here, odd-symmetry SOT current J_o^{SOT} (e.g., due to inverse spin Hall effect), and the dynamic fields H_o^{SOT} and H_{dipole} are at maximum amplitude. Note that the dipolar signal is proportional to $\partial_t(H_{\text{dipole}} \cdot \hat{y})$, and not simply to H_{dipole} . Spin flow direction \hat{Q}_s due to spin pumping into the NM is also shown. (d) Amplitude of driving field h_y and different signal sources as a function of time (left), and viewed in the complex plane at time t_0 (right). Relative amplitudes not indicated. For further discussion of signal phases, see Ref. [23].

in the direction $\hat{z} \times \mathbf{J}$. Finally, we use the usual convention for the direction of SHE and iSHE currents: $\mathbf{Q}_s \propto \hat{z} \times \mathbf{J}$ and $\mathbf{J} \propto \mathbf{Q}_s \times \hat{s}$, for spin current flow in the \mathbf{Q} direction and spin orientation \hat{s} , as in Ref. [18].

First, consider the Faraday conductivity, σ_e^F . In the forward process, an electric field \mathbf{E} produces a charge current, which by Ampere's law produces a magnetic field. This field exerts a torque \mathbf{T} on the magnetization of the FM layer. In the reverse process, magnetization dynamics $\partial_t \hat{m}$ produce an ac magnetic field, which by Faraday's law induces a charge current \mathbf{J} in the NM layer. In this way, σ_e^F quantifies the reciprocity between Ampere's and Faraday's law [see Eq. (31) for an estimate of the σ_e^F magnitude based on material properties]. Inclusion of the terms in Eq. (1) due to electrodynamic reciprocity is critical for the proper interpretation of inverse spin-orbit torque experiments [12].

Also present in the off-diagonal terms are SOT conductivities due to spin-charge conversion. In Eq. (6), these manifest as electric-field driven dampinglike torques, which are proportional to $\hat{m} \times (\hat{m} \times (\hat{z} \times \mathbf{E}))$, and fieldlike torques, which are proportional to $\hat{m} \times (\hat{z} \times \mathbf{E})$. The constants of proportionality between applied electric field and SOTs are σ_o^{SOT} and σ_e^{SOT} . In the reverse direction [Eq. (7)], these effects are responsible for spin-to-charge conversion (e.g., inverse spin Hall effect (iSHE) [19] or inverse Rashba-Edelstein effect (iREE) [20]).

Reporting effective conductivities, as opposed to spin-charge conversion parameters like the spin Hall angle, directly relates the microwave inputs and charge current outputs of an iSOT device without the need for separate characterization of spin-mixing conductance or spin diffusion length. Reciprocally, in a spin torque experiment with charge current inputs and magnetization dynamics (or switching) as output, the effective conductivities provide the ideal figure of merit for determining magnetization oscillation and switching thresholds of the applied current. To estimate the critical current density J_c needed to switch the magnetization of a ferromagnetic layer at 0 K [21,22], one simply needs to equate the Gilbert damping torque [Eq. (3)] and odd (anti-damping-like) SOT [Eq. (6)]:

$$J_c = \alpha M_s d_{\text{FM}} \frac{\omega}{\gamma} \frac{2e}{\hbar} \left(\frac{\sigma}{\sigma_o^{\text{SOT}}} \right), \quad (8)$$

where ω is the FMR frequency with no applied fields (e.g., for in-plane magnetization, $\omega = \mu_0 \gamma \sqrt{H_k(M_s + H_k)}$, with anisotropy field H_k). Using α as determined for these $\text{Ni}_{80}\text{Fe}_{20}/\text{Pt}$ films (see Ref. [23]), $M_s = 700 \text{ kA/m}$, $H_k = 160 \text{ kA/m}$ (for thermal stability considerations), bulk Pt resistivity [24], and the measured σ_o^{SOT} (see Table I), we estimate a critical current density of $2 \times 10^{12} \text{ A/m}^2$ for a 2-nm $\text{Ni}_{80}\text{Fe}_{20}$ film.

While the effective conductivity is the directly measured quantity, in Sec. VA, we nevertheless derive expressions

TABLE I. Effective conductivities (in units of $10^5 \Omega^{-1} \text{m}^{-1}$) for various FM/NM samples. Measured values are calculated from measured inductances (Fig. 5). Corrected values are calculated by subtraction of Cu control to remove the Faraday contribution (in the case of σ_e) and any contribution from the Ta interfaces, followed by application of the shunting correction (see Ref. [23]).

Sample	$(\sigma_e^F - \sigma_e^{\text{SOT}})_{\text{meas}}$	$(\sigma_o^{\text{SOT}})_{\text{meas}}$	$(\sigma_e^{\text{SOT}})_{\text{corr}}$	$(\sigma_o^{\text{SOT}})_{\text{corr}}$
Py/Pt	-0.45(3)	1.0(1)	-1.48(7)	2.4(3)
Pt/Py	-0.69(5)	0.31(6)	-1.8(2)	0.6(2)
Py/Cu	0.143(6)	0.07(3)		
Cu/Py	0.04(3)	0.06(1)		

relating the effective conductivities to microscopic spin-charge conversion parameters. Extraction of the microscopic parameters is necessarily contingent on the details of the model employed and parameters assumed.

The effective conductivities can also be related to the often used quantity of effective flux density per unit current density [25] B_{eff}/J , with units of $\text{T m}^2 \text{A}^{-1}$ via the equation $B_{\text{eff}}/J = \sigma_{e,o}^{\text{SOT}} \hbar / (2M_s \sigma d_{\text{FM}} e)$ (where σ is the ordinary charge conductivity of the NM). However, our definition for the effective conductivity is more general insofar as it allows one to calculate the actual SOT without the need to independently determine the sample magnetization, conductivity, or actual thickness.

Equation (1) is consistent with the phenomenological formulation presented by Freimuth, Bluegel, and Mokrousov [1], although it has been expanded to include the purely electrodynamic contributions. Our use of the descriptors “even” and “odd” are different from that of Freimuth *et al.*, who use the symmetry of the spin-orbit torques with respect to magnetization-reversal as the symmetry identifier. We instead use the symmetry of the torque with respect to time-reversal because this is the relevant symmetry with regard to the off-diagonal components in the phenomenological Eq. (1). Any process for which the torque is odd under time-reversal qualifies as microscopically nonreversible in the sense of Onsager reciprocity, where microscopic reversibility pertains solely to forces that are even functions of velocity, as well as position [13]. (We also note that all axial vectors such as magnetic field are odd under time reversal.)

III. EXPERIMENTAL TECHNIQUE

The broadband, phase-sensitive FMR measurements utilize a coplanar waveguide (CPW) as both the excitation and detection transducer [see Fig. 1(a)]. Any source of ac magnetic flux generated by the bilayer is inductively detected in the CPW. Therefore the inductive load that the sample contributes to the CPW circuit consists of four terms: (1) the real-valued L_0 due to the oscillating magnetic dipolar fields produced by the resonating FM magnetization; (2) the Faraday-effect currents induced in the NM layer by the precessing FM magnetization; (3) currents produced by dampinglike iSOT effects (e.g., spin pumping + iSHE); and (4) currents produced by fieldlike iSOT effects (e.g., iREE). The latter three inductances, which we collectively define as complex-valued L_{NM} , are produced by currents in the NM which generate Oersted fields that

inductively couple to the CPW. We quantify these currents with the effective conductivities σ_e^F , σ_o^{SOT} , and σ_e^{SOT} , described above. Importantly, as shown below, while L_0 is independent of frequency, L_{NM} is linear in frequency, as the currents in the NM are driven by $\partial_t \hat{m}$. Hence frequency-dependent measurements allow us to disentangle L_0 and L_{NM} .

Figures 1(b) and 1(c) show schematics of these four signal sources at two instants in time: when the dipolar and even SOT effects are maximal [Fig. 1(b)] and when the odd SOT effect is maximal [Fig. 1(c)]. Figure 1(d) shows the time dependence of each of these signal sources, and their distinct phase relationships to the driving field h_y , which we exploit below to determine their contributions separately.

For our measurements, we place samples onto a coplanar waveguide (CPW) with the metallic film side facing down (see Fig. 1). This setup is positioned between the pole pieces of a room-temperature electromagnet capable of producing fields up to $\approx 2.2 \text{ T}$. Using a VNA, we measure the change in microwave transmission through the CPW loaded with the bilayer sample as an out-of-plane dc magnetic field ($\mathbf{H}_0 \parallel \hat{z}$) is swept through the FMR condition of the $\text{Ni}_{80}\text{Fe}_{20}$ (Permalloy, Py) layer. We acquire the microwave transmission S parameter $S_{21} \equiv V_{\text{in},2} / V_{\text{out},1}$, where $V_{\text{in(out)},1(2)}$ is the voltage input (output) at port 1 (2) of the VNA. Field sweeps were repeated to average the transmission data until an appropriate signal-to-noise ratio was obtained.

Typically, VNA-FMR measurements focus on the resonance field and linewidth. Our method additionally makes use of the signal magnitude and phase in order to directly probe the ac charge currents produced by iSOT. Previous studies of ac charge currents in spin pumping experiments have relied on intricate experimental setups or techniques that suppress or are insensitive to spurious background signals [12,26,27]. Our technique remains sensitive to currents induced by the Faraday effect, but is able to separate them from spin-charge conversion currents through the combination of phase-sensitive analysis and comparison to control samples in which the heavy metal NM (here, Pt) is substituted with a Cu layer of nominally negligible intrinsic spin-orbit effects. Furthermore, because the CPW is inductively coupled to the sample, no electrical connections need to be made directly to the FM/NM sample.

The sample adds a complex inductance L in series with the impedance of the bare CPW, Z_0 (here, 50Ω). The change in microwave transmission ΔS_{21} is therefore that of a simple voltage divider [28]:

$$\Delta S_{21} = -\frac{1}{2} \left(\frac{i\omega L}{Z_0 + i\omega L} \right) \approx \frac{-i\omega L}{2Z_0}, \quad (9)$$

for $Z_0 \gg \omega L$, where ω is the microwave frequency. The factor of $1/2$ is needed because the port 2 voltage measurement is between the CPW signal and ground (and not between port 2 and port 1).

A. Inductance derivations

In order to extract values for the SOT effects from the measured ΔS_{21} , we derive expressions for each contribution to L .

1. Inductance due to dipole field of dynamic magnetization

To derive the inductance due to ac dipolar fields produced by the precessing FM magnetization, we follow Ref. [28]:

$$\begin{aligned}
L_0 &= \frac{\mu_0 \ell}{W_{\text{wg}} d_{\text{FM}} I^2} \\
&\times \left[\int_{-\infty}^{+\infty} dy \int_{d_{\text{wg}}}^{d_{\text{FM}}+d_{\text{wg}}} dz [\mathbf{q}(y, z) \cdot \chi(\omega, H_0) \cdot \mathbf{h}_1(y, z, I)] \right] \\
&\times \left[\int_{-\infty}^{+\infty} dy \int_{d_{\text{wg}}}^{d_{\text{FM}}+d_{\text{wg}}} dz [\mathbf{q}(y, z) \cdot \mathbf{h}_1(y, z, I)] \right] \\
&\cong \frac{\mu_0 \ell}{W_{\text{wg}} d_{\text{FM}} I^2} \chi_{yy}(\omega, H_0) h_y^2(I, z) d_{\text{FM}}^2 W_{\text{wg}}^2 \\
&\cong \frac{\mu_0 \ell}{W_{\text{wg}} d_{\text{FM}} I^2} \chi_{yy}(\omega, H_0) \left(\frac{I}{2W_{\text{wg}}} \eta(z, W_{\text{wg}}) \right)^2 d_{\text{FM}}^2 W_{\text{wg}}^2 \\
&= \frac{\mu_0 \ell d_{\text{FM}}}{4W_{\text{wg}}} \chi_{yy}(\omega, H_0) \eta^2(z, W_{\text{wg}}), \tag{10}
\end{aligned}$$

where μ_0 is the vacuum permeability, ℓ is the sample length, d_{FM} is the FM thickness, W_{wg} is the width of the CPW signal line (here, 100 μm), and $\chi_{yy}(\omega)$ is the frequency-dependent magnetic susceptibility. $\eta(z, W_{\text{wg}}) \equiv (2/\pi) \arctan(W_{\text{wg}}/2z)$ is the spacing loss, ranging from 0 to 1, due to a finite distance z between sample and waveguide. We have assumed the coordinate system described in Fig. 1 (\hat{x} along the CPW signal propagation direction, \hat{z} along the CPW and sample normal). The function $\mathbf{q}(y, z)$ describes the normalized spatial amplitude of the FMR mode. For the uniform mode, $\mathbf{q}(y, z) = 1$ over the entire sample. The first set of integrals in brackets captures the integrated amplitude of the mode as excited by the driving microwave field $\mathbf{h}_1 = h_y \hat{y}$, while the second describes the inductive pickup sensitivity of the CPW. The first approximation assumes uniform microwave field over the sample dimensions. The second approximation utilizes the Karlqvist equation [29] to approximate the microwave field as $h_y(I, z) \cong I/(2W_{\text{wg}})\eta(z, W_{\text{wg}})$.

2. Inductance due to ac current flow in NM

Following Rosa [30], we model the sample and CPW as two thin current-carrying sheets of width $w = W_{\text{wg}}$, separation z , and length l , so that the mutual inductance is given by

$$L_{12} = \frac{\mu_0}{4\pi} 2l \left[\ln \left(\frac{2l}{R} \right) - 1 \right], \tag{11}$$

where R is defined as

$$\begin{aligned}
R &\equiv \sqrt{w^2 + z^2} \left(\frac{z}{\sqrt{w^2 + z^2}} \right)^{\left(\frac{z}{w}\right)^2} \\
&\times \exp \left[\frac{2z}{w} \arctan \left(\frac{w}{z} \right) - \frac{3}{2} \right]. \tag{12}
\end{aligned}$$

Viewing the sample-CPW system as a voltage transformer (two mutually-coupled inductors), the voltage induced in the CPW due to current I_{NM} in the NM and the mutual inductance L_{12} is given by $V = -L_{12}(\partial I_{\text{NM}}/\partial t)$. If instead we consider the

system to be a single lumped-element inductor, the voltage due to the self-inductance contributed by the sample L_{NM} and applied current I_{CPW} is $V = L_{\text{NM}}(\partial I_{\text{CPW}}/\partial t)$. Therefore we can calculate L_{NM} as

$$L_{\text{NM}} = -L_{12} \frac{I_{\text{NM}}}{I_{\text{CPW}}}. \tag{13}$$

The charge current we are interested in is that driven by the magnetization dynamics of the FM layer, and given by the off-diagonal term of Eq. (1):

$$\begin{aligned}
I_{\text{NM}} &= \hat{x} \cdot \left[\int_{-d_{\text{NM}}}^{+d_{\text{FM}}} \mathbf{J}(z) dz \right] W_{\text{wg}} \\
&= \hat{x} \cdot \left[\hat{z} \times \left(-\sigma_e^{\text{F}} + \sigma_e^{\text{SOT}} - \sigma_0^{\text{SOT}}[\hat{m} \times] \right) \partial_t \hat{m} \right] \\
&\quad \times \text{sgn}(\hat{z} \cdot \hat{n}) \left(\frac{\hbar}{2e} \right) W_{\text{wg}}. \tag{14}
\end{aligned}$$

Assuming a linear solution to the Landau-Lifshitz-Gilbert equation of motion for the magnetization, we write a simple relation between the dynamic component of the magnetization \mathbf{m} and microwave field \mathbf{h}_1 :

$$\partial_t \hat{m} = i\omega \frac{\chi}{M_s} \mathbf{h}_1. \tag{15}$$

To convert the vector cross products in Eq. (14) to the complex plane, we use χ in the frequency domain [31]:

$$\begin{aligned}
\chi &= \frac{\gamma \mu_0 M_s}{\omega_{\text{res}}^2 - \omega^2 + i\omega \Delta\omega} \\
&\times \begin{bmatrix} (1 + \alpha^2)\omega_y - i\alpha\omega & i\omega \\ -i\omega & (1 + \alpha^2)\omega_x - i\alpha\omega \end{bmatrix}, \tag{16}
\end{aligned}$$

where $\omega_{x,y} \equiv \gamma \mu_0 H_{x,y}$, $H_{x,y}$ is the stiffness field in the x or y direction (including external, anisotropy, and demagnetizing fields), $\omega_{\text{res}} \equiv \sqrt{\omega_x \omega_y}$, and $\Delta\omega \equiv \alpha(\omega_x + \omega_y)$. For compactness in the following derivation, we utilize the tensor components of the susceptibility as defined in Eq. S1.

Equation (14) has even terms along $\hat{z} \times \partial_t \hat{m}$ and odd terms along $\hat{z} \times (\hat{m} \times \partial_t \hat{m})$. Using Eq. (15) for $\partial_t \hat{m}$, we can work out these cross products assuming $\hat{m} \parallel \hat{z}$ (small-angle FMR excitation). The vector components of the even terms are given by

$$\begin{aligned}
\hat{z} \times \partial_t \hat{m} &= \hat{z} \times \left(\begin{bmatrix} \chi_{xx} & \chi_{xy} \\ \chi_{yx} & \chi_{yy} \end{bmatrix} \begin{bmatrix} 0 \\ h_y \end{bmatrix} \right) \left(\frac{i\omega}{M_s} \right) \\
&= \hat{z} \times (\chi_{xy} h_y \hat{x} + \chi_{yy} h_y \hat{y}) \left(\frac{i\omega}{M_s} \right) \\
&= (-\chi_{yy} h_y \hat{x} + \chi_{xy} h_y \hat{y}) \left(\frac{i\omega}{M_s} \right). \tag{17}
\end{aligned}$$

Similarly, we find for the odd terms:

$$\begin{aligned}
\hat{z} \times (\hat{m} \times \partial_t \hat{m}) &= \hat{z} \times (-\chi_{yy} h_y \hat{x} + \chi_{xy} h_y \hat{y}) \left(\frac{i\omega}{M_s} \right) \\
&= (-\chi_{xy} h_y \hat{x} - \chi_{yy} h_y \hat{y}) \left(\frac{i\omega}{M_s} \right). \tag{18}
\end{aligned}$$

Noting from Eq. (16) that $\chi_{xy} = i\chi_{yy}$ (ignoring terms of order α or α^2 , and working near resonance such that $\omega_x = \omega$), the vector relationships of Eqs. (17) and (18) are substituted

into Eq. (14). After evaluating the \hat{x} projection as prescribed by Eq. (14) and grouping even and odd terms, we find

$$I_{\text{NM}} = [(\sigma_e^{\text{F}} - \sigma_e^{\text{SOT}}) + i\sigma_o^{\text{SOT}}] \text{sgn}(\hat{z} \cdot \hat{n}) \frac{i\chi_{yy}h_y}{M_s} \left(\frac{\hbar\omega}{2e}\right) W_{\text{wg}}, \quad (19)$$

from which we define $\tilde{\sigma}_{\text{NM}} = (\sigma_e^{\text{F}} - \sigma_e^{\text{SOT}}) + i\sigma_o^{\text{SOT}}$. On resonance, $\chi_{yy} = -i\gamma\mu_0M_s/(2\alpha_{\text{eff}}\omega_{\text{res}})$, such that Eq. (19) produces the current phases depicted in Fig. 1.

Finally, using the Karlqvist equation [29], we approximate the field of the CPW. With these substitutions into Eq. (13), we arrive at the final result for the inductance due to all ac currents in the NM:

$$L_{\text{NM}} = \text{sgn}(\hat{z} \cdot \hat{n}) L_{12}(z, W_{\text{wg}}, l) \eta(z, W_{\text{wg}}) \times \frac{\hbar\omega}{4M_s e} i\chi_{yy}(\omega, H_0) \tilde{\sigma}_{\text{NM}}. \quad (20)$$

The different frequency dependencies of L_0 and L_{NM} is critical for our analysis. When normalized to $\chi_{yy}(\omega, H_0)$, L_0 is a frequency-independent inductance. By contrast, L_{NM} has an extra factor of ω , reflecting the fact that both Faraday and SOT effects are driven by $\partial_t \hat{m}$, rather than by $\mathbf{m}(t)$ itself.

Careful attention needs to be paid to the signal phase in order to properly add the inductive effects of L_0 and L_{NM} . As discussed in detail in Ref. [23], it is the current phase in the CPW that determines the propagating signal phase. Using the excitation current in the CPW as the phase reference, we work out the phase of the induced currents due to the perturbative inductance of the sample-on-CPW, and find that the inductances add according to $L = L_0 + iL_{\text{NM}}$.

After normalizing by the fitted susceptibility $\tilde{L} \equiv L/\chi_{yy}(\omega, H_0)$, the real and imaginary normalized inductance amplitudes are given by

$$\text{Re}(\tilde{L}) = \frac{\mu_0 l}{4} \left[\frac{d_{\text{FM}}}{W_{\text{wg}}} \eta^2(z, W_{\text{wg}}) - \text{sgn}(\hat{z} \cdot \hat{n}) \eta(z, W_{\text{wg}}) \times \frac{L_{12}(z, W_{\text{wg}}, l) \hbar\omega}{\mu_0 l M_s} (\sigma_e^{\text{F}} - \sigma_e^{\text{SOT}}) \right], \quad (21)$$

$$\text{Im}(\tilde{L}) = -\frac{\mu_0 l}{4} \left[\text{sgn}(\hat{z} \cdot \hat{n}) \eta(z, W_{\text{wg}}) \times \frac{L_{12}(z, W_{\text{wg}}, l) \hbar\omega}{\mu_0 l M_s} \sigma_o^{\text{SOT}} \right]. \quad (22)$$

Note that when the stacking order of FM and NM is reversed, so is the sign of the SOT and Faraday currents (and therefore their inductance contributions).

3. Magnetization dynamics driven by forward SOT

From the transformer analogy developed above and discussed in Ref. [23], we see that ‘‘image currents’’ are produced in the CPW when currents flow in the conducting sample. Reciprocity requires that the excitation currents in the CPW drive image currents in the sample. This current will produce Amperian torque and forward SOT effects according to Eq. (6), exciting additional magnetization dynamics, which are then picked up by the CPW. This series of transduction effects is

fully reciprocal with the Faraday and iSOT sequence described above. In the first case, a drive current in the CPW excites magnetization dynamics [via the coupling factor, $\eta(z, W_{\text{wg}})$]. Those magnetization dynamics drive charge current in the NM via $\tilde{\sigma}_{\text{NM}}$. Finally, these charge currents couple into the CPW via the mutual inductance $L_{12}(z, W_{\text{wg}}, l)$. In the second case, the order is simply reversed: the CPW currents create image currents in the NM [via $L_{12}(z, W_{\text{wg}}, l)$], which drive magnetization dynamics (via $\tilde{\sigma}_{\text{NM}}$), which are picked up by the CPW [via $\eta(z, W_{\text{wg}})$]. It can be shown that the induced signal due to forward Amperian or SOT-driven magnetization dynamics add together in-phase with their inverse counterparts, increasing the inductive response from each contribution by a factor of 2. The inductance in Eq. (20) [and hence (21) and (22)] is therefore too small by a factor of 2. Therefore, in the below calculation of $\tilde{\sigma}_{\text{NM}}$ based on measured values of \tilde{L}_{NM} , we include this factor.

B. Background correction

To make use of the phase and amplitude information in the VNA-FMR spectra, we first fit the raw spectra to

$$S_{21}(\omega, H_0) = A e^{i\phi} \chi_{yy}(\omega, H_0) + C_0 + C_1 H_0, \quad (23)$$

where A is the signal amplitude, ϕ is the raw phase (inclusive of signal line delay), and C_0 and C_1 are complex offset and slope corrections to the background. Utilizing the information in this complex background is key to our data processing method. The background-corrected signal can be plotted from the measured values of S_{21} as

$$\Delta S_{21}(\omega, H_0) = \frac{S_{21}(\omega, H_0) - (C_0 + C_1 H_0)}{C_0 + C_1 H_0}. \quad (24)$$

This corrects the signal phase for the finite length of the signal line between the VNA source and receiver ports and the sample, effectively placing the ports at the sample position. Additionally, it normalizes the signal amplitude by the frequency-dependent losses due to the complete microwave circuit (cables + CPW + sample). In Figs. 2(a) and 2(b), we plot the raw and de-embedded data, respectively. The large complex offset on top of which the resonance signal is superimposed in (a) represents C_0 and C_1 .

Comparison of Eqs. (23) and (24) shows that the change in microwave transmission can be written as

$$\Delta S_{21}(\omega, H_0) = \frac{A e^{i\phi}}{C_0 + C_1 H_0} \chi_{yy}(\omega, H_0). \quad (25)$$

Using this form for the background-corrected ΔS_{21} , the inductance amplitude $\tilde{L}(f)$ is calculated as $[\Delta S_{21}/\chi_{yy}(\omega, H_0)][i2Z_0/(2\pi f)]$. When \tilde{L} is plotted versus frequency as in Fig. 4, we note that there can be a small phase error that causes $\text{Im}(\tilde{L})(f \rightarrow 0) \neq 0$. The correction for this phase error is discussed in Ref. [23].

C. Calculation of $\tilde{\sigma}_{\text{NM}}$ from measured L

Using the results for $\text{Re}(\tilde{L})$ and $\text{Im}(\tilde{L})$ [Eqs. (21) and (22)], we can isolate the $\tilde{\sigma}_{\text{NM}}$ contribution as follows. First, the slope

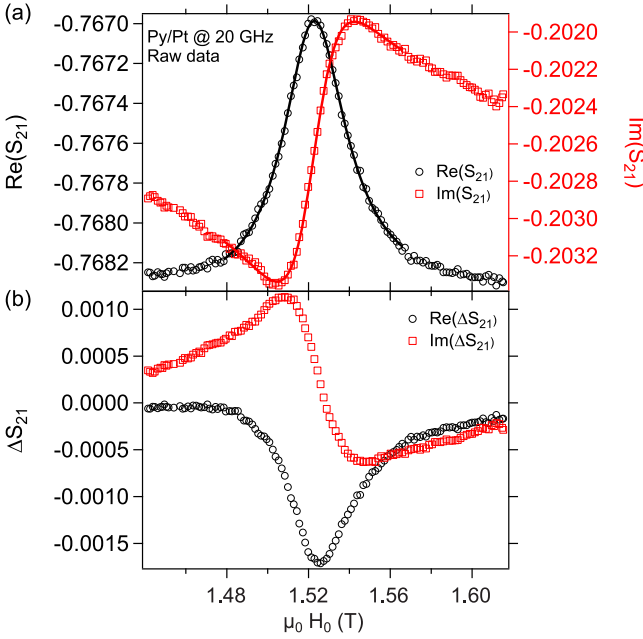


FIG. 2. Example S_{21} spectrum, acquired at $f = 20.0$ GHz. (a) Raw data, with fits. Note the different background offsets of the Re and Im data (left and right axes). (b) De-embedded ΔS_{21} signal.

of \tilde{L} is used to isolate the contribution of \tilde{L}_{NM} :

$$\frac{d\tilde{L}}{df} = -\frac{1}{2} \text{sgn}(\hat{z} \cdot \hat{n}) \eta(z, W_{\text{wg}}) \frac{L_{12}(z, W_{\text{wg}}, l)}{M_s} \times \frac{h}{e} [(\sigma_e^{\text{F}} - \sigma_e^{\text{SOT}}) + i\sigma_o^{\text{SOT}}]. \quad (26)$$

We normalize $d\tilde{L}/df$ by \tilde{L}_0 in order to remove any residual differences in sample-CPW coupling from sample to sample. Variation in \tilde{L}_0 (e.g., as seen in Fig. 4) can be caused by sample-to-sample variations in magnetization, including dead layer effects at the various FM/NM interfaces, as well as measurement-to-measurement variations in the sample-waveguide spacing, which could be affected by small dust particles in the measurement environment. Finally, we solve for the effective conductivity:

$$\begin{aligned} & [(\sigma_e^{\text{F}} - \sigma_e^{\text{SOT}}) + i\sigma_o^{\text{SOT}}] \\ &= -\text{sgn}(\hat{z} \cdot \hat{n}) \left(\frac{d\tilde{L}}{df} \right) \frac{\mu_0 l}{2\tilde{L}_0} \frac{M_s d_{\text{FM}}}{W_{\text{wg}}} \eta(z, W_{\text{wg}}) \frac{e}{h}. \end{aligned} \quad (27)$$

We note that in Eq. (27), the inductance quantities $d\tilde{L}/df$ and \tilde{L}_0 are experimentally measured values as determined from ΔS_{21} by application of Eq. (9), while the remaining terms follow from normalization of the right-hand side of Eq. (26) with that of Eq. (10).

D. Analysis protocol

Our quantitative VNA-FMR analysis protocol is summarized as follows [32]. (1) Complex VNA-FMR data are collected and fit with Eq. (23). (2) ΔS_{21} is calculated with Eq. (25) to de-embed the sample contribution to the inductance.

(3) ΔS_{21} is converted to sample inductance L using Eq. (9). (4) L is normalized by magnetic susceptibility χ_{yy} , yielding the complex inductance amplitude given by Eqs. (21) and (22) [$\text{Re}(\tilde{L})$ and $\text{Im}(\tilde{L})$]. (5) The phase error of \tilde{L} is corrected as described in Ref. [23]. (6) Linear fits of $\tilde{L}(\omega)$ [using Eqs. (21) and (22)] are used to extract \tilde{L}_0 and $\tilde{L}_{\text{NM}}(\omega)$. (7) The effective conductivities σ_o^{SOT} and $(\sigma_e^{\text{F}} - \sigma_e^{\text{SOT}})$ are obtained from $(\partial\tilde{L}/\partial f)/\tilde{L}_0$ according to Eq. (27).

IV. DATA AND ANALYSIS

To demonstrate the quantitative VNA-FMR technique, we measured FMR in metallic stacks consisting of substrate/Ta(1.5)/Py(3.5)/NM/Ta(3) and inverted stacks of substrate/Ta(1.5)/NM/Py(3.5)/Ta(3) (where the numbers in parentheses indicate thickness in nanometers). We focus on a Pt(6) NM layer due to its large intrinsic SOC, and use Cu(3.3) as a control material with nominally negligible SOC [19,33,34]. We collected room-temperature FMR spectra as a function of out-of-plane external magnetic field H_0 with microwave frequencies from 5 GHz to 35 GHz and VNA output power of 0 dBm. Exemplary $\text{Re}(\Delta S_{21})$ spectra are shown in Fig. 3. Each raw spectrum has been normalized by the complex signal background (see Sec. III B). In the following discussion, we use a notation for the bilayers which indicates the sample growth order as read from left to right. For example, Py/Pt indicates Py is first deposited onto the substrate, followed by Pt.

Both Py/Cu and Cu/Py samples exhibit a mostly real normalized inductance amplitude [symmetric Lorentzian dip for $\text{Re}(\Delta S_{21})$ in Figs. 3(a) and 3(b)] with a magnitude largely independent of frequency, in accordance with $\tilde{L}_{\text{NM}} \approx 0$. That is, the signal is dominated by the dipolar inductance. In contrast, the lineshape and magnitude of the Py/Pt and Pt/Py data in Figs. 3(c) and 3(d) exhibit a clear frequency dependence as expected for $\tilde{L}_{\text{NM}} \neq 0$. In particular, the data for Py/Pt indicate that \tilde{L}_{NM} adds constructively with L_0 , such that $\text{Re}(\tilde{L})$ increases with increasing f . The Pt/Py inductance evolves in an opposite sense due to the stack inversion, leading to a decrease and eventual compensation of $\text{Re}(\tilde{L})$ at high f . The increasingly antisymmetric lineshape for both Py/Pt and Pt/Py reveals that the magnitude of $\text{Im}(\tilde{L})$ also increases with frequency, with a sign given by the stacking order.

By normalizing the spectra in Fig. 3 to the magnetic susceptibility $\chi(\omega, H_0)$ defined in Eq. S2, we extract the complex inductance amplitude \tilde{L} . $\text{Re}(\tilde{L})$ and $\text{Im}(\tilde{L})$ are shown in Fig. 4 for all investigated bilayers with a length l of 8 mm. As shown in Eqs. (21) and (22), $\text{Re}(\tilde{L})$ provides information about the dipolar inductance (\tilde{L}_0 , zero-frequency intercept), and $-(\sigma_e^{\text{F}} - \sigma_e^{\text{SOT}})$ (slope). Similarly, the slope of $\text{Im}(\tilde{L})$ reflects $-\sigma_o^{\text{SOT}}$. Immediately evident is the reversal of the slope for Py/Pt compared to Pt/Py, which is captured by the sgn function (where \hat{n} is the FM/NM interface normal, pointing into the FM, and \hat{z} is defined by the coordinate system in Fig. 1). This sign-reversal is consistent with the phenomenology expected for interface-symmetry sensitive effects, e.g., combined spin pumping and iSHE, as well as iREE. There is also a marked difference in the slope magnitude for Py/Pt

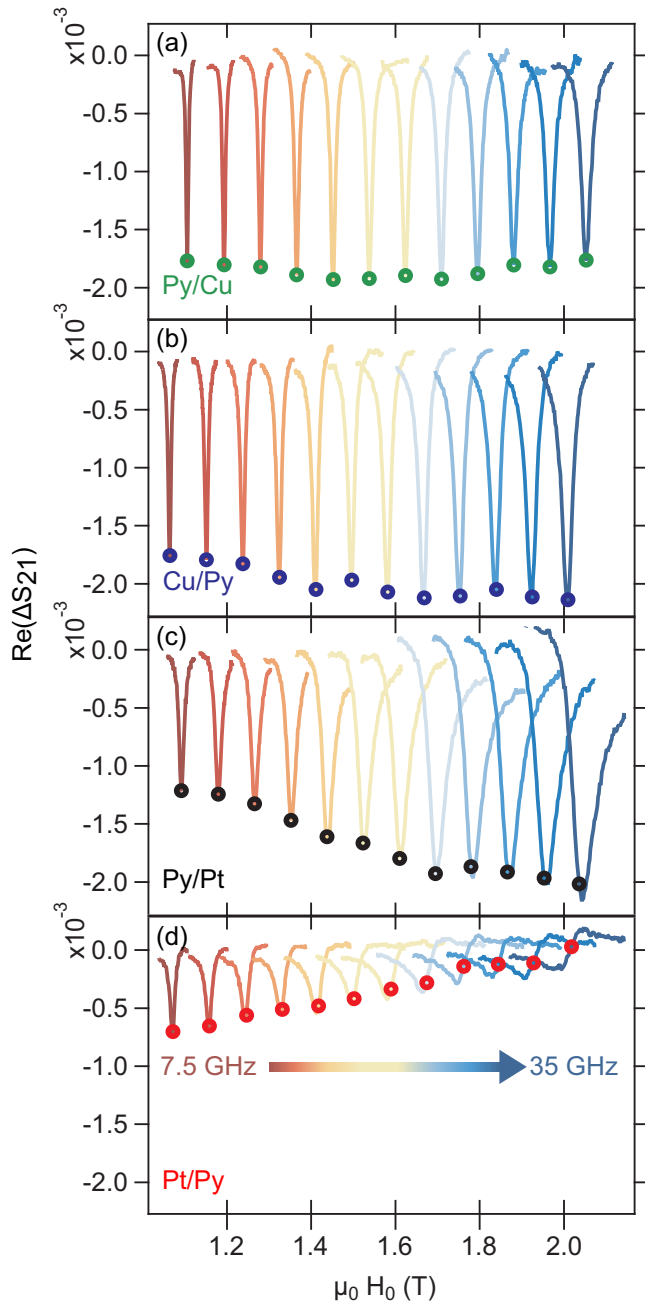


FIG. 3. FMR spectra for FM/NM bilayers. $\text{Re}(\Delta S_{21})$ at several excitation frequencies for different samples: (a) Py/Cu, (b) Cu/Py, (c) Py/Pt, and (d) Pt/Py. The change in line shape and amplitude for Py/Pt and Pt/Py clearly shows the presence of frequency-dependent inductive terms not present in the Py/Cu and Cu/Py control samples. The colored circles indicate the value of $\text{Re}(\Delta S_{21}) \propto \text{Re}(L)$ when H_0 satisfies the out-of-plane FMR condition.

and Pt/Py in panel (b), the implications of which are discussed below.

Each of the inductance terms has some dependence on sample length: linear for the dipolar contribution, and slightly nonlinear for the inductances due to charge flow in the NM [see Eqs. (10) and (11)]. We therefore repeated the measurements shown in Fig. 4 for a variety of sample lengths from 4 to 10 mm. Figure 5 shows the measured inductance terms \tilde{L}_0 ,

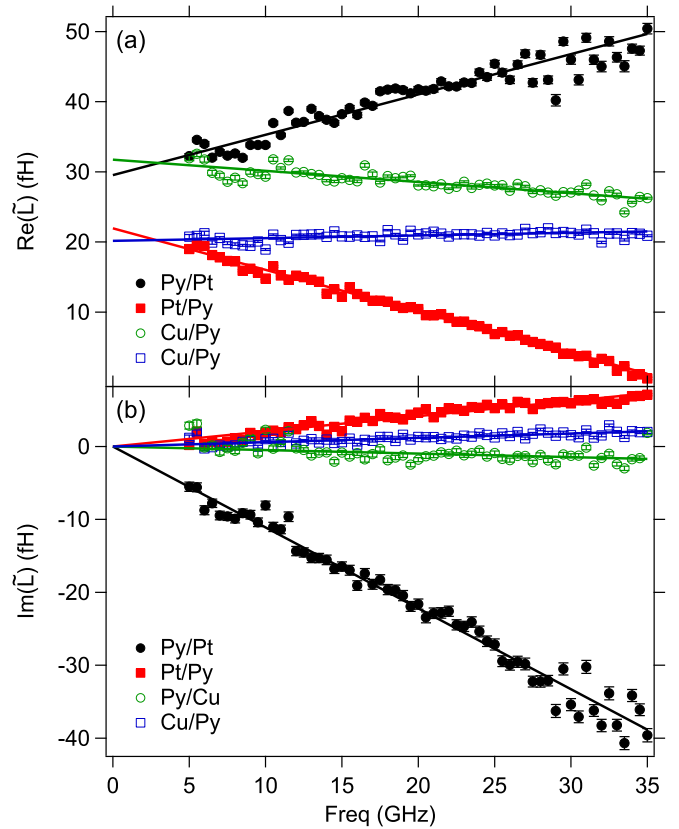


FIG. 4. Frequency dependence of real and imaginary inductances extracted from S_{21} spectra (symbols) and fits to Eqs. (21) and (22) (lines). (a) $\text{Re}(\tilde{L})$ for all samples with $l = 8$ mm. Zero-frequency intercept indicates the dipolar inductive coupling, while the linear slope reflects $(\sigma_e^F - \sigma_e^{\text{SOT}})$. (b) $\text{Im}(\tilde{L})$ for all samples, as a function of frequency, where the linear slope is governed by σ_0^{SOT} .

$\partial \text{Re}(\tilde{L}) / \partial f$ [intercept and slope of curves in Fig. 4(a)], and $\partial \text{Im}(\tilde{L}) / \partial f$ [slope of curves in Fig. 4(b)] as a function of sample length. Following normalization by its corresponding \tilde{L}_0 , each data point in Fig. 5(b) provides a value of $(\sigma_e^F - \sigma_e^{\text{SOT}})$ [see Eq. (27)]. Similarly, data points in panel (c) provide values of σ_0^{SOT} . These values are averaged to provide a single $(\sigma_e^F - \sigma_e^{\text{SOT}})$ and σ_0^{SOT} for each sample type. Results are summarized in Table I. The dashed lines in Figs. 5(b) and 5(c) are calculated curves based on these average values and the length dependence of \tilde{L} .

Because σ_e^{SOT} and σ_e^F have the same phase and frequency dependence, we use control samples where we replace the Pt with Cu, wherein it is generally accepted that both the SHE for Cu and the REE at the Py/Cu interface are negligible [19,33,34]. Furthermore, the Cu thickness is chosen so that it exhibits the same sheet resistance as the Pt layer, so that the two samples have identical σ_e^F [see Eq. (31)]. Subtraction of the time-reversal-even conductivity for the Py/Cu control samples from the time-reversal-even conductivity for the Py/Pt samples therefore isolates σ_e^{SOT} specifically for the Py/Pt interface. Likewise, any dampinglike contributions to σ_0^{SOT} due to the Ta seed layer should also be removed by subtraction of the Py/Cu inductance data.

Additional data collected for varied NM thickness (to be presented in a future publication) indicate that the charge

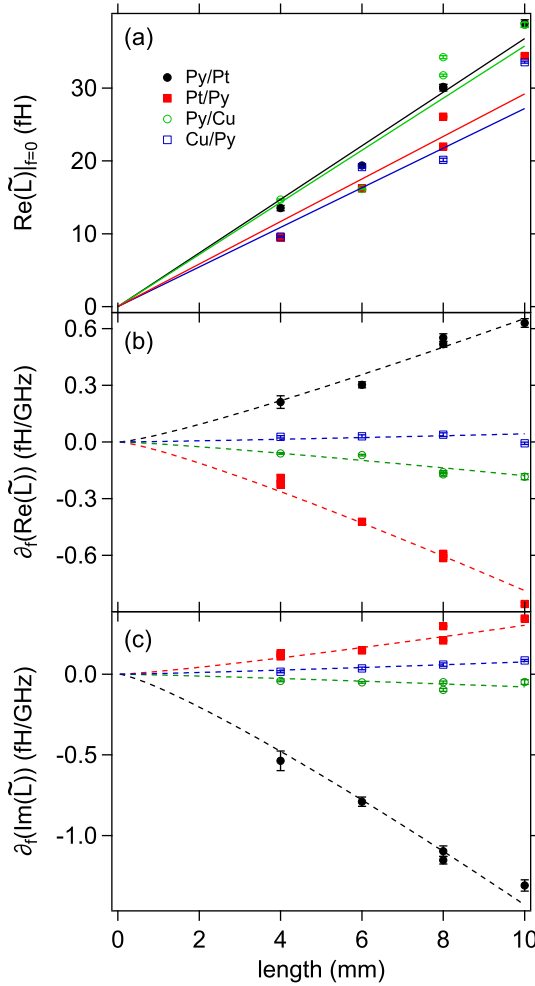


FIG. 5. $\tilde{L}(f=0)$ and $\partial\tilde{L}/\partial f$ extracted from data as in Fig. 4 vs sample length for all samples. (a) Dipolar inductive coupling \tilde{L}_0 . (b) From $\partial[\text{Re}(\tilde{L})]/\partial f$, we extract $(\sigma_e^F - \sigma_e^{\text{SOT}})$. (c) From $\partial[\text{Im}(\tilde{L})]/\partial f$, we extract σ_o^{SOT} . Dashed lines are guides based on Eqs. (21) and (22) with values of σ_o^{SOT} and $(\sigma_e^F - \sigma_e^{\text{SOT}})$ calculated as described in Sec. III C. Several measurements were repeated to demonstrate reproducibility.

currents produced by iSOT effects experience a shunting effect, whereby some fraction of the interfacial charge current flows back through the sample thickness, reducing the inductive signal. This can be modeled as a current divider with some of the iSOT-generated current coupling to the 50- Ω CPW via image currents, and the remainder shunted by the sheet conductance of the sample. Final values of the extracted conductivities reported in Table I have been corrected to account for current shunting (see Ref. [23] for more details). Comparison of the shunt-corrected SOT conductivities makes evident that the fieldlike charge currents are comparable to those due to dampinglike spin-charge conversion processes.

We can compare our measured values of σ_e^{SOT} and σ_o^{SOT} to measurements made by other groups using different techniques. Garello *et al.* [9] use the harmonic Hall technique and Miron *et al.* [2] investigate domain wall nucleation to quantify the spin-orbit torque exerted on Co sandwiched between Pt and AlO_x . Converting their measured values of fieldlike SOT

field per unit current density to our metric σ_e^{SOT} , they find 1.1×10^6 and $1.9 \times 10^7 \Omega^{-1} \text{m}^{-1}$. Nguyen *et al.* [25] find a similar value of $\approx 1.3 \times 10^6 \Omega^{-1} \text{m}^{-1}$ for a Pt/Co bilayer using harmonic Hall methods. The Garello and Nguyen results are within an order of magnitude of our findings ($-1.48 \pm 0.07 \times 10^5 \Omega^{-1} \text{m}^{-1}$ for Pt/Py and $-1.8 \pm 0.2 \times 10^5 \Omega^{-1} \text{m}^{-1}$ for Py/Pt).

Garello and Nguyen also report dampinglike values for their effective SOT fields. Converted to σ_o^{SOT} , they find $5.8 \times 10^5 \Omega^{-1} \text{m}^{-1}$ and $\approx 2.9 \times 10^5 \Omega^{-1} \text{m}^{-1}$, respectively, which are again within an order of magnitude of our values: $2.4 \pm 0.3 \times 10^5 \Omega^{-1} \text{m}^{-1}$ (Py/Pt) and $0.6 \pm 0.2 \times 10^5 \Omega^{-1} \text{m}^{-1}$ (Pt/Py).

The difference in stacking-order dependence for σ_e^{SOT} and σ_o^{SOT} may come as a surprise, since some degree of correlation between the fieldlike and dampinglike torques is suggested by intuition. However, this need not be the case if the two effects have different physical origins. As is discussed below, in the case of the dampinglike torque, the proportionality between the spin accumulation and the spin current entering or exiting the FM is given by the real part of the spin-mixing conductance. By contrast, an interfacial SOC of the Rashba form can give rise to a spin accumulation (and hence SOT) that has no dependence on the spin-mixing conductance (see, for example, the theory in by Kim *et al.* [17]). Therefore empirical observation of uncorrelated even and odd effective conductivities is not unexpected [35].

V. DISCUSSION

For comparison to previous measurements and to theory, we can relate the effective conductivities σ_e^{SOT} and σ_o^{SOT} to microscopic spin-charge conversion parameters under the assumptions that the dampinglike iSOT is due to iSHE only, and the fieldlike iSOT is from iREE only. We also relate the Faraday contribution to the ac charge currents in the NM—that is, σ_e^F —to sample properties.

A. Contributions to effective conductivity, $\tilde{\sigma}_{\text{NM}}$

1. Effective Faraday conductivity, σ_e^F

To relate the effective Faraday conductivity, σ_e^F , to sample parameters, we isolate the Faraday component of the induced charge current from Eq. (7):

$$\left[\int_{-d_{\text{NM}}}^{+d_{\text{FM}}} \mathbf{J}^F(z) dz \right] = -\text{sgn}(\hat{z} \cdot \hat{n}) \left(\frac{\hbar}{2e} \right) \sigma_e^F (\hat{z} \times \partial_t \hat{m}). \quad (28)$$

The charge current is driven by the induced electromotive force (e.m.f.), V_x , according to

$$\begin{aligned} \hat{x} \cdot \left[\int_{-d_{\text{NM}}}^{+d_{\text{FM}}} \mathbf{J}^F(z) dz \right] &= \frac{I_x}{w} \\ &= \frac{V_x}{Z_{\text{eff}} l}. \end{aligned} \quad (29)$$

The induced e.m.f. is derived from inductive reciprocity [36]

$$V_x = -\frac{\partial \phi}{\partial t} = -\mu_0 M_s \int_{V_{\text{FM}}} [\mathbf{h}(\mathbf{r}) \cdot \partial_t \hat{m}] d^3 r, \quad (30)$$

where $\mathbf{h}(\mathbf{r})$ is the magnetic sensitivity function for a current of unit amplitude in the NM layer. We assume this field can be approximated with the Karlvqvist equation, and use the results for $\partial_t \hat{m}$ from Sec. III A. Substituting Eq. (30) into Eq. (29), and equating the result with Eq. (28) yields the final expression for σ_e^F :

$$\sigma_e^F = \frac{e\mu_0 M_s d_{\text{FM}}}{\hbar Z_{\text{eff}}}. \quad (31)$$

2. Rashba parameter and σ_e^{SOT}

We can relate the even spin-orbit torque conductivity σ_e^{SOT} to the Rashba parameter α_R . We start from the fieldlike interfacial spin torque per spin \mathbf{t}_{fl} introduced by Kim *et al.* (Eq. (12) in Ref. [17]):

$$\mathbf{t}_{\text{fl}} = \text{sgn}(\hat{z} \cdot \hat{n}) k_R v_s [\hat{m} \times (\hat{j} \times \hat{z})] \left(\frac{\hbar}{2} \right), \quad (32)$$

where $k_R = 2\alpha_R m_e / \hbar^2$ is a wave vector corresponding to the Rashba energy parameter α_R , m_e is the mass of the electron, and $v_s = P J_{\text{int}} g \mu_B / (2e M_s)$ is the spin velocity, with charge current density J_{int} at the FM/NM interface at which the Rashba effect is present, spin polarization of the charge current P , Landé g -factor g , and Bohr magneton μ_B . Note that $\mathbf{t}_{\text{fl}} / (\hbar/2)$ has units of hertz; that is, the same units as $\partial_t \hat{m}$. We can therefore relate Eq. (32) to the volume-averaged magnetic torque density \mathbf{T} from Eqs. (5) and (6) through the time rate of change of the magnetization: $\mathbf{t}_{\text{fl}} d_{\text{int}} \delta(z) / (\hbar/2) = \partial_t \hat{m}$, where we have added $d_{\text{int}} \delta(z)$ to account for the interfacial nature of this torque (where d_{int} is an effective thickness of the interface):

$$\frac{2}{\hbar} \int_0^{d_{\text{FM}}} \mathbf{t}_{\text{fl}} d_{\text{int}} \delta(z) dz = -\frac{\gamma}{M_s} \int_0^{d_{\text{FM}}} \mathbf{T}(z) dz, \quad (33)$$

$$k_R v_s \hat{m} \times (\hat{j} \times \hat{z}) d_{\text{int}} = -\frac{\gamma}{M_s} \frac{\hbar}{2e} \sigma_e^{\text{SOT}} \hat{m} \times (\hat{z} \times \mathbf{E}). \quad (34)$$

The final line results from substituting Eq. (32) and the even SOT term from Eq. (6) into Eq. (33). Making the substitutions for k_R and v_s , and using $\mathbf{E} = (J_{\text{int}} / \sigma_{\text{int}}) \hat{j}$ yields

$$\alpha_R = \frac{\hbar^2}{2m_e} \frac{\sigma_e^{\text{SOT}}}{\sigma_{\text{int}}} \frac{1}{P d_{\text{int}}}. \quad (35)$$

Here, σ_{int} is the interfacial conductivity of the FM/NM interface (extracted by measuring resistance versus Py thickness; see Ref. [23]) and P is the spin polarization at the FM/NM interface. We use $P = 0.6$ as determined via spin-wave Doppler measurements in Ref. [37], and assume d_{int} is one Py lattice constant (0.354 nm) [38]. We therefore find $\alpha_R = -5.8 \pm 0.3$ meV nm for the Py/Pt sample, and -7.5 ± 0.7 meV nm for Pt/Py. These values are smaller than those measured with angle-resolved photoelectron spectroscopy (ARPES) for the surface state of Au(111) (33 meV nm) [39], Bi(111) (56 meV nm) [40], and Ge(111) (24 meV nm) [41], and much smaller than the Bi/Ag(111) interface (305 meV nm) [42].

We can also compare our results for the Rashba parameter to a recent theoretical calculation. Kim, Lee, and Stiles (KLLS) [17] have shown that SOT and the Dzyaloshinskii-Moriya interaction (DMI) at a FM/NM interface are both manifestations of an underlying Rashba Hamiltonian, and predict

a straightforward relationship between the Rashba parameter α_R , interfacial DMI strength $D_{\text{DMI}}^{\text{int}}$, and the interfacial fieldlike SOT per spin t_{fl} :

$$\alpha_R = \frac{\hbar^2}{2m_e} \left(\frac{D_{\text{DMI}}^{\text{int}}}{2A} \right) = \frac{\hbar}{m_e} \left(\frac{t_{\text{fl}}}{v_s} \right), \quad (36)$$

where A is the exchange stiffness.

For the Pt/Py stack, the ratio of interfacial DMI, $D_{\text{DMI}}^{\text{int}}$, to bulk exchange A was previously measured via a combination of Brillouin light scattering (BLS) and superconducting quantum interference device (SQUID) magnetometry for samples prepared under nearly identical growth conditions, albeit with a stack geometry that was optimized for optical BLS measurements [43]. The ratio is a constant value of -0.25 ± 0.01 nm⁻¹ over a Py thickness range of 1.3 to 15 nm. As such, this material system is an ideal candidate to test the quantitative prediction of the KLLS theory. Using the experimentally determined value for $D_{\text{DMI}}^{\text{int}}/A$ with Eq. (36) predicts a Rashba strength of -4.8 ± 0.2 meV nm, which agrees well in sign and magnitude with the result of our iSOT measurement for the Pt/Py sample of the same stacking order, as well as the Py/Pt sample with opposite stacking order. Together, the spin wave spectroscopy and iSOT measurements clarify the role of the Rashba spin-orbit interaction as the underlying physical mechanism for both DMI and fieldlike SOT in the Py/Pt system.

3. Spin Hall angle and σ_0^{SOT}

In order to develop intuition for Eq. (7), we first derive an approximate relationship between σ_0^{SOT} and the spin Hall angle, θ_{SH} , applicable when the NM thickness is much thicker than its spin diffusion length. We assume series resistors $1/G_{\uparrow\downarrow} + 1/G_{\text{ext}}$ (interfacial spin-mixing conductance + spin conductance of the NM) in a voltage divider model for the spin accumulation at the FM/NM interface due to spin pumping:

$$\mu_{\hat{s}}(z=0^+) \hat{s} = \frac{\hbar}{2} \left(\hat{m} \times \frac{\partial \hat{m}}{\partial t} \right) \left(\frac{G_{\uparrow\downarrow}}{G_{\uparrow\downarrow} + G_{\text{ext}}} \right), \quad (37)$$

where $\mu_{\hat{s}}(z=0^+)$ is the spin accumulation at the FM/NM interface. Using the result of Eq. (6) from Ref. [44] for the effective one-dimensional spin conductance of a NM (where we have set $G_2^{\text{NM}} = 0$ because we are interested in only a FM/NM bilayer, not a FM/NM1/NM2 multilayer):

$$G_{\text{ext}} = \frac{\sigma}{2\lambda_s} \tanh \left(\frac{d_{\text{NM}}}{\lambda_s} \right), \quad (38)$$

where λ_s is the spin diffusion length in the NM. The integrated charge current in the NM layer driven by the resulting spin chemical potential gradient $-\nabla \mu_{\hat{s}} = \mathbf{Q}_{\hat{s}}$ and the inverse spin Hall effect ($\mathbf{J} \propto \mathbf{Q}_{\hat{s}} \times \hat{s}$) is given by

$$\int_0^{d_{\text{NM}}} \mathbf{J}(z) dz = \int_0^{d_{\text{Pt}}} \left[\sigma_{\text{SH}} \frac{-\nabla \mu_{\hat{s}}(z)}{e} \times \hat{s} \right] dz \quad (39)$$

$$= \sigma_{\text{SH}} \frac{\mu_{\hat{s}}(z=0^+)}{e} (-\hat{z} \times \hat{s}) \quad (40)$$

assuming $d_{\text{NM}} \gg \lambda_s$. The spin Hall conductivity is related to the spin Hall angle via the Pt charge conductivity: $\sigma_{\text{SH}} = \theta_{\text{SH}} \sigma_{\text{Pt}}$. If we combine Eqs. (37), (38), and (40) and equate the integrated charge current to that from σ_0^{SOT} in Eq. (7), we arrive

at the final result:

$$\sigma_0^{\text{SOT}} = \sigma \left\{ \theta_{\text{SH}} \text{Re} \left[\frac{G_{\uparrow\downarrow}}{\frac{\sigma}{2\lambda_s} \tanh\left(\frac{d_{\text{NM}}}{\lambda_s}\right) + G_{\uparrow\downarrow}} \right] \right\} \epsilon. \quad (41)$$

The model also accounts for less-than-unity efficiency ϵ for spin transmission into the NM (such that $(1 - \epsilon)$ is the

spin loss fraction, which has been attributed to processes such as spin memory loss [45] or proximity magnetism [46]).

A more accurate version of Eq. (41) is obtained by replacing the unitless term in curly brackets with Eq. (11) from Ref. [35]:

$$\sigma_0^{\text{SOT}} = \sigma \left[\theta_{\text{SH}} \frac{(1 - e^{-d_{\text{NM}}/\lambda_s})^2}{(1 + e^{-2d_{\text{NM}}/\lambda_s})} \frac{|\tilde{G}_{\uparrow\downarrow}|^2 + \text{Re}(\tilde{G}_{\uparrow\downarrow}) \tanh^2\left(\frac{d_{\text{NM}}}{\lambda_s}\right)}{|\tilde{G}_{\uparrow\downarrow}|^2 + 2\text{Re}(\tilde{G}_{\uparrow\downarrow}) \tanh^2\left(\frac{d_{\text{NM}}}{\lambda_s}\right) + \tanh^4\left(\frac{d_{\text{NM}}}{\lambda_s}\right)} \right] \epsilon, \quad (42)$$

where $\tilde{G}_{\uparrow\downarrow} = G_{\uparrow\downarrow} 2\lambda_s \tanh(d_{\text{NM}}/\lambda_s)/\sigma$. This properly accounts for the boundary condition that the spin current goes to zero at the distant surface of the NM.

Equation (42) can be used to calculate θ_{SH} if we assume values for λ_s , $G_{\uparrow\downarrow}$, and ϵ . If these parameters are presumed identical for the two stacking orders, we would find spin Hall angles that differ by a factor of 4 depending on whether Pt is deposited on Py or vice versa. Instead, the large discrepancy in σ_0^{SOT} for the two stacking orders suggests differences in the FM/NM interface that affect $G_{\uparrow\downarrow}$ and ϵ . Indeed, stacking-order dependence of dampinglike torque has been observed in previous works [47,48]. Given the data presented here, it is possible for us to estimate the efficiency with which spins are pumped into the Pt layer as follows. The total Gilbert damping α_{tot} is the sum of intrinsic processes α_{int} , spin pumping into the Pt and Ta layers $\alpha_{\text{Pt(Ta)}}$, and possible spin memory loss α_{SML} :

$$\alpha_{\text{tot}} = \alpha_{\text{int}} + \alpha_{\text{Pt}} + \alpha_{\text{Ta}} + \alpha_{\text{SML}}. \quad (43)$$

We can apply Eq. (43) to each of the stacking orders (Py/Pt and Pt/Py) and use the damping measurements for Py/Cu and Cu/Py control samples as a measure of $\alpha_{\text{int}} + \alpha_{\text{Ta}}$ for Py/Pt and Pt/Py, respectively. We note that the total Gilbert damping for the two stacking orders differs by only 8% (see Table S2), while the odd SOT conductivity differs by a factor of 4. This suggests that the dampinglike processes contributing to σ_0^{SOT} (i.e., iSHE) add only a small amount of enhanced damping, while the majority of spin current pumped out of the FM experiences spin memory loss and is not available for iSHE conversion [45]. If we therefore assume that α_{SML} is identical for the two stacking orders, and that the difference in σ_0^{SOT} for the two stacks is due entirely to a difference in spin-mixing conductance, such that $\alpha_{\text{Pt}}(\text{Py/Pt}) = 4\alpha_{\text{Pt}}(\text{Pt/Py})$, then the resulting system of equations is solvable for $\alpha_{\text{Pt}}(\text{Py/Pt})$ and $\alpha_{\text{Pt}}(\text{Pt/Py})$, as well as α_{SML} (see Ref. [23]). Using the results, we can estimate the spin pumping efficiency factor $\epsilon \equiv \alpha_{\text{Pt}}/(\alpha_{\text{Pt}} + \alpha_{\text{SML}})$. We find that only 31% or 10% of the spin current pumped through the Pt interface is available for iSHE conversion, for Py/Pt and Pt/Py samples, respectively.

A more rigorous calculation can be done to estimate $G_{\uparrow\downarrow}$, ϵ , and θ_{SH} by simultaneously fitting Eqs. (42) and (43) for the two stacking orders [using the corrected values $(\sigma_0^{\text{SOT}})_{\text{corr}}$ from Table I and total damping values from Table S2]. To perform this optimization, we use the functional form for the spin pumping damping contributions as presented in Ref. [44], such that $\alpha_{\text{Pt(Ta)}}$ depends on λ_s , $G_{\uparrow\downarrow}$, and σ in order to implement the

spin current backflow correction. We obtained a value for the Pt charge conductivity $\sigma = 4.16 \times 10^6 \Omega^{-1} \text{m}^{-1}$ from four-probe resistance measurement on a series of Py/Pt samples with varying Pt thickness, to allow isolation of the Pt contribution to the total conductivity. Using a value of $\lambda_s = 3.4 \text{ nm}$ from Ref. [45], we obtain a spin Hall angle of $\theta_{\text{SH}} = 0.28$. This falls within the range of published values from dc spin Hall measurements (0.01–0.33) [7,12,49–55]. In good agreement with the estimate above, we find efficiencies of 34% and 18% for Py/Pt and Pt/Py, respectively. Furthermore, this optimization yields $G_{\uparrow\downarrow} = 8.9 \times 10^{14} \Omega^{-1} \text{m}^{-2}$ (for Py/Pt) and $2.3 \times 10^{14} \Omega^{-1} \text{m}^{-2}$ (for Pt/Py). Both of these values are below the Sharvin conductance [56] ($G_{\uparrow\downarrow} = 1 \times 10^{15} \Omega^{-1} \text{m}^{-2}$), which serves as the theoretical upper bound for the spin-mixing conductance. This result demonstrates clearly that when Py is deposited on Pt, the details of the FM/NM interface can result in significant SML and a reduced spin-mixing conductance.

Finally, we note that the contributions of iSHE and iREE may not separate neatly into dampinglike and fieldlike torques as was assumed for the above analyses. For example, a more sophisticated three-dimensional model of the Rashba effect in FM/NM bilayers has been used to demonstrate that dampinglike torques can be present and comparable to fieldlike torques [57]. This nevertheless emphasizes the utility of σ_c^{SOT} and σ_0^{SOT} without reliance on underlying assumptions or models.

VI. CONCLUSION

In summary, we have quantified both field- and dampinglike inverse spin-orbit torques in $\text{Ni}_{80}\text{Fe}_{20}/\text{Pt}$ bilayers using phase-sensitive VNA-FMR measurements and an analysis of the sample's complex inductance that arises in part from the ac currents due to spin-charge conversion. The magnitude of these currents is determined by their respective SOT conductivities, a key figure of merit for characterizing and optimizing operational spintronic devices. Because our technique entails straightforward postmeasurement data processing for an experimental technique that is well established in the field, it provides a powerful way to unpick a highly complex experimental system and represents a broadly applicable tool for studying strong SOC material systems. The technique could even be applied to previously-acquired VNA-FMR data sets in which only spectroscopic analysis was performed. The measurements presented here demonstrate that both Rashba-Edelstein and

spin Hall effects must be considered in FM/NM metallic bilayers. Together with the observation of significant variation in σ_0^{SOT} with respect to FM/NM stacking order, these results point to interfacial engineering as an opportunity for enhancing current-controlled magnetism.

ACKNOWLEDGMENTS

The authors would like to thank Mark Stiles and Mark Keller for many helpful discussions and illuminating insights. Contribution of the National Institute of Standards and Technology; not subject to copyright.

-
- [1] F. Freimuth, S. Blügel, and Y. Mokrousov, *Phys. Rev. B* **92**, 064415 (2015).
- [2] I. Mihai Miron, G. Gaudin, S. Auffret, B. Rodmacq, A. Schuhl, S. Pizzini, J. Vogel, and P. Gambardella, *Nat. Mater.* **9**, 230 (2010).
- [3] Z. Duan, A. Smith, L. Yang, B. Youngblood, J. Lindner, V. E. Demidov, S. O. Demokritov, and I. N. Krivorotov, *Nat. Commun.* **5**, 5616 (2014).
- [4] L. Liu, C.-F. Pai, Y. Li, H. W. Tseng, D. C. Ralph, and R. A. Buhrman, *Science* **336**, 555 (2012).
- [5] A. Manchon, H. C. Koo, J. Nitta, S. M. Frolov, and R. A. Duine, *Nat. Mater.* **14**, 871 (2015).
- [6] F. D. Czeschka, L. Dreher, M. S. Brandt, M. Weiler, M. Althammer, I.-M. Imort, G. Reiss, A. Thomas, W. Schoch, W. Limmer, H. Huebl, R. Gross, and S. T. B. Goennenwein, *Phys. Rev. Lett.* **107**, 046601 (2011).
- [7] M. Weiler, J. M. Shaw, H. T. Nembach, and T. J. Silva, *IEEE Magnetics Letters* **5**, 3700104 (2014).
- [8] H. L. Wang, C. H. Du, Y. Pu, R. Adur, P. C. Hammel, and F. Y. Yang, *Phys. Rev. Lett.* **112**, 197201 (2014).
- [9] K. Garello, I. M. Miron, C. O. Avci, F. Freimuth, Y. Mokrousov, S. Blügel, S. Auffret, O. Boulle, G. Gaudin, and P. Gambardella, *Nat. Nanotechnol.* **8**, 587 (2013).
- [10] C. O. Avci, K. Garello, C. Nistor, S. Godey, B. Ballesteros, A. Mugarza, A. Barla, M. Valvidares, E. Pellegrin, A. Ghosh, I. M. Miron, O. Boulle, S. Auffret, G. Gaudin, and P. Gambardella, *Phys. Rev. B* **89**, 214419 (2014).
- [11] X. Fan, H. Celik, J. Wu, C. Ni, K.-J. Lee, V. O. Lorenz, and J. Q. Xiao, *Nat. Commun.* **5**, 3042 (2014).
- [12] M. Weiler, J. M. Shaw, H. T. Nembach, and T. J. Silva, *Phys. Rev. Lett.* **113**, 157204 (2014).
- [13] L. Onsager, *Phys. Rev.* **37**, 405 (1931).
- [14] S. Ramo, J. R. Whinnery, and T. V. Duzer, *Fields and Waves in Communication Electronics*, 3rd ed. (Wiley-India, 2008).
- [15] R. M. White, *Introduction to Magnetic Recording* (IEEE Press, New York, NY, 1985).
- [16] S. Emori, U. Bauer, S.-M. Ahn, E. Martinez, and G. S. D. Beach, *Nat. Mater.* **12**, 611 (2013).
- [17] K.-W. Kim, H.-W. Lee, K.-J. Lee, and M. D. Stiles, *Phys. Rev. Lett.* **111**, 216601 (2013).
- [18] M. Schreier, G. E. W. Bauer, V. I. Vasyuchka, J. Flipse, K.-i. Uchida, Johannes Lotze, V. Lauer, A. V. Chumak, A. A. Serga, S. Daimon, T. Kikkawa, Eiji Saitoh, B. J. v. Wees, B. Hillebrands, R. Gross, and S. T. B. Goennenwein, *J. Phys. D* **48**, 025001 (2015).
- [19] E. Saitoh, M. Ueda, H. Miyajima, and G. Tatara, *Appl. Phys. Lett.* **88**, 182509 (2006).
- [20] J. C. R. Sánchez, L. Vila, G. Desfonds, S. Gambarelli, J. P. Attané, J. M. De Teresa, C. Magén, and A. Fert, *Nat. Commun.* **4**, 2944 (2013).
- [21] J. A. Katine, F. J. Albert, R. A. Buhrman, E. B. Myers, and D. C. Ralph, *Phys. Rev. Lett.* **84**, 3149 (2000).
- [22] S. Mangin, D. Ravelosona, J. A. Katine, M. J. Carey, B. D. Terris, and E. E. Fullerton, *Nat. Mater.* **5**, 210 (2006).
- [23] See Supplemental Material at <http://link.aps.org/supplemental/10.1103/PhysRevB.97.094407> for details of sample fabrication, magnetic characterization, and data analysis.
- [24] D. R. Lide, *CRC Handbook of Chemistry and Physics*, 84th ed. (CRC Press, Boca Raton, FL, 2003).
- [25] M.-H. Nguyen, D. C. Ralph, and R. A. Buhrman, *Phys. Rev. Lett.* **116**, 126601 (2016).
- [26] D. Wei, M. Obstbaum, M. Ribow, C. H. Back, and G. Woltersdorf, *Nat. Commun.* **5**, 3768 (2014).
- [27] C. Hahn, G. de Loubens, M. Viret, O. Klein, V. V. Naletov, and J. Ben Youssef, *Phys. Rev. Lett.* **111**, 217204 (2013).
- [28] T. J. Silva, H. T. Nembach, J. M. Shaw, B. Doyle, K. Oguz, K. O'Brien, and M. Doczy, in *Metrology and Diagnostic Techniques for Nanoelectronics*, edited by Z. Ma and D. G. Seiler (Pan Stanford, Singapore, 2016).
- [29] J. C. Mallinson, *The Foundations of Magnetic Recording* (Academic, San Diego, CA, 2012).
- [30] E. B. Rosa, *The Self and Mutual Inductances of Linear Conductors* (US Department of Commerce and Labor, Bureau of Standards, 1908).
- [31] M. L. Schneider, J. M. Shaw, A. B. Kos, T. Gerrits, T. J. Silva, and R. D. McMichael, *J. Appl. Phys.* **102**, 103909 (2007).
- [32] PYTHON code to execute this analysis is shared publicly at https://github.com/berger156/VNA_FMR.
- [33] Y. Niimi, M. Morota, D. H. Wei, C. Deranlot, M. Basletic, A. Hamzic, A. Fert, and Y. Otani, *Phys. Rev. Lett.* **106**, 126601 (2011).
- [34] J. Sinova, S. O. Valenzuela, J. Wunderlich, C. Back, and T. Jungwirth, *Rev. Mod. Phys.* **87**, 1213 (2015).
- [35] P. M. Haney, H.-W. Lee, K.-J. Lee, A. Manchon, and M. D. Stiles, *Phys. Rev. B* **87**, 174411 (2013).
- [36] T. Wessel-Berg and H. Bertram, *IEEE Trans. Magn.* **14**, 129 (1978).
- [37] M. Zhu, C. L. Dennis, and R. D. McMichael, *Phys. Rev. B* **81**, 140407 (2010).
- [38] P. M. Haney, H.-W. Lee, K.-J. Lee, A. Manchon, and M. D. Stiles, *Phys. Rev. B* **88**, 214417 (2013).
- [39] H. Cercellier, C. Didiot, Y. Fagot-Reverat, B. Kierren, L. Moreau, D. Malterre, and F. Reinert, *Phys. Rev. B* **73**, 195413 (2006).
- [40] Y. M. Koroteev, G. Bihlmayer, J. E. Gayone, E. V. Chulkov, S. Blügel, P. M. Echenique, and P. Hofmann, *Phys. Rev. Lett.* **93**, 046403 (2004).
- [41] K. Yaji, Y. Ohtsubo, S. Hatta, H. Okuyama, K. Miyamoto, T. Okuda, A. Kimura, H. Namatame, M. Taniguchi, and T. Aruga, *Nat. Commun.* **1**, 17 (2010).

- [42] C. R. Ast, J. Henk, A. Ernst, L. Moreschini, M. C. Falub, D. Pacilé, P. Bruno, K. Kern, and M. Gioni, *Phys. Rev. Lett.* **98**, 186807 (2007).
- [43] H. T. Nembach, J. M. Shaw, M. Weiler, E. Jué, and T. J. Silva, *Nat. Phys.* **11**, 825 (2015).
- [44] C. T. Boone, H. T. Nembach, J. M. Shaw, and T. J. Silva, *J. Appl. Phys.* **113**, 153906 (2013).
- [45] J.-C. Rojas-Sánchez, N. Reyren, P. Laczkowski, W. Savero, J.-P. Attané, C. Deranlot, M. Jamet, J.-M. George, L. Vila, and H. Jaffrès, *Phys. Rev. Lett.* **112**, 106602 (2014).
- [46] M. Caminale, A. Ghosh, S. Auffret, U. Ebels, K. Ollefs, F. Wilhelm, A. Rogalev, and W. E. Bailey, *Phys. Rev. B* **94**, 014414 (2016).
- [47] Y. Ou, S. Shi, D. C. Ralph, and R. A. Buhrman, *Phys. Rev. B* **93**, 220405 (2016).
- [48] V. Vlaminc, J. E. Pearson, S. D. Bader, and A. Hoffmann, *Phys. Rev. B* **88**, 064414 (2013).
- [49] M. Isasa, E. Villamor, L. E. Hueso, M. Gradhand, and F. Casanova, *Phys. Rev. B* **91**, 024402 (2015).
- [50] O. Mosendz, V. Vlaminc, J. E. Pearson, F. Y. Fradin, G. E. W. Bauer, S. D. Bader, and A. Hoffmann, *Phys. Rev. B* **82**, 214403 (2010).
- [51] M. Morota, Y. Niimi, K. Ohnishi, D. H. Wei, T. Tanaka, H. Kontani, T. Kimura, and Y. Otani, *Phys. Rev. B* **83**, 174405 (2011).
- [52] L. Liu, T. Moriyama, D. C. Ralph, and R. A. Buhrman, *Phys. Rev. Lett.* **106**, 036601 (2011).
- [53] M. Weiler, M. Althammer, M. Schreier, J. Lotze, M. Pernpeintner, S. Meyer, H. Huebl, R. Gross, A. Kamra, J. Xiao, Y.-T. Chen, H. J. Jiao, G. E. W. Bauer, and S. T. B. Goennenwein, *Phys. Rev. Lett.* **111**, 176601 (2013).
- [54] M. Obstbaum, M. Hürtinger, H. G. Bauer, T. Meier, F. Swientek, C. H. Back, and G. Woltersdorf, *Phys. Rev. B* **89**, 060407(R) (2014).
- [55] C.-F. Pai, Y. Ou, L. H. Vilela-Leão, D. C. Ralph, and R. A. Buhrman, *Phys. Rev. B* **92**, 064426 (2015).
- [56] Y. Liu, Z. Yuan, R. J. H. Wesselink, A. A. Starikov, and P. J. Kelly, *Phys. Rev. Lett.* **113**, 207202 (2014).
- [57] K.-W. Kim, K.-J. Lee, J. Sinova, H.-W. Lee, and M. D. Stiles, *Phys. Rev. B* **96**, 104438 (2017).

Correction: A sign error has been fixed in an inline equation in Sec. III A 2, in the second paragraph after Eq. (20).