

Parity-Broken Chiral Spin Dynamics in $\text{Ba}_3\text{NbFe}_3\text{Si}_2\text{O}_{14}$

M. Loire,¹ V. Simonet,¹ S. Petit,² K. Marty,^{1,3} P. Bordet,¹ P. Lejay,¹ J. Ollivier,⁴ M. Enderle,⁴ P. Steffens,⁴ E. Ressouche,⁵ A. Zorko,^{6,7} and R. Ballou^{1,*}

¹Institut Néel, CNRS and Université Joseph Fourier, BP166, 38042 Grenoble Cedex 9, France

²Laboratoire Léon Brillouin, CEA-CNRS, CE-Saclay, F-91191 Gif sur Yvette, France

³Oak Ridge National Laboratory, Oak Ridge, Tennessee 37831, USA

⁴Institut Laue Langevin, BP156, 38042 Grenoble Cedex 9, France

⁵Institut de Nanosciences et Cryogénie, SPSMS/MDN, CEA-Grenoble, 38054 Grenoble Cedex 9, France

⁶“Jožef Stefan” Institute, Jamova 39, 1000 Ljubljana, Slovenia

⁷EN → FIST Centre of Excellence, Dunajska 156, SI-1000 Ljubljana, Slovenia

(Received 21 September 2010; revised manuscript received 22 December 2010; published 16 May 2011)

The spin-wave excitations emerging from the chiral helically modulated 120° magnetic order in a langasite $\text{Ba}_3\text{NbFe}_3\text{Si}_2\text{O}_{14}$ enantiopure crystal were investigated by unpolarized and polarized inelastic neutron scattering. A dynamical fingerprint of the chiral ground state is obtained, singularized by (i) spectral weight asymmetries answerable to the structural chirality and (ii) a full chirality of the spin correlations observed over the whole energy spectrum. The intrinsic chiral nature of the spin waves' elementary excitations is shown in the absence of macroscopic time-reversal symmetry breaking.

DOI: 10.1103/PhysRevLett.106.207201

PACS numbers: 75.30.Ds, 75.25.-j, 75.40.Gb, 75.50.Ee

Ubiquitous in nature, chirality is what distinguishes a phenomenon from its materialization in a mirror [1]. Condensed matter physics and especially magnetism provide a rich playground to investigate this phenomenon as it appears naturally to describe the arrangement of magnetic moments in noncollinear magnets. The chirality accounts there for the sense of rotation of the spins on moving along an oriented line. The latter can be a straight line around which the spins form a helix, or an oriented loop, for instance a triangle, at the summits of which the spins are orientated at 120° of each other (see Fig. 1). For such coplanar spin configurations, it can be uniquely characterized on a bond connecting two consecutive spins \vec{S}_i and \vec{S}_j by the parity-breaking vector product $\vec{\chi}_{ij} = \vec{S}_i \wedge \vec{S}_j$, defining the magnetic vector chirality. As far as domains of opposite chiralities are equipopulated, the chirality is usually averaged to zero in centrosymmetric magnets. However, neutron scattering evidenced a pure chiral phase in noncentrosymmetric compounds [2,3], as for instance the $\text{Ba}_3\text{NbFe}_3\text{Si}_2\text{O}_{14}$ langasite (BNFS) [4]. While these studies focused on the ground state properties, the way the associated excited states inherit from the chiral properties remains an open issue. In this Letter, we address this question, investigating the spin dynamics in a BNFS single crystal by means of polarized neutron scattering. Our study provides evidence for a fully chiral spin excitation spectrum over the whole energy range. Chiral dynamics was already evidenced in a variety of magnetic materials [5–11], but we emphasize that these studies were carried out under a magnetic field, revealing the chirality through a macroscopic breaking of the time-reversal symmetry. In the BNFS case, the chiral dynamics is observed in zero field, thus ascribable solely to the space inversion symmetry breaking. To our knowledge, this has never been reported before.

The langasite BNFS presents static chirality properties [4,12,13] hereafter briefly recalled. It crystallizes in the acentric space group P321 which confers the compound a *structural chirality* denoted $\epsilon_T = +(-)1$ for right- (left-) handedness. The magnetic carriers are the Fe^{3+} ions ($S = 5/2, L = 0$), arranged on small triangle units (trimers) whose centers form triangular lattices perpendicular to the trigonal c axis (see Fig. 1). A magnetic order sets in below the Néel temperature $T_N = 27$ K with spins lying in the (a, b) plane and with the same 120° configuration on each trimer. This arrangement is helically modulated along the c axis with the period $1/\tau \approx 7$ (see Fig. 4 of Ref. [4]). This magnetic order exhibits a single chirality of the helical order (named helicity), denoted ϵ_H , and a single triangular chirality, denoted ϵ_Δ (see Fig. 1). We note that $\vec{\chi}_{ij} = S^2 \sin(2\pi\tau)\epsilon_H \hat{c}$ for consecutive spins along c and $\sum_{\Delta\cup}\vec{\chi}_{ij} = (3\sqrt{3}/2)S^2\epsilon_\Delta \hat{c}$ for the spins of an oriented triangle, with ϵ_H and ϵ_Δ equal to $+1(-1)$ for the right- (left-) handed sense of rotation.

According to [14,15], polarized inelastic neutron scattering can probe the dynamical spin chirality. This extends the concept of static chirality to the dynamics by following

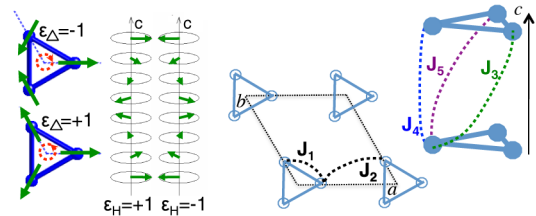


FIG. 1 (color online). From left to right: The two triangular chiralities $\epsilon_\Delta = \pm 1$, the two helicities $\epsilon_H = \pm 1$, and the magnetic exchange paths J_1 – J_5 in BNFS.

the orientation changes during coherent motions of spins in space and time. Its statistical average is proportional to the antisymmetric off-diagonal dynamical magnetic susceptibility [16,17]. We thus conducted experiments on the triple-axis spectrometer IN20 at the ILL (France) in its polarized neutron setup, with polarizing Heusler crystals as monochromator and analyzer. We used the CRYOPAD device, to obtain strict zero-field environment at the sample position, and to prepare incoming and outgoing neutron polarization independently. $E_f = 14.7$ meV was kept fixed yielding an energy resolution of ≈ 1 meV, and second order contaminations were removed by a PG(002) filter. The crystal, aligned with $(0, k, \ell)$ as scattering plane, was cooled down to 1.5 K in an Orange cryostat. Different cross sections were measured, $\sigma_{\uparrow\uparrow}$, $\sigma_{\uparrow\downarrow}$, and $\sigma_{\downarrow\uparrow}$, where the subscripts indicate the incoming or outgoing neutron polarization parallel \uparrow or antiparallel \downarrow to the scattering vector \vec{Q} . Additional cross sections were measured at selected points in \vec{Q} and energy transfers $\hbar\omega$, allowing us to separate the magnetic signal from background, and to verify that phonon and incoherent scattering are negligible in the investigated region. $\sigma_{\uparrow\uparrow}$ could therefore be used as background above ≈ 1.5 meV. The magnetic dynamical structure factor was then obtained by $S(\vec{Q}, \omega) = \frac{1}{2\pi\hbar} \int \langle M_y(\vec{Q}, 0)M_y(-\vec{Q}, t) + M_z(\vec{Q}, 0)M_z(-\vec{Q}, t) \rangle e^{-i\omega t} dt = (\sigma_{\uparrow\downarrow} + \sigma_{\downarrow\uparrow})/2 - \sigma_{\uparrow\uparrow}$ and the chiral magnetic dynamical scattering by $C(\vec{Q}, \omega) = \frac{1}{2\pi\hbar} \int \langle M_y(\vec{Q}, 0)M_z(-\vec{Q}, t) - M_z(\vec{Q}, 0)M_y(-\vec{Q}, t) \rangle e^{-i\omega t} dt = (\sigma_{\uparrow\downarrow} - \sigma_{\downarrow\uparrow})/2$. Here, $M_{y,z}(\vec{Q}, t)$ are the Fourier transformed spin components at time t perpendicular to \vec{Q} within (y) or perpendicular (z) to the scattering plane.

To get first a global overview of the spin waves, an experiment using unpolarized neutrons was performed on the time-of-flight spectrometer IN5 at the ILL on a single crystal in rotation around the vertical zone axis a [18]. The incident wavelength was fixed to 4 Å, the chopper speed to 16000 rpm, yielding an elastic energy resolution ≈ 0.1 meV. Standard corrections and a background (high temperature scan) subtraction were performed. The data were then reduced with the Horace suite software [19] to obtain the excitation spectra as function of (\vec{Q}, ω) .

Figure 2 summarizes our inelastic unpolarized neutron scattering results obtained on IN5. Two spin-wave branches emerging from the $\pm\tau$ magnetic satellites are identified [20]. They form delicate arches, with different maximum energies (lower branch clearly visible on IN5, maximum of the upper branch only observable on IN20). One of the branches is gapped with a minimum at around 0.4 meV whereas the other branch is found ungapped down to the resolution (0.1 meV). A first unusual observation is the difference of intensities of the excitations emerging from the $\pm\tau$ satellites associated to a node of the reciprocal lattice. This effect strongly depends on the considered reciprocal lattice node and is clearly visible for instance

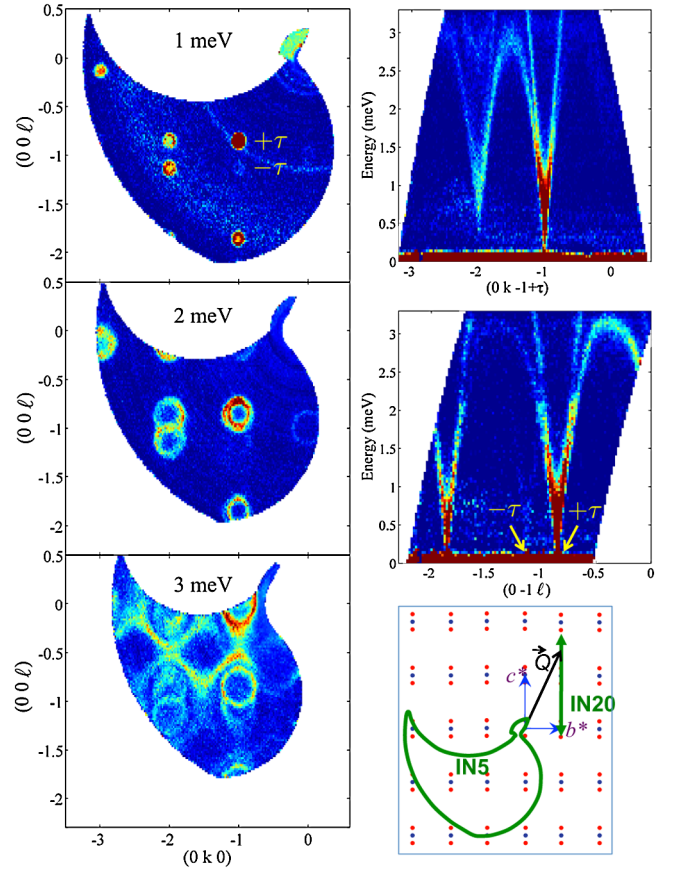


FIG. 2 (color online). Inelastic neutron scattering intensities at 1.6 K in the (b^*, c^*) scattering plane on the time-of-flight spectrometer IN5. Displayed are intensity maps at constant transfer energy (energy cuts) and intensity maps along $(0, k, -1 + \tau)$ and $(0, -1, \ell)$ lines in the reciprocal space (\vec{Q} cuts). In the bottom right-hand sketch, the green outlined area and arrow show the probed reciprocal vectors on the IN5 and IN20 spectrometers.

around $(0, -1, -1)$ in Fig. 2. This is a signature of the structural chirality as detailed below.

Figure 3 gathers our inelastic polarized neutrons scattering results of IN20. Energy scans at constant \vec{Q} were performed for different ℓ values along $(0, 1, \ell)$ with ℓ ranging from $-\tau = -\frac{1}{2}$ to 1.7 (see sketch in Fig. 2). The magnetic scattering $S(\vec{Q}, \omega)$ [light gray (red) lines in Figs. 3(a)–3(d)] confirms the magnetic origin of the two modes, although they are not as well separated as on IN5, due to the lower energy resolution. By extracting the chiral contribution $C(\vec{Q}, \omega)$ [in dark gray (blue)], it is found that the lower mode is achiral [$C(\vec{Q}, \omega) = 0$] whereas the upper mode has finite chirality [see Figs. 3(d) and 3(e)]. In addition, $C(\vec{Q}, \omega)$ is positive and has a tendency to become negative for negative ℓ [compare Figs. 3(a) and 3(c) at low energy]. This change of sign is due to the fact that the neutron probes the moment component perpendicular to \vec{Q} , $C(\vec{Q}, \omega)$ corresponding then to the projection of the Fourier transformed dynamical chirality onto \vec{Q} . This result actually perfectly reflects a globally unchanged chirality of the

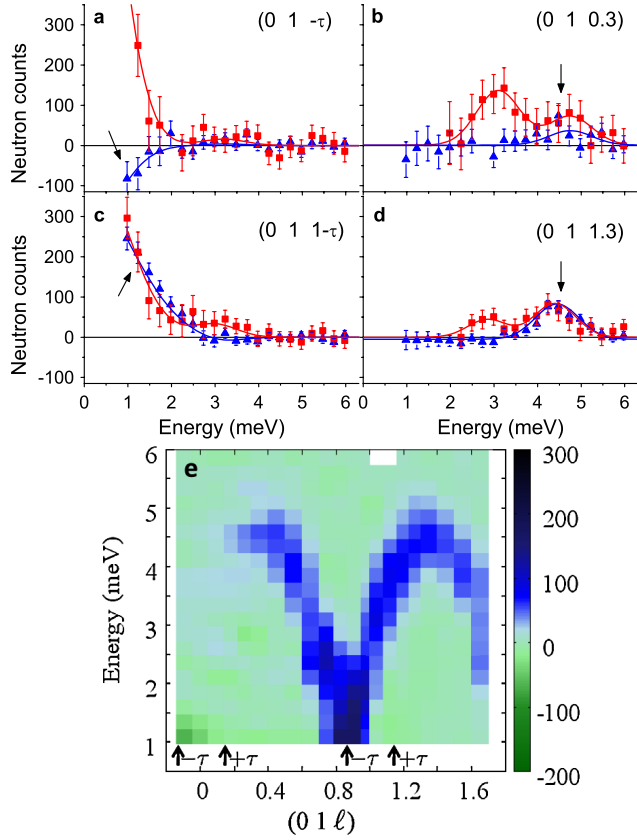


FIG. 3 (color online). (a)–(d) Magnetic scattering $S(\vec{Q}, \omega)$ [light gray (red)] and chiral contribution $C(\vec{Q}, \omega)$ [dark gray (blue)] as a function of the transfer energy at selected scattering wave vectors $(0, 1, \ell)$, extracted at 1.5 K by longitudinal neutron polarimetry on the triple-axis spectrometer IN20. The spectral weight is only significant for the branch emerging from the $-\tau$ magnetic satellites. (e) Dispersion of the chiral scattering $C(\vec{Q}, \omega)$ obtained by gathering the measurements at all ℓ .

upper branch all the way up to the maximum of the dispersion. At large ℓ values, $C(\vec{Q}, \omega)$ equals the amplitude of $S(\vec{Q}, \omega)$ [see Fig. 3(d)], pointing at a full chirality of the upper branch without chirality mixing.

To shed light on this remarkable result, a characterization of the ground state can be done from a careful analysis of the spin waves. We propose a model, based on mean-field calculations, that accounts qualitatively for the magnetic order [4] (see Fig. 1). The in-plane 120° spin arrangement is first stabilized by antiferromagnetic intratrimer J_1 and intertrimer J_2 interactions within the (a, b) planes. Next, three interplane interactions, J_3 – J_5 , connect each moment to the 3 moments of the upper or lower trimer along the c axis. The acentric structure imposes different J_3 and J_5 , oppositely twisted around c . The dominant one drives the helical modulation according to the structural chirality ($J_5 > J_3, J_4$ for $\epsilon_T = -1$ and $J_3 > J_4, J_5$ for $\epsilon_T = +1$). The two weakest interactions allow tuning the periodicity τ of the helix. This model implies that the magnetic and structural chiralities are related ($\epsilon_\Delta = \epsilon_T \epsilon_H$): for the investigated crystal, $\epsilon_T = -1$ is observed

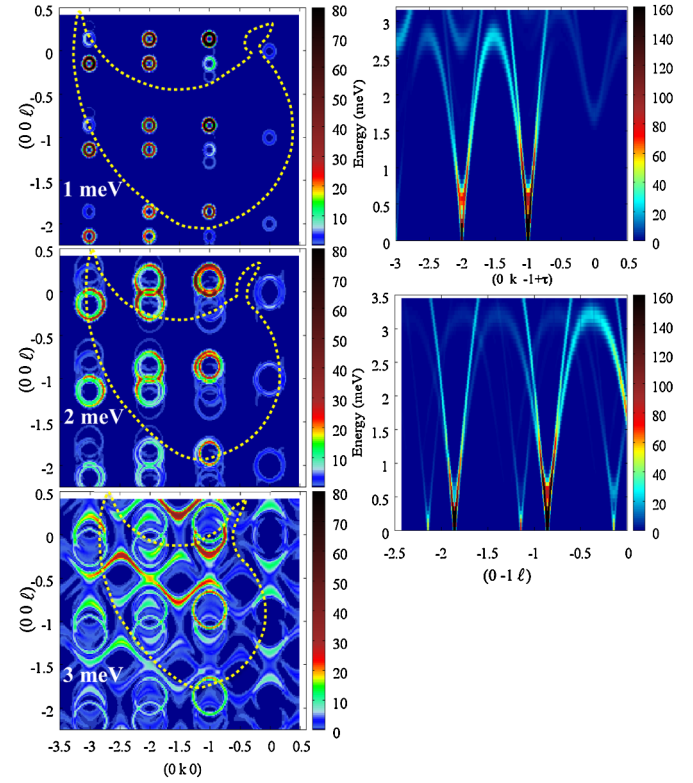


FIG. 4 (color online). Dynamical structure factor calculated in the linear approximation from the minimal model (see text) to compare with the measurements of Fig. 2.

(strong J_5), imposing opposite senses of rotation for the helicity and the triangular chirality. We are left with two different solutions (out of four) for the magnetic chiralities ($\epsilon_H = +1, \epsilon_\Delta = -1$) and ($\epsilon_H = -1, \epsilon_\Delta = +1$). The observed ultimate selection of a single magnetic chirality was proposed [4] to originate from the antisymmetric Dzyaloshinskii-Moriya (DM) exchange interaction $\vec{D} \cdot (\vec{S}_i \times \vec{S}_j)$ with \vec{D} the DM vector, allowed in the absence of inversion symmetry center between spins \vec{S}_i and \vec{S}_j . It suffices to consider the DM interaction inside the trimer with the same DM vector along the c axis for the three bonds [21]. This favors planar spin components, and its sign selects a triangular chirality ϵ_Δ , and hence a helicity ϵ_H since $\epsilon_\Delta = \epsilon_T \epsilon_H$.

Using the standard Holstein-Primakov formalism in the linear approximation [22], we computed $S(\vec{Q}, \omega)$ and $C(\vec{Q}, \omega)$ at zero temperature. As shown by the comparison of Figs. 2 and 4, a good agreement between experiment and calculation is achieved with the exchange parameters (in meV) $J_1 = 0.85 \pm 0.1$, $J_2 = 0.24 \pm 0.05$, $J_3 = 0.053 \pm 0.03$, $J_4 = 0.017$, and $J_5 = 0.24 \pm 0.05$ and a DM vector along c of $\approx 1\%|J_1|$. The latter was checked to produce the lower branch gap and to select a triangular chirality [23]. J_3, J_4, J_5 were constrained to fulfill the $\tau = 1/7$ conditions, and the set of best parameters yields a Curie-Weiss temperature of 191 K, within less than 10% of the values obtained from susceptibility measurements

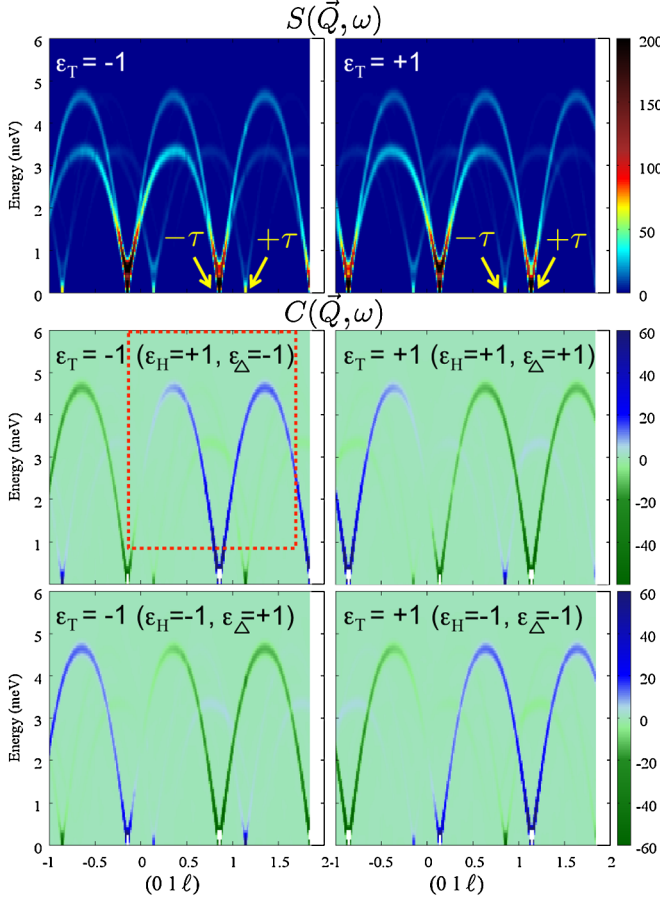


FIG. 5 (color online). Top: Computed magnetic scattering for the two structural chiralities $\epsilon_T \pm 1$. Below each of them, computed chiral contribution for the 2 associated magnetic ground states ($\epsilon_H, \epsilon_\Delta = \epsilon_H \epsilon_T$). The dotted red frame points out the calculation agreeing with the experiment in Fig. 3(e).

[4,24]. Other models have been proposed from spin-wave measurements in BNFS, but they fail in reproducing all the features revealed in our measurements [25,26]. Interestingly, as shown by the calculations in Fig. 5, $S(\vec{Q}, \omega)$ reflects the structural chirality: the asymmetric spectral weight of the branches emerging from the $+\tau$ and $-\tau$ satellites is inverted for $\epsilon_T = \pm 1$. On the other hand, for a given ϵ_T , $S(\vec{Q}, \omega)$ does not depend on ϵ_Δ . The two corresponding magnetic ground states yield, however, $C(\vec{Q}, \omega)$ with opposite sign (see Fig. 5). $S(\vec{Q}, \omega)$ and $C(\vec{Q}, \omega)$ therefore provide us with a strong dynamical fingerprint of the ground state chirality. Finally, the calculated chiral scattering for ($\epsilon_H = +1, \epsilon_\Delta = -1$) reproduces very well the measurements of Fig. 3: its sign, the absence of chirality of the lower branch, and the full chirality of the upper branch. The calculated correlation functions show that the spin components involved are along a and b for the upper branch, and only along c for the lower branch, which yields a zero spin cross product and explains the absence of chirality.

In summary, the spin waves' excitation modes emerging from the totally chiral magnetic order in a structurally

enantiopure single crystal of BNFS are singular. A spectral asymmetry is evidenced by inelastic unpolarized neutron scattering as a fingerprint of the crystal chirality. In addition, the use of polarized neutrons and polarization analysis led to the discovery that the spin waves with in-plane spin correlations are fully chiral at all energies. Chiral dynamics was predicted from spin-waves calculation for a Heisenberg triangular antiferromagnet with unbalanced domains of opposite triangular chirality [17]. This condition is obviously realized with a single chirality domain in BNFS. However, the absence of chirality mixing of the spin dynamics is not only observed close to the magnetic satellites as calculated [17] but up to the maximum of the dispersion branches (≈ 4.8 meV). It finally will be emphasized that the crystal was in a strictly zero magnetic field (even Earth's magnetic field is excluded from it) during the experiment on IN20. This establishes the observation of a dynamical chirality unbiased by macroscopic time-reversal symmetry breaking.

This work was financially supported by the ANR 06-BLAN-01871. We would like to thank B. Canals and A. Ralko for fruitful discussions, and A. Hadj-Azzem, J. Balay, and J. Debray for the sample preparation.

*rafik.ballou@grenoble.cnrs.fr

- [1] G. H. Wagnière, *On Chirality and the Universal Asymmetry* (Wiley VCH, Zürich, 2007).
- [2] M. Ishida *et al.*, *J. Phys. Soc. Jpn.* **54**, 2975 (1985).
- [3] M. Janoschek *et al.*, *Phys. Rev. B* **81**, 094429 (2010).
- [4] K. Marty *et al.*, *Phys. Rev. Lett.* **101**, 247201 (2008).
- [5] B. Roessli *et al.*, *Phys. Rev. Lett.* **88**, 237204 (2002).
- [6] D. Grohol *et al.*, *Nature Mater.* **4**, 323 (2005).
- [7] V. P. Plakhty *et al.*, *Physica (Amsterdam)* **385B**, 288 (2006).
- [8] H. Braun *et al.*, *Nature Phys.* **1**, 159 (2005).
- [9] R. M. Moon, T. Riste, and W. C. Koehler, *Phys. Rev.* **181**, 920 (1969).
- [10] S. W. Lovesey and G. I. Watson, *J. Phys. Condens. Matter* **10**, 6761 (1998).
- [11] A. Gukasov, *Physica (Amsterdam)* **267B**, 97 (1999).
- [12] K. Marty *et al.*, *J. Magn. Magn. Mater.* **321**, 1778 (2009).
- [13] K. Marty *et al.*, *Phys. Rev. B* **81**, 054416 (2010).
- [14] M. Blume, *Phys. Rev.* **130**, 1670 (1963).
- [15] S. V. Maleyev, V. G. Bar'yakhtar, and R. A. Suris, *Fiz. Tverd. Tela (Leningrad)* **4**, 3461 (1962).
- [16] S. V. Maleyev, *Phys. Rev. Lett.* **75**, 4682 (1995).
- [17] A. V. Syromyatnikov, *Phys. Rev. B* **71**, 144408 (2005).
- [18] J. Ollivier *et al.*, *Neutron News* **21**, 22 (2010).
- [19] T. G. Perring *et al.* (unpublished).
- [20] Less intense modes are also detected dispersing from the $\pm 2\tau$ satellites and from the nodes of the reciprocal lattice.
- [21] T. Moriya, *Phys. Rev.* **120**, 91 (1960).
- [22] T. Holstein and H. Primakoff, *Phys. Rev.* **58**, 1098 (1940).
- [23] A magnetocrystalline anisotropy and a symmetry-allowed component of the intratriangle DM vector along the bond connecting two spins were also considered without further improving the neutron data interpretation.
- [24] H. D. Zhou *et al.*, *Chem. Mater.* **21**, 156 (2009).
- [25] C. Stock *et al.*, *Phys. Rev. B* **83**, 104426 (2011).
- [26] H. D. Zhou *et al.*, *Phys. Rev. B* **82**, 132408 (2010).