

Rheology of Ring Polymer Melts: From Linear Contaminants to Ring-Linear Blends

Jonathan D. Halverson,¹ Gary S. Grest,² Alexander Y. Grosberg,³ and Kurt Kremer^{1,*}

¹Max Planck Institute for Polymer Research, Ackermannweg 10, 55128 Mainz, Germany

²Sandia National Laboratories, Albuquerque, New Mexico 87185, USA

³Department of Physics, New York University, 4 Washington Place, New York, New York 10003, USA

(Received 8 July 2011; published 18 January 2012)

Ring polymers remain a challenge to our understanding of polymer dynamics. Experiments are difficult to interpret because of the uncertainty in the purity and dispersity of the sample. Using both equilibrium and nonequilibrium molecular dynamics simulations we have investigated the structure, dynamics, and rheology of perfectly controlled ring-linear polymer blends of chains of up to about 14 entanglements per chain, comparable to experimental systems. Linear contaminants increase the zero-shear viscosity of a ring polymer melt by about 10% around one-fifth of their overlap concentration. For equal concentrations of linear and ring polymers, the blend viscosity is about twice that of the pure linear melt. The diffusion coefficient of the rings decreases dramatically, while the linear polymers are mostly unaffected. Our results are supported by a primitive path analysis.

DOI: 10.1103/PhysRevLett.108.038301

PACS numbers: 83.80.Tc, 82.35.Lr, 83.10.Rs, 83.80.Sg

While much has been learned about linear and branched polymers [1,2], a comparable understanding of ring or cyclic polymers is lacking. Ring polymers, as they do not have free ends, represent the simplest model system where reptation is completely suppressed. Also, mitochondrial and plasmid DNA are usually cyclic, and melts of rings are considered highly relevant model systems used to understand chromatin folding in the cell nucleus [3,4]. This makes ring polymers perfect test cases for both fundamental polymer and biophysics.

Early experimental studies on pure ring polymer melts gave inconsistent results, most likely because the samples were contaminated with linear chains [5–7]. Also the existence of self-knots could not be controlled. More recently experiments have been conducted [8] based on new characterization and purification techniques [9,10]. For melts of nonconcatenated polystyrene rings with molecular weight (MW) to entanglement MW ratios of 9.2 and 11.3, where the entanglement MW is 17 500 g/mol, Kapnistos *et al.* [8] reported that the stress relaxation modulus $G(t)$ follows a power-law decay with no sign of a rubbery plateau. The authors used scaling arguments to show $G(t) \sim t^{-2/5}$, a result in agreement with the data up to the terminal time. Milner and Newhall [11] introduced the “diffusion of centrality” concept and mapped the ring conformations to annealed treelike structures and found a similar prediction of $G(t) \sim t^{-1/2}$. Kapnistos *et al.* [8] also reported that the smallest concentration of linear contaminants that affects the rheology of the ring melt is almost two decades below the overlap concentration of the linear chains. Despite the synthetic effort, the characterization and control of the experimental systems including polydispersity, knotting, concatenation, and linear contaminants is far from perfect. Because of this, computer simulations of optimized models, which by now easily reach effective

experimental molecular weights, are perfect to test concepts for precisely defined systems under well-controlled conditions. Our own recent simulations [12] of a melt of nonconcatenated and unknotted ring polymers have shown that $G(t) \sim t^{-\alpha}$ with α decreasing from 0.5 to 0.45 with increasing chain length.

Here we employ molecular dynamics (MD) simulations to study the structure, dynamics, and rheology of ring-linear polymer blends of equal chain length. We consider two lengths of $N = 200$ and 400 monomers per chain. For the model used here the entanglement length of a melt of linear polymers is $N_e = 28 \pm 1$ [13] which corresponds to $N/N_e \approx 7.1$ and 14.3 entanglements per chain. For this a bond bending potential ($k_\theta = 1.5\epsilon$) along the chains is introduced, leading to a Kuhn length of $l_k \approx 2.79\sigma$ [13], where ϵ and σ are the energy and length scales, respectively. N_e is determined by a primitive path analysis [13,14], which is known to yield N_e values which properly reproduce rheological data [15,16]. In our systems, all rings are perfectly monodisperse, unknotted, and nonconcatenated, thus allowing for a rather stringent test of various concepts currently discussed in the literature. Previous simulations of such mixtures have only considered short chain lengths and did not measure any rheological properties [17,18]. While different polymer melts can be related to each other by the N/N_e ratio, we note that for the present comparison to experiment [8] also the ratio of the Kuhn length and the packing length l_k/p are not that different, namely, 6.5 for our simulation model [13] and 3.8 for a polystyrene melt [19].

The topological constraint that a ring must remain unknotted and nonconcatenated leads to nontrivial behavior even for the static properties of a melt or concentrated solution of rings. Rings are found to be approximately Gaussian at short chain lengths, while for larger lengths

the nonconcatenation dominates the conformational statistics. Cates and Deutsch [20] conjectured that the exponent in the mean-square gyration radius, $\langle R_g^2 \rangle \sim N^{2\nu}$, should be less than $\nu = 1/2$ and greater than $1/3$ and used a simple free energy argument to arrive at a value of $2/5$, which was later supported by simulation [21,22] and experiment [23] for systems with less than 13 entanglements per chain. However, for larger rings a scaling of $\langle R_g^2 \rangle \sim N^{2/3}$ has been shown [24–26]. Altogether we expect a smooth crossover from a Gaussian regime ($\nu = 1/2$) via a regime with $\nu = 2/5$ for rings of length of a few N_e to the “crumpled globule” regime ($\nu = 1/3$) for rings significantly exceeding N_e . The universal scaling behavior of $\langle R_g^2(N) \rangle$ for a pure ring polymer melt is demonstrated in Fig. 1 using results from many different simulations. Only short-chain atomistic data for polyethylene [27] deviate from the curve [28]. From $N/N_e \approx 15$ the onset of the collapsed regime is clearly observed in agreement with the predictions of Vettorel *et al.* [24].

We present new MD simulations using the same semiflexible bead-spring model [29] as in our previous work [12,26]. The production runs were carried out using LAMMPS [30] with a time step of 0.01τ , τ being the time scale, and an overall monomer density of $\rho = 0.85/\sigma^3$. The largest simulations ran in parallel on 2048 Blue Gene/P cores. Systems studied range from $\phi_{\text{linear}} \equiv M_{\text{linear}}/(M_{\text{linear}} + M_{\text{rings}}) = 0$ to 1, where M is the number of chains of a given architecture. For $N = 200$ the total number of chains ranged from 200–260 while for $N = 400$ the systems were composed of 200–400 chains. The initial configuration for each blend system with $\phi_{\text{linear}} \leq 0.115$ was created by adding linear chains at random locations

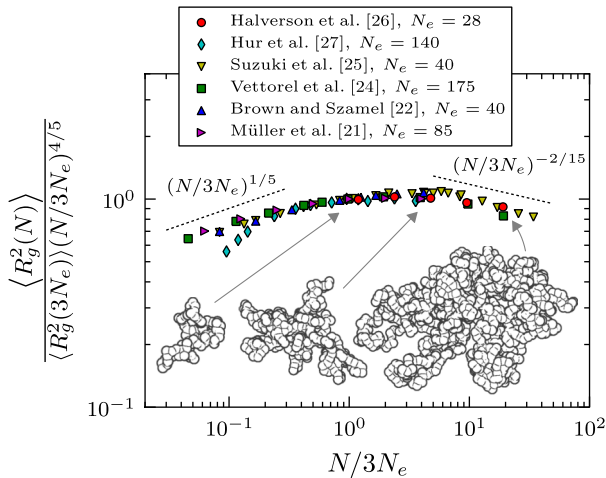


FIG. 1 (color online). Universal behavior of $\langle R_g^2(N) \rangle$ for pure ring polymer melts. The data were obtained using different simulation methods and different models. The reference line with slope $1/5$ corresponds to the Gaussian regime while that with a slope of $-2/15$ corresponds to the collapsed regime. Representative conformations from Ref. [26] are shown.

within an equilibrated ring melt configuration. Chains which most closely matched a Gaussian chain were taken from an equilibrated pure linear melt. For the cases with $\phi_{\text{linear}} \approx 0.25$ and 0.5 the appropriate number of rings were randomly removed while for the case with $M_{\text{rings}} = 10$ and $M_{\text{linear}} = 250$, rings were taken from an equilibrated pure ring melt and inserted into a linear melt making sure that the nonconcatenation constraint was observed. Because these insertions lead to monomers being very nearly overlapping, a short simulation was carried out for 100τ while limiting the bead displacement at every step to 0.001σ . During this short run the box size was increased linearly so as to give the correct density at the final step. This procedure produces nonequilibrated starting configurations. Long MD simulations of $4\text{--}8 \times 10^7\tau$ were performed to equilibrate each system where each architecture moved at least twice its root-mean-square gyration radius and in some cases more than 20 times this value.

Results for the mean-square gyration radius for the rings and linear chains normalized by their respective pure melt values are shown in Fig. 2(a). For the rings with $N = 200$, $\langle R_g^2 \rangle$ is found to increase with increasing linear concentration. At $\phi_{\text{linear}} \approx 0.96$, $\langle R_g^2 \rangle = 45.3 \pm 2.2\sigma^2$, which is 1.5 times larger than the value of the pure ring melt. For a Gaussian ring $\langle R_g^2 \rangle = Nl_k l/12 = 45.2\sigma^2$, where l is the average bond length. For the rings with $\phi_{\text{linear}} \approx 0.96$ the static structure function scales as $S(q) \sim q^{-2}$ for $2\pi/\langle R_g^2 \rangle^{1/2} < q < 2\pi/l_k$, even though the rings cannot sample the whole conformational space of a Gaussian ring [31]. For the $N = 400$ systems a similar swelling behavior is found for the rings. The linear chains are found to be Gaussian for all combinations of N and ϕ_{linear} . At small values of ϕ_{linear} the rings are partially collapsed as discussed above. As the fraction of linear chains increases, the size of the rings grows because it is entropically favorable for the linear chains to thread the rings. At infinite dilution the nonconcatenation constraint vanishes and the rings are found to be multiply threaded and nearly Gaussian [17,31,32].

The diffusion coefficients D , which are determined by the long-time behavior of the mean-square displacement of the center-of-mass of the chains, are shown in Fig. 2(b). The diffusivity of the rings for both values of N is found to steadily decrease with increasing fraction of linear chains until a dramatic decrease is observed. With the overlap concentration of linear chains being $c^* = \phi_{\text{linear}}^* \rho = N/(4/3)\pi\langle R_g^2 \rangle^{3/2}$, this transition corresponds to approximately $0.1\rho = 1.5c^*$ for $N = 200$ and $0.04\rho = 0.9c^*$ for $N = 400$. For $N = 400$ the diffusion coefficient of the rings at $\phi_{\text{linear}} = 0.5$ is reduced by a factor of about 75 compared to the pure ring melt. While the linear chains clearly restrict the motion of the rings, the motion of the linear chains for both values of N is largely independent of the blend composition, which is consistent with early experimental results [33].

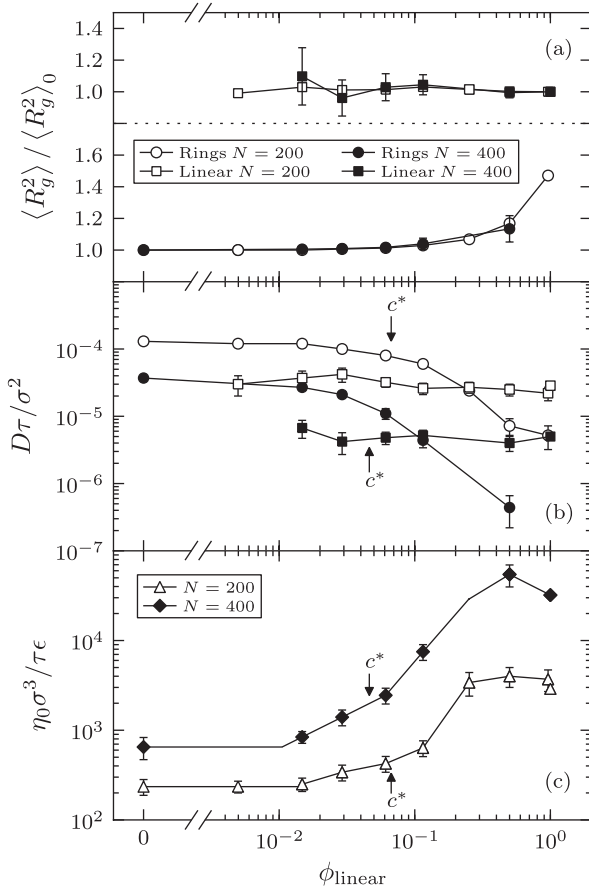


FIG. 2. (a) Mean-square gyration radii, (b) diffusion coefficients, and (c) zero-shear viscosity versus ϕ_{linear} . The overlap concentration of linear chains c^* is indicated for the two values of N . For the rings with $N = 200$ and 400 , $\langle R_g^2 \rangle_0 = 30.8$ and $52.9\sigma^2$, respectively, while for the linear chains $\langle R_g^2 \rangle_0 = 88.9$ and $180.8\sigma^2$. Note that the horizontal axis is interrupted. Lines are drawn as a guide for the eye.

Linear chains have free ends and undergo reptation independently of whether the surrounding chains are rings or linear, and accordingly their diffusion is found to be independent of ϕ_{linear} . Rings in a pure melt do not reptate like linear chains. As linear chains are added to the ring melt, the rings become threaded and the nature of their motion changes. A threaded ring can only diffuse through the release of threads. For a one-thread situation Mills *et al.* [34] have shown that the diffusion coefficient of the ring is $D \sim N_{\text{ring}}^{-1} N_{\text{linear}}^{-1}$. At high fractions of linear chains the rings become multiply threaded and their diffusion is severely hindered. In this regime the motion of a ring monomer is coupled to the motion of surrounding linear chains. This implies Rouse dynamics for the ring with a monomer relaxation time governed by the reptation relaxation of the linear chains, leading to a relaxation time scaling of $N_{\text{ring}}^2 N_{\text{linear}}^3$. This argument is due to Graessley [35] and predicts $D \sim N_{\text{ring}}^{-1} N_{\text{linear}}^{-3}$.

The zero-shear viscosity computed as $\eta_0 = \int_0^\infty G(t)dt$ is shown as a function of ϕ_{linear} in Fig. 2(c). A striking result is the clear indication that the smallest concentration at which linear contaminants alter the viscosity of a ring melt considerably (about 10%) for the chain lengths considered here is $\phi_{\text{linear}} \approx 1/100$ or $c^*/5$ with a strong increase around c^* . This threshold concentration is roughly consistent with the change in D for the rings. We have confirmed our values of η_0 by conducting nonequilibrium MD simulations [36] where simple steady shear is imposed. For these simulations a Nosé-Hoover thermostat [30,36] with a relaxation time of 10τ was used. Note that the thermal velocity is much larger than the largest velocity difference imposed by the shear. As shown in Fig. 3 for $N = 400$, when $\eta(\dot{\gamma})$ is extrapolated to $\dot{\gamma} \rightarrow 0$ the agreement with η_0 is very good [37]. Similar agreement is found for $N = 200$. For both values of N the viscosity at $\phi_{\text{linear}} = 0.5$ is larger than the viscosity at all other concentrations investigated. For the simulated blends with 14.3 entanglements per chain we find $\eta(\phi_{\text{linear}} = 0.5)/\eta_0(\phi_{\text{linear}} = 1) \approx 1.8$, where η of the blend is taken from the nonequilibrium MD simulations (cf. Figure 3) which gives a value that is still increasing slightly. These findings are in good agreement with the experimental results of Roovers [38] who showed for ring-linear blends of polybutadiene with approximately 15.3 entanglements per chain that the maximum in η_0 occurs at $\phi_{\text{linear}} = 0.6$ and $\eta_0(\phi_{\text{linear}} \approx 0.5)/\eta_0(\phi_{\text{linear}} = 1) \approx 2.2$. The viscosity results in Fig. 2(c) provide a direct macroscopic indication of the concentration of linear contaminants in experimental samples. As pointed out by Kapnistos *et al.* [8], the data also suggest how the viscosity of a linear melt may be tuned by adding ring polymers.

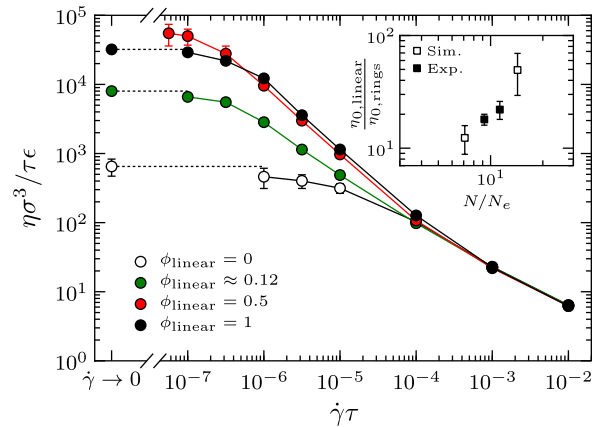


FIG. 3 (color online). Viscosity versus shear rate $\dot{\gamma}$ for $N = 400$ obtained from nonequilibrium MD simulations [36]. Zero-shear viscosities obtained from the equilibrium simulations are shown on the far left, for $\Phi_{\text{linear}} = 0, 0.12, 1$. Note that the horizontal scale is interrupted. Inset: Ratio of pure linear to pure ring melt viscosity versus number of entanglements per chain for the simulated systems and the experimental data of Refs. [8,39].

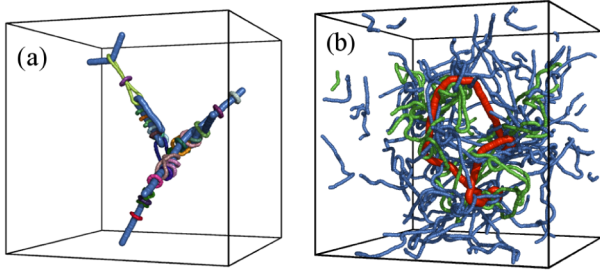


FIG. 4 (color online). Final configurations from a primitive path analysis for $N = 400$. (a) $\phi_{\text{linear}} = 3/203 \approx 0.015$ and all three linear chains (blue, dark gray in print) are shown as well as only the rings which did not collapse to points. At this low concentration of linear chains on average 86% of the rings are found to be unthreaded. (b) $\phi_{\text{linear}} = 113/226 = 0.5$ and a selected ring (red, medium gray in print) is shown along with the rings (green, light gray in print) and linear chains (blue, dark gray in print) which it is either threaded by or entangled with. For clarity all other chains are not shown.

To quantify the extent of threading, a primitive path analysis [13,14] was conducted where the end monomers of the linear chains were fixed and the rings were allowed to relax freely. This procedure causes the linear chains to be pulled taut while the rings shrink towards their center with unthreaded rings collapsing to points. The time scale for the primitive path procedure is $10^3\tau$ which satisfies the condition of being equal to or faster than $\tau_e = 3200\tau$, the Rouse time of a linear chain of N_e . Averaging over 10–20 configurations incremented by $2 \times 10^6\tau$, with $N = 200$ the percentage of unthreaded rings for $\phi_{\text{linear}} \approx 0.03, 0.12, 0.25, 0.96$ is 80.0%, 30.3%, 11.7%, 0.0%, respectively. For $N = 400$ with $\phi_{\text{linear}} \approx 0.015, 0.03, 0.12, 0.5$ we find 86.0%, 59.0%, 7.0%, 0.0%, respectively. Figure 4(a) shows a final configuration for $\phi_{\text{linear}} \approx 0.015$ where the vast majority of rings are found to be unthreaded. The sensitivity of a ring melt to linear contaminants is demonstrated by the fact that the viscosity of this system is already 1.4 times larger than the pure ring melt value. Figure 4(b) shows a final configuration for $\phi_{\text{linear}} = 0.5$ where a selected ring and the polymers it is entangled with are shown. Given the large number of entanglements at this composition, the dramatic decrease in the diffusivity of the rings and the increase in the blend viscosity in comparison to the pure ring melt value are easily understood.

The present work provides a complete scan of compositions of two different ring polymer-linear polymer melts for dynamical quantities such as viscosity and chain diffusion. One striking result is that the linear contaminants start significantly affecting the ring melt viscosity at a concentration well below their overlap concentration. This simulation result is in perfect qualitative agreement with the experimental observation of Ref. [8]: according to both simulation and experiment, there is clearly an effect below the overlap concentration. However, quantitatively we detect the onset of a viscosity change (10% increase for rings

and linear chains with $N/N_e \approx 10$) at $\phi_{\text{linear}} \approx 0.01$, while Kapnistos *et al.* [8] reported a twofold viscosity increase in comparison to the “pure as currently possible rings” at a much smaller concentration of $\phi_{\text{linear}} = 0.0007$. To provide an intuitive picture of these concentrations one can estimate what would be the typical distances between chains. For $\phi_{\text{linear}} = 0.0007$ the typical distance between linear chains $(\rho/N)^{-1/3}$ would be about 66σ for $N = 200$ and 83σ for $N = 400$. The diameter $(2\langle R_g^2 \rangle^{1/2})$ of the rings is about 11σ and 15σ and of the linear chains about 19σ and 27σ , respectively. Thus two linear chains would be separated on average by about 4–5 ring diameters for $N = 200$, or by 4 ring diameters for $N = 400$. And, importantly, these rings would not be entangled since they are unconcatenated and have no free ends. At $\phi_{\text{linear}} = 0.01$, where our data indicate a 10% viscosity increase, distances and chain extensions are all rather similar. While the two works differ with respect to the onset concentration, fair agreement is found for the ratio of the pure linear melt viscosity to that of the (almost) pure ring melt as shown in the inset of Fig. 3 [8,39]. Additionally, the simulation and experimental results for the dependence of $\eta_{0,\text{linear}}/\eta_{0,\text{rings}}$ on N/N_e are consistent not only with one another, but also with the theoretical framework of Ref. [8] and our previous result [12] which suggest a power-law dependence with power close to 2.

This work significantly benefited from discussions with R. Everaers and M. Rubinstein. We also thank M. Rubinstein for additional data [39] concerning Ref. [8]. K. K. acknowledges the hospitality of the Center for Soft Matter Research at NYU where part of this work was done. Funding was provided in part by the Multiscale Materials Modeling (MMM) initiative of the Max Planck Society. This work is supported by the Laboratory Directed Research and Development program at Sandia National Laboratories. Sandia National Laboratories is a multiprogram laboratory managed and operated by Sandia Corporation, a wholly owned subsidiary of Lockheed Martin Corporation, for the U.S. Department of Energy’s National Nuclear Security Administration under Contract No. DE-AC04-94AL85000.

*kremer@mpip-mainz.mpg.de.

- [1] P. de Gennes, *Scaling Concepts in Polymer Physics* (Cornell University Press, Ithaca, 1979).
- [2] M. Doi and S.F. Edwards, *The Theory of Polymer Dynamics* (Oxford University Press, Oxford, 1986).
- [3] T. Cremer and C. Cremer, *Nat. Rev. Genet.* **2**, 292 (2001).
- [4] A. Rosa and R. Everaers, *PLoS Comput. Biol.* **4**, e1000153 (2008).
- [5] G. Hild, C. Strazielle, and P. Rempp, *Eur. Polym. J.* **19**, 721 (1983).
- [6] J. Roovers and P.M. Toporowski, *Macromolecules* **16**, 843 (1983).

- [7] G. B. McKenna, G. Hadziioannou, P. Lutz, G. Hild, C. Strazielle, C. Straupe, and P. Rempp, *Macromolecules* **20**, 498 (1987).
- [8] M. Kapnistos, M. Lang, D. Vlassopoulos, W. Pyckhou-Hintzen, D. Richter, D. Cho, T. Chang, and M. Rubinstein, *Nature Mater.* **7**, 997 (2008).
- [9] H. Pasch and B. Trathnigg, *HPLC of Polymers* (Springer, New York, 1997).
- [10] H. C. Lee, H. Lee, W. Lee, T. Chang, and J. Roovers, *Macromolecules* **33**, 8119 (2000).
- [11] S. T. Milner and J. D. Newhall, *Phys. Rev. Lett.* **105**, 208302 (2010).
- [12] J. D. Halverson, W. B. Lee, G. S. Grest, A. Y. Grosberg, and K. Kremer, *J. Chem. Phys.* **134**, 204905 (2011).
- [13] R. Everaers, S. K. Sukumaran, G. S. Grest, C. Svaneborg, A. Sivasubramanian, and K. Kremer, *Science* **303**, 823 (2004).
- [14] S. K. Sukumaran, G. S. Grest, K. Kremer, and R. Everaers, *J. Polym. Sci. B* **43**, 917 (2005).
- [15] R. S. Hoy, K. Foteinopoulou, and M. Kröger, *Phys. Rev. E* **80**, 031803 (2009).
- [16] R. Everaers, [arXiv.org/abs/1111.4895v1](https://arxiv.org/abs/1111.4895v1).
- [17] B. Iyer, A. K. Lee, and S. Shanbhag, *Macromolecules* **40**, 5995 (2007).
- [18] G. Subramanian and S. Shanbhag, *Phys. Rev. E* **77**, 011801 (2008).
- [19] L. J. Fetters, D. J. Lohse, and S. T. Milner, *Macromolecules* **32**, 6847 (1999).
- [20] M. E. Cates and J. M. Deutsch, *J. Phys. (Paris)* **47**, 2121 (1986).
- [21] M. Müller, J. P. Wittmer, and M. E. Cates, *Phys. Rev. E* **53**, 5063 (1996).
- [22] S. Brown and G. Szamel, *J. Chem. Phys.* **109**, 6184 (1998).
- [23] V. Arrighi, S. Gagliardi, A. C. Dagger, J. A. Semlyen, J. S. Higgins, and M. J. Shenton, *Macromolecules* **37**, 8057 (2004).
- [24] T. Vettorel, A. Y. Grosberg, and K. Kremer, *Phys. Biol.* **6**, 025013 (2009).
- [25] J. Suzuki, A. Takano, T. Deguchi, and Y. Matsushita, *J. Chem. Phys.* **131**, 144902 (2009).
- [26] J. D. Halverson, W. B. Lee, G. S. Grest, A. Y. Grosberg, and K. Kremer, *J. Chem. Phys.* **134**, 204904 (2011).
- [27] K. Hur, C. Jeong, R. G. Winkler, N. Lacevic, R. H. Gee, and D. Y. Yoon, *Macromolecules* **44**, 2311 (2011).
- [28] The data of Hur *et al.* [27] do not fall on the curve in this regime because polyethylene conformations are too extended as also known from linear chains.
- [29] K. Kremer and G. S. Grest, *J. Chem. Phys.* **92**, 5057 (1990).
- [30] S. J. Plimpton, *J. Comput. Phys.* **117**, 1 (1995).
- [31] N. T. Moore and A. Y. Grosberg, *Phys. Rev. E* **72**, 061803 (2005).
- [32] Y.-B. Yang, Z.-Y. Sun, C.-L. Fu, L.-J. An, and Z.-G. Wang, *J. Chem. Phys.* **133**, 064901 (2010).
- [33] S. F. Tead, E. J. Kramer, G. Hadziioannou, M. Antonietti, H. Sillescu, P. Lutz, and C. Strazielle, *Macromolecules* **25**, 3942 (1992).
- [34] P. J. Mills, J. W. Mayer, E. J. Kramer, G. Hadziioannou, P. Lutz, C. Strazielle, P. Rempp, and A. J. Kovacs, *Macromolecules* **20**, 513 (1987).
- [35] W. W. Graessley, *Adv. Polym. Sci.* **47**, 67 (1982).
- [36] M. E. Tuckerman, C. J. Mundy, S. Balasubramanian, and M. L. Klein, *J. Chem. Phys.* **106**, 5615 (1997).
- [37] In Fig. 3, η_0 is not given for the $\phi_{\text{linear}} = 0.5$ system because D for the rings is very small and an extremely long simulation time would be required to resolve $G(t)$.
- [38] J. Roovers, *Macromolecules* **21**, 1517 (1988).
- [39] M. Rubinstein (private communication).