

## Predicting a Ferrimagnetic Phase of $\text{Zn}_2\text{FeOsO}_6$ with Strong Magnetoelectric Coupling

P. S. Wang,<sup>1</sup> W. Ren,<sup>2</sup> L. Bellaiche,<sup>3</sup> and H. J. Xiang<sup>1,\*</sup>

<sup>1</sup>Key Laboratory of Computational Physical Sciences (Ministry of Education), State Key Laboratory of Surface Physics, Collaborative Innovation Center of Advanced Microstructures, and Department of Physics, Fudan University, Shanghai 200433, People's Republic of China

<sup>2</sup>Department of Physics, and International Center of Quantum and Molecular Structures, Shanghai University, Shanghai 200444, People's Republic of China

<sup>3</sup>Physics Department and Institute for Nanoscience and Engineering, University of Arkansas, Fayetteville, Arkansas 72701, USA

(Received 1 August 2014; revised manuscript received 10 November 2014; published 8 April 2015)

Multiferroic materials, in which ferroelectric and magnetic ordering coexist, are of practical interest for the development of novel memory devices that allow for electrical writing and nondestructive magnetic readout operation. The great challenge is to create room temperature multiferroic materials with strongly coupled ferroelectric and ferromagnetic (or ferrimagnetic) orderings.  $\text{BiFeO}_3$  is the most heavily investigated single-phase multiferroic to date due to the coexistence of its magnetic order and ferroelectric order at room temperature. However, there is no net magnetic moment in the cycloidal (antiferromagnetic-like) magnetic state of bulk  $\text{BiFeO}_3$ , which severely limits its realistic applications in electric field controlled memory devices. Here, we predict that  $\text{LiNbO}_3$ -type  $\text{Zn}_2\text{FeOsO}_6$  is a new multiferroic with properties superior to  $\text{BiFeO}_3$ . First, there are strong ferroelectricity and strong ferrimagnetism at room temperature in  $\text{Zn}_2\text{FeOsO}_6$ . Second, the easy plane of the spontaneous magnetization can be switched by an external electric field, evidencing the strong magnetoelectric coupling existing in this system. Our results suggest that ferrimagnetic  $3d$ - $5d$   $\text{LiNbO}_3$ -type material may therefore be used to achieve voltage control of magnetism in future memory devices.

DOI: 10.1103/PhysRevLett.114.147204

PACS numbers: 75.85.+t, 71.15.Mb, 71.15.Rf, 75.50.Gg

The highly efficient control of magnetism by an electric field in a solid may widen the bottleneck of the state-of-the-art spin-electronics technology, such as magnetic storage and magnetic random-access memory. Multiferroics [1–7], which show simultaneous ferroelectric and magnetic orderings, provide an ideal platform for the electric field control of magnetism because of the coupling between their dual order parameters. For realistic applications, one needs to design or discover room temperature multiferroic materials with strong coupled ferroelectric and ferromagnetic (or ferrimagnetic) ordering.

Perovskite-structure bismuth ferrite ( $\text{BiFeO}_3$ ) is currently the most studied room temperature single-phase multiferroic, mostly because its large polarization and high ferroelectric Curie temperature ( $\sim 820^\circ\text{C}$ ) make it appealing for applications in ferroelectric nonvolatile memories and high temperature electronics. Bulk  $\text{BiFeO}_3$  is an antiferromagnet with Néel temperature  $T_N \approx 643$  K [8]. The Fe magnetic moments order almost in a checkerboard  $G$ -type manner with a cycloidal spiral spin structure in which the antiferromagnetic (AFM) axis rotates through the crystal with an incommensurate long-wavelength period [9]. This spiral spin structure leads to a cancellation of any macroscopic magnetization. The magnetic properties of  $\text{BiFeO}_3$  thin films were found to be markedly different from those of the bulk: the spiral spin structure seems to be suppressed and a weak magnetization appears [10].

Nevertheless, the magnetization is too small for many applications [11]. In addition, an interesting low-field magnetoelectric (ME) effect at room temperature was discovered in  $Z$ -type hexaferrite  $\text{Sr}_3\text{Co}_2\text{Fe}_{24}\text{O}_{41}$  by Kitagawa *et al.* [12]. Unfortunately, the electric polarization (about  $20 \mu\text{C}/\text{m}^2$ ) induced by the spin order is too low [13].

In searching for new multiferroic compounds, the double perovskite system was proposed as a promising candidate [14,15]. The double perovskite structure  $A_2BB'O_6$  is derived from the  $ABO_3$  perovskite structure. The two cations  $B$  and  $B'$  occupy the octahedral  $B$  sites of perovskite with the rocksalt ordering. Double perovskite  $\text{Bi}_2\text{NiMnO}_6$  was successfully synthesized under high pressure, which displays the multiferroic behavior with a high ferroelectric transition temperature (485 K) but a low ferromagnetic transition temperature (140 K) [14]. Polar  $\text{LiNbO}_3$ -type (LN-type)  $\text{Mn}_2\text{FeMO}_6$  ( $M = \text{Nb}, \text{Ta}$ ) compounds were prepared at 1573 K under 7 GPa [16]. Unfortunately, the magnetic ground state of  $\text{Mn}_2\text{FeMO}_6$  is AFM with a rather low Néel temperature (around 80 K). Very recently, LN-type polar magnetic  $\text{Zn}_2\text{FeTaO}_6$  was obtained via high pressure and temperature synthesis [17]. The AFM magnetic transition temperature ( $T_N \sim 22$  K) for  $\text{Zn}_2\text{FeTaO}_6$  is also low. In a pioneering work, Ležaić and Spaldin proposed to design multiferroics based on  $3d$ - $5d$  ordered double perovskites [18]. They found that  $\text{Bi}_2\text{NiReO}_6$  and  $\text{Bi}_2\text{MnReO}_6$  are insulating and exhibit a robust

ferrimagnetism that persists above room temperature. Although coherent heteroepitaxy strain may stabilize the  $R3$  ferroelectric (FE) state, freestanding bulk of  $\text{Bi}_2\text{NiReO}_6$  and  $\text{Bi}_2\text{MnReO}_6$  unfortunately take the nonpolar  $P2_1/n$  structure as the ground state. The magnetic properties of nonpolar double perovskites  $\text{Ca}_2\text{FeOsO}_6$  [19] and  $\text{Sr}_2\text{FeOsO}_6$  [20] were also theoretically investigated. Recently, Zhao *et al.* predicted that double perovskite superlattices  $\text{R}_2\text{NiMnO}_6/\text{La}_2\text{NiMnO}_6$  ( $R$  is a rare-earth ion) exhibit an electrical polarization and strong ferromagnetic order near room temperature [21]. However, the ME coupling in these superlattices appears to be weak and the polarization to be small.

In this Letter, we predict that perovskite-derived material  $\text{Zn}_2\text{FeOsO}_6$  takes the FE LN-type structure as the ground state through a global structure searching. Similar to  $\text{Bi}_2\text{NiReO}_6$  and  $\text{Bi}_2\text{MnReO}_6$ ,  $\text{Zn}_2\text{FeOsO}_6$  exhibit a strong ferrimagnetism at room temperature. Importantly, there is a rather strong magnetic anisotropy with the easy plane of magnetization perpendicular to the FE polarization due to the presence of the significant  $3d$ - $5d$  Dzyaloshinskii-Moriya (DM) interaction. This suggests that the switching between the  $71^\circ$  or  $109^\circ$  FE domains by the electric field will cause the rotation of the magnetic easy plane. Our work therefore indicates that  $\text{Zn}_2\text{FeOsO}_6$  may be a material of choice for realizing voltage control of magnetism at room temperature.

In this work, we focus on the  $\text{Zn}_2\text{FeOsO}_6$  material derived from the cubic double-perovskite phase. It is well-known that there are several lattice instabilities including ferroelectric distortions and oxygen octahedron rotations in perovskite materials. We now examine how the double-perovskite parent phase of  $\text{Zn}_2\text{FeOsO}_6$  distorts to lower the total energy. For this purpose, we perform a global search for the lowest energy structure based on the genetic algorithm (GA) specially designed for finding the optimal structural distortion [22]. We repeat the simulations 3 times. All three simulations consistently show that the polar rhombohedral structure with the  $R3$  space group [shown in Figs. 1(b) and 1(c)] has the lowest energy for  $\text{Zn}_2\text{FeOsO}_6$ . Similar to  $\text{Zn}_2\text{FeTaO}_6$ ,  $\text{Zn}_2\text{FeOsO}_6$  with the  $R3$  structure is based on the  $R3c$  LN-type structure. Previous experiments showed that double perovskite  $A_2BB'O_6$  may adopt other structures, such as the  $P2_1/n$  [23],  $R\bar{3}$  [24], and  $C2$  structures [25]. Our density functional theory (DFT) calculations show that the  $R3$  phase of  $\text{Zn}_2\text{FeOsO}_6$  has a lower energy than the  $P2_1/n$ ,  $R\bar{3}$ , and  $C2$  structures by 0.22, 0.09, 0.45 eV/f.u., respectively. This strongly suggests that the perovskite-derived material  $\text{Zn}_2\text{FeOsO}_6$  adopts the  $R3$  structure as its ground state. This can be understood by using the tolerance factor defined for the LN-type  $ABO_3$  system. It was shown that when the tolerance factor ( $t_R = [(r_A + r_O)/\sqrt{2}(r_B + r_O)]$ , where  $r_A$ ,  $r_B$ , and  $r_O$  are the ionic radii of the  $A$ -site ion,  $B$ -site ion, and O ion) is smaller than 1, the polar  $R3c$

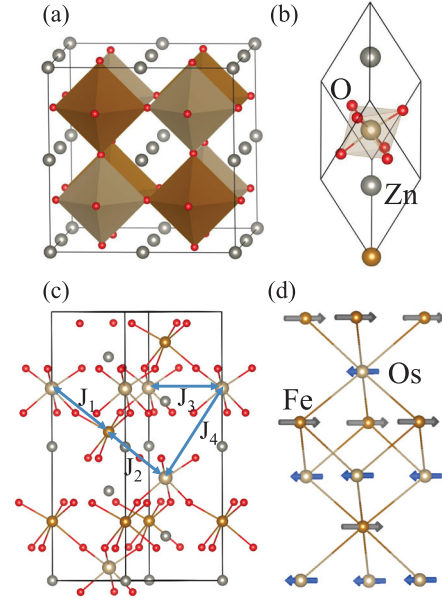


FIG. 1 (color online). (a) The ideal cubic structure of double perovskite, which is adopted as the parent phase in our GA search for the lowest energy structure of  $\text{Zn}_2\text{FeOsO}_6$ . Two different kinds of octahedra are displayed in brown and gray, respectively. (b) The primitive cell of LN-type  $\text{Zn}_2\text{FeOsO}_6$ . (c) The Fe-Os superexchange interactions mediated by the corner-sharing O ions ( $J_1$  and  $J_2$ ) and the AFM super-superexchange interaction ( $J_3$  and  $J_4$ ) between the Os ions. (d) The ferrimagnetic structure with the Fe and Os spin moments aligned in the  $ab$  plane.

structure is more stable than the  $R\bar{3}c$   $ABO_3$  structure due to the  $A$ -site instability [26]. In the case of  $\text{Zn}_2\text{FeOsO}_6$ , the average tolerance factor (0.81) is smaller than 1, which suggests that the  $R3$  structure is more stable than the nonpolar  $R\bar{3}$  structure. Note that phonon calculations shows that the  $R3$  state of  $\text{Zn}_2\text{FeOsO}_6$  is dynamically stable [27]. Additional tests indicate that the Fe and Os ions tend to order in a rocksalt manner (i.e., double perovskite configuration) to lower the Coulomb interaction energy [27,37].

Our electronic structure calculation shows that the  $R3$  phase of  $\text{Zn}_2\text{FeOsO}_6$  in the ferrimagnetic state is insulating [27]. The density of states plot shows that the Fe majority  $3d$  states are almost fully occupied, while the minority states are almost empty. This suggests that the Fe ion takes the high-spin  $\text{Fe}^{3+}$  ( $d^5$ ) valence state. It is also clear that the Os ion takes the high-spin  $\text{Os}^{5+}$  ( $d^3$ ) valence state, which contrasts with the case of  $\text{Ba}_2\text{NaOsO}_6$  where the Os atom takes a  $5d^1$  valence electron configuration [38]. This is also consistent with the total magnetic moment of  $2 \mu_B/\text{f.u.}$  for the ferrimagnetic state from the collinear spin-polarized calculation. Through the four-state mapping approach which is able to deal with spin interactions between two different atomic types [34], we compute the symmetric exchange parameters to find that the magnetic ground state of  $R3$   $\text{Zn}_2\text{FeOsO}_6$  is indeed ferrimagnetic. The Fe-Os superexchange interactions mediated by the corner-sharing

O ions [ $J_1$  and  $J_2$ , see Fig. 1(c)] are strongly AFM ( $J_1 = 31.68$  meV,  $J_2 = 29.62$  meV). Here, the spin interaction parameters are effective by setting the spin values of  $\text{Fe}^{3+}$  and  $\text{Os}^{5+}$  to 1. Our results seem to be in contradiction with the Goodenough-Kanamori rule which predicts a ferromagnetic interaction between a  $d^5$  ion and a  $d^3$  ion since the virtual electron transfer from a half filled  $\sigma$ -bond  $e$  orbital on the  $d^5$  ion to an empty  $e$  orbital on the  $d^3$  ion dominates the antiferromagnetic  $\pi$ -bonding  $t$ -electron transfer [39]. This discrepancy is because the  $\langle \text{Fe-O-Os} \rangle$  angle (about  $140^\circ$ ) in  $\text{Zn}_2\text{FeOsO}_6$  is much smaller than  $180^\circ$  (which is the case for which the Goodenough-Kanamori rule applies). The AFM super-superexchange interaction [ $J_3$  and  $J_4$ , see Fig. 1(c)] between the Os ions is much weaker ( $J_3 = 7.25$  meV,  $J_4 = 3.24$  meV) than  $J_1$  and  $J_2$ , but not negligible. Since the Fe  $3d$  orbitals are much more localized than Os  $5d$  orbitals, the super-superexchange interactions between the Fe ions are negligible. The dominance of the AFM Fe-Os exchange interactions suggests that the magnetic ground state of  $R3$   $\text{Zn}_2\text{FeOsO}_6$  should be ferrimagnetic, which is also confirmed by the Monte Carlo (MC) simulations to be discussed below.

The magnetic anisotropy in  $R3$   $\text{Zn}_2\text{FeOsO}_6$  is investigated by including spin-orbit coupling (SOC) in the DFT calculation. The DFT +  $U$  + SOC ( $U$  represents the on site Coulomb repulsion) calculation shows that the magnetic moments tend to lie in the hexagonal  $ab$  plane. Interestingly, when magnetic moments are in the  $ab$  plane, there is a spin canting between the Fe  $3d$  moments and Os  $5d$  moments. We perform a test calculation to explicitly illustrate this point. We fix the Fe spin moments along the  $x$  direction, and compute the total energies as a function of the angle ( $\alpha$ ) between Fe and Os moments. Figure 2(a) shows that the total energy has a minimum at  $\alpha_{\min} \approx 174^\circ$  and the total energy curve is asymmetric with respect to the axis of  $\alpha = 180^\circ$ . This is solely due to the SOC effect since the total energy from the DFT +  $U$  calculations has a minimum at  $\alpha = 180^\circ$ . The deviation of  $\alpha_{\min}$  by  $6^\circ$  from  $180^\circ$  implies that the magnetic moment also acquires a weak component along the  $y$  axis, which can be naturally understood by the universal law proposed in Ref. [40]. As shown in Fig. 2(b), the ferrimagnetic state with the moments along the  $c$  axis is higher in energy by  $0.55$  meV/f.u. than the ferrimagnetic state with the Fe and Os moments aligned oppositely in the  $ab$  plane ( $\alpha = 180^\circ$ ). The canting of the spins ( $\alpha = 174^\circ$ ) further lowers the total energy by  $0.97$  meV/f.u.. Therefore, the spin canting is extremely important for the easy-plane behavior.

To understand the magnetic anisotropy in  $R3$   $\text{Zn}_2\text{FeOsO}_6$ , we consider the general spin Hamiltonian [34]:  $H_{\text{spin}} = \sum_{i<j} J_{ij} \mathbf{S}_i \cdot \mathbf{S}_j + \sum_{i<j} \vec{D}_{ij} \cdot (\mathbf{S}_i \times \mathbf{S}_j) + \sum_i A_i S_{iz}^2$ , which includes symmetric exchange interactions, antisymmetric DM interactions, and single-ion anisotropy. For the magnetic structure in which the magnetic unit cell only contains one

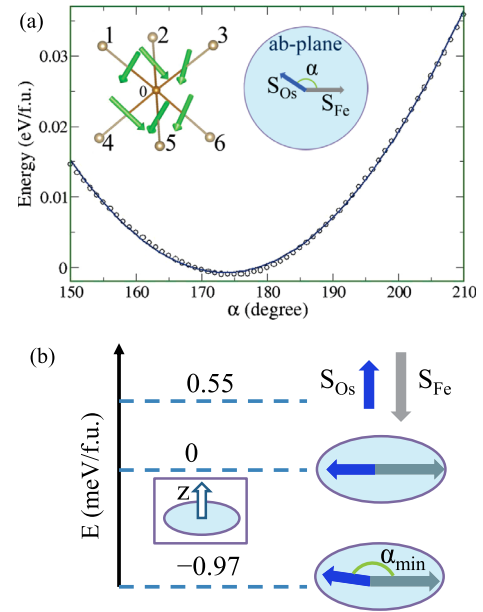


FIG. 2 (color online). (a) The total energies as a function of the angle  $\alpha$  [see the inset] from the direct DFT +  $U$  + SOC calculations (small circles). The total energy curve can be described rather well by the formula  $E_{\text{spin}} = 3(J_1 + J_2) \cos \alpha + 3(D_{01}^z + D_{04}^z) \sin \alpha$  (blue line). The insert shows the DM interaction vectors  $\mathbf{D}_{0i}$  ( $i = 1, 6$ ) between a Fe ion and six Os ions and the definition of the angle  $\alpha$  between the Fe spin and Os spin in the  $ab$  plane. (b) Relative energies between different spin configurations. The ferrimagnetic state with the moments along the  $c$  axis is higher in energy by  $0.55$  meV/f.u. than the ferrimagnetic state with the Fe and Os moments aligned oppositely in the  $ab$  plane ( $\alpha = 180^\circ$ ), and the canting of the spins ( $\alpha = 174^\circ$ ) further lowers the total energy by  $0.97$  meV/f.u.

Fe ion and one Os ion, the total spin interaction energy can be written as:

$$E_{\text{spin}} = 3(J_1 + J_2) \mathbf{S}_{\text{Fe}} \cdot \mathbf{S}_{\text{Os}} + \sum_{i=1,6} \mathbf{D}_{0i} \cdot (\mathbf{S}_{\text{Fe}} \times \mathbf{S}_{\text{Os}}) + A_{\text{Fe}} (S_{\text{Fe}}^z)^2 + A_{\text{Os}} (S_{\text{Os}}^z)^2,$$

where the DM interaction vectors  $\mathbf{D}_{0i}$  are shown in the insert of Fig. 2(a),  $A_{\text{Fe}}$  and  $A_{\text{Os}}$  are the effective single-ion anisotropy parameters. Here, the DM interactions between two different kinds of atoms are considered [41–43]. Our calculations show that  $A_{\text{Fe}} = 0.89$  meV and  $A_{\text{Os}} = -0.34$  meV, suggesting an overall weak easy-plane behavior resulting from the single-ion anisotropy term. The exchange interaction between the Os ions is omitted since it is a constant for such magnetic structure. Our analysis shows that the DM interaction results in the spin canting, and subsequently, contributes dominantly to the easy-plane anisotropy [27].

By performing the parallel tempering (PT) MC simulation using the full spin Hamiltonian (containing symmetric

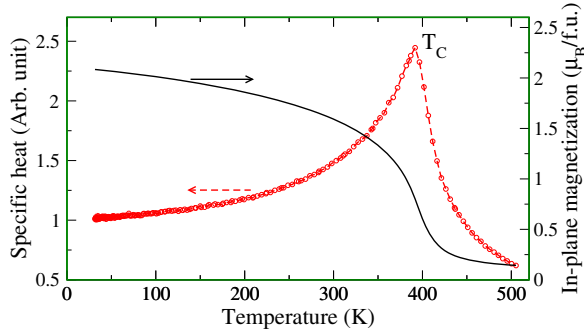


FIG. 3 (color online). The specific heat and the total in-plane spin moment ( $M_{ab}$ ) as a function of temperature from the PTMC simulations. The specific heat curve indicates that the ferrimagnetic Curie temperature ( $T_c$ ) is 394 K. The in-plane total spin moment increases rapidly near  $T_c$ .

exchange interactions, antisymmetric DM interactions, and single-ion anisotropy), we obtain the thermodynamic behavior of the magnetism in the  $R3$  phase of  $\text{Zn}_2\text{FeOsO}_6$  [32]. As shown in Fig. 3, there is a peak at 394 K in the specific heat curve, indicating that there is a magnetic phase transition at 394 K. The total spin moment ( $M_{ab}$ ) in the  $ab$  plane is also plotted as a function of temperature. We can see that the in-plane total spin moment increases rapidly near the magnetic phase transition point. This suggests that the in-plane total spin moment can be chosen as the order parameter, and the paramagnetic phase transforms to the ferrimagnetic phase with moments in the  $ab$ -plane at 394 K. We notice that the in-plane total spin moment is larger than  $2 \mu_B/\text{f.u.}$  at low temperature. This is a consequence of the spin canting resulting from the DM interactions. Our MC simulation suggests that  $R3 \text{ Zn}_2\text{FeOsO}_6$  is a room temperature ferrimagnet. Note also that test calculations show that the ferrimagnetic transition temperatures of  $\text{Zn}_2\text{FeOsO}_6$  with the low-energy phases  $R\bar{3}$  and  $P2_1/n$  are 344 and 356 K, respectively. This indicates that the effect of the ferroelectric displacement, oxygen octahedron tilts, and the associated magnetoelectric coupling on the ferrimagnetic transition temperature is rather weak and does not prevent  $\text{Zn}_2\text{FeOsO}_6$  from having a magnetic transition temperature above 300 K.

Similar to the  $\text{LiNbO}_3$  case where the paraelectric structure has the  $R\bar{3}c$  symmetry, the paraelectric state corresponding to the FE  $R3 \text{ Zn}_2\text{FeOsO}_6$  can be chosen to be  $R\bar{3}$ . Figure 4(a) shows the double well potential for  $\text{Zn}_2\text{FeOsO}_6$ . We can see that the barrier between the two FE state with opposite electric polarizations along the pseudo-cubic direction [111] is 0.09 eV/f.u., which is smaller than the value (about 0.20 eV/f.u.) in the case of  $\text{PbTiO}_3$  [44]. Taking the  $R\bar{3}$  structure as the reference structure, the electric polarization of  $R3 \text{ Zn}_2\text{FeOsO}_6$  is computed to be  $54.7 \mu\text{C}/\text{cm}^2$ , which is much higher than that ( $25.0 \mu\text{C}/\text{cm}^2$ ) in bulk tetragonal  $\text{BaTiO}_3$  [45]. Thus,  $R3 \text{ Zn}_2\text{FeOsO}_6$  should be a switchable ferroelectric with a

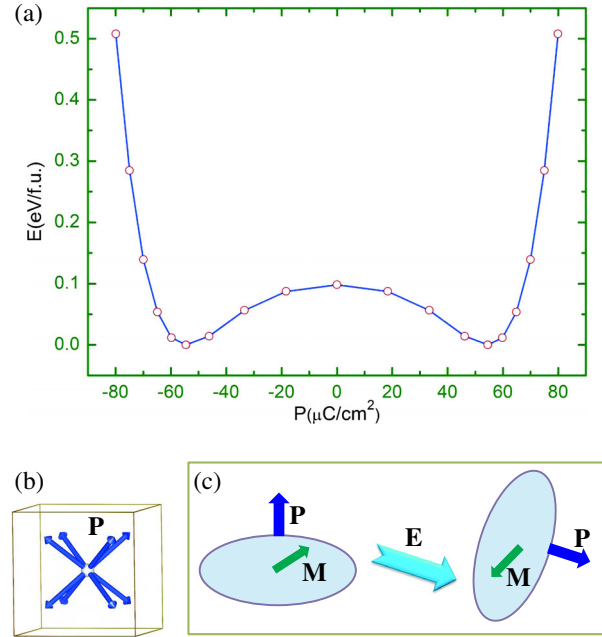


FIG. 4 (color online). (a) The total energy as a function of the electric polarization for  $\text{Zn}_2\text{FeOsO}_6$ . It displays the double well potential with an energy barrier of 0.09 eV/f.u. (b) Eight possible orientations of the FE polarization vector ( $\mathbf{P}$ ) in the sample of LN-type  $\text{Zn}_2\text{FeOsO}_6$ . (c) Illustration of the ME coupling in  $\text{Zn}_2\text{FeOsO}_6$ . A  $71^\circ$  or  $109^\circ$  switch of the FE domains by the external electric field will be associated with the reorientation of the easy-plane of magnetization.

high electric polarization. Our tests based on an effective model Hamiltonian and molecular dynamics simulations show that the ferroelectric transition temperature of  $\text{Zn}_2\text{FeOsO}_6$  is well above room temperature (see Parts 9 and 10 of [27]).

Let us now discuss the possible ME coupling in LN-type  $\text{Zn}_2\text{FeOsO}_6$ . Because of the cubic symmetry of the parent perovskite structure, there are eight symmetrically equivalent  $\langle 111 \rangle$  directions. In rhombohedral  $\text{Zn}_2\text{FeOsO}_6$ , the spontaneous electric polarization is directed along one of the eight  $\langle 111 \rangle$  axes of the perovskite structure. Thus, in the sample of LN-type  $\text{Zn}_2\text{FeOsO}_6$ , there might occur eight different FE domains [see Fig. 4(b)]. Our above calculations show that the easy plane of magnetization is always perpendicular to the direction of the electric polarization. Although a  $180^\circ$  switching of the ferroelectric polarization should not affect the magnetic state, a  $71^\circ$  or  $109^\circ$  switch of the FE domains by the electric field will change the orientation of the easy plane of magnetization, as shown schematically in Fig. 4(c). This could be a promising route to manipulate the orientation of the ferrimagnetism by an electric field. A similar ME coupling mechanism in  $\text{BiFeO}_3$  thin films has been demonstrated experimentally by Zhao *et al.*, who showed that the AFM plane can be switched by an electric field [46]. Note that magnetoelectric effects can be classified into two different types: one for

which changing the magnitude of the polarization affects the magnitude of the magnetization (energy form containing  $P^2 \cdot M^2$ ) and one for which changing the direction of  $\vec{P}$  changes the direction of  $\vec{M}$  (energy form containing  $\vec{P} \times \vec{M}$ ). In  $\text{Zn}_2\text{FeOsO}_6$ , the first type of ME effect is weak, while the second type of ME effect is strong.

We now compare  $\text{Zn}_2\text{FeOsO}_6$  with the classic multiferroic  $\text{BiFeO}_3$ . First, they adopt similar rhombohedral structures. Second, both compounds have high electrical polarizations. Third, both compounds are room temperature multiferroics. Fourth, the ME coupling mechanism is rather similar in that the magnetic easy plane can be manipulated by electric field. However, the magnetic ground state of  $R3\text{Zn}_2\text{FeOsO}_6$  is dramatically different from  $\text{BiFeO}_3$ .  $\text{Zn}_2\text{FeOsO}_6$  has a ferrimagnetic ground state, while  $\text{BiFeO}_3$  is AFM. And the magnetic anisotropy in  $\text{Zn}_2\text{FeOsO}_6$  is stronger than that (0.2 meV when  $U(\text{Fe}) = 5$  eV [47]) in  $\text{BiFeO}_3$  because of the strong SOC effect of the  $5d$  Os ion. These desirable properties make  $\text{Zn}_2\text{FeOsO}_6$  suitable for realizing electric-field control of magnetism at room temperature.

The reason why we practically proposed  $\text{Zn}_2\text{FeOsO}_6$  as a possible multiferroic is twofold. First, polar  $\text{Zn}_2\text{FeTaO}_6$  [17] and  $\text{ZnTiO}_3$  [48] have already been synthesized under high pressure. Second, it was experimentally showed that  $\text{Ca}_2\text{FeOsO}_6$  crystallizes into an ordered double-perovskite structure with a space group of  $P2_1/n$  under high pressure and high temperature, and  $\text{Ca}_2\text{FeOsO}_6$  presents a long-range ferrimagnetic transition above room temperature ( $T_c \sim 320$  K) [24]. Therefore, we expect that  $\text{Zn}_2\text{FeOsO}_6$  is synthesizable and would most likely exhibit both ferroelectricity and ferrimagnetism at room temperature.

Work at Fudan was supported by NSFC (Grant No. 11374056), the Special Funds for Major State Basic Research (Grants No. 2012CB921400, No. 2015CB921700), Program for Professor of Special Appointment (Eastern Scholar), Fok Ying Tung Education Foundation, FANEDD, and NCET-10-0351. L. B. thanks the Department of Energy, Office of Basic Energy Sciences, under Contract No. ER-46612. W. R. thanks the NSFC (Grant No. 11274222), QiMingXing Project (Project No. 14QA1402000) from Shanghai Municipal Science and Technology Commission, Eastern Scholar Program and ShuGuang Program (Program No. 12SG34) from Shanghai Municipal Education Commission.

\*hxiang@fudan.edu.cn

- [1] S.-W. Cheong and M. Mostovoy, *Nat. Mater.* **6**, 13 (2007).
- [2] R. Ramesh and N. Spaldin, *Nat. Mater.* **6**, 21 (2007).
- [3] S. Picozzi and C. Ederer, *J. Phys. Condens. Matter* **21**, 303201 (2009).
- [4] K. F. Wang, J.-M. Liu, and Z. Ren, *Adv. Phys.* **58**, 321 (2009).
- [5] J. van den Brink and D. Khomskii, *J. Phys. Condens. Matter* **20**, 434217 (2008).
- [6] Y. Tokura and S. Seki, *Adv. Mater.* **22**, 1554 (2010).
- [7] J. Ma, J. M. Hu, Z. Li, and C. W. Nan, *Adv. Mater.* **23**, 1062 (2011).
- [8] S. V. Kiselev, R. P. Ozerov, and G. S. Zhdanov, *Sov. Phys. Dokl.* **7**, 742 (1963); D. Rahmedov, D. Wang, J. Íñiguez, and L. Bellaiche, *Phys. Rev. Lett.* **109**, 037207 (2012); I. C. Infante, S. Lisenkov, B. Dupé, M. Bibes, S. Fusil, E. Jacquet, G. Geneste, S. Petit, A. Courtial, J. Juraszek, L. Bellaiche, A. Barthélémy, and B. Dkhil, *Phys. Rev. Lett.* **105**, 057601 (2010).
- [9] I. Sosnowska, T. Peterlin-Neumaier, and E. Streichele, *J. Phys. C* **15**, 4835 (1982).
- [10] J. Wang, J. B. Neaton, H. Zheng, V. Nagarajan, S. B. Ogale, B. Liu, D. Viehland, V. Vaithyanathan, D. G. Schlom, U. V. Waghmare, N. A. Spaldin, K. M. Rabe, M. Wuttig, and R. Ramesh, *Science* **299**, 1719 (2003).
- [11] W. Eerenstein, F. D. Morrison, J. Dho, M. G. Blamire, J. F. Scott, and N. D. Mathur, *Science* **307**, 1203 (2005).
- [12] Y. Kitagawa, Y. Hiraoka, T. Honda, T. Ishikura, H. Nakamura, and T. Kimura, *Nat. Mater.* **9**, 797 (2010).
- [13] H. J. Xiang, E. J. Kan, Y. Zhang, M.-H. Whangbo, and X. G. Gong, *Phys. Rev. Lett.* **107**, 157202 (2011); H. J. Xiang, P. S. Wang, M.-H. Whangbo, and X. G. Gong, *Phys. Rev. B* **88**, 054404 (2013).
- [14] M. Azuma, K. Takata, T. Saito, S. Ishiwata, Y. Shimakawa, and M. Takano, *J. Am. Chem. Soc.* **127**, 8889 (2005).
- [15] S. Kumar, G. Giovannetti, J. van den Brink, and S. Picozzi, *Phys. Rev. B* **82**, 134429 (2010).
- [16] M.-R. Li, D. Walker, M. Retuerto, T. Sarkar, J. Hadermann, P. W. Stephens, M. Croft, A. Ignatov, C. P. Grams, J. Hemberger, I. Nowik, P. S. Halasyamani, T. T. Tran, S. Mukherjee, T. S. Dasgupta, and M. Greenblatt, *Angew. Chem., Int. Ed. Engl.* **52**, 8406 (2013).
- [17] M.-R. Li, P. W. Stephens, M. Retuerto, T. Sarkar, C. P. Grams, J. Hemberger, M. C. Croft, D. Walker, and M. Greenblatt, *J. Am. Chem. Soc.* **136**, 8508 (2014).
- [18] M. Ležaić and N. A. Spaldin, *Phys. Rev. B* **83**, 024410 (2011).
- [19] H. Wang, S. Zhu, X. Ou, and H. Wu, *Phys. Rev. B* **90**, 054406 (2014).
- [20] J. Wang, N. Zu, X. Hao, Y. Xu, Z. Li, Z. Wu, and F. Gao, *Phys. Status Solidi RRL* **08**, 776 (2014).
- [21] H. J. Zhao, W. Ren, Y. Yang, J. Íñiguez, X. M. Chen, and L. Bellaiche, *Nat. Commun.* **5**, 4021 (2014).
- [22] X. Z. Lu, X. G. Gong, and H. J. Xiang, *Comput. Mater. Sci.* **91**, 310 (2014).
- [23] Y. Krockenberger, K. Mogare, M. Reehuis, M. Tovar, M. Jansen, G. Vaitheeswaran, V. Kanchana, F. Bultmark, A. Delin, F. Wilhelm, A. Rogalev, A. Winkler, and L. Alff, *Phys. Rev. B* **75**, 020404 (2007).
- [24] H. L. Feng, M. Arai, Y. Matsushita, Y. Tsujimoto, Y. Guo, C. I. Sathish, X. Wang, Y.-H. Yuan, M. Tanaka, and K. Yamaura, *J. Am. Chem. Soc.* **136**, 3326 (2014).
- [25] Y. Shimakawa, M. Azuma, and N. Ichikawa, *Materials* **4**, 153 (2011).
- [26] H. J. Xiang, *Phys. Rev. B* **90**, 094108 (2014).
- [27] See Supplemental Material for details at <http://link.aps.org/supplemental/10.1103/PhysRevLett.114.147204>, which includes Refs. [28–37], for computational details, structural parameters, band structure, density of states, phonon

- dispersion, ordering of Fe and Os ions on the B sites, effect of U on the magnetic properties, origin of the spin canting, effective Hamiltonian study and molecular dynamics simulations on the finite temperature effect on ferroelectric and magnetic properties.
- [28] A. I. Liechtenstein, V. I. Anisimov, and J. Zaanen, *Phys. Rev. B* **52**, R5467 (1995).
- [29] J. P. Perdew, K. Burke, and M. Ernzerhof, *Phys. Rev. Lett.* **77**, 3865 (1996).
- [30] P. E. Blöchl, *Phys. Rev. B* **50**, 17953 (1994); G. Kresse and D. Joubert, *Phys. Rev. B* **59**, 1758 (1999).
- [31] G. Kresse and J. Furthmüller, *Comput. Mater. Sci.* **6**, 15 (1996); *Phys. Rev. B* **54**, 11169 (1996).
- [32] P. S. Wang and H. J. Xiang, *Phys. Rev. X* **4**, 011035 (2014).
- [33] J. C. Wojdeł and J. Íñiguez, *Phys. Rev. Lett.* **103**, 267205 (2009).
- [34] H. J. Xiang, C. Lee, H.-J. Koo, X. G. Gong, and M.-H. Whangbo, *Dalton Trans.* **42**, 823 (2013); H. J. Xiang, E. J. Kan, S.-H. Wei, M.-H. Whangbo, and X. G. Gong, *Phys. Rev. B* **84**, 224429 (2011).
- [35] K. Hukushima and K. Nemoto, *J. Phys. Soc. Jpn.* **65**, 1604 (1996).
- [36] A. Togo, F. Oba, and I. Tanaka, *Phys. Rev. B* **78**, 134106 (2008).
- [37] L. Bellaïche and D. Vanderbilt, *Phys. Rev. Lett.* **81**, 1318 (1998).
- [38] H. J. Xiang and M.-H. Whangbo, *Phys. Rev. B* **75**, 052407 (2007).
- [39] J. B. Goodenough, *Phys. Rev.* **100**, 564 (1955); J. Kanamori, *J. Phys. Chem. Solids* **10**, 87 (1959).
- [40] The law proposed by Bellaïche, *et al.* [L. Bellaïche, Z. Gui, and I. A. Kornev, *J. Phys. Condens. Matter* **24**, 312201 (2012)] states that the weak component of the magnetization has a direction that is given by the cross product of the oxygen octahedral tilting vector (that is lying along the  $c$  direction in the hexagonal setting of the  $R\bar{3}$  phase) with the  $G$ -type antiferromagnetic vector (that is chosen here to be along the  $x$  axis). Note that this law also implies that choosing a  $G$ -type antiferromagnetic vector being along the same direction as the oxygen octahedral tilting vector (that is, the  $c$  axis) should not produce any weak component of the magnetization perpendicularly to the  $G$ -type antiferromagnetic vector. This is precisely what we further found in the simulations when the Fe and Os moments are chosen to lie (in antiparallel fashion) along the  $c$  axis.
- [41] A. Fert and P. M. Levy, *Phys. Rev. Lett.* **44**, 1538 (1980).
- [42] M. Heide, G. Bihlmayer, and S. Blügel, *Physica (Amsterdam)* **404B**, 2678 (2009).
- [43] Y. A. Izyumov, *Sov. Phys. Usp.* **27**, 845 (1984).
- [44] R. E. Cohen, *Nature (London)* **358**, 136 (1992); C. Ederer and N. A. Spaldin, *Phys. Rev. B* **74**, 024102 (2006).
- [45] J. B. Neaton and K. M. Rabe, *Appl. Phys. Lett.* **82**, 1586 (2003).
- [46] T. Zhao, A. Scholl, F. Zavaliche, K. Lee, M. Barry, A. Doran, M. P. Cruz, Y. H. Chu, C. Ederer, N. A. Spaldin, R. R. Das, D. M. Kim, S. H. Baek, C. B. Eom, and R. Ramesh, *Nat. Mater.* **5**, 823 (2006).
- [47] C. Ederer and N. A. Spaldin, *Phys. Rev. B* **71**, 060401(R) (2005).
- [48] Y. Inaguma, A. Aimi, Y. Shirako, D. Sakurai, D. Mori, H. Kojitani, M. Akaogi, and M. Nakayama, *J. Am. Chem. Soc.* **136**, 2748 (2014).