



Phonon-Assisted Resonant Tunneling of Electrons in Graphene–Boron Nitride Transistors

E. E. Vdovin,^{1,5,6} A. Mishchenko,² M. T. Greenaway,^{1,*} M. J. Zhu,² D. Ghazaryan,² A. Misra,³ Y. Cao,⁴
S. V. Morozov,^{5,6} O. Makarovskiy,¹ T. M. Fromhold,¹ A. Patané,¹ G. J. Slotman,⁷ M. I. Katsnelson,⁷
A. K. Geim,^{2,4} K. S. Novoselov,^{2,3} and L. Eaves^{1,2}

¹*School of Physics and Astronomy, University of Nottingham, Nottingham NG7 2RD, United Kingdom*

²*School of Physics and Astronomy, University of Manchester, Manchester M13 9PL, United Kingdom*

³*National Graphene Institute, University of Manchester, Manchester M13 9PL, United Kingdom*

⁴*Centre for Mesoscience and Nanotechnology, University of Manchester, Manchester M13 9PL, United Kingdom*

⁵*Institute of Microelectronics Technology and High Purity Materials, RAS, Chernogolovka 142432, Russia*

⁶*National University of Science and Technology “MISIS,” 119049 Leninsky Prospect 4, Moscow, Russia*

⁷*Radboud University, Institute for Molecules and Materials, Heyendaalseweg 135, 6525 AJ Nijmegen, The Netherlands*

(Received 8 December 2015; published 5 May 2016)

We observe a series of sharp resonant features in the differential conductance of graphene-hexagonal boron nitride-graphene tunnel transistors over a wide range of bias voltages between 10 and 200 mV. We attribute them to electron tunneling assisted by the emission of phonons of well-defined energy. The bias voltages at which they occur are insensitive to the applied gate voltage and hence independent of the carrier densities in the graphene electrodes, so plasmonic effects can be ruled out. The phonon energies corresponding to the resonances are compared with the lattice dispersion curves of graphene–boron nitride heterostructures and are close to peaks in the single phonon density of states.

DOI: 10.1103/PhysRevLett.116.186603

The discovery of the remarkable electronic properties of graphene [1,2] has been followed by an upsurge of interest in other layered materials such as hexagonal boron nitride (hBN), the transition metal dichalcogenides, and the III-VI family of layered semiconductors. These anisotropic layered materials have strong in-plane bonds of covalent character, whereas the interlayer bonding arises from weaker van der Waals (vdW)-like forces, so crystalline flakes, one or a few atomic layers thick, can be exfoliated mechanically from bulk crystals. These developments have led to the realization of a new class of materials, vdW heterostructures, in which nanoflakes of different materials are stacked together in an ordered way [3–5]. These heterostructures possess unique properties that can be exploited for novel device applications. An example is a tunnel transistor in which a barrier is sandwiched between two graphene layers and mounted on the oxidized surface layer of a doped Si substrate [6,7]. The tunnel current flowing between the two graphene layers can be controlled by applying a gate voltage to the doped Si layer and arises predominantly from resonant processes in which the energy, in-plane momentum, and chirality of the tunneling electron are conserved [8–10].

Previous investigations of electron tunneling in a variety of metal-insulator diodes [11] and conventional semiconductor heterostructures [12] have demonstrated that electrons can tunnel inelastically, with the emission of one or multiple phonons. Atomically resolved scanning tunneling spectroscopy measurements on mechanically cleaved graphene flakes with a tunable back gate have revealed the presence of phonon-assisted tunneling [13–16]. The multi-component nature of our vdW heterostructure gives rise to a more complex set of lattice dispersion curves than for graphene [17–21] and to phonon-assisted tunneling, as shown recently for a graphite-hBN-graphene transistor [22]. The study of electron-phonon interactions is relevant to interlayer conduction in twisted graphene bilayers [23] and, more generally, to the recent discovery of superconductivity in graphene-based vdW heterostructures [24–27].

Here we investigate tunnel transistors in which a ~ 1 -nm layer of hBN is sandwiched between monolayer graphene electrodes. Unlike the devices reported in Refs. [9,10], which have a similar composition, the crystalline lattices of the component layers in the two devices investigated here are not intentionally aligned. We estimate the lattice misalignment of the two graphene electrodes to be at least 3° . This gives rise to a misalignment in k space of the Dirac cones at the corners of the hexagonal Brillouin zones of the two electrodes, so the momentum-conserving elastic transitions cannot occur over the bias voltage range over which the device characteristics are measured. Under these

Published by the American Physical Society under the terms of the Creative Commons Attribution 3.0 License. Further distribution of this work must maintain attribution to the author(s) and the published article's title, journal citation, and DOI.

conditions interlayer conductance is dominated by phonon-assisted tunneling processes that relax the momentum conservation rule [23].

We observe a series of sharp resonant steps in the electrical conductance over a wide range of bias voltage, gate voltage, and temperature. This spectrum can be understood in terms of inelastic transitions whereby electrons tunneling through the hBN barrier emit phonons of different and well-defined energies between ~ 12 and 200 meV, covering the range of lattice phonon energies in these heterostructures. The resonances correspond closely to van Hove-like peaks in the single phonon density of states of the heterostructure, with the strongest peaks arising from the emission of low- and high-energy optical mode phonons.

A schematic energy band diagram of our devices and circuit is shown in the inset of Fig. 1(a). The bottom graphene layer is mounted on an atomically flat hBN layer, placed above the silicon oxide substrate, and the active region of the device is capped with a hBN protective top layer. The tunnel current I was measured as a function of the bias voltage V_b applied between the two graphene electrodes and the gate voltage V_g applied across the bottom graphene electrode and the doped Si gate electrode.

Figure 1(a) shows plots of differential tunnel conductance, $G(V_b) = dI/dV_b$, measured at a temperature of $T = 4$ K. The form of the $G(V_b)$ curves is strongly dependent on V_g . Close to $V_b = 0$, $G \approx 0$ at all gate voltages. With increasing $|V_b|$, the conductance increases in a series of well-defined steps, indicated by vertical arrows. We attribute each step to inelastic phonon-assisted tunneling in which an electron emits a phonon and tunnels from close to the Fermi energy in one electrode to an empty state near the Fermi energy in the other electrode, with the emission of a phonon of well-defined energy, $\hbar\omega_p$. Figure 1(b) shows a color map of $G(V_b, V_g)$ in which some of these steplike features are discernible as a series of faint vertical striped modulations in the color map. Also visible is a dark blue, X-shaped region in which G is small. This corresponds to the passage of the chemical potential through the Dirac point of the two monolayer graphene electrodes as V_b and V_g are varied; here, the conductance is suppressed due to the small density of electronic states into which electrons can tunnel. Using an electrostatic model [7], which includes a small amount of doping in the bottom electrode (p -type, $2.5 \times 10^{11} \text{ cm}^{-2}$) as a fitting parameter, we determine the condition for the intersection of the chemical potential with a Dirac point in each of the two graphene electrodes. The calculated loci of these intersections are shown by the yellow dashed line in Fig. 1(b); they correspond closely with the measured X-shaped low conductance region.

The vertical stripes in the $G(V_b, V_g)$ map are faint because the steplike modulation in $G(V_b)$ is only a small fraction of the total conductance. Most of the monotonic

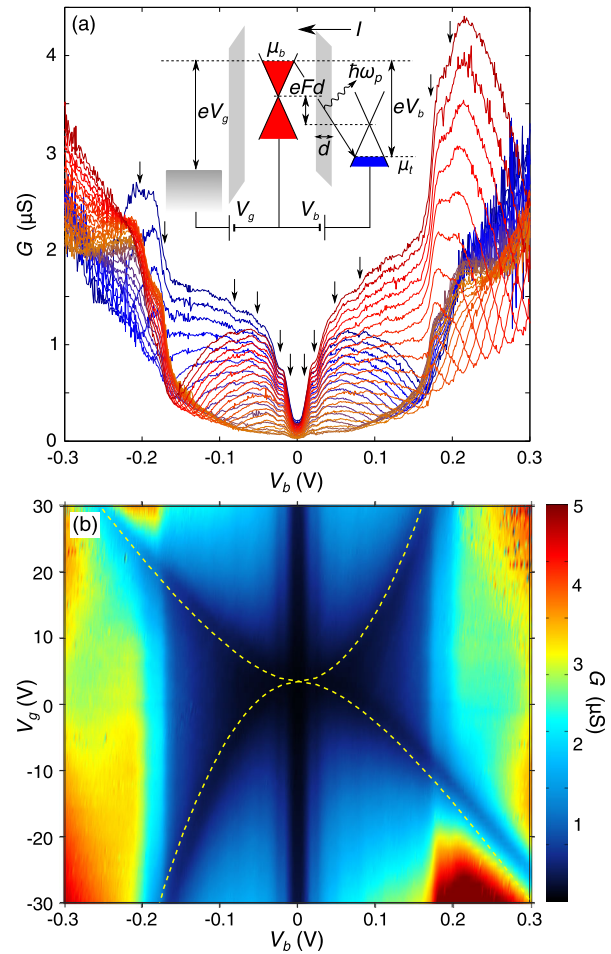


FIG. 1. Differential conductance of Device 1 at $T = 4$ K. (a) $G(V_b)$ for $V_g = -30$ V (red) to 30 V (blue) and intervals $\Delta V_g = 2$ V. Inset: Schematic band diagram of Device 1 with bias V_b and gate V_g voltages applied to the monolayer graphene electrodes, which are separated by an hBN barrier of thickness $d = 0.9$ nm. Here, $\mu_{b,t}$ are the chemical potentials of the bottom and top electrodes and F is the electric field across the barrier. A phonon-assisted tunnel process is shown schematically. (b) Color map of dI/dV_b for a range of V_g and V_b .

increase of $G(V_b)$ with V_b can be partly eliminated by taking the second derivative dG/dV_b , which reveals the weak but sharp phonon-assisted resonances more clearly. Figure 2(a) shows a gray-scale contour map of $\alpha dG/dV_b$, where $\alpha = |V_b|/V_b = \pm 1$. Here, the phonon-assisted tunneling features appear as easily discernible bright vertical stripes, indicated by arrows, at well-defined values of V_b , at which $G(V_b)$ rapidly increases. These values are independent of gate voltage, but their amplitudes at low V_b are significantly stronger at large positive and negative values of V_g .

Interestingly, the vertical stripe features are not observed in the conductance maps of similar devices in which the graphene electrodes are closely aligned to within 2° (see Figs. 2 and 3 of Ref. [9]). We can exclude the possibility

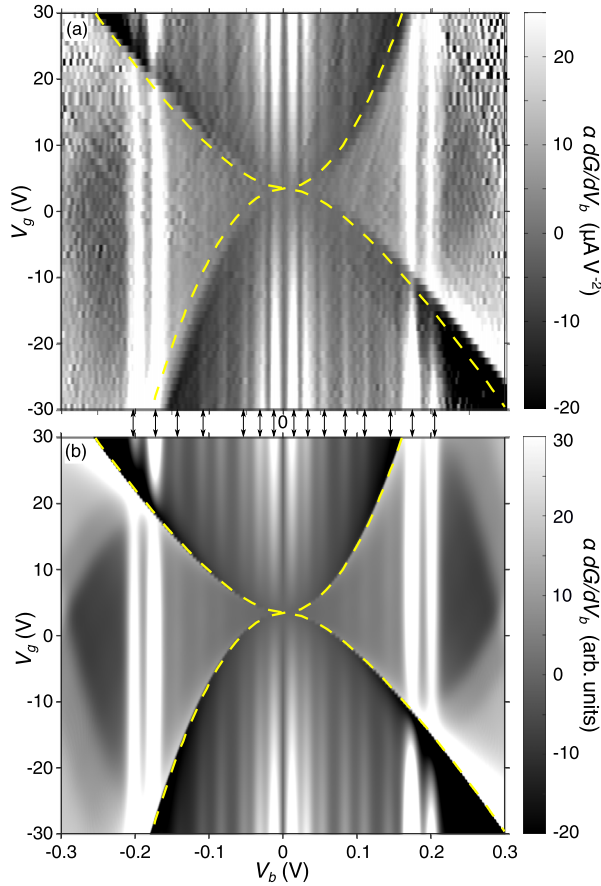


FIG. 2. (a) Measured plots adG/dV_b for Device 1 and (b) calculated gray-scale map of adG/dV_b for $T = 4$ K, best fit to data in Fig. 2(a) using the model described in the text and in Table I. Yellow dashed curves show where the chemical potential in a graphene layer intersects with the Dirac point in that layer.

that the features are plasmon related as the sheet density n in both graphene electrodes is strongly dependent on V_g : n varies from $\sim 10^{12}$ cm^{-2} (holes) through zero to $\sim 10^{12}$ cm^{-2} (electrons) between $V_g = -30$ V and 30 V. Even though the plasma frequency of carriers in graphene varies relatively weakly with n ($\sim n^{1/4}$) [28], plasmon-related resonances would have a significant gate voltage dependence, which is not observed.

Since the bias voltage values $|V_b|$ of the weak resonant features are independent of gate voltage and are the same in both negative and positive biases, we can display them more clearly by averaging over all 60 of the measured adG/dV_b plots in the range -30 V $< V_g < 30$ V. This procedure significantly reduces the level of background noise. The result of this averaging procedure for Device 1 is shown in Fig. 3(a). It reveals the phonon-assisted resonances as a series of well-defined peaks. The corresponding plot for another device, Device 2, is also shown. The overall forms of the two curves are qualitatively similar, with the exception of some notable differences, e.g., the position of the strong peaks at high $V_b > 0.12$ V.

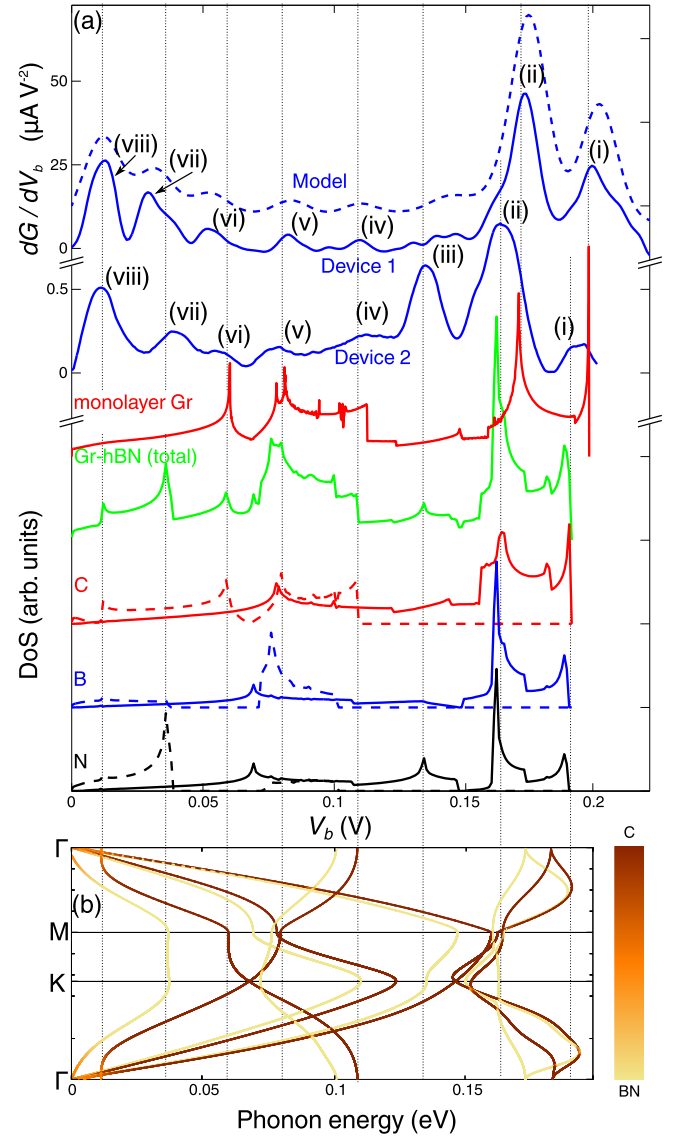


FIG. 3. (a) The three top curves (blue): dG/dV_b averaged over all gate voltages for our model (dashed) and measured data for Devices 1 and 2 (both solid). Lower curves: Total density of phonon states for monolayer graphene (red, monolayer Gr) and a graphene-hBN heterostructure [green, Gr-hBN (total)]. Lower three curves: The partial density of states associated with the carbon (red, C), boron (blue, B), and nitrogen (black, N) atoms of a graphene-hBN heterostructure. Solid and dashed curves show contributions by in- and out-of-plane phonons, respectively. (b) Phonon dispersion of a graphene-hBN heterostructure [17]. Vertical dotted curves are guides to the eye, highlighting the alignments.

To understand the physical origin of the peaks in Fig. 3(a), we compare them to the one-phonon densities of states of monolayer graphene (red curve) and a graphene-hBN bilayer (green); the lower three curves show the partial density of states associated with the predominant motion of the carbon, boron, and nitrogen atoms in the bilayer; the solid and dashed curves show contributions by

in- and out-of-plane phonons, respectively. The full phonon dispersion curves of the graphene-hBN bilayer [17] are shown in Fig. 3(b).

The phonon density of states and the phonon dispersion curves were determined by using the “phonopy” package [29] with the force constants obtained by the finite displacement method [30,31], using the Vienna *ab initio* simulation package (VASP) [32,33]. For the phonon density of states, a tetrahedron smearing was applied for higher accuracy. A detailed description of the computational methods can be found in Ref. [17].

At high bias, the two peaks labeled (i) and (ii) are close to the energies of the large densities of states associated with the weakly dispersed, high-energy optic phonons of monolayer graphene (Device 1) and a bilayer of graphene and hBN (Device 2). Note that peak (iii) at 130 meV in Device 2 is absent in Device 1. This energy corresponds closely to the flat region of the dispersion curve of the graphene-hBN bilayer near the *K* point of the Brillouin zone, which arises predominantly from vibrations of the nitrogen atom. This difference, and the variation of the position of peaks (i) and (ii), between the two devices may arise from differences in the relative lattice orientation of the graphene and hBN layers in the device.

Both devices exhibit peaks around 110, 84, and 53 mV, labeled (iv), (v), and (vi), corresponding to prominent features in the calculated density-of-state plots and the flat regions of the dispersion curves. An interesting feature of the data for both devices is the strong peak (viii) at low bias, around 12 mV, which we attribute to the weakly dispersed low-energy phonons close to the Γ point of the graphene-hBN bilayer. This low-energy “out-of-plane” mode was intensively studied in inelastic x-ray spectroscopy measurement of bulk graphite and hBN [18]. Note that the resonant peak (vii) observed at 32 mV can be associated with a peak in the phonon density of states of the graphene-hBN bilayer, which arises predominantly from the motion of the nitrogen atoms and corresponds to the flat region of the lowest-energy acoustic mode at ~ 30 meV in the vicinity of the *M* and *K* points of the Brillouin zone.

As shown in Fig. 4, the resonant peaks broaden and their amplitudes decrease with increasing temperature, disappearing completely at temperatures $T \geq 150$ K.

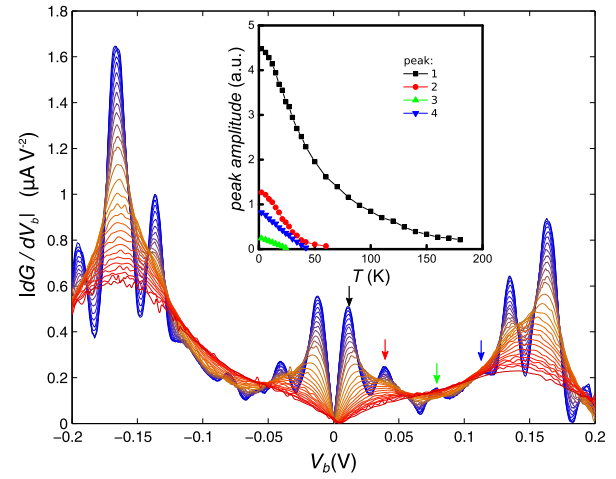


FIG. 4. Temperature dependence of $|d^2I/dV_b^2|$ vs V_b in Device 2 measured from $T = 2.3$ K to $T = 180$ K (blue to red) for $V_g = 40$ V. Inset: Peak amplitude vs T . Curve colors match peaks marked by correspondingly colored arrows in the main plot.

This is consistent with the thermal broadening of the electron distribution functions around the Fermi energies of the two graphene electrodes so that Pauli blocking of electron tunneling for $eV_b < \hbar\omega_p$ is diminished as more states become available with increasing thermal smearing around the Fermi energies.

We fit the data in Fig. 2(a) using a model in which an inelastic tunneling transition is allowed only when the difference between the chemical potentials μ_b and μ_t in the bottom (*b*) and top (*t*) graphene layers, respectively, exceeds $\hbar\omega_p^i$, which corresponds to the bias voltage of a particular phonon-assisted resonance peak *i* in the conductance. At low temperatures (4 K), $eV_b = \mu_b - \mu_t - eFd$ greatly exceeds the thermal smearing $\sim 2k_B T$ of the Fermi seas of the two graphene electrodes. The emission of a phonon of energy, $\hbar\omega_p^i$, becomes possible when eV_b exceeds $\hbar\omega_p^i$, thus opening up an inelastic scattering channel and resulting in a steplike rise in the current and a resonant peak in dG/dV_b when $eV_b = \hbar\omega_p^i$. In our model the current is given by

$$I = \sum_i T(i) \int dE_b \int dE_t D_b(E_b) D_t(E_t) \{ \Gamma(E_b - E_t - \hbar\omega_p^i) f_b(E_b) [1 - f_t(E_t)] - \Gamma(E_t - E_b - \hbar\omega_p^i) f_t(E_t) [1 - f_b(E_b)] \}, \quad (1)$$

where $E_{b,t}$ is the electron energy in the *b* and *t* layers, $D_{b,t}(E)$ is the density of electronic states in these layers (which are shifted energetically by eFd), $\Gamma(E) = \exp(-E^2/2\gamma^2)$ with energy broadening $\gamma = 5$ meV, and $f_{b,t}$ is the Fermi function in the bottom and top electrodes. $T(i)$ is a relative weighting factor that depends on the electron-phonon coupling and phonon density of

states for each inelastic transition. We show the values of $T(i)$ used in our model in Table I, which provides a qualitative indication of the relative strengths of the phonon-assisted processes.

Using this model, and including phonon emission processes at threshold energies corresponding to the values of V_b , we obtain the gray-scale plot in Fig. 2(b), which accurately

TABLE I. Phonon energies $\hbar\omega_p^i$ and weighting factors $T(i)$ used in Eq. (1) to obtain the fit to the experimental data shown in Fig. 2(b).

i	1	2	3	4	5	6	7	8
$\hbar\omega_p^i$ (meV)	12	32	53	84	110	143	174	201
$T(i)$	1.0	0.58	0.30	0.26	0.24	0.23	3.53	1.81

simulates the measured data in Fig. 2(a). In particular, the relative intensities of the vertical stripes are in good agreement with the measured data. At high positive and negative V_g , the asymmetry in the measured intensities of the resonances for positive and negative V_b is replicated by the model. This confirms that the peaks arise from tunneling of carriers, mediated by phonon emission, from filled states near the chemical potential in one electrode into the empty states just above the chemical potential in the other.

In conclusion, our measurements reveal a rich spectrum of inelastic phonon-assisted electron tunneling peaks in the conductance of multilayer graphene–hBN–graphene tunnel transistors. They allow us to probe electron-phonon interactions in this type of device and spectroscopically identify the energies and nature of the emitted phonons. Our results provide spectroscopic evidence that the tunnel current in van der Waals heterostructures is strongly suppressed by the large lateral momentum mismatch that arises when the crystalline lattices of the component electrodes are misaligned. Under these conditions, inelastic electron tunneling with emission of phonons with well-defined energy plays a dominant role in carrying current perpendicular to the layers.

This work was supported by the EU FP7 Graphene Flagship Project 604391, ERC Synergy Grant, Hetero2D, EPSRC, the Royal Society, U.S. Army Research Office, U.S. Navy Research Office, and U.S. Airforce Research Office. M. T. G. acknowledges The Leverhulme Trust for support. S. V. M. and E. E. V. were supported by NUST MISiS (Grant No. K1-2015-046) and RFBR (Grants No. 15-02-01221 and No. 14-02-00792). G. J. S. and M. I. K. acknowledge financial support from the ERC Advanced Grant No. 338957 FEMTO/NANO. We are grateful to Gilles de Wijs and Annalisa Fasolino for useful discussions.

*mark.greenaway@nottingham.ac.uk

- [1] K. S. Novoselov, A. K. Geim, S. V. Morozov, D. Jiang, Y. Zhang, S. V. Dubonos, I. V. Grigorieva, and A. A. Firsov, *Science* **306**, 666 (2004).
- [2] K. S. Novoselov, D. Jiang, F. Schedin, T. J. Booth, V. V. Khotkevich, S. V. Morozov, and A. K. Geim, *Proc. Natl. Acad. Sci. USA* **102**, 10451 (2005).
- [3] C. R. Dean *et al.*, *Nat. Nanotechnol.* **5**, 722 (2010).

- [4] A. K. Geim and I. V. Grigorieva, *Nature (London)* **499**, 419 (2013).
- [5] A. C. Ferrari *et al.*, *Nanoscale* **7**, 4598 (2015).
- [6] R. M. Feenstra, D. Jena, and G. Gu, *J. Appl. Phys.* **111**, 043711 (2012).
- [7] L. Britnell *et al.*, *Science* **335**, 947 (2012).
- [8] L. Britnell, R. V. Gorbachev, A. K. Geim, L. A. Ponomarenko, A. Mishchenko, M. T. Greenaway, T. M. Fromhold, K. S. Novoselov, and L. Eaves, *Nat. Commun.* **4**, 1794 (2013).
- [9] A. Mishchenko *et al.*, *Nat. Nanotechnol.* **9**, 808 (2014).
- [10] M. T. Greenaway *et al.*, *Nat. Phys.* **11**, 1057 (2015).
- [11] A. G. Chynoweth, R. A. Logan, and D. E. Thomas, *Phys. Rev.* **125**, 877 (1962).
- [12] L. Eaves, P. S. S. Guimaranes, B. R. Snell, D. C. Taylor, and K. E. Singer, *Phys. Rev. Lett.* **55**, 262 (1985).
- [13] V. W. Brar, Y. Zhang, Y. Yayon, T. Ohta, J. L. McClesney, A. Bostwick, E. Rotenberg, K. Horn, and M. F. Crommie, *Appl. Phys. Lett.* **91**, 122102 (2007).
- [14] Y. Zhang, V. W. Brar, F. Wang, C. Girit, Y. Yayon, M. Panlasigui, A. Zettl, and M. F. Crommie, *Nat. Phys.* **4**, 627 (2008).
- [15] T. O. Wehling, I. Grigorenko, A. I. Lichtenstein, and A. V. Balatsky, *Phys. Rev. Lett.* **101**, 216803 (2008).
- [16] F. D. Natterer, Y. Zhao, J. Wyrick, Y.-H. Chan, W.-Y. Ruan, M.-Y. Chou, K. Watanabe, T. Taniguchi, N. B. Zhitenev, and J. A. Stroscio, *Phys. Rev. Lett.* **114**, 245502 (2015).
- [17] G. J. Slotman, G. A. de Wijs, A. Fasolino, and M. I. Katsnelson, *Ann. Phys. (Berlin)* **526**, 381 (2014).
- [18] J. Serrano, A. Bosak, R. Arenal, M. Krisch, K. Watanabe, T. Taniguchi, H. Kanda, A. Rubio, and L. Wirtz, *Phys. Rev. Lett.* **98**, 095503 (2007).
- [19] J. Maultzsch, S. Reich, C. Thomsen, H. Requardt, and P. Ordejón, *Phys. Rev. Lett.* **92**, 075501 (2004).
- [20] L. Wirtz and A. Rubio, *Solid State Commun.* **131**, 141 (2004).
- [21] A. C. Ferrari *et al.*, *Phys. Rev. Lett.* **97**, 187401 (2006).
- [22] S. Jung, M. Park, J. Park, T.-Y. Jeong, H.-J. Kim, K. Watanabe, T. Taniguchi, D. H. Ha, C. Hwang, and Y.-S. Kim, *Sci. Rep.* **5**, 16642 (2015).
- [23] V. Perebeinos, J. Tersoff, and Ph. Avouris, *Phys. Rev. Lett.* **109**, 236604 (2012).
- [24] J. Chapman, Y. Su, C. A. Howard, D. Kundys, A. N. Grigorenko, F. Guinea, A. K. Geim, I. V. Grigorieva, and R. R. Nair, *Sci. Rep.* **6**, 23254 (2016).
- [25] M. Xue, G. Chen, H. Yang, Y. Zhu, D. Wang, J. He, and T. Cao, *J. Am. Chem. Soc.* **134**, 6536 (2012).
- [26] M. Petrović *et al.*, *Nat. Commun.* **4**, 2772 (2013).
- [27] D. M. Guzman, H. M. Alyahyaei, and R. A. Jishi, *2D Mater.* **1**, 021005 (2014).
- [28] E. H. Hwang and S. Das Sarma, *Phys. Rev. B* **75**, 205418 (2007).
- [29] A. Togo and I. Tanaka, *Scr. Mater.* **108**, 1 (2015).
- [30] G. Kresse, J. Furthmüller, and J. Hafner, *Europhys. Lett.* **32**, 729 (1995).
- [31] K. Parlinski, Z.-Q. Li, and Y. Kawazoe, *Phys. Rev. Lett.* **78**, 4063 (1997).
- [32] G. Kresse and J. Furthmüller, *Comput. Mater. Sci.* **6**, 15 (1996).
- [33] G. Kresse and J. Furthmüller, *Phys. Rev. B* **54**, 11169 (1996).