

## Stable Liquid Jets Bouncing off Soft Gels

Dan Daniel,<sup>1,2,\*</sup> Xi Yao,<sup>3</sup> and Joanna Aizenberg<sup>1,4,5,†</sup>

<sup>1</sup>*John A. Paulson School of Engineering and Applied Sciences, Harvard University, Cambridge, Massachusetts 02138, USA*

<sup>2</sup>*Institute of Materials Research and Engineering, 2 Fusionopolis Way, Singapore 138634*

<sup>3</sup>*Department of Biomedical Sciences, City University of Hong Kong, Kowloon, Hong Kong, China*

<sup>4</sup>*Kavli Institute for Bionano Science and Technology, Harvard University, Cambridge, Massachusetts 02138, USA*

<sup>5</sup>*Wyss Institute for Biologically Inspired Engineering, Harvard University, Cambridge, Massachusetts 02138, USA*



(Received 20 July 2017; published 12 January 2018)

A liquid jet can stably bounce off a sufficiently soft gel by following the contour of the dimple created upon impact. This new phenomenon is insensitive to the wetting properties of the gels and was observed for different liquids over a wide range of surface tensions,  $\gamma = 24 - 72$  mN/m. In contrast, other jet rebound phenomena are typically sensitive to  $\gamma$ : only a high  $\gamma$  jet rebounds off a hard solid (e.g. superhydrophobic surface) and only a low  $\gamma$  jet bounces off a liquid bath. This is because an air layer must be stabilized between the two interfaces. For a soft gel, no air layer is necessary and the jet rebound remains stable even when there is direct liquid-gel contact.

DOI: [10.1103/PhysRevLett.120.028006](https://doi.org/10.1103/PhysRevLett.120.028006)

The ability of surfaces to repel liquids, either in the form of droplets or jets, is of broad interest and has numerous applications [1–3]. The rebound of single impinging water droplets off a rigid solid substrate, be it a superhydrophobic surface [4–6] or a leidenfrost solid such as dry ice [7], is a well-known phenomenon; the equivalent rebound of a liquid jet, on the other hand, is relatively less studied, despite the pervasiveness of liquid jets in various applications [8]. It was shown, only in recent years, that a water jet can stably bounce off a superhydrophobic surface with minimal energy loss at a low Weber number,  $We = \rho R U^2 / \gamma < 10$ , where  $\rho$ ,  $R$ ,  $U$ , and  $\gamma$  are the density, radius, velocity, and surface tension of the jet, respectively [9]. However, even a slight decrease of the surface tension of the liquid destabilizes the jet rebound, and no stable jet rebounds of low-surface-tension liquids were observed on superhydrophobic surfaces. The behavior of a soft material or a fluid in contact with a liquid droplet has also been widely studied, but their interaction with a liquid jet is rarely so [8,10–12]. Stable jets have also been observed in the case of a liquid bouncing off a bath of the same liquid, but such rebound is only possible for low-surface-tension liquids [13–16].

All the cases described above share one common feature: the rebound of droplets or jets is facilitated by a cushion of air layer between the two interfaces (liquid-solid or liquid-liquid). When this air layer becomes unstable or disrupted, for example due to increased wettability of the solid or the presence of dirt or defects along the interface, the rebound phenomenon is suppressed [17–19]. In this Letter, we describe the mechanism and stability of a jet rebound as it impacts a soft gel. This stable rebound phenomenon was observed for liquid jets over a wide range of surface

tensions,  $\gamma = 24 - 72$  mN/m, and for a variety of soft gels. We show that this phenomenon does not rely on either the formation of an air cushion to stabilize the jet or the wetting characteristics of the liquids; it is driven instead by the deformability of the soft substrate, and therefore applicable to a wide range of soft, elastomeric materials, irrespective of their surface energies.

We begin the demonstration of this new phenomenon by showing that a water jet (diameter  $D \sim 1.0$  mm, velocity  $U \sim 1$  m/s) can bounce off a hydrophilic gelatin gel that is 98.5 wt% water [Fig. 1(a), see also Supplemental Material, Movie S1 [20]]; in other words, a stable high-surface-tension liquid jet bounces off a high-surface-energy substrate containing the same liquid. In contrast, no rebound of water can occur off either a water bath or a stiff, hydrophilic substrate. The same rebound phenomenon was observed not only for other hydrophilic hydrogels, such as polyacrylamide, but also for hydrophobic gels, such as polydimethylsiloxane gels (PDMS, 78–82 wt% silicone oil, contact angle of water =  $90 \pm 5^\circ$ ). Unlike superhydrophobic (SH) surfaces that lose their repellence for low  $\gamma$  liquids, the PDMS gel was able to repel the liquid jet with  $\gamma$  as low as 24 mN/m. Figure 1(b) illustrates this: the soap-water jet ( $D = 0.3$  mm,  $U \sim 2$  m/s,  $\gamma = 30$  mN/m) could bounce off the PDMS gel (78 wt% silicone oil), but not the SH surface. The water jet, in comparison, was repelled by both surfaces.

To uncover the mechanism of such a stable jet rebound phenomenon and to avoid the complications of a hydrogel expanding (contracting) due to absorption (evaporation) of water, we chose to concentrate on the jet rebound behavior on PDMS gels. Silicone oil is immiscible with water and has a low vapor pressure  $\sim 5$  mm Hg. The Young's modulus

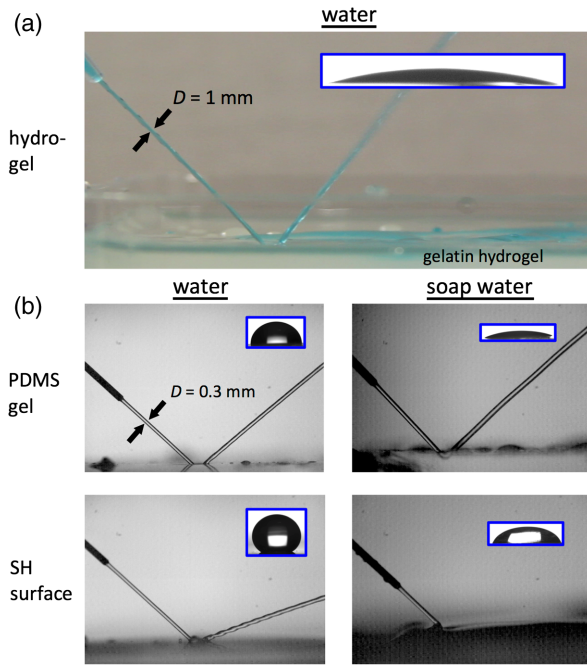


FIG. 1. (a) A water jet can bounce off a hydrophilic gelatin gel that is 98.5 wt% water. The inset shows the resulting gelatin contact angle of  $16^\circ$  for a  $10 \mu\text{L}$  water droplet. (b) A soft PDMS gel ( $E = 1.2 \text{ kPa}$ ) can repel both water and soap-water, while a superhydrophobic (SH) surface loses its liquid repellence for soap-water. The corresponding contact angles of  $10 \mu\text{L}$  water or soap-water droplets shown in the insets are (left to right, top to bottom):  $90^\circ$ ,  $30^\circ$ ,  $150^\circ$ , and  $60^\circ$ . The SH surface was a hexagonal array of a micropores monolayer of size  $\sim 1 \mu\text{m}$ , with static contact angle for water  $\theta = 150^\circ$ , and contact angle hysteresis  $\Delta\theta = 10^\circ$ . Detailed methods to fabricate the SH surface and PDMS gels used in this study are described elsewhere [21,22].

$E$  of a PDMS gel can also be varied easily by using different wt% of silicone oil. In our experiment, we used 78, 80, and 82 wt% silicone oil gel to obtain  $E = 5 \pm 1$ ,  $1.5 \pm 0.3$ , and  $0.6 \pm 0.1 \text{ kPa}$ , respectively. The ratio (mass) of the sylgard 184 PDMS base and the curing agent was kept at 1 : 1. For the data presented below, the value of  $E$  for each gel sample was measured individually using a rheometer. The PDMS gels used here behave mostly as elastic solids; the viscous component can be safely ignored, since  $G''/G' \sim 0.05$ , where  $G''$  and  $G'$  are the loss and elastic moduli.

When a jet impacts a PDMS gel obliquely at an angle  $\theta_i$  and speed  $U$ , a dimple of depth  $h$  and width  $w$  is formed on the gel surface due to the pressure of the impact (inset I, Fig. 2). In our experiments, the Weber number  $We = 1 - 10$ ; at the lower end of this range, the jet should retain its cylindrical shape upon impact, whereas at the higher end, the jet is likely to flatten into a sheet, but recovers its cylindrical shape as it emerges from the dimple.

In both cases, the liquid exits the dimple (at an angle  $\theta_r$ ) as a stable cylindrical jet. After travelling a certain distance,

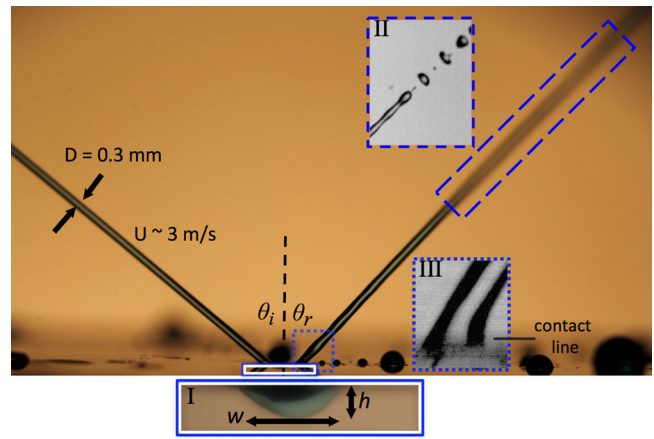


FIG. 2. The pressure of the impacting jet creates a dimple of depth  $h$  and width  $w$  on the PDMS gel, facilitating the jet rebound. Inset I shows the side view of the dimple, inset II shows the eventual breakup of the jet into droplets, while inset III shows the three-phase contact line of an exiting EtOH jet. Note that inset I was taken at a different focal plane from the jet above it, because the refractive index of the PDMS gel/silicone oil introduced an additional optical path length.

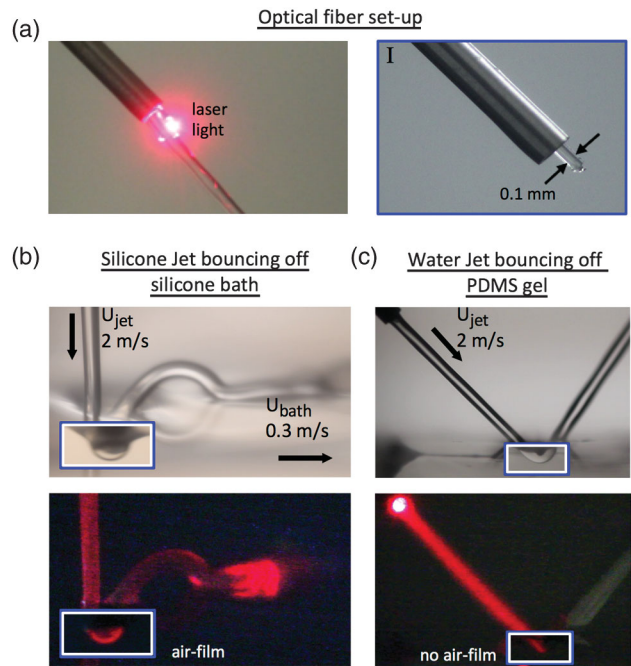


FIG. 3. (a) An optical fiber with clad diameter of 0.1 mm (inset I shown on the right) was placed coaxial with the needle to couple laser light into the liquid jet. (b) Laser light (red) followed the contour of the silicone oil jet as it bounced off a silicone oil bath, because of a stable air layer that separated the two. (c) In contrast, there was no air layer separating the water jet bouncing off a PDMS gel. Hence, the laser light passed through undeflected into the PDMS gel. A small amount of alumina particles and milk (0.05 wt% and 0.01 wt%, respectively) were added to silicone oil and water jets to act as light scatterers so that the laser path inside the jet could be visualized, with insignificant change to the surface tension (measured  $\Delta\gamma < 0.2 \text{ mN/m}$ ).

the liquid jet then breaks up into droplets of size  $\sim D$  and satellite droplets of size  $\ll D$ , due to Plateau-Rayleigh instability (inset II, Fig. 2; see also the Supplemental Material, Movie S2 [20]). We note that while a similar mechanism—dimple formation, followed by rebound—has been observed in the case of a liquid jet (Newtonian and non-Newtonian) bouncing off a bath of the same liquid, such rebound was only possible for low  $\gamma$  liquids, where there is a stable air layer separating the liquid jet and bath [13–16]. The existence of this air layer is crucial for liquid-liquid rebound; without it, the liquid jet (e.g., water) simply merges with the liquid bath [16,23,24].

In comparison, the jet rebound off a soft gel does not require an air layer; experimentally, no air layer was detected as described below. For low  $\gamma$  liquids, such as an ethanol solution (70 wt%,  $\gamma = 24$  mN/m), a three-phase contact line was always observed where the jet exited the dimple, ruling out the existence of a continuous air layer (Inset III, Fig. 2). For a water jet, this three-phase contact line was not readily observable. However, we were able to confirm the absence of the air layer by shining laser light into the water jet [Fig. 3(a)]. If there were an air layer—as is the case for a liquid jet (e.g. silicone oil) bouncing off a liquid bath—the liquid jet would act as an optical fiber and

the laser light would remain inside the jet, following its contour, due to total internal reflection [Fig. 3(b)]. In contrast, for a water jet bouncing off a PDMS gel, the laser light passed through undeflected into the PDMS gel [Fig. 3(c)]. This suggests that either there was no air layer or that the air layer was nanometric in size, such that there was evanescent wave coupling between the liquid jet and the gel. The latter seems implausible since at such a thickness, the air layer can easily be destabilized by van der Waals' interactions.

Intuitively, we should expect the rebound behavior of the jet to depend on the size and geometry of the dimple. For example, just to accommodate the jet, there should be a threshold dimple size  $h_{\min}, w_{\min} \sim D$ , for jetting to occur. For a small dimple,  $(w/2)/h \approx \tan \theta_i$ , i.e.,  $w \approx 2h \tan \theta_i$ . This is well obeyed when  $w < 2$  mm for a wide range of experimental conditions [Fig. 4(a)]. Since this indentation is an elastic response to the pressure of water impact  $\sim \rho U^2$ , we expect  $h/D$  to depend on  $\rho U_{\perp}^2/E$ , i.e.,  $h/D \sim (\rho U_{\perp}^2/E)^{\nu}$ , where  $\rho$  is the density of the liquid,  $U_{\perp} = U \cos \theta_i$  is the perpendicular component of the jet speed, and  $\nu$  is an unknown scaling exponent.

The raw data [Fig. 4(b)] show that  $h$  is linearly proportional to flow rate  $Q$ , which suggests that the correct scaling

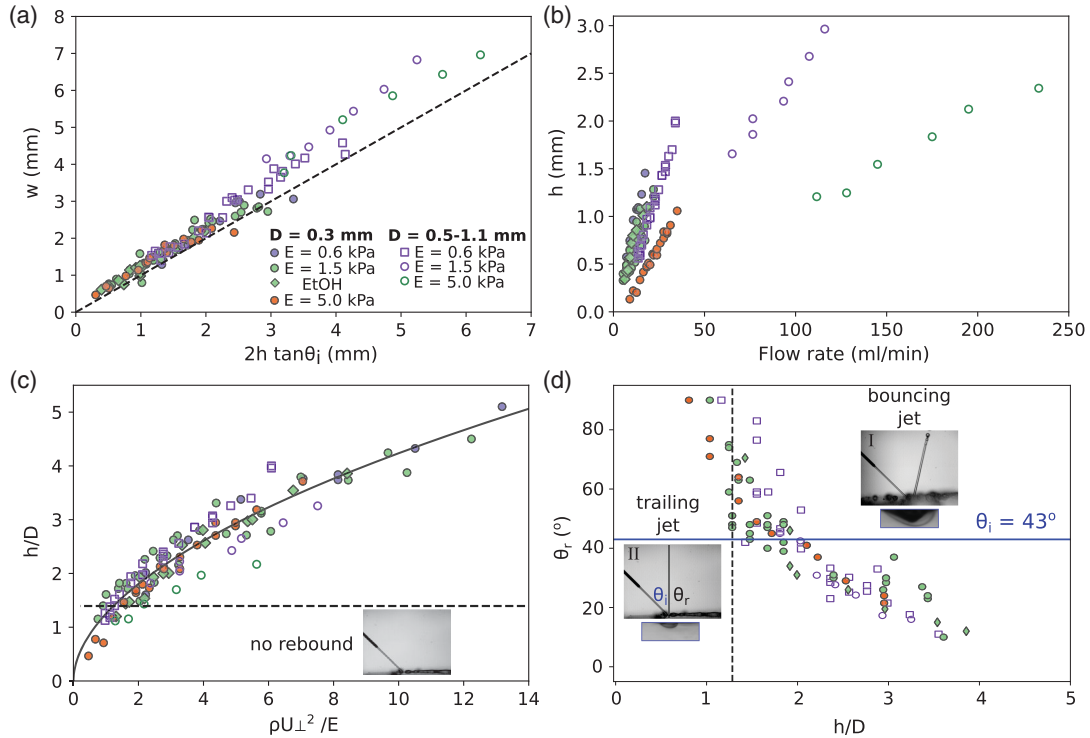


FIG. 4. (a) Dimple width  $w$  plotted against  $2h \tan \theta_i$ , where  $h$  is the dimple depth and  $\theta_i$  is the incident angle for liquid jets (diameter  $D = 0.29-1.1$  mm) impacting PDMS gels (Young's moduli  $E = 0.6-1.5$  kPa) at flow rates  $Q = 5-250$  ml/min. The liquid used was water, except for the data points labeled with green diamonds, which were obtained for 30 wt% ethanol (surface tension  $\gamma = 35$  mN/m). (b)  $h$  increases with increasing flow rate  $Q$ , albeit at different rates depending on exact experimental conditions. (c) The results in (b) can be collapsed into one curve, when  $h/D$  is plotted against  $\rho U_{\perp}^2/E$ , where  $\rho$  is the density of the liquid and  $U_{\perp}$  is the perpendicular component of the jet speed, i.e.,  $U \cos \theta_i$ . (d) The rebound angle  $\theta_r$  for a fixed  $\theta_i$  is a function of the ratio  $h/D$ . The transition from a bouncing jet (inset I) to a trailing jet (inset II) occurred at around  $h/D = 1.4$ .

should be  $h/D \sim (\rho U_{\perp}^2/E)^{1/2}$ , i.e.,  $\nu = 1/2$ . This was verified experimentally for liquid jets of different surface tensions (water and 30 wt% ethanol solution,  $\gamma = 72$  and 35 mN/m, respectively), different jet diameters  $D = 0.29\text{--}1.1$  mm, flow rates  $Q = 5\text{--}250$  ml/min, and impinging angles  $\theta_i = 30^{\circ}\text{--}50^{\circ}$  bouncing off PDMS gels with a range of Young's moduli  $E = 0.6\text{--}5$  kPa [Figs. 4(b) and 4(c)]. The best-fit line on Fig. 4(c) is the relation

$$h/D = 1.25(\rho U_{\perp}^2/E)^{1/2}. \quad (1)$$

Since the elastic energy stored in the deformation is equal to the work done by the impacting jet, we expect  $E\epsilon^2 \sim \rho U_{\perp}^2$ , i.e.,  $\epsilon \sim (\rho U_{\perp}^2/E)^{1/2}$ , where  $\epsilon$  is the characteristic strain in the system. Comparing this to Eq. (1), we find that  $h/D \approx \epsilon$ . Finally,  $h_{\min}/D$  was found to be 1.4, below which the jet rebound becomes unstable [dashed black line, Figs. 4(c) and 4(d)].

There is some departure from the general trend of Eq. (1) for  $h > 2.0$  mm [see purple and green unfilled circles in Figs. 4(b) and 4(c)], because  $h$  starts to approach the thickness of the PDMS gel, which was kept at 8 mm for all the experiments, and the effects of the underlying hard, solid substrate become apparent. For a given incident  $\theta_i$ , the rebound angle  $\theta_r$  is simply a function of  $h/D$  [Fig. 4(d)], and below  $h/D = 1.4$  (dashed vertical line),  $\theta_r$  approaches  $90^{\circ}$  precipitously, i.e., the jet transitions from bouncing (inset I) to trailing (inset II). Upon landing on the gel, the trailing jet initially moves in a straight line before starting to meander [25].

Looking at the data for the 30 wt% ethanol solution (green diamonds), we see that  $\gamma$  does not affect dimple size or shape and rebound direction. This is because  $h$  and  $w \sim \text{mm}$ ; the effect of  $\gamma$  becomes important only when the dimple size approaches the elastocapillary length,  $|S|/E$ , where  $|S|$  is the spreading parameter [11,26]. Typically,  $|S| \sim 10$  mN/m, and for  $E \sim 1$  kPa, this length is  $\sim 10$   $\mu\text{m}$  [27].

In summary, we have shown that a liquid jet with a wide range of  $\gamma = 24\text{--}72$  mN/m can bounce off a soft gel, irrespective of the gel's wetting properties and composition, by following the contour of the dimple formed upon impact. Our experimental data and dimensional analysis show that the size and geometry of the dimple determine (1) whether jetting is possible and (2) the direction of jetting. We have further shown that this jet rebound phenomenon is possible even when there is direct liquid-gel contact, which is unlike other jet rebound phenomena that require a stable air layer separating the jet and the substrate.

The strategy described in this Letter is fundamentally different from previous work: we demonstrate that the liquid repellency can be made independent of the surface tension of the liquid and wetting properties or structuring of the surface. Instead, it can simply be controlled by the

deformability of the soft substrate. The ability to tailor the Young's modulus of a flat material, with no micro- or nanotexturing or chemical functionalization, to repel both high- and low-surface-tension liquid jets, may have wide-ranging implications for the development of liquid-repellent surfaces and the science of wetting.

We would like to thank Prof. Michael Brenner, Prof. L. Mahadevan, and Prof. Kyoo-Chul Park for useful discussions. The work was supported partially by the ONR MURI Grant No. N00014-12-1-0875 (fluid dynamics studies) and the U.S. Department of Energy Award No. DE-SC0005247 (materials synthesis). We acknowledge support from the Harvard Materials Research Science and Engineering Center (MRSEC) through Grant No. DMR-1420570.

\*daniel@imre.a-star.edu.sg

†jaiz@seas.harvard.edu

- [1] D. Quéré, *Rep. Prog. Phys.* **68**, 2495 (2005).
- [2] T.-S. Wong, T. Sun, L. Feng, and J. Aizenberg, *MRS Bull.* **38**, 366 (2013).
- [3] X. J. Feng and L. Jiang, *Adv. Mater.* **18**, 3063 (2006).
- [4] D. Richard, C. Clanet, and D. Quéré, *Nature (London)* **417**, 811 (2002).
- [5] J. C. Bird, R. Dhiman, H.-M. Kwon, and K. K. Varanasi, *Nature (London)* **503**, 385 (2013).
- [6] Y. Liu, L. Moevius, X. Xu, T. Qian, J. M. Yeomans, and Z. Wang, *Nat. Phys.* **10**, 515 (2014).
- [7] C. Antonini, I. Bernagozzi, S. Jung, D. Poulikakos, and M. Marengo, *Phys. Rev. Lett.* **111**, 014501 (2013).
- [8] J. Eggers and E. Villermaux, *Rep. Prog. Phys.* **71**, 036601 (2008).
- [9] F. Celestini, R. Kofman, X. Noblin, and M. Pellegrin, *Soft Matter* **6**, 5872 (2010).
- [10] C. W. Extrand and Y. Kumagai, *J. Colloid Interface Sci.* **184**, 191 (1996).
- [11] B. Roman and J. Bico, *J. Phys. Condens. Matter* **22**, 493101 (2010).
- [12] R. W. Style, Y. Che, S. J. Park, B. M. Weon, J. H. Je, C. Hyland, G. K. German, M. P. Power, L. A. Wilen, J. S. Wettlaufer, and E. R. Dufresne, *Proc. Natl. Acad. Sci. U.S.A.* **110**, 12541 (2013).
- [13] A. A. Collyer and P. J. Fisher, *Nature (London)* **261**, 682 (1976).
- [14] M. Versluis, C. Blom, D. van der Meer, K. van der Weele, and D. Lohse, *J. Stat. Mech.* P07007 (2006).
- [15] S. Lee, E. Q. Li, J. O. Marston, A. Bonito, and S. T. Thoroddsen, *Phys. Rev. E* **87**, 061001 (2013).
- [16] M. Thrasher, S. Jung, Y. K. Pang, C.-P. Chuu, and H. L. Swinney, *Phys. Rev. E* **76**, 056319 (2007).
- [17] A. Yarin, *Annu. Rev. Fluid Mech.* **38**, 159 (2006).
- [18] X. Deng, F. Schellenberger, P. Papadopoulos, D. Vollmer, and H.-J. Butt, *Langmuir* **29**, 7847 (2013).
- [19] J. M. Kolinski, L. Mahadevan, and S. Rubinstein, *Europhys. Lett.* **108**, 24001 (2014).
- [20] See Supplemental Material at <http://link.aps.org/supplemental/10.1103/PhysRevLett.120.028006> for movies

- showing the stable rebound of a water jet off a hydrogel and its eventual breakup into microdroplets.
- [21] N. Vogel, R. A. Belisle, B. Hatton, T.-S. Wong, and J. Aizenberg, *Nat. Commun.* **4**, 2176 (2013).
- [22] N. MacCallum, C. Howell, P. Kim, D. Sun, R. Friedlander, J. Ranisau, O. Ahanotu, J. J. Lin, A. Vena, B. Hatton, T.-S. Wong, and J. Aizenberg, *ACS Biomater. Sci. Eng.* **1**, 43 (2015).
- [23] É. Lorceau, D. Quéré, and J. Eggers, *Phys. Rev. Lett.* **93**, 254501 (2004).
- [24] N. Wadhwa, P. Vlachos, and S. Jung, *Phys. Rev. Lett.* **110**, 124502 (2013).
- [25] N. Le Grand-Piteira, A. Daerr, and L. Limat, *Phys. Rev. Lett.* **96**, 254503 (2006).
- [26] P.-G. de Gennes, F. Brochard-Wyart, and D. Quere, *Capillarity and Wetting Phenomena* (Springer-Verlag, New York, 2008).
- [27] C. Duez, C. Ybert, C. Clanet, and L. Bocquet *Phys. Rev. Lett.* **104**, 084503 (2010).