

Polarization Selectivity in Vibrational Electron-Energy-Loss Spectroscopy

G. Radtke,^{1,*} D. Taverna,¹ N. Menguy,¹ S. Pandolfi,¹ A. Courac,¹ Y. Le Godec,¹ O. L. Krivanek,² and T. C. Lovejoy²

¹*Sorbonne Université, Muséum National d'Histoire Naturelle, UMR CNRS 7590, IRD, Institut de Minéralogie, de Physique des Matériaux et de Cosmochimie, IMPMC, 75005 Paris, France*

²*Nion Co., 11511 NE 118th Street, Kirkland, Washington 98034, USA*



(Received 19 September 2019; published 19 December 2019)

Orientation-dependent aloof-beam vibrational electron-energy-loss spectroscopy is carried out on uniaxial icosahedral $B_{12}P_2$ submicron crystals. We demonstrate that the high sensitivity of the signal to the crystal orientation allows for an unambiguous determination of the symmetry of normal modes occurring at the Brillouin zone center of this anisotropic compound. The experimental results are assessed using first-principles quantum mechanical calculations (density functional theory) of the dielectric response of the specimen. The high spatial resolution inherent to this technique when implemented in the transmission electron microscope thus opens the door to nanoscale orientation-dependent vibrational spectroscopy.

DOI: [10.1103/PhysRevLett.123.256001](https://doi.org/10.1103/PhysRevLett.123.256001)

Ultrahigh resolution electron-energy-loss spectroscopy (EELS) in the (scanning) transmission electron microscope [(S)TEM] has recently attracted considerable attention as an emerging technique to investigate the vibrational properties of condensed matter with an unprecedented spatial resolution [1–3]. When implemented in a nonpenetrating geometry, i.e., using an electron beam positioned at a finite distance away from the edge of the sample, energy loss processes are dominated by dipole scattering arising from long-range electric fields generated through lattice or molecular vibrations of polar specimens. This *aloof* geometry has recently proved very effective for imaging confined surface phonon modes in nanostructures [2,4] and highly beneficial for studying vibrational properties of beam-sensitive specimens [5–7] due to the drastic reduction of damage caused by the aloof electron beam when compared to more standard transmission geometries [8].

In this Letter, we add a new dimension to this approach by demonstrating that it can also be employed to assess the symmetry of normal modes occurring at the Brillouin zone center of anisotropic materials. Indeed, although the electron probe lacks the intrinsic angular selectivity of polarized photons used in optical spectroscopies, the scattering geometry in EELS provides a similar insight into the symmetry of vibrational excitations with the further advantage of a high spatial resolution. This is illustrated through the study of uniaxial icosahedral boron subphosphide $B_{12}P_2$ where phonon mode symmetry is unambiguously retrieved from spectra acquired on crystals with distinct orientations.

$B_{12}P_2$ is a member of the α -rhombohedral boron structure group that includes compounds such as α - B_{12} , $B_{12}As_2$, $B_{12}O_2$, or $B_{12}C_3$ and, as most of them, displays a number of technologically interesting properties. $B_{12}P_2$ is a wide band gap semiconductor (3.35 eV) [9], a thermoelectric with a

high positive Seebeck coefficient [10], and displays both high thermal and chemical stabilities as well as an extreme resistance to damage induced by high energy particle radiations [11,12]. This peculiar behavior is attributed to a self-healing mechanism whose origin has recently been proposed to lie in the very low activation energy for the diffusion and recombination of interstitial-vacancy pairs [13] and makes it a potential candidate for betavoltaics [12].

This compound crystallizes in the $R\bar{3}m$ rhombohedral space group. Its atomic structure is represented in Fig. 1 within the hexagonal triple cell. It consists in B_{12} icosahedra linked together either through B-B bonds along the c axis of the crystal or through B-P-B bonds in the perpendicular plane. Two crystallographically inequivalent boron sites are therefore present in the structure. The *polar* sites, represented with dark green atoms in Fig. 1, are located on six vertices of the 12-atom cluster to form the top and bottom triangular faces and are exclusively bonded to boron atoms, belonging either to the same or to an adjacent icosahedron. The *equatorial* sites, represented by light green atoms, form a puckered hexagon in the plane perpendicular to the c axis. As shown in Fig. 1, phosphorus cations are fourfold coordinated, forming bonds with another cation and with three adjacent equatorial boron atoms.

As for its symmetry, $B_{12}P_2$ is a uniaxial material, leading to EELS active modes with well-defined characteristics at the Γ point. The decomposition of the vibrational degrees of freedom on the irreducible representations of the crystal point group (D_{3d}) gives [14]

$$\Gamma_{\text{vib.}} = 5A_{1g} \oplus 2A_{1u} \oplus 2A_{2g} \oplus 5A_{2u} \oplus 7E_u \oplus 7E_g,$$

from which the $A_{2u} \oplus E_u$ acoustic modes should be removed to obtain the symmetry properties of the 39 remaining optical modes

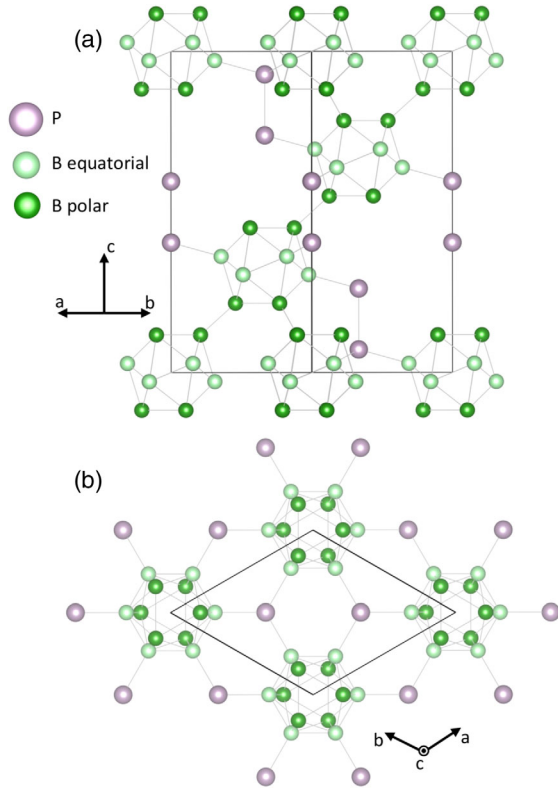


FIG. 1. Structure of $B_{12}P_2$: (a) Side view and (b) top view of the hexagonal triple cell. For clarity, parts of the lattice have been omitted in (b). Phosphorus atoms are in light purple, *polar* boron in deep green, and *equatorial* boron in light green.

$$\Gamma_{\text{op.}} = 5A_{1g} \oplus 2A_{1u} \oplus 2A_{2g} \oplus 4A_{2u} \oplus 6E_u \oplus 7E_g.$$

As EELS active modes in aloof geometry are necessarily those generating a nonzero electric polarization, we can conclude that a maximum of ten distinct peaks can be observed on the experimental spectra, four of A_{2u} and six of E_u symmetry, the former giving rise to a macroscopic polarization parallel to the c axis and the latter, to a polarization in the perpendicular plane.

The structure and vibrational properties of $B_{12}P_2$ have been determined in the framework of density functional theory (DFT) using the QUANTUM ESPRESSO [15] package. Calculations were performed in the 14-atom trigonal unit cell, using ultrasoft pseudopotentials [16] with plane-wave and charge-density cutoffs of 80 and 640 Ry, respectively. The Brillouin zone of the trigonal crystal was sampled using a $8 \times 8 \times 8$ $\mathbf{k}$ -point Monkhorst-Pack grid [17] and the generalized gradient approximation of Perdew, Burke, and Ernzerhof [18] (GGA-PBE) employed for exchange and correlation. This choice has been guided by the fairly accurate results usually provided by GGAs on the structural properties of strongly bound solids [19] and confirmed *a posteriori* by the excellent agreement obtained between optimized lattice parameters of $a = 5.990$ and $c = 11.845$ Å (hexagonal triple cell) and the

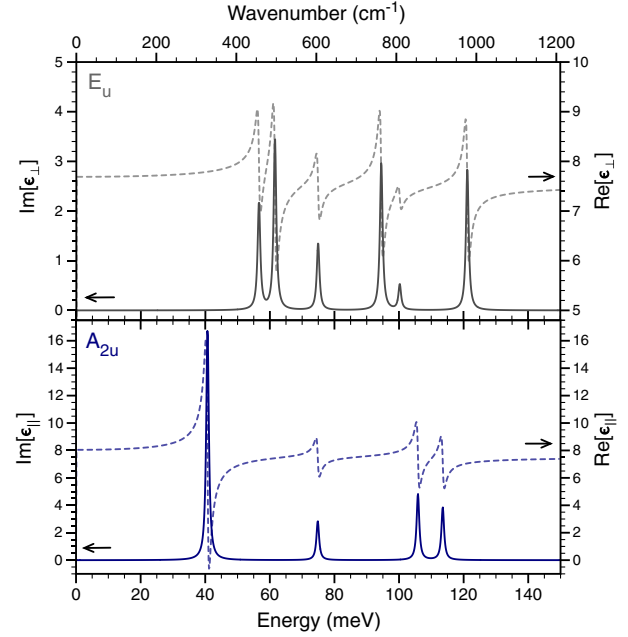


FIG. 2. Principal components of the local dielectric tensor $\hat{\epsilon}(\omega)$ of $B_{12}P_2$ in the infrared domain of frequencies calculated with a damping parameter $\Gamma_m = 4$ cm $^{-1}$. Component perpendicular ($\epsilon_{\perp}$) and parallel ($\epsilon_{\parallel}$) to the c axis of the crystal are shown in the lower and upper panels, respectively. Real and imaginary parts of the dielectric tensor components are represented, respectively, with dashed and solid lines.

average experimental values of 5.986 and 11.848 Å reported in Ref. [20] for stoichiometric $B_{12}P_2$. The dynamical matrix at the Γ point, electronic dielectric, and Born effective charge tensors obtained using density functional perturbation theory (DFPT) were employed to calculate the principal components of the low-frequency *local* ($\mathbf{q} = 0$) dielectric tensor $\hat{\epsilon}(\omega)$ shown in Fig. 2, entirely from first-principles [21,22]. Throughout this study, an average atomic mass of 10.811 a.m.u. was employed for boron, accounting for the relative natural abundance of ^{10}B and ^{11}B isotopes [23]. Consistently with our previous group-theoretical analysis, $\epsilon_{\parallel}(\omega)$ and $\epsilon_{\perp}(\omega)$, where the parallel and perpendicular subscripts refer to the c axis of the hexagonal triple cell, are, respectively, built from four resonances associated with the four modes of A_{2u} symmetry and six resonances associated with the six modes of E_u symmetry occurring at the Brillouin zone center of $B_{12}P_2$. A schematic representation of these modes is provided in the Supplemental Material [26]. Note that these modes could be distinguished in polarized infrared absorption (IR) experiments carried out on single crystals as the former are active when light is polarized parallel to the c axis and the latter when light is polarized in the perpendicular plane.

The local dielectric tensor is the key component entering the classical description of electron scattering by surface

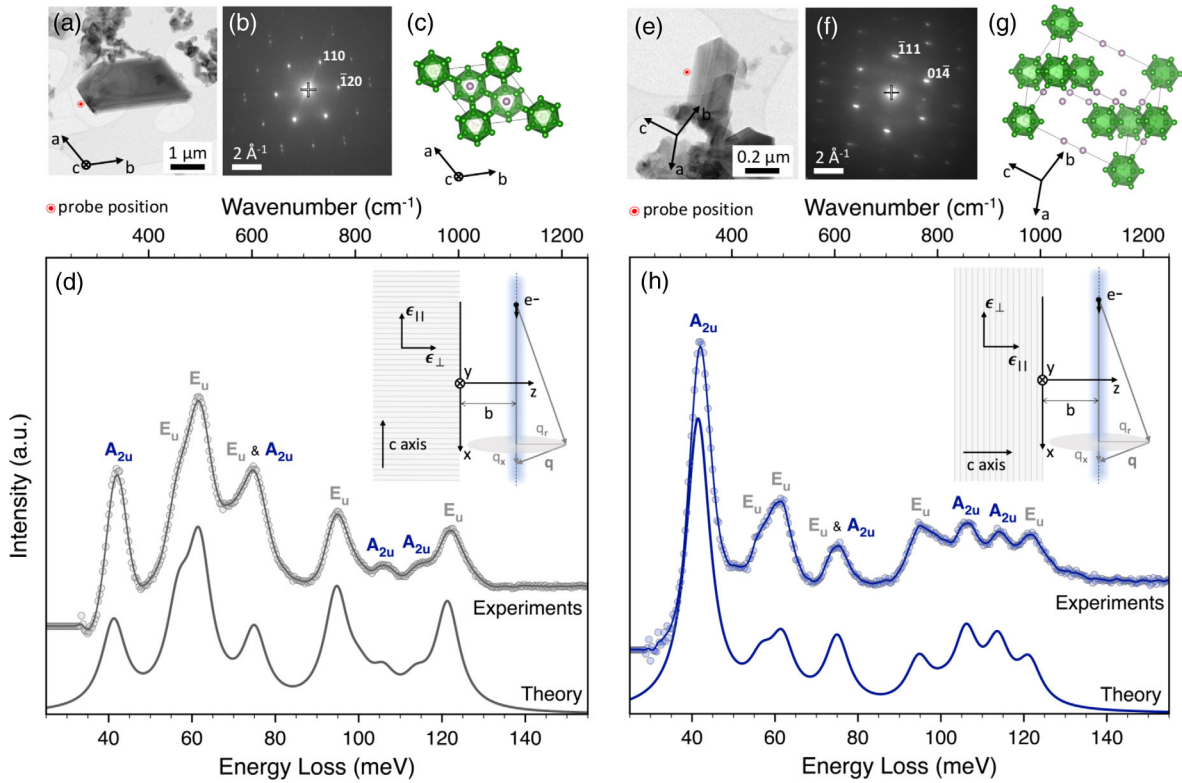


FIG. 3. Comparison between the experimental and theoretical vibrational EELS spectra of $B_{12}P_2$ for two microcrystals with different crystallographic orientations. (a) Conventional bright-field TEM image of the crystal acquired at 200 keV prior to the STEM experiment. The approximate beam position used for the 30 keV STEM-EELS experiment is indicated with a red point. (b) Indexed 30 keV diffraction pattern acquired in the STEM just before the EELS experiment showing that the electron beam propagates parallel to the c axis of the crystal. (c) Corresponding orientation of the hexagonal triple crystal cell. (d) Comparison between the experimental EELS spectrum acquired in aloof geometry at a distance $b \approx 10$ nm from the specimen edge and the theoretical spectrum calculated using Eq. (1) and the principal components of the dielectric tensor shown in Fig. 2. The symmetry of the modes corresponding to each peak is indicated. The idealized geometry employed in the calculations is shown in the inset. (e)–(h) Same as (a)–(d) with the c axis of the microcrystal close to perpendicular to the electron beam.

phonons occurring in aloof geometry in the context of the local continuum dielectric model [4,27]. In this classical, quasistatic approach [27–30], the energy-loss probability per unit angular frequency and path length, for an electron traveling along a rectilinear trajectory parallel to, and at a finite distance b from, the surface of a specimen occupying a half-space, is given by

$$\frac{d^2 P(\omega, b)}{d\omega dx} = \frac{e^2}{(2\pi)^2 v^2 \epsilon_0 \hbar} \times \int_{-\infty}^{\infty} \text{Im}[\alpha(\omega, q_x, q_y)] \frac{e^{-2b\sqrt{q_x^2 + q_y^2}}}{\sqrt{q_x^2 + q_y^2}} dq_y, \quad (1)$$

where v is the electron velocity and (q_x, q_y) are the components of the scattering vector in the surface plane [see the scattering geometry in the insets of Figs. 3(d) and 3(h) for the orientation of the cartesian coordinates]. This expression involves the imaginary part of the polarizability of the specimen, which maxima correspond to the energy of the surface vibrational excitations. When both the

surface and the electron beam are parallel to the c axis, the polarizability can be expressed as

$$\alpha(\omega) = \frac{\sqrt{\epsilon_{\perp}(\omega)[q_x^2 \epsilon_{\parallel}(\omega) + q_y^2 \epsilon_{\perp}(\omega)]/Q^2 - 1}}{\sqrt{\epsilon_{\perp}(\omega)[q_x^2 \epsilon_{\parallel}(\omega) + q_y^2 \epsilon_{\perp}(\omega)]/Q^2 + 1}}. \quad (2)$$

In this expression, $Q = \sqrt{q_x^2 + q_y^2}$ is the norm of the component of the scattering vector parallel to the surface [27]. It should be stressed here that Eq. (2) depends explicitly on the scattering vector, leading to an imbalance in the role played by the two dielectric components. On the contrary, for a surface perpendicular to the c axis of the crystal, the expression of the polarizability is particularly simple as it becomes independent of the scattering vector

$$\alpha(\omega) = \frac{\sqrt{\epsilon_{\parallel}(\omega)\epsilon_{\perp}(\omega) - 1}}{\sqrt{\epsilon_{\parallel}(\omega)\epsilon_{\perp}(\omega) + 1}}, \quad (3)$$

and only involves the geometrical mean of the two dielectric components [31].

In expressions (1) and (2), the component of the scattering vector along the electron trajectory is given by $q_x = \omega/v$ which, for a typical loss of 70 meV and a primary electron energy of 30 keV, is of the order of $10^{-4} \text{ \AA}^{-1}$. The amplitude of the perpendicular component [q_r in insets of Figs. 3(d) and 3(h)] is more difficult to assess as it is usually not limited by the relatively large collection angle used in the experiments, but most likely by the low- q filter term occurring in the integral of Eq. (1). A typical average value up to an order of magnitude larger than the parallel component can, however, be estimated based on Eq. (1), resulting in a scattering vector oriented predominantly in the plane perpendicular to the beam trajectory.

Anisotropy resulting from the differences between Eqs. (2) and (3) was measured experimentally on B_{12}P_2 microcrystals with different orientations. Polycrystalline B_{12}P_2 , synthesized by the ultrafast mechanochemical method through a reaction between BPO_4 , Mg, and MgB_2 [32], was crushed into powder and dispersed on a lacey carbon grid. A first TEM inspection of the specimen led to the identification of micron or submicron crystals with sharp edges located in large carbon film holes and distinct crystallographic orientations, as shown in Figs. 3(a) and 3(e). The specimen was then analyzed in a Nion U-HERMES 200 system operated at 30 kV. Diffraction patterns recorded prior to the EELS acquisition and shown in Figs. 3(b) and 3(f) illustrate the geometry of these experiments: for the crystal shown in (a), the c axis is parallel to the electron beam and parallel to the surface, whereas for the crystal shown in (e), the c axis is approximately perpendicular to the electron beam and to the surface. Figures 3(c) and 3(g) summarize these results by showing the hexagonal triple cell viewed along the beam direction.

Vibrational EELS spectra were acquired in aloof geometry at a distance of 10 nm from the edge of the specimen. The final spectra shown in Figs. 3(d) and 3(h) result from the acquisition of 5000 spectra of 50 ms each, subsequently realigned and summed, leading to an overall energy resolution of 6 meV. Convergence and collection semi-angles were set to $\alpha = \beta = 10 \text{ mrad}$. In both cases, a total number of eight peaks [33], including the low intensity shoulder of the peak located at 62 meV, is observed in the 40–125 meV energy range. The essential difference between the two spectra arises from the dramatic variations of the peak intensities induced by the crystal orientation.

In order to gain insight into the origin of these variations, theoretical spectra were calculated using Eq. (1), the dielectric components shown in Fig. 2, and the polarizabilities given in Eqs. (2) and (3). These last two expressions correspond to the simplified geometries shown in insets of Figs. 3(d) and 3(h). Although significant deviations from these idealized geometries are observed

in actual experiments, the predictions provided by the local continuum dielectric model reproduce very well the experimental results for both orientations. These results allow for precise symmetry assignment of each visible peak and lead to an important observation: whereas the intensity of the peaks associated with phonon modes of E_u symmetry is largely enhanced in the first orientation [see Fig. 3(d)], it is strongly reduced in the second [see Fig. 3(h)]. Conversely, the intensity of the peaks corresponding to phonons of A_{2u} symmetry is relatively weak in the first orientation but reinforced in the second. This behavior is a direct consequence of Eq. (2) where the larger perpendicular (q_y) component of the scattering vector strengthens the intensity of modes generating an in-plane polarization compared to the geometrical average of Eq. (3). The high sensitivity of the aloof-beam EELS signal to the crystal orientation therefore appears as a very efficient means to discriminate phonon modes according to the direction of the macroscopic polarization they are building, either parallel or perpendicular to the crystal c axis. This crystal orientation dependence can thus be employed to determine the symmetry of EELS active normal modes. Note that although similar information can be retrieved from polarized IR absorption experiments, the lack of sufficiently large single crystals, however, often hinders such analysis [24,25].

In conclusion, the present work demonstrates the capability of aloof-beam vibrational EELS to access the symmetry of phonon modes observed in anisotropic crystals. Distinct intensity variations are observed for peaks associated with phonon modes building macroscopic polarizations with different spatial orientations when changing the geometry of the experiment, i.e., changing the relative orientation of the electron beam and the surface with respect to the crystal axes. A great advantage of this approach resides in the high spatial resolution of EELS when implemented in a (S)TEM, therefore allowing us to carry out this type of analysis at the nanoscale.

This work was granted access to the HPC resources of IDRIS under the allocation 2019-A0060910820 attributed by GENCI (Grand Equipement National de Calcul Intensif). The authors thank V. A. Mukhanov for the sample synthesis as well as K. March, E. Balan, and P. Giura for very fruitful discussions. This work was supported by Innovation Program Satt IDF Innov. (Grant Agreement No. L14S495).

*guillaume.radtke@sorbonne-universite.fr

- [1] O. L. Krivanek, T. C. Lovejoy, N. Dellby, T. Aoki, R. W. Carpenter, P. Rez, E. Soignard, J. Zhu, P. E. Batson, M. J. Lagos, R. F. Egerton, and P. A. Crozier, *Nature (London)* **514**, 209 (2014).
- [2] M. J. Lagos, A. Trügler, U. Hohenester, and P. E. Batson, *Nature (London)* **543**, 529 (2017).

- [3] F. S. Hage, D. M. Kepaptsoglou, Q. M. Ramasse, and L. J. Allen, *Phys. Rev. Lett.* **122**, 016103 (2019).
- [4] H. Lourenço-Martins and M. Kociak, *Phys. Rev. X* **7**, 041059 (2017).
- [5] P. Rez, T. Aoki, K. March, D. Gur, O. L. Krivanek, N. Dellby, T. C. Lovejoy, S. G. Wolf, and H. Cohen, *Nat. Commun.* **7**, 10945 (2016).
- [6] J. A. Hachtel, J. Huang, I. Popovs, S. Jansone-Popova, J. K. Keum, J. Jakowski, T. C. Lovejoy, N. Dellby, O. L. Krivanek, and J. C. Idrobo, *Science* **363**, 525 (2019).
- [7] P. Crozier, T. Aoki, and Q. Liu, *Ultramicroscopy* **169**, 30 (2016).
- [8] R. F. Egerton, *Ultramicroscopy* **159**, 95 (2015).
- [9] G. A. Slack, T. F. McNelly, and E. A. Taft, *J. Phys. Chem. Solids* **44**, 1009 (1983).
- [10] Y. Kumashiro, T. Yokoyama, K. Sato, and Y. Ando, *J. Solid State Chem.* **154**, 33 (2000).
- [11] M. Carrard, D. Emin, and L. Zuppiroli, *Phys. Rev. B* **51**, 11270 (1995).
- [12] D. Emin, *J. Solid State Chem.* **179**, 2791 (2006).
- [13] S. P. Huber, E. Gullikson, C. D. Frye, J. H. Edgar, R. W. E. van de Kruijs, F. Bijkerk, and D. Prendergast, *Chem. Mater.* **28**, 8415 (2016).
- [14] P. M. A. Sherwood, *Vibrational Spectroscopy of Solids* (Cambridge University Press, Cambridge, England, 1972).
- [15] P. Giannozzi *et al.*, *J. Phys. Condens. Matter* **21**, 395502 (2009).
- [16] K. F. Garrity, J. W. Bennett, K. M. Rabe, and D. Vanderbilt, *Comput. Mater. Sci.* **81**, 446 (2014).
- [17] H. J. Monkhorst and J. D. Pack, *Phys. Rev. B* **13**, 5188 (1976).
- [18] J. P. Perdew, K. Burke, and M. Ernzerhof, *Phys. Rev. Lett.* **77**, 3865 (1996).
- [19] F. Tran, J. Stelzl, and P. Blaha, *J. Chem. Phys.* **144**, 204120 (2016).
- [20] G. A. Slack and K. E. Morgan, *J. Phys. Chem. Solids* **75**, 1054 (2014).
- [21] X. Gonze and C. Lee, *Phys. Rev. B* **55**, 10355 (1997).
- [22] S. Baroni, S. de Gironcoli, A. Dal Corso, and P. Giannozzi, *Rev. Mod. Phys.* **73**, 515 (2001).
- [23] Although previous studies (see, e.g., Refs. [24,25]) on IR absorption in B₁₂P₂ report the presence of split phonon bands built from a strong ¹¹B line and a weaker ¹⁰B shoulder at higher energy, they were not distinguishable in the present experiments due to our limited energy resolution. We therefore only considered an averaged boron atomic mass in the calculations.
- [24] H. J. Becher and F. Thévenot, *Z. Anorg. Allg. Chem.* **410**, 274 (1974).
- [25] H. Werheit, U. Kuhlmann, K. Shiraib, and Y. Kumashiro, *J. Alloys Compd.* **233**, 121 (1996).
- [26] See Supplemental Material at <http://link.aps.org/supplemental/10.1103/PhysRevLett.123.256001> for a schematic representation of the atomic displacements associated with the modes contributing to the dielectric tensor.
- [27] G. Radtke, D. Taverna, M. Lazzeri, and E. Balan, *Phys. Rev. Lett.* **119**, 027402 (2017).
- [28] P. Batson, *Ultramicroscopy* **11**, 299 (1983).
- [29] A. Howie, *Ultramicroscopy* **11**, 141 (1983).
- [30] A. A. Govyadinov, A. Konečná, A. Chuvilin, S. Vélez, I. Dolado, A. Y. Nikitin, S. Lopatin, F. Casanova, L. E. Hueso, J. Aizpurua, and R. Hillenbrand, *Nat. Commun.* **8**, 95 (2017).
- [31] A. A. Lucas and J. P. Vigneron, *Solid State Commun.* **49**, 327 (1984).
- [32] V. A. Mukhanov, D. Vrel, P. S. P. Sokolov, Y. Le Godec, and V. Solozhenko, *Dalton Trans.* **45**, 10122 (2016).
- [33] Only eight peaks are visible on the experimental spectra out of a total of ten predicted EELS active modes. This is due to both an overlap of two modes of A_{2u} and E_u symmetries occurring around 75 meV (see Fig. 2) and to the low intensity of the E_u mode at 100 meV which is not resolved with our energy resolution.