

Shear Softening in a Metallic Glass: First-Principles Local-Stress Analysis

I. Lobzenko^{*} and Y. Shihara

Toyota Technological Institute, Hisakata, Tempaku-ku, Nagoya 468-8511, Japan

T. Iwashita

Department of Integrated Science and Technology, Oita University, Oita 870-1192, Japan

T. Egami

*University of Tennessee, Knoxville, Tennessee 37996, USA
and Oak Ridge National Laboratory, Oak Ridge, Tennessee 37831, USA*



(Received 23 August 2019; accepted 28 January 2020; published 27 February 2020)

Metallic glasses deform elastically under stress. However, the atomic-level origin of elastic properties of metallic glasses remain unclear. In this Letter using *ab initio* molecular dynamics simulations of the $\text{Cu}_{50}\text{Zr}_{50}$ metallic glass under shear strain, we show that the heterogeneous stress relaxation results in the increased charge transfer from Zr to Cu atoms, enhancing the softening of the shear modulus. Changes in compositional short-range order and atomic position shifts due to the nonaffine deformation are discussed. It is shown that the Zr subsystem exhibits a stiff behavior, whereas the displacements of Cu atoms from their initial positions, induced by the strain, provide the stress drop and softening.

DOI: 10.1103/PhysRevLett.124.085503

Amorphous materials formed by metal atoms, usually referred to as metallic glasses (MG) or glassy metals, have gained significant attention after the procedure of mass production of the bulk form of such materials had been developed in the 1990s [1,2], made possible by the discovery of glass-forming alloys requiring relatively low cooling rates of $<100 \text{ K s}^{-1}$ [3]. This enabled broad applications of MGs, for instance, for nanoimprinted technology, bioimplants, and coating, to name a few examples [2,4].

Along with the applications, metallic glasses have received intense scientific interest. One of the striking features of MGs is shear modulus softening (SMS), namely the shear modulus of MGs is significantly lower than that of crystalline counterparts [5]. This phenomenon has been extensively studied theoretically with assumptions being supported by computer simulations in a number of early [6,7] and more recent [8–11] works, and the microscopic origin has been attributed to nonaffine heterogeneous atomic motions during deformation. However, the precise atomic mechanisms of SMS remain elusive. Particularly, little quantum level understanding of SMS has been achieved [9].

In the case of crystalline materials, inelastic behavior is governed by the well-defined lattice defects in the periodic structure. However, attempts of defining defects in glasses face a formidable conceptual and practical barrier because of structural disorder. A number of theories of deformation in MG were proposed, among which the most widely used relies on the so-called shear transformation zone (STZ) [12–14]. It attributes the deformation in amorphous material to the emergence and development of regions

with higher mobility. Despite advances in the STZ theory, a number of its key features remain veiled. For example, many simulations and experiments show contradictory results for STZ sizes, from a few atoms to several hundred, and also the precise physical picture of the STZ is missing [15–18]. Furthermore, the particular mechanism of STZ emergence is yet to be understood.

Advances in modern computational methods allow one to obtain insights into the deformation behavior of individual atoms. One of the most accurate atomistic modeling methods is based on the density functional theory (DFT), which provides the evaluation of structural parameters with accuracy up to 1% [19]. This approach is effective in defining the starting point of shear transformation zone in metallic glass since relatively small structures (order of 20 atoms) are involved in the STZ [20]. In order to examine the local stress state around the STZ, which is highly heterogeneous at the microscopic scale, we use the atomic-level stresses analysis [21–23], coupled with the DFT calculation [24].

In the current Letter, we study $\text{Cu}_{50}\text{Zr}_{50}$ glass under shear strain. The choice of the system is dictated by the fact that a large amount of data are available for CuZr alloys in both crystalline and glassy structures [24,25]. It is known that the CuZr glass could be obtained in a wide composition range. Therefore, the influence of the stoichiometry presented in the current work may be verified by future experimental work.

This Letter is organized as follows. At first, the details on the structures under study and settings for the first principle calculations are given. Next, the main results are presented

and discussed with emphasis on the fundamental properties of the structure leading to shear modulus softening.

Initially, a random atomic configuration of 96 atoms was prepared at a density of 57.1 nm^{-3} [25]. The first principle molecular dynamics (FPMD) simulation at 3000 K for 2 ps was performed under the micro-canonical ensemble conserving number of particles, system's volume and the total energy (NVE) ensemble with periodic boundary conditions to thermalize the original structure, thus obtaining an equilibrium liquid structure. The time step of the simulations was 2 fs. The system was quenched to a supercooled state at 1200 K, which led to the relatively stable glass structure, then FPMD was performed for 1 ps. Next the system was gradually cooled down to a glass state at 700 K with a cooling rate of 0.5 K/fs, and in addition, another thermalization at 300 K was performed for 1 ps to stabilize the glass structure. Finally, the glass structure was relaxed to 0 K by applying energy minimization using the conjugate gradient method under zero macroscopic stress, allowing the box size and shape to vary during the iterations. The described procedure provides us with an equilibrium structure of the metallic glass ready for subsequent analyses.

In our study, the quantum mechanical approach in the framework of density functional theory was used, which is implemented in the Vienna *ab initio* simulation package (VASP) [26]. The generalized gradient approximation was used for the exchange-correlation energy, which is essential for the achievement of high accuracy. The energy cutoff regulating the number of basis functions was set to 410 eV. Because of the relatively large size of the system, only the Γ point was used in the reciprocal space. The convergence of the self-consistent calculation was enhanced by the Methfessel-Paxton method [27] with the smearing of 0.1 eV. In the energy minimization process, structures were optimized until the atomic forces become less than 0.01 eV/\AA .

To model the response of the CuZr system to strain, the athermal quasistatic shear (AQS) simulations, which are usually used in the framework of classical molecular dynamics, was performed at the quantum mechanics level using the FPMD. Firstly the glass structure at 0 K obtained by cooling is uniformly deformed with a simple shear strain ε_{xy} (affine deformation). Next, atomic positions optimization is performed with the box geometry fixed. That results in the stress relaxation from the affine state during the energy minimization. To improve statistics, four different original structures, each of which is deformed independently at the same strain in six different directions, were prepared and the results were averaged over 24 samples ($=4 \times 6$) in total.

In the process of analyzing the mechanical properties of materials under strain, local stress calculation is a standard tool to unveil atomic-level correlations. Nevertheless, until recently that tool was available only in the classical approximation. Lately, several approaches were proposed allowing the calculation of atomic level stress in a

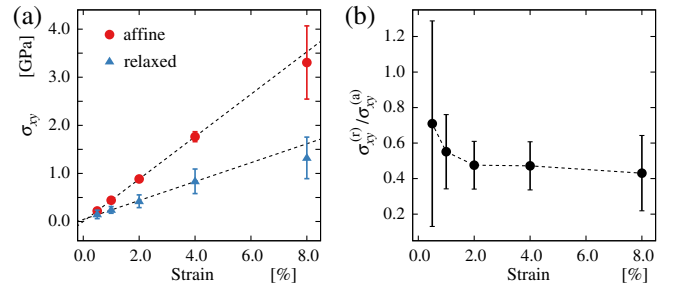


FIG. 1. (a) Stress-strain curves of $\text{Cu}_{50}\text{Zr}_{50}$ glass for affine and relaxed structures. (b) Ratio of relaxed stress $\sigma_{xy}^{(r)}$ to affine stress $\sigma_{xy}^{(a)}$ for various shear strains. Vertical bars show errors due to averaging (see discussion in text).

quantum-mechanical framework (see [24] for the detailed discussion of differences between those approaches). In particular, in this technique, the local stress is obtained as the strain derivative of local energy assigned to a single atom, as it is done in [28] and [24]. The calculations were performed using the open source package for material explorer (OpenMX), which utilizes the orbital-based energy decomposition scheme [29]. Such approach allows direct calculation of the derivatives of atomic energy with respect to the strain tensor.

Figure 1(a) shows stress as a function of strain for several shear strains (0.005, 0.01, 0.02, 0.04, 0.08). To capture the effect of shear modulus softening [9], under particular strain we analyzed two structures: the *affine* one (obtained directly from the original structure by applying affine strain) and the *relaxed* one (obtained after performing the optimization of atomic positions in the deformed structure). We see that stress is linearly proportional to applied strain for both cases of deformation. The estimated shear modulus is 44 GPa for the affine deformation and 21 GPa for the relaxed deformation. That is to say, the stress decreases during the relaxation process from the affine state by about 50%, as shown in Fig. 1(b), which is consistent with previous results based on classical AQS simulations (see [30] as an example).

In order to study the origin of the stress drop, we decomposed the macroscopic stress into the contributions of individual atoms and investigated the responses of the atomic-level stress under the shear for Cu and Zr. As shown in Fig. 2(a), the local stress analysis revealed a fascinating behavior. The local stress of Zr increases positively, as expected, with the strain for affine and relaxed structures, whereas the local stress of Cu becomes more negative with the strain, which is a quite unusual opposite behavior. Also, it can be seen that the relaxation decreases the magnitude of the stress on each atom, and the deviation, $\delta = (\sigma_{\text{relaxed}} - \sigma_{\text{affine}}) / |\sigma_{\text{affine}}|$ of the stress from the affine stress is plotted in Fig. 2(b). Interestingly Zr atoms show a negative contribution to the stress drop, while Cu atoms have a positive contribution. The origin of this behavior will be discussed later. At the highest strain of 8%, the

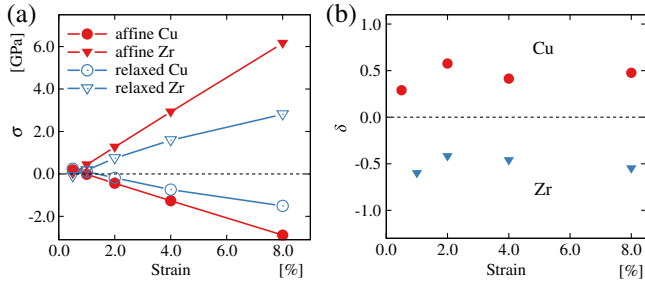


FIG. 2. (a) Shear stress in the affine and relaxed structures for Cu₅₀Zr₅₀ under shear strain. Red filled circles (triangles) show Cu (Zr) contribution to the stress in the affine structure, while blue empty circles (triangles) show Cu (Zr) contribution to stress in the relaxed structure. (b) Deviation [$\delta = (\sigma_{\text{relaxed}} - \sigma_{\text{affine}})/|\sigma_{\text{affine}}|$] of the xy component of stress in the relaxed system from the xy component of stress in the affine system. Red circles (blue triangles) represent Cu (Zr) atoms.

change in the stress corresponds to 1.38 GPa for Cu atoms and -3.31 GPa for Zr atoms, thus leading to the stress drop of -1.93 GP in total. Therefore, we see that the change in the local environment around Zr atoms should be mainly contributing to the total stress drop.

We investigate the role of charge on the stress drop under deformation. Figure 3 shows the strain dependence on the charge transfer, δQ , between the affine and the relaxed states for Cu and Zr atoms. Units of δQ are number of electrons per atom. At small strains ($\epsilon \leq 4\%$) Cu atoms gain more charge during relaxation, whereas Zr atoms lose it. These results indicate that the nonaffine relaxation enhances charge transfer from Zr to Cu, which is explained by the fact that the original structure obtained by rapid quench is unstable and deformation leads to the formation of more bonds between Cu and Zr, resulting in a more stable structure. At the highest strain of 8%, the sign of δQ becomes opposite, which may be due to the plastic flow far from the elastic region which tends to increase the effective temperature of the system and rejuvenate it [31].

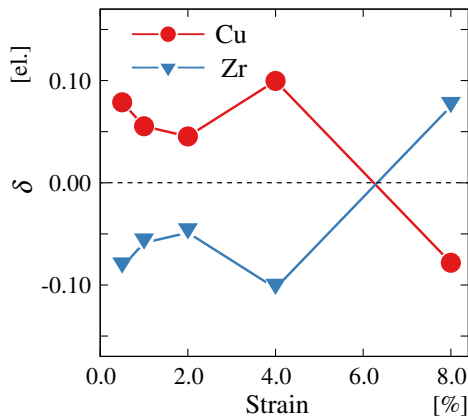


FIG. 3. Averaged total charge difference (δQ , relaxed to affine) expressed in number of electrons for Cu (red circles) and Zr (blue triangles) atoms with shear strain.

Finally, we show a clear correlation between the local shear stress deviation [$\delta = (\sigma_{\text{relaxed}} - \sigma_{\text{affine}})/|\sigma_{\text{affine}}|$] and charge difference δQ for small strains in Fig. 4(a). The data for the highest 8% strain beyond the elastic region was not included in the Figure. Particular example of the structure rearrangement and associated charge change of an atom can be found in the Supplemental Material [32]. We can conclude that, during the relaxation process, Cu gains charge, which positively increases the stress, whereas Zr loses charge, which makes the stress more negative. It is worth mentioning that there is no direct correlation between the atomic-level pressure deviation and δQ , although the data are not shown here.

To show the difference in the behavior of the Cu and Zr subsystems under strain, let us discuss the three-atoms angle change induced by the relaxation of atom positions from the affine structure. For each atom, we found closest neighbors of the same type. Next, for that group of atoms, the change of all unique three-atoms angles was calculated with the targeted atom being the vertex. All angle change values were averaged and associated with each atom type [see Fig. 5(a)]. The optimization process for the system under the 8% shear strain changes angles of the Cu subsystem by the value of 7.06 degrees, while for the Zr subsystem that parameter equals only to 2.24 degrees. The Cu d -electron states are full and do not participate in bonding, whereas the Zr d states are only partially filled and form covalent bonds [33]. The significant difference in the changes in angle induced by relaxation between Cu and Zr is consistent with this difference in the d -states occupation.

Taking only the neighbors of the same type, we can analyze the Cu subsystem and the Zr subsystem separately. However, the interplay between the Cu and Zr subsystems can only be understood if we take into account the types of neighboring atoms (see the Supplemental Material [32] for more data). The Cu subsystem is rearranged significantly during the relaxation process, resulting in the stress of an

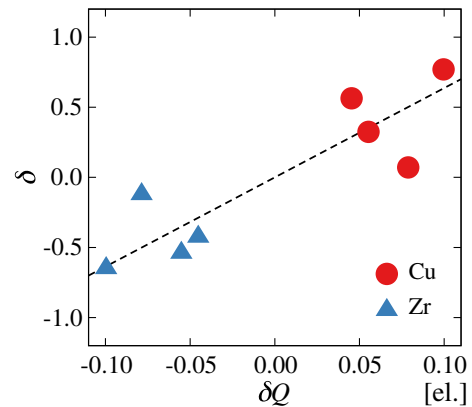


FIG. 4. Correlation between the local stress deviation [$\delta = (\sigma_{\text{relaxed}} - \sigma_{\text{affine}})/|\sigma_{\text{affine}}|$] and the change in atomic charge ($\delta Q = Q_{\text{relaxed}} - Q_{\text{affine}}$) for Cu₅₀Zr₅₀ under elastic deformation. The dashed line is a guide for eyes.

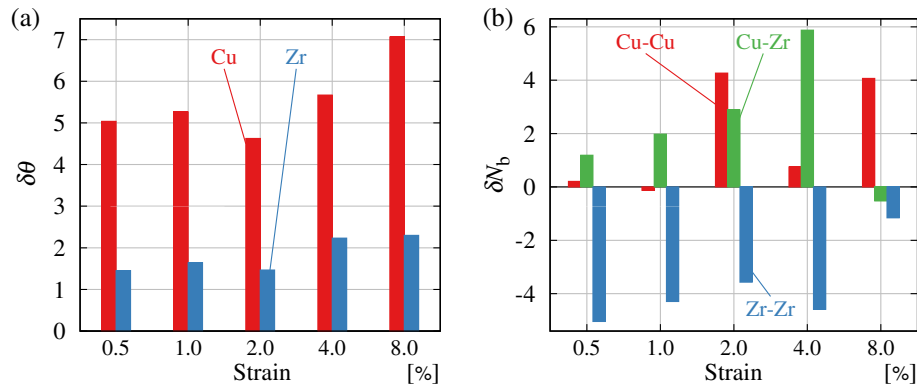


FIG. 5. Relaxation induced changes of Cu and Zr subsystems for studied shear strain values. (a) Change in same type angles (see discussion in text). (b) Change in the number of chemical bonds.

opposite sign, whereas the Zr-Zr angles are affected only slightly. At the same time, the Zr-Cu compositional short-range order (CSRO) is changed by deformation [see Fig. 5(b)]. The fraction of the Zr-Cu pairs is increased at the expense of the Zr-Zr pairs. The increased CSRO induces more charge transfer, and the lowering of the potential energy, resulting in softening. However, the CSRO of the system before deformation depends on the condition of the system preparation through the fictive temperature. When we start with the system with a high degree of CSRO, deformation could degrade the CSRO, rather than to enhance it as observed here, resulting in a lesser amount of softening. Such a possibility remains to be studied.

Compelling, we found that the Cu subsystem is affected more strongly by deformation than the Zr subsystem. However, deformation decreases the number of Zr-Zr bonds and increases the Zr-Cu neighbors, thus increasing the charge transfer. Consequently, the stress on Cu is reduced by deformation, leading to the shear softening. Thus, in a $\text{Cu}_{50}\text{Zr}_{50}$ system, not only a geometrical rearrangement of atoms but also a change in a CSRO contributes to the softening of shear modulus.

In summary, the effect of elastic deformation on the electronic states in metallic glass is studied under shear strain by means of *ab initio* calculations. The simulations of $\text{Cu}_{50}\text{Zr}_{50}$ glassy alloy under shear strain show that atoms undergo nonaffine deformation even in the elastic regime, accompanied by substantial charge transfer. In particular the Cu subsystem is severely rearranged under the shear strain, surprisingly resulting in the shear stress of the opposite sign on Cu atoms. On the other hand the Zr subsystem deforms in a nearly affine manner. Deformation produces increased Zr-Cu CSRO, decreasing Zr-Zr bonds, which leads to increased charge transfer. This work demonstrates that the change in the CSRO contributes to the softening of the shear modulus through increased charge transfer, along with the geometrical transformation. The evidence from our results points toward the need of considering the effect of the deformation on the CSRO in metallic glasses.

Y. S. is grateful to M. Kohyama and T. Ozaki for discussion and comments. This work was partly supported by Grant-in-Aid for Scientific Research in Innovative Areas to Y. S. (Grants No. 26109705 and No. 19H05177). T. E. was supported by the U.S. Department of Energy, Office of Science, Basic Energy Sciences, Materials Science and Engineering Division. T. I. was supported by JSPS KAKENHI Grant No. JP19K03771.

*Corresponding author.

ivan.lobzenko@gmail.com

- [1] A. Inoue, T. Zhang, and T. Masumoto, Production of amorphous cylinder and sheet of $\text{La}_{55}\text{Al}_{25}\text{Ni}_{20}$ alloy by a metallic mold casting method, *Mater. Trans., JIM* **31**, 425 (1990).
- [2] A. Inoue and A. Takeuchi, Recent development and application products of bulk glassy alloys, *Acta Mater.* **59**, 2243 (2011).
- [3] W. Johnson, Bulk glass-forming metallic alloys: Science and technology, *MRS Bull.* **24**, 42 (1999).
- [4] G. Kumar, A. Desai, and J. Schroers, Bulk metallic glass: The smaller the better, *Adv. Mater.* **23**, 461 (2010).
- [5] L. Davis, Mechanics of metallic glasses, in *Rapidly Quenched Metals* (Massachusetts Institute of Technology, Cambridge, 1976), pp. 369–391.
- [6] D. Weaire, M. Ashby, J. Logan, and M. Weins, On the use of pair potentials to calculate the properties of amorphous metals, *Acta Metall.* **19**, 779 (1971).
- [7] Y. Suzuki and T. Egami, Shear deformation of glassy metals: Breakdown of cauchy relationship and anelasticity, *J. Non-Cryst. Solids* **75**, 361 (1985).
- [8] W. Dmowski, T. Iwashita, C.-P. Chuang, J. Almer, and T. Egami, Elastic Heterogeneity in Metallic Glasses, *Phys. Rev. Lett.* **105**, 205502 (2010).
- [9] T. Egami, T. Iwashita, and W. Dmowski, Mechanical properties of metallic glasses, *Metals* **3**, 77 (2013).
- [10] S. Saw and P. Harrowell, Rigidity in Condensed Matter and Its Origin in Configurational Constraint, *Phys. Rev. Lett.* **116**, 137801 (2016).

- [11] H.-B. Yu, R. Richert, and K. Samwer, Correlation between viscoelastic moduli and atomic rearrangements in metallic glasses, *J. Phys. Chem. Lett.* **7**, 3747 (2016).
- [12] A. Argon, Plastic deformation in metallic glasses, *Acta Metall.* **27**, 47 (1979).
- [13] A. Argon and H. Kuo, Plastic flow in a disordered bubble raft (an analog of a metallic glass), *Mater. Sci. Eng.* **39**, 101 (1979).
- [14] J. S. Langer, Dynamics of shear-transformation zones in amorphous plasticity: Formulation in terms of an effective disorder temperature, *Phys. Rev. E* **70**, 041502 (2004).
- [15] J. D. Ju, D. Jang, A. Nwankpa, and M. Atzmon, An atomically quantized hierarchy of shear transformation zones in a metallic glass, *J. Appl. Phys.* **109**, 053522 (2011).
- [16] I.-C. Choi, Y. Zhao, B.-G. Yoo, Y.-J. Kim, J.-Y. Suh, U. Ramamurty, and J. il Jang, Estimation of the shear transformation zone size in a bulk metallic glass through statistical analysis of the first pop-in stresses during spherical nanoindentation, *Scr. Mater.* **66**, 923 (2012), viewpoint set no. 49: Strengthening effect of nano-scale twins.
- [17] C. A. Schuh, A. C. Lund, and T. Nieh, New regime of homogeneous flow in the deformation map of metallic glasses: Elevated temperature nanoindentation experiments and mechanistic modeling, *Acta Mater.* **52**, 5879 (2004).
- [18] D. Pan, A. Inoue, T. Sakurai, and M. W. Chen, Experimental characterization of shear transformation zones for plastic flow of bulk metallic glasses, *Proc. Natl. Acad. Sci. U.S.A.* **105**, 14769 (2008).
- [19] W. Kohn, Nobel lecture: Electronic structure of matter-wave functions and density functionals, *Rev. Mod. Phys.* **71**, 1253 (1999).
- [20] Y. Fan, T. Iwashita, and T. Egami, Crossover From Localized to Cascade Relaxations in Metallic Glasses, *Phys. Rev. Lett.* **115**, 045501 (2015).
- [21] T. Egami, K. Maeda, and V. Vitek, Structural defects in amorphous solids a computer simulation study, *Philos. Mag. A* **41**, 883 (1980).
- [22] T. Egami, Elementary excitation and energy landscape in simple liquids, *Mod. Phys. Lett. B* **28**, 1430006 (2014).
- [23] T. Egami, Y. Fan, and T. Iwashita, Mechanical deformation in metallic liquids and glasses: From atomic bond-breaking to avalanches, in *Avalanches in Functional Materials and Geophysics*, edited by E. K. Salje, A. Saxena, and A. Planes (Springer International Publishing, Cham, 2017), pp. 199–225.
- [24] D. M. Nicholson, M. Ojha, and T. Egami, First-principles local stress in crystalline and amorphous metals, *J. Phys. Condens. Matter* **25**, 435505 (2013).
- [25] N. Mattern, A. Schops, U. Kühn, J. Acker, O. Khvostikova, and J. Eckert, Structural behavior of $\text{Cu}_x\text{Zr}_{100-x}$ metallic glass ($x = 35\text{--}70$), *J. Non-Cryst. Solids* **354**, 1054 (2008).
- [26] The VASP website, <https://www.vasp.at>.
- [27] M. Methfessel and A. T. Paxton, High-precision sampling for Brillouin-zone integration in metals, *Phys. Rev. B* **40**, 3616 (1989).
- [28] Y. Shihara, M. Kohyama, and S. Ishibashi, Ab initio local stress and its application to Al (111) surfaces, *Phys. Rev. B* **81**, 075441 (2010).
- [29] The openmx web-site, <http://www.openmx-square.org/>.
- [30] A. Nakamura, Y. Kamimura, K. Edagawa, and S. Takeuchi, Elastic and plastic characteristics of a model CuZr amorphous alloy, *Mater. Sci. Eng. A* **614**, 16 (2014).
- [31] W. Dmowski, Y. Yokoyama, A. Chuang, Y. Ren, M. Umemoto, K. Tsuchiya, A. Inoue, and T. Egami, Structural rejuvenation in a bulk metallic glass induced by severe plastic deformation, *Acta Mater.* **58**, 429 (2010).
- [32] See the Supplemental Material at <http://link.aps.org/supplemental/10.1103/PhysRevLett.124.085503> for the distribution of the difference in atomic stress at each strain value.
- [33] W. Dmowski, S. Gierlotka, Z. Wang, Y. Yokoyama, B. Palosz, and T. Egami, Pressure induced liquid-to-liquid transition in Zr-based supercooled melts and pressure quenched glasses, *Sci. Rep.* **7**, 6564 (2017).