

## Topological Phases in Graphene Nanoribbons Tuned by Electric Fields

Fangzhou Zhao<sup>1,2</sup>, Ting Cao<sup>1,2,3</sup> and Steven G. Louie<sup>1,2,\*</sup>

<sup>1</sup>Department of Physics, University of California at Berkeley, Berkeley, California 94720, USA

<sup>2</sup>Materials Sciences Division, Lawrence Berkeley National Laboratory, 1 Cyclotron Road, Berkeley, California 94720, USA

<sup>3</sup>Department of Materials Science and Engineering, University of Washington, Seattle, Washington 98195, USA

(Received 11 February 2021; accepted 8 September 2021; published 12 October 2021)

Graphene nanoribbons (GNRs) possess distinct symmetry-protected topological phases. We show, through first-principles calculations, that by applying an experimentally accessible transverse electric field, certain boron and nitrogen periodically codoped GNRs have tunable topological phases. The tunability arises from a field-induced band inversion due to an opposite response of the conduction- and valence-band states to the electric field. With a spatially varying applied field, segments of GNRs of distinct topological phases are created, resulting in a field-programmable array of topological junction states, each may be occupied with charge or spin. Our findings not only show that electric field may be used as an easy tuning knob for topological phases in quasi-one-dimensional systems, but also provide new design principles for future GNR-based quantum electronic devices through their topological characters.

DOI: 10.1103/PhysRevLett.127.166401

The topology of a crystal's electronic structure, on par with its band structure and electron filling, plays an essential role in its electronic properties [1–3]. For example, joining two insulators of different topological classes produce robust junction states in the band gap of these insulators [2–6]. Recently, a wide range of graphene nanoribbons (GNRs), including the armchair, cove-edged, and chevron GNRs, have been shown to host rich electronic topological phases depending on their width, edge shape, and end terminations [7–10]. Moreover, the recent rapid development of bottom-up synthesis of GNRs from precursor molecules enables atomically precise design of a large variety of GNRs, including control of widths [11–13], dopant atoms [14–16], and diverse edge shapes [17–20]. Such synthesis capabilities have led to the striking experimental discovery of 1D superlattices formed by alternating segments of topologically distinct GNRs which have been measured to host a one-dimensional array of topological junction states [21,22], as predicted by theory [7].

Having the ability to controllably tune the topological invariants of materials is an actively pursued topic since it opens new opportunities for scientific studies and applications. Despite proposals on switching between normal and topological insulators in 2D and 3D based on first-principles calculations, using external electric fields [23], tensile strains [24,25], temperature and alloying [26–29], and so on [30–32], strategies for tuning topological phases in 1D systems remain relatively underexplored. In this work, by first-principles calculations, we discover that topological phases of certain quasi-1D systems may be practically tuned by a new strategy that exploits external transverse electric fields (TEFs). We demonstrate this

strategy using a designed GNR periodically codoped with nitrogen and boron [Fig. 1(a)].

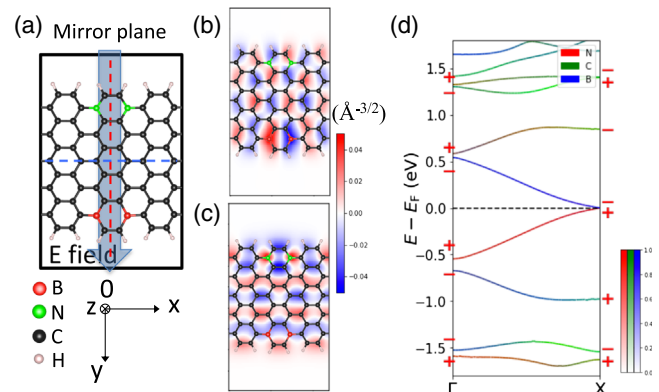


FIG. 1. (a) A unit cell of the B&N-11AGNR (commensurate with a zigzag end termination). The blue arrow shows the direction of a positive TEF. The red dashed line shows a mirror plane of the system, and the blue dashed line defines a normal plane about which the positions of the boron and nitrogen dimers are switched upon reflection. (b),(c) The BCB wave function (b) and TVB wave function (c) at the  $\Gamma$  point on a plane at 1 Å above the GNR basal plane. (d) The B&N-11AGNR band structure without any applied field. The blue, red, and green colors in the band structure denote the module squared weights of the wave function that are projected onto the boron, nitrogen, and carbon atomic orbitals, respectively. The scale bar defines the mapping between the color scale and the percentage weight. The projection is normalized according to the total number of atoms of each species per unit cell. The parity eigenvalues  $\langle \psi_{n\Gamma_i} | \hat{M} | \psi_{n\Gamma_i} \rangle$  of the eight bands near the Fermi level  $E_F$  at  $\Gamma$  and  $X$  are marked as “+” (“−”) for a value of +1 (−1).

The band topological invariant of a 1D insulating crystal with multiple atoms per unit cell depends on the assignment of its unit cell, which in turn is dictated by the atomic structure at the end termination of the 1D system (i.e., the unit cell should be commensurate with the boundary geometry) [7]. For instance, using the approximate chiral symmetry (the  $A/B$  sublattice symmetry) of the GNRs, the band topology of this multiband system can be characterized by a winding number  $Z$ , which may be obtained using the *difference* between the intercell part of the Zak phase contributed by the  $A$  sublattice and that contributed by the  $B$  sublattice, summed over all bands up to the charge neutrality gap [10]. For such a system with a winding number  $Z$ , there will be  $Z$  topologically protected localized in-gap states at its end termination with vacuum, according to the bulk-edge correspondence [33]. On the other hand, a  $Z_2$  topological classification can be exactly applied to a 1D insulating crystal with spinless time reversal symmetry (TRS) and spatial inversion or mirror symmetry [7].

In a 1D crystal, the Zak phase [34] for the  $n$ th band is defined as the integral of the Berry's connection across the 1D Brillouin zone (BZ):  $\gamma_n = i(2\pi/d) \int_{-\pi/d}^{\pi/d} dk \langle u_{nk} | (\partial u_{nk} / \partial k) \rangle$ , where  $u_{nk}$  is the lattice-periodic part of the Bloch state,  $d$  is the unit cell size, and  $k$  is the wave vector. The Zak phase of an isolated band of a general 1D insulator can take on any value, depending on the choice of the shape and origin of the unit cell. Nevertheless, if the unit cell of the crystal has inversion or mirror symmetry, the intercell (origin-independent) part of the Zak phase is uniquely determined for a given unit cell shape and is quantized to 0 or  $\pi$  (mod  $2\pi$ ) [7,8]. The  $Z_2$  invariant of a 1D insulator with such symmetries is then given by  $(-1)^{Z_2} = e^{i\sum_{n \in \text{occ}} \gamma_n}$ , where the sum is over the occupied bands. When the total intercell Zak phase is  $\pi$  (0) (mod  $2\pi$ ), the  $Z_2$  invariant is 1 (0). As shown in previous work [4,7], for a unit cell with inversion  $\hat{I}$  or mirror  $\hat{M}$  symmetry ( $\hat{O} = \hat{I}$  or  $\hat{M}$ ), the  $Z_2$  invariant of a GNR may be determined by the product of the eigenvalues of  $\hat{O}$  of the states at all the time reversal invariant momentum (TRIM)  $k$  points in the occupied band manifold:  $(-1)^{Z_2} = \prod_{n \in \text{occ}} \prod_{\Gamma_i} \langle \psi_{n\Gamma_i} | \hat{O} | \psi_{n\Gamma_i} \rangle$ , where  $\psi_{n\Gamma_i}$  is the wave function at the TRIM  $\Gamma_i = \Gamma, X$  in the 1D BZ. In this study, we analyze our system using both classification schemes since it possesses TRS and spatial symmetries, as well as, to a very high degree, chiral symmetry.

For experimentally bottom-up synthesized GNR systems, the dangling  $\sigma$  orbitals of the edge carbon atoms are capped by hydrogen and are removed in energy from the band gap region, so these  $\sigma$  states are not involved in the formation of the end or junction in-gap states. Also, because the GNRs considered in this work have a mirror symmetry with respect to the carbon basal plane, the  $\sigma$  (mirror even) and  $\pi$  (mirror odd) bands do not hybridize. Only the bands account for the in-gap physics of interest.

Thus, both the  $Z$  and  $Z_2$  invariants of the GNRs of interest are calculated from the occupied band manifold of  $\pi$  electrons (denoted by  $\pi$  and occ) only. For example,  $Z_2$  is given by

$$(-1)^{Z_2} = \prod_{n \in \pi \text{ and occ}} \langle \psi_{n\Gamma} | \hat{O} | \psi_{n\Gamma} \rangle \langle \psi_{nX} | \hat{O} | \psi_{nX} \rangle. \quad (1)$$

In general, a transition from one topological phase to another for an insulator requires its band gap to close and reopen by external tuning parameters while preserving the symmetries desired. In our case, a TEF along the width of the GNR (the  $y$  axis) [Fig. 1(a)] is used because it preserves both the approximate chiral symmetry in the GNR (see Supplemental Material, Sec. I [35]) and the mirror symmetry of the GNR unit cell.

As indicated by Eq. (1), changing the  $Z_2$  invariant by band reordering at the fundamental band gap requires the wave functions at the minimum of the bottom conduction band (BCB) and the maximum of the top valence band (TVB) to have opposite parities at one of the  $\Gamma_i$  points, i.e.,  $\langle \psi_{\text{BCB}\Gamma_i} | \hat{M} | \psi_{\text{BCB}\Gamma_i} \rangle \langle \psi_{\text{TVB}\Gamma_i} | \hat{M} | \psi_{\text{TVB}\Gamma_i} \rangle = -1$ . This ensures zero wave function mixing between the two states at this  $\Gamma_i$  point of the BCB and TVB as a function of the TEF strength, so a band gap closing is ensured during the induced band inversion process.

We satisfy this requirement by designing an armchair GNR (AGNR) with periodic arrays of substitutional boron-dimer and nitrogen-dimer dopants [Fig. 1(a)]. From our density functional theory (DFT) calculations, comparing results for an isolated boron dimer to a nitrogen dimer substitutionally doped onto the backbone of an AGNR shows that these two dimer defects introduce dopant states of opposite parity in the fundamental band gap of the pristine AGNR. We therefore incorporate both boron- and nitrogen-dimer arrays into the same AGNR and achieve having a boron-dimer (nitrogen-dimer) dopant band as its new BCB (TVB) with  $-1$  ( $+1$ ) parity eigenvalue at both  $\Gamma$  and  $X$ .

Second, to make possible a field-induced band inversion, the BCB and TVB should have opposite energy shift in response to the applied TEF, requiring the wave function amplitude of BCB and TVB (and thus the GNR structure) to be asymmetric along the transverse (widthwise) direction of the GNR. Thus, we put the boron- and nitrogen-dimer dopants near the opposite edges of the AGNR [Fig. 1(a)].

The boron- and nitrogen-dimer dopants are symmetric to a mirror plane [red dashed vertical line in Fig. 1(a)] which retains the mirror symmetry of the system. In addition, in AGNRs with an odd number of rows of atoms forming the width, the boron- and nitrogen-dimer exchange positions upon a reflection with respect to the perpendicular plane at the central backbone defined by the blue dashed line in Fig. 1(a). This ensures the system to have chiral symmetry within the nearest-neighbor tight-binding model, with and

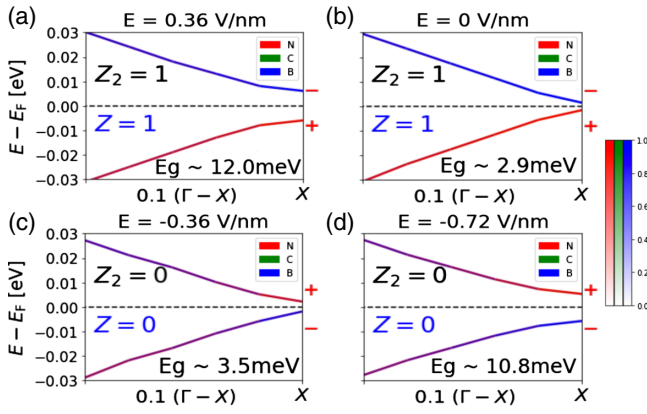


FIG. 2. The band inversion process under changing TEFs from DFT-LDA calculations. As the TEF goes below a critical field strength of  $E_c \sim -0.2$  V/nm, the characters (and parities) of the states of the BCB and TVB at the  $X$  point are inverted, and both the  $Z$  and  $Z_2$  invariants of this system change from 1 to 0. The bands are enlarged in a region near the  $X$  point in reciprocal space spanning over  $1/10$  of the  $\Gamma - X$  length.

without the presence of the TEF (see Supplemental Material, Sec. I [35]). Thus, the topology of the system can be classified by either a  $Z_2$  index (using the former) or a  $Z$  index (using the latter).

Among a series of GNR structures designed, guided by the above design principles, an AGNR having 11 rows of carbon atoms with one boron-dimer dopant and one nitrogen-dimer dopant in every three pentacene units (abbreviated as B&N-11AGNR) [Fig. 1(a)] is found to have the desired properties for field-tunable topological phases. The pristine B&N-11AGNR without any applied field has a direct band gap of  $\sim 2.9$  meV calculated using DFT within the local density approximation (LDA) as implemented in the Quantum ESPRESSO (QE) package [36]. This small gap (dictated by the ribbon width [53], density, and exact positions of dopants) makes an electric-field-induced band inversion experimentally feasible.

The evolution of the DFT-LDA band structure with different applied TEFs (Fig. 2) is calculated using a supercell method that has a sawtooth potential changing along the  $y$  direction and accounts for dipole correction and depolarization field appropriately [54]. We find that band inversion at the  $X$  point happens at a critical TEF [with positive direction defined in Fig. 1(a)] strength of  $E_c \sim -0.2$  V/nm. For TEF with  $E < E_c$ , the orbital characters and parity eigenvalues of the bottom of the BCB and the top of the TVB at the  $X$  point switch with each other, giving rise to inverted bands. A wave function projection analysis shows that, for  $E < E_c$ , the orbital character of the band states, as a function of the wave vector  $k$ , does recover to its original character at some distance away from the  $X$  point [Figs. 2(c) and 2(d)]. From Eq. (1), we obtain that the value of  $Z_2$  changes from 1 to 0 as  $E$  goes below  $E_c$ . We also evaluate the  $Z_2$  invariant

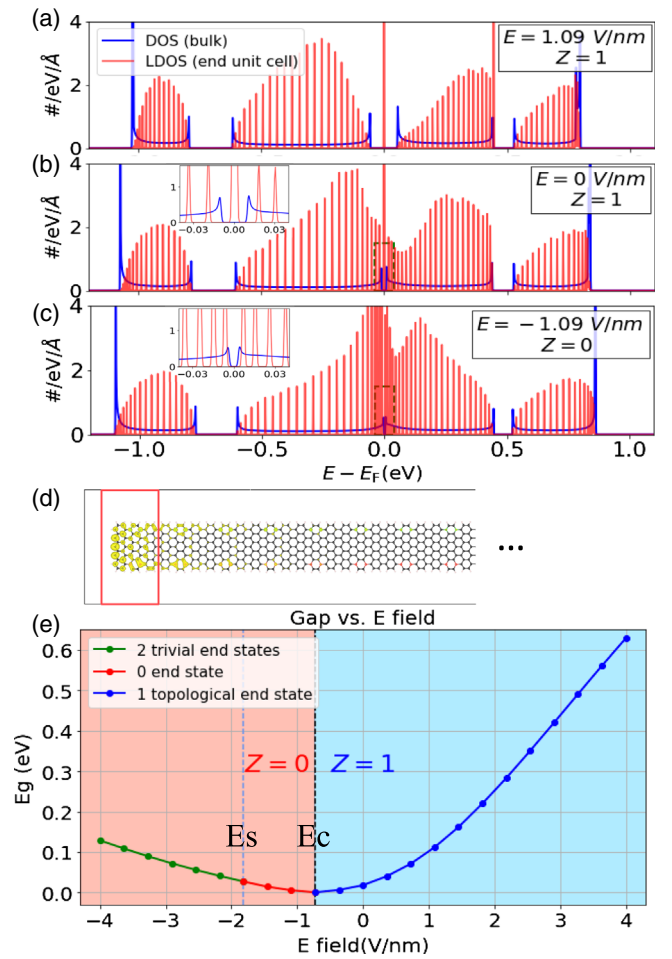


FIG. 3. Bulk-boundary correspondence. (a)–(c) The red curves show the calculated end-cell LDOS [integrated in the red rectangular region in (d)] of the 24-unit-cell finite-length GNR with TEF of  $E = 1.09$  V/nm (a),  $0$  V/nm (b), and  $-1.09$  V/nm (c), while the blue curves show the bulk DOS per unit cell at the same TEFs. Both the LDOS and DOS are in units of number of states per energy per length without considering spin degeneracy. The Gaussian broadening factor is  $1$  meV for both the LDOS and bulk DOS. The insets enlarge the green dashed rectangular regions. (d) The isosurface charge density plot at  $1.4 \times 10^{-5} \text{ \AA}^{-3}$  (1% of the maximum value) of the topological end state in the 24-unit-cell finite segment (only the left  $1/3$  of the segment is shown). The TEF is  $1.09$  V/nm ( $Z = 1$ ). (e) DFT-LDA band gap versus TEF calculated using the SIESTA package ( $E_c \sim -0.8$  V/nm). The calculated  $Z$  invariant is 1 (0) for  $E > E_c$  ( $E < E_c$ ). The colors on different parts of the curve denote the number of end states per end for the system.

by calculating the center of the Wannier functions [37–40] using the WANNIER90 package [41] (see Supplemental Material, Sec. V [35]). Moreover, we show that the DFT Hamiltonian for our system may be mapped approximately to a chiral Hamiltonian in a maximally localized Wannier function basis (see Supplemental Material, Sec. III [35]), and that its  $Z$  index changes from 1 to 0 as the  $E$  goes below  $E_c$ , consistent with the above  $Z_2$  classification. Thus, the

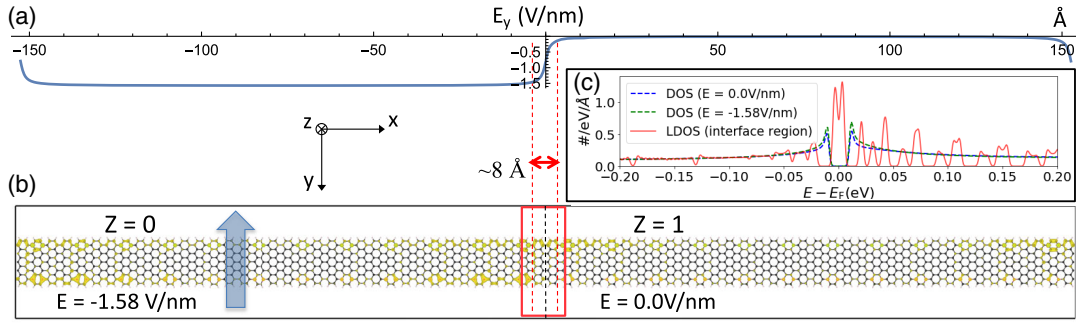


FIG. 4. (a) The TEF profile in one repeating period as a function of coordinate  $x$  which is along the axis of the ribbon. (b) The isosurface charge density plot at  $2.7 \times 10^{-6} \text{ \AA}^{-3}$  (2% of the maximum value) of the topological junction state (evaluated at the  $\Gamma$  point of the superlattice) of a B&N-11AGNR with the superlattice electric field in (a) applied. One repeating period of the TEF [the supercell shown in (b)] contains 24 B&N-11AGNR unit cells. The field strengths in the center of the left (right) region are  $-1.58$  V/nm (0 V/nm) resulting in the system with  $Z$  being 0 (1). (c) DOS of the GNR in a superlattice electric field. The red solid curve shows the LDOS computed in the junction region [the red rectangle in (b)]. The green (blue) dashed curves show the bulk DOS per unit cell with a uniform TEF of  $E = -1.58$  V/nm (0 V/nm).

B&N-11AGNR satisfies all our designing principles and has a topological  $Z_2$  invariant and a  $Z$  invariant that are tunable with an experimental realizable TEF in the order of  $0.1$  V/nm [55–57].

We next investigate the topological end states of a B&N-11AGNR finite-length segment and the relation between the number of the end states and the value of  $Z$ , namely, the bulk-boundary correspondence [6,10,33]. We perform a DFT calculation of the electronic structure of a finite-length B&N-11AGNR including 24 repeating unit cells of the form shown in Fig. 1(a), with the SIESTA package [42] using a limited single zeta atomic basis. All the dangling bonds at the end of the ribbon (which is a zigzag termination) are capped by hydrogen atoms. The number of in-gap end states at one end in the charge neutrality gap as a function of the TEF strength and direction have three regions of distinct behavior [Fig. 3(e)]. For  $E > E_c$  (with the critical field  $E_c \sim -0.8$  V/nm for band inversion from the SIESTA calculation), one topological in-gap end state appears at each end, while for  $E_s < E < E_c$ , no in-gap end state emerges ( $E_s \sim -1.8$  V/nm). For  $E < E_s$ , two localized states emerge in the band gap at each end. However, these two end states, unlike the topologically protected one in the case of  $E > E_c$ , can be eliminated by small perturbations on the end atoms (see Supplemental Material, Sec. IV [35]), so they are trivial end states. Thus, as expected, the bulk-boundary correspondence holds in this system. The plane wave basis set used in the QE calculation of the periodic system (Fig. 2) is well converged. However, for the finite segment SIESTA calculations (Fig. 3), a limited basis set was used (because of the large number of atoms), leading to less converged band gap values. This results in different values of  $E_c$  and  $E_s$  obtained by the two packages. Nevertheless, the topological character of the bands of the two calculations remains the same.

From our theory, the TEF strength not only changes the number of end states, it also controls how localized the end

states are. The local density of states (LDOS) at the end unit cell of the finite segment for three different TEFs [Figs. 3(a)–3(c)] are compared with the bulk density of states (DOS) per unit cell. For  $E = 1.09$  V/nm ( $Z = 1$ ), the end-cell LDOS shows a sharp and big peak at  $E - E_F = 0$ , arising from a very localized in-gap state at each end [Fig. 3(a)]. A smaller bulk gap at  $E = 0$  V/nm makes the end states less localized, resulting in a lower peak height at  $E - E_F = 0$  [Fig. 3(b)]. For  $E = -1.09$  V/nm ( $Z = 0$ ), no in-gap peak emerges in the end-cell LDOS [Fig. 3(c)], showing an absence of in-gap end states.

A field switchable topological phase enables the use of a spatially varying TEF to create and confine topological junction states between two insulating regions of different  $Z$  invariants. To illustrate this effect, we apply a superlattice electric field [i.e., a periodically repeated pattern of TEF with a repeating unit profile shown in Fig. 4(a)] on a B&N-11AGNR as shown in Fig. 4(b). The TEF is negative (zero) in the left (right) half of the supercell and has a form  $E_y = (E_0/\pi)[\arctan(x) - \arctan(x - (d_{SC}/2)) - \arctan(x + (d_{SC}/2)) - (\pi/2)]$ , where the length of the supercell along the  $x$  direction is  $d_{SC} = 305.2 \text{ \AA}$ . A TEF of such a pattern may be created by a periodic array of parallel gates with alternating bias voltages [58]. For example, a topological junction state is confined at the junction between the left part with  $E = -1.58$  V/nm and the right part with  $E = 0$  V/nm ( $E_0 = 1.58$  V/nm) [Fig. 4(b)] because the  $Z$  invariant changes by 1 across the junction under this field profile. The *two* junctions in one supercell each hosts a protected junction state, which form two bands with small dispersions ( $\sim 5$  meV) inside the common gap of the left and right “bulk” region. Hence, the LDOS of the unit cell at the junction [the red rectangle in Fig. 4(b)] shows two  $\sim 5$  meV wide peaks inside the common bulk gap [Fig. 4(c)]. In contrast to heterostructures of

geometrically different GNRs of distinct topological phases in which junction states appear at the junction [7,8,10,21,22], the topological junction states of the B&N-11AGNR are created by the profile of the TEF and can be moved freely to different locations in the material by varying the field profile. This gives us another degree of freedom in the rational control of topological junction states in 1D systems [7]. Furthermore, the coupling between two nearby localized states of the junction array, given by the junction separation, is programmable by the spatial profile of the field.

In conclusion, we have proposed a scheme for designing GNRs with tunable topological phase by an applied TEF and have demonstrated its feasibility through *ab initio* studies. Our analyses and first-principles calculations have shown that topological end states can be created or annihilated by a uniform applied TEF on a GNR finite segment, and topological junction states can be generated in a homogeneous GNR by applying specific profiles of piecewise uniform TEFs. Our study has provided a new way of controlling topological junction or end states in 1D systems which may be used in building quantum dot spin qubits with tunable couplings, and this is a promising new approach for designing future GNR-based quantum electronic devices.

We thank Z. Li, J. Jiang and M. Wu for helpful discussions. This study was supported by the Theory of Materials Program at the Lawrence Berkeley National Laboratory through the Office of Basic Energy Sciences, U.S. Department of Energy under Contract No. DE-AC02-05CH11231, which provided for the structural and electric-field-effect DFT calculations and by the Office of Naval Research MURI under Grant No. N00014-16-1-2921 which provided the topological analyses. Advanced codes were provided by the Center for Computational Study of Excited-State Phenomena in Energy Materials (C2SEPEM) at LBNL, which is funded by the U.S. Department of Energy, Office of Science, Basic Energy Sciences, Materials Sciences and Engineering Division under Contract No. DE-AC02-05CH11231, as part of the Computational Materials Sciences Program., T. C. acknowledges support from the Micron Foundation. Computational resources were provided by the DOE at Lawrence Berkeley National Laboratory's NERSC facility and the NSF through XSEDE resources at National Institute for Computational Sciences (NICS).

\*sglouie@berkeley.edu

- [1] D. J. Thouless, M. Kohmoto, M. P. Nightingale, and M. den Nijs, *Phys. Rev. Lett.* **49**, 405 (1982).
- [2] M. Z. Hasan and C. L. Kane, *Rev. Mod. Phys.* **82**, 3045 (2010).
- [3] X.-L. Qi and S.-C. Zhang, *Rev. Mod. Phys.* **83**, 1057 (2011).
- [4] L. Fu and C. L. Kane, *Phys. Rev. B* **76**, 045302 (2007).

- [5] S. Ryu, A. P. Schnyder, A. Furusaki, and A. W. Ludwig, *New J. Phys.* **12**, 065010 (2010).
- [6] J. K. Asbóth, L. Oroszlány, and A. Pályi, *A Short Course on Topological Insulators* (Springer, New York, 2016).
- [7] T. Cao, F. Zhao, and S. G. Louie, *Phys. Rev. Lett.* **119**, 076401 (2017).
- [8] Y.-L. Lee, F. Zhao, T. Cao, J. Ihm, and S. G. Louie, *Nano Lett.* **18**, 7247 (2018).
- [9] K. S. Lin and M. Y. Chou, *Nano Lett.* **18**, 7254 (2018).
- [10] J. Jiang and S. G. Louie, *Nano Lett.* **21**, 197 (2021).
- [11] J. Cai *et al.*, *Nature (London)* **466**, 470 (2010).
- [12] Y.-C. Chen, D. G. de Oteyza, Z. Pedramrazi, C. Chen, F. R. Fischer, and M. F. Crommie, *ACS Nano* **7**, 6123 (2013).
- [13] P. B. Bennett, Z. Pedramrazi, A. Madani, Y. C. Chen, D. G. de Oteyza, C. Chen, F. R. Fischer, M. F. Crommie, and J. Bokor, *Appl. Phys. Lett.* **103**, 253114 (2013).
- [14] G. D. Nguyen *et al.*, *J. Phys. Chem. C* **120**, 2684 (2016).
- [15] Z. Pedramrazi *et al.*, *Nano Lett.* **18**, 3550 (2018).
- [16] P. Ruffieux *et al.*, *Nature (London)* **531**, 489 (2016).
- [17] J. Cai *et al.*, *Nat. Nanotechnol.* **9**, 896 (2014).
- [18] Y.-C. Chen, T. Cao, C. Chen, Z. Pedramrazi, D. Haberer, D. G. de Oteyza, F. R. Fischer, S. G. Louie, and M. F. Crommie, *Nat. Nanotechnol.* **10**, 156 (2015).
- [19] A. Narita, A. Feng, and K. Müllen, *Chem. Rec.* **15**, 295 (2015).
- [20] L. Talirz *et al.*, *J. Am. Chem. Soc.* **135**, 2060 (2013).
- [21] D. J. Rizzo, G. Veber, T. Cao, C. Bronner, T. Chen, F. Zhao, H. Rodriguez, S. G. Louie, M. F. Crommie, and F. R. Fischer, *Nature (London)* **560**, 204 (2018).
- [22] O. Gröning *et al.*, *Nature (London)* **560**, 209 (2018).
- [23] Q. Liu, X. Zhang, L. B. Abdalla, A. Fazzio, and A. Zunger, *Nano Lett.* **15**, 1222 (2015).
- [24] F.-C. Chuang, C.-H. Hsu, C.-Y. Chen, Z.-Q. Huang, V. Ozolins, H. Lin, and A. Bansil, *Appl. Phys. Lett.* **102**, 022424 (2013).
- [25] S. S. Li, W.-X. Ji, P. Li, S.-J. Hu, L. Cai, C.-W. Zhang, and S.-S. Yan, *ACS Appl. Mater. Interfaces* **9**, 21515 (2017).
- [26] G. Antonius and S. G. Louie, *Phys. Rev. Lett.* **117**, 246401 (2016).
- [27] B. Monserrat and D. Vanderbilt, *Phys. Rev. Lett.* **117**, 226801 (2016).
- [28] J. Liu and D. Vanderbilt, *Phys. Rev. B* **88**, 224202 (2013).
- [29] L. B. Abdalla, J. E. Padilha, T. M. Schmidt, R. H. Miwa, and A. Fazzio, *J. Phys. Condens. Matter* **27**, 255501 (2015).
- [30] J. Li and K. Chang, *Appl. Phys. Lett.* **95**, 222110 (2009).
- [31] M. S. Miao, Q. Yan, C. G. Van de Walle, W. K. Lou, L. L. Li, and K. Chang, *Phys. Rev. Lett.* **109**, 186803 (2012).
- [32] D. Zhang, W. Lou, M. Miao, S.-C. Zhang, and K. Chang, *Phys. Rev. Lett.* **111**, 156402 (2013).
- [33] E. Prodan and H. Schulz-Baldes, *Bulk and Boundary Invariants for Complex Topological Insulators: From K-Theory to Physics* (Springer, Berlin, 2016).
- [34] J. Zak, *Phys. Rev. Lett.* **62**, 2747 (1989).
- [35] See Supplemental Material at <http://link.aps.org/supplemental/10.1103/PhysRevLett.127.166401> for (i) approximate chiral symmetry in boron-dimer and nitrogen-dimer periodically codoped armchair graphene nanoribbon with 11 rows of carbon atoms (11AGNR), (ii) Z index invariant or winding number of B&N-11AGNR with zigzag termination; a simplified tight-binding model, (iii) Z index invariant or winding number of B&N-11AGNR with

- zigzag termination; Hamiltonian in the maximally localized Wannier function basis, (iv) trivial end states when  $E < E_s$  and the robustness of the topological end state when  $E > E_c$ , (v) the  $Z_2$  invariant calculated using Wannier centers, (vi) calculation of the  $Z_2$  invariants from parity eigenvalues of TRIM points, (vii) additional plots on the spatial confinement of the topological junction states, (viii) end state spectrum of a finite-length B&N-11AGNR, (ix) outlooks on the experimental synthesizability of B&N-11AGNR, (x) tunable topological phases in B&N-AGNR of different widths, and (xi) correlation effects in B&N-11AGNR, which includes Refs. [6,7,11,15,36–52].
- [36] P. Giannozzi *et al.*, *J. Phys. Condens. Matter* **21**, 395502 (2009).
- [37] E. I. Blount, *Solid State Phys.* **13**, 305 (1962).
- [38] N. Marzari and D. Vanderbilt, *Phys. Rev. B* **56**, 12847 (1997).
- [39] A. A. Soluyanov and D. Vanderbilt, *Phys. Rev. B* **83**, 235401 (2011).
- [40] A. A. Soluyanov and D. Vanderbilt, *Phys. Rev. B* **83**, 035108 (2011).
- [41] A. A. Mostofi, J. R. Yates, G. Pizzi, Y. S. Lee, I. Souza, D. Vanderbilt, and N. Marzari, *Comput. Phys. Commun.* **185**, 2309 (2014).
- [42] J. M. Soler, E. Artacho, J. D. Gale, A. García, J. Junquera, P. Ordejón, and D. Sánchez-Portal, *J. Phys. Condens. Matter* **14**, 2745 (2002).
- [43] Y. Ralchenko, A. E. Kramida, and J. Reader (NIST ASD Team), <http://physics.nist.gov/asd>.
- [44] F. Liu, *Phys. Rev. B* **52**, 10677 (1995).
- [45] M. P. Lopez Sancho, J. M. Lopez Sancho, and J. Rubio, *J. Phys. F* **14**, 1205 (1984).
- [46] L. Talirz *et al.*, *ACS Nano* **11**, 1380 (2017).
- [47] J. P. Llinas *et al.*, *Nat. Commun.* **8**, 633 (2017).
- [48] B. V. Senkovskiy *et al.*, *Phys. Status Solidi* **11**, 1700157 (2017).
- [49] Z. Pedramrazi, C. Chen, D. Haberer, W. Perkins, F. R. Fischer, and M. F. Crommie, *Bull. Am. Phys. Soc. W* **6**, 015 (2015).
- [50] I. Piskun, R. Blackwell, J. Jornet-Somoza, F. Zhao, A. Rubio, S. G. Louie, and F. R. Fischer, *J. Am. Chem. Soc.* **142**, 3696 (2020).
- [51] M. S. Hybertsen and S. G. Louie, *Phys. Rev. B* **34**, 5390 (1986).
- [52] J. Jung and A. H. MacDonald, *Phys. Rev. B* **79**, 235433 (2009).
- [53] Y.-W. Son, M. L. Cohen, and S. G. Louie, *Phys. Rev. Lett.* **97**, 216803 (2006).
- [54] L. Bengtsson, *Phys. Rev. B* **59**, 12301 (1999).
- [55] E. V. Castro, K. S. Novoselov, S. V. Morozov, N. M. R. Peres, J. M. B. Lopes dos Santos, J. Nilsson, F. Guinea, A. K. Geim, and A. H. Castro Neto, *Phys. Rev. Lett.* **99**, 216802 (2007).
- [56] C. H. Lui, Z. Li, K. F. Mak, E. Cappelluti, and T. F. Heinz, *Nat. Phys.* **7**, 944 (2011).
- [57] M. H. D. Guimarães, P. J. Zomer, J. Ingla-Aynés, J. C. Brant, N. Tombros, and B. J. van Wees, *Phys. Rev. Lett.* **113**, 086602 (2014).
- [58] R. Steinacher, A. A. Kozikov, C. Rössler, C. Reichl, W. Wegscheider, T. Ihn, and K. Ensslin, *New J. Phys.* **17**, 043043 (2015).