

Electrical Control and Transport of Tightly Bound Interlayer Excitons in a MoSe₂/hBN/MoSe₂ Heterostructure

Lifu Zhang,^{1,*} Liuxin Gu,^{1,*} Ruihao Ni¹ ,¹ Ming Xie,² Suji Park,³ Houk Jang,³ Rundong Ma,¹ Takashi Taniguchi⁴ ,⁴ Kenji Watanabe⁵ ,⁵ and You Zhou^{1,6,†} 

¹*Department of Materials Science and Engineering, University of Maryland, College Park, Maryland 20742, USA*

²*Condensed Matter Theory Center, University of Maryland, College Park, Maryland 20742, USA*

³*Center for Functional Nanomaterials, Brookhaven National Laboratory, Upton, New York 11973, USA*

⁴*Research Center for Electronic and Optical Materials, National Institute for Materials Science, 1-1 Namiki, Tsukuba 305-0044, Japan*

⁵*Research Center for Materials Nanoarchitectonics, National Institute for Materials Science, 1-1 Namiki, Tsukuba 305-0044, Japan*

⁶*Maryland Quantum Materials Center, College Park, Maryland 20742, USA*



(Received 3 January 2024; revised 11 March 2024; accepted 15 April 2024; published 24 May 2024)

Controlling interlayer excitons in Van der Waals heterostructures holds promise for exploring Bose-Einstein condensates and developing novel optoelectronic applications, such as excitonic integrated circuits. Despite intensive studies, several key fundamental properties of interlayer excitons, such as their binding energies and interactions with charges, remain not well understood. Here we report the formation of momentum-direct interlayer excitons in a high-quality MoSe₂/hBN/MoSe₂ heterostructure under an electric field, characterized by bright photoluminescence (PL) emission with high quantum yield and a narrow linewidth of less than 4 meV. These interlayer excitons show electrically tunable emission energy spanning ~ 180 meV through the Stark effect, and exhibit a sizable binding energy of ~ 81 meV in the intrinsic regime, along with trion binding energies of a few millielectronvolts. Remarkably, we demonstrate the long-range transport of interlayer excitons with a characteristic diffusion length exceeding 10 μm , which can be attributed, in part, to their dipolar repulsive interactions. Spatially and polarization-resolved spectroscopic studies reveal rich exciton physics in the system, such as valley polarization, local trapping, and the possible existence of dark interlayer excitons. The formation and transport of tightly bound interlayer excitons with narrow linewidth, coupled with the ability to electrically manipulate their properties, open exciting new avenues for exploring quantum many-body physics, including excitonic condensate and superfluidity, and for developing novel optoelectronic devices, such as exciton and photon routers.

DOI: [10.1103/PhysRevLett.132.216903](https://doi.org/10.1103/PhysRevLett.132.216903)

Spatially indirect excitons (IXs) with long lifetimes and electric dipole moments can form macroscopic coherent quantum phases, such as exciton superfluidity, at high densities and low temperatures [1–4]. The quantum degeneracy temperature of IXs, which scales proportionally to the exciton binding energy, is limited in traditional III-V double-quantum well systems [4,5]. Transition metal dichalcogenide (TMD) heterostructures, predicted to host tightly bound IXs [4], have recently emerged as an exciting new platform for exploring coherent high-temperature condensate and superfluid states [6–9]. Furthermore, these IXs exhibit spin-valley coupling [10,11], strong dipolar interactions [12,13], and electrical tunability via the Stark effect [14–16], thereby offering a system rich for exploring exciton physics.

To date, optical studies of interlayer excitons have primarily focused on multilayer TMD hetero- and homo-junctions [10–22]. In heterostructures, local variations in the twist angle and strain can induce substantial inhomogeneous broadening of IXs, for instance, by lattice

reconstruction, introducing a disorder potential atop the periodic moiré lattice [17–20,23,24]. On the other hand, although disorder potential can be greatly reduced in natural homolayered TMDs, these systems become momentum-indirect [16,21,22], which feature significant nonradiative broadening of IX. As a result, IXs in TMDs typically manifest much larger linewidths than their intralayer counterpart in monolayers, which hinders the formation of exciton superfluidity and limits our understanding of their critical properties, such as their binding energies and their interactions with free carriers.

Here, we employ a homobilayer TMD system, with two MoSe₂ monolayers separated by an atomically thin layer of hBN. The thin hBN spacer preserves the direct bandgap in bilayers while allowing for carrier tunneling and IX emission. Although IX PL has been observed in similar structures, earlier works focused on the hybridization of IXs and intralayer excitons [25,26]. In this work, we demonstrate a low-disorder system with degenerate

intralayer exciton energies and sharp IX PL linewidth. The high optical quality allows us to directly measure the interlayer exciton and trion binding energies and observe the long-range transport and trapping of IXs, creating a new platform for studying exciton transport, photophysics, and condensates.

We first establish the electric-field and doping control of interlayer excitons in a $\text{MoSe}_2/\text{hBN}/\text{MoSe}_2$ device. We align the two monolayers close to zero degree to promote the carrier tunneling and IX emission [Fig. 1(a), see Table S1 in [27] for hBN thickness in different devices]. Under zero electric field, the sample's PL spectrum at 6 K is dominated by intralayer neutral exciton X_0 and charged

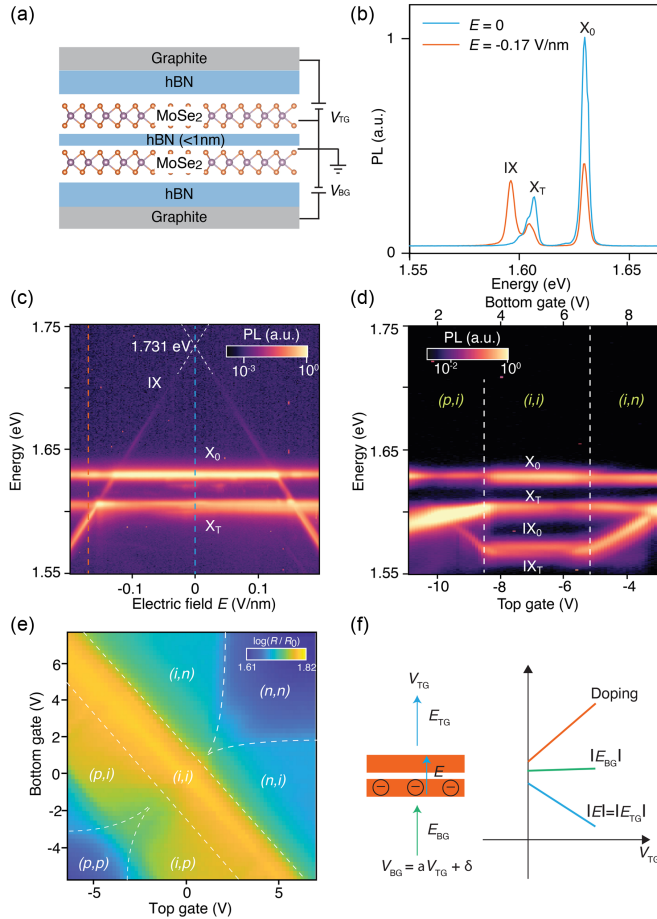


FIG. 1. Electrical control of IX. (a) Schematic of the designed device. (b) Representative PL spectrum under no electric field and -0.17 V/nm (negative defined as pointing upward). (c) Electric field dependence of PL spectra when both layers are intrinsic. Dashed lines indicate where the spectra in (b) are collected. (d) Doping dependence of PL spectra ($V_{BG} = 1.12 V_{TG} + 12$ V). (e) A 2D map of reflection contrast at X_0 as a function of top and bottom gates. (f) Left: schematic of the electric field across the device under an asymmetric doping scan ($V_{BG} = 1.12 V_{TG} + \delta$ and $\delta > 0$). A larger bottom gate voltage induces layer-polarized doping. Right: the magnitude of doping and E field across the two layers versus V_{TG} .

excitons X_T [Fig. 1(b)]. The two monolayers have degenerate X_0 energies, suggesting minimal strain difference. Next, we apply an electric field while keeping both layers intrinsic ($V_{BG} = -\alpha V_{TG}$, where α is the thickness ratio of the top and bottom hBN layers, Fig. S1 [27]). Under a large electric field, an additional peak, IX, emerges at a lower energy of 1.596 eV with a narrow linewidth of ~ 3.7 meV, accompanied by a reduction in X_0 and X_T intensities. Remarkably, the quantum yield of IX is comparable to that of the intralayer excitons in monolayer MoSe_2 under zero electric field (Fig. S2c [27]). The electric-field dependent PL spectra in Fig. 1(c) show a clear Stark effect of IX, from which we estimate a permanent out-of-plane dipole of $u = e * 0.81$ nm for IX (Supplemental Material [27]), consistent with the thickness of the hBN spacer (two layers) plus the finite thickness of MoSe_2 . From reflectance measurements, we verify that both layers are intrinsic, and the X_T emission likely originates from in-gap states in MoSe_2 (Fig. S2a [27]).

We attribute IXs to the momentum-direct interlayer exciton at the K - K transition and extract their binding energies. In particular, we calculate the IX energy under zero electric field to be 1.731 eV from the Stark effect, which is given by the difference between the quasiparticle band gap and the interlayer binding energy. By measuring the Rydberg states of X_0 , we estimate the quasiparticle band gap of monolayer MoSe_2 to be ~ 1.812 eV using a screened Keldysh potential model [33,34] (Supplemental Material, Fig. S2a [27]). Therefore we estimate the binding energy of IX to be ~ 81 meV, consistent with theoretical calculations [4,35] (see Table S1 [27] for its dependence on hBN thickness). We note that, different from other studies [25], we did not observe clear signatures of IX or their anticrossings with X_0 in reflectance (Fig. S2b [27]), suggesting their low oscillator strength and weaker carrier tunneling.

We further investigate the doping dependence of IX. Under symmetric gating with $V_{BG} = \alpha V_{TG}$, the measured doping-dependent PL resembles that of monolayers without any IX emission, as the carriers are evenly distributed across the two layers (Fig. S3a [27]). To make IX energetically favorable and detectable through PL, we vary the total doping under a large electric field, following $V_{BG} = \alpha V_{TG} + \delta$ [Fig. 1(d)]. The X_0 intensity reduces upon doping but remains finite. This is because the applied field polarizes carriers into one layer and makes the other layer intrinsic, which is further verified by measuring X_0 reflectance [Figs. 1(e), S2d, and S4]. In contrast, the intrinsic IX_0 vanishes upon doping one layer, with an additional peak appearing below it, which we identify as charged interlayer excitons, i.e., interlayer trions or polarons [IX_T in Fig. 1(d)]. The trion binding energy (in the low doping regimes) is estimated to be ~ 3 meV for negatively charged and ~ 5 meV for positively charged IXs, with the difference likely due to the varying effective masses of electrons and holes ($m_e^* > m_h^*$) [36,37].

The charged IX shows a significant blueshift with increasing total gate voltages on both electron and hole sides (also in Fig. S3b–d [27]). In such a bilayer with layer-polarized carriers, varying the gate voltage alters both the doping level and the electric field between layers. The effective screening by the highly doped layer and weak screening by the intrinsic layer leads to a reduction in the electric field magnitude and blueshift of IX with increasing voltage [see Fig. 1(f) and Discussion III [27]]. To separate doping and electric-field influences on this blueshift, we measure the field-dependent PL of charged IXs at various doping levels and extract their energies at zero field, from which we find that the blueshift is primarily due to the electric-field effect (Fig. S5 [27]).

We then investigate the valley polarization properties of IX by exciting the sample with a circularly polarized laser at 1.95 eV and detecting the preservation of circular polarization in PL. Intriguingly, IX exhibits a $\sim 20\%$ degree of circular polarization (DOCP), defined as $(I_{\text{co}} - I_{\text{cross}})/(I_{\text{co}} + I_{\text{cross}})$, while the DOCP of intralayer excitons is almost zero [Figs. 2(a) and S6 in [27]]. In MoSe_2 , the absence of intralayer excitons DOCP is due to rapid valley mixing caused by electron-hole exchange [38,39]. In contrast, the electron-hole exchange of IX can be much weaker thanks to the spatial separation of the electron-hole wave function [10,40,41]. The finite DOCP also suggests that the

formation of IXs occurs faster than intervalley electron-hole exchange. The DOCP of IX does not vary significantly with the electric field except in the crossover region, where it hybridizes with intralayer species, as expected [Fig. 2(b)].

Next, we examine the optical nonlinearity of IX by measuring their PL spectra under different excitation powers [Fig. 2(c)]. With higher power, IX blueshifts while no obvious shift of X_0 and X_T can be observed (Figs. S7 [27]). The stronger nonlinearity of IX compared to intralayer excitons arises from their repulsive dipole-dipole interactions due to the aligned electric dipoles [12,16]. The n -doped IX exhibits a similar trend but with a larger blueshift at the same excitation powers (Fig. S7 [27]). In the hole-doped case, however, we observe a shift in the X_T energy, which suggests optical pumping may alter the doping levels (Fig. S8 [27]), likely due to Auger-assisted hole tunneling across hBN dielectrics [42].

We focus our analysis of the power-dependent PL on the intrinsic and n -doped regimes to avoid photo-doping effects. From fitting, we find a ~ 3.1 meV blueshift of neutral IX and ~ 4.1 meV blueshift of n -doped IX along with linewidth broadening of ~ 2 – 3 meV when the excitation reaches $16 \mu\text{W}$ [Fig. 2(d)]. The IX density, n_{IX} , can be estimated using the mean-field parallel plate-capacitance model [15] following: $\delta E = e n_{\text{IX}} / \epsilon$, where δE is the energy shift, e is the electron charge and ϵ is the dielectric constant (Discussion II and IV [27]). Notably, we estimate a maximum exciton density, n_{IX} of $\sim 7.6 \times 10^{10}$ and $\sim 1.3 \times 10^{11} \text{ cm}^{-2}$ under our highest excitation power of 16 and $64 \mu\text{W}$, for the intrinsic and n -doped case, respectively. The integrated IX PL intensity has a linear dependence on n_{IX} in the n -doped case and has a nearly quadratic dependence in the intrinsic region (Fig. S7d [27]). This suggests that radiative recombination in n -doped IX is relatively independent of exciton density, whereas in the intrinsic region, the recombination can be density-dependent due to processes like collective radiation, biexciton formation, and Auger recombination [43–45].

The electrical control of spectrally sharp IXs with strong dipolar interactions in our device allows us to probe the transport properties of IX. Figures 3(a), 3(b), and S9 in [27] show the spatial map of IX PL under different excitation powers. With the excitation laser fixed near the sample's bottom right corner, the IX PL is visible away from the laser spot and extends further with increasing excitation power, showing distinct local bright areas. In contrast, no long-range transport is observed for intralayer excitons, even at the highest power (Fig. S9c [27]).

To quantify the IX transport, we extract the normalized, radially averaged PL intensity $I_{\text{norm}}(r)$ from these spatial maps, where r is the distance from the center of the laser spot. Since spatial inhomogeneities significantly affect diffusion profiles, we focus on data collected from another sample area with a more uniform IX distribution [Figs. 3(c) and S10 in [27]]. Exciton density near the laser resembles

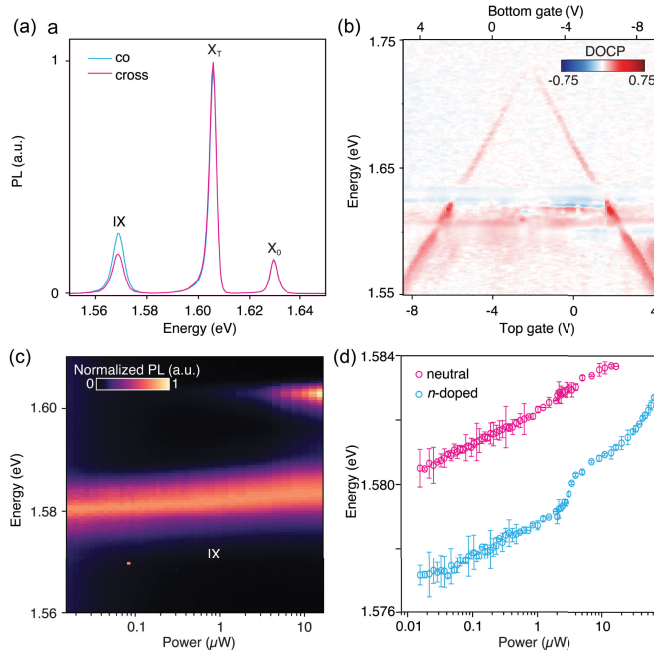


FIG. 2. Valley polarization and dipolar interactions of IX. (a) Polarization resolved PL emission from $\text{MoSe}_2/\text{hBN}/\text{MoSe}_2$ under a circularly polarized laser excitation. (b) DOCP as a function of the electric field under hole doping. (c) Power-dependent PL emission from IX under an electric field of -0.2 V/nm in the intrinsic regime. A long-pass filter is used to block the intralayer exciton signals. (d) Blueshift of the neutral and n -doped IX as a function of the laser power.

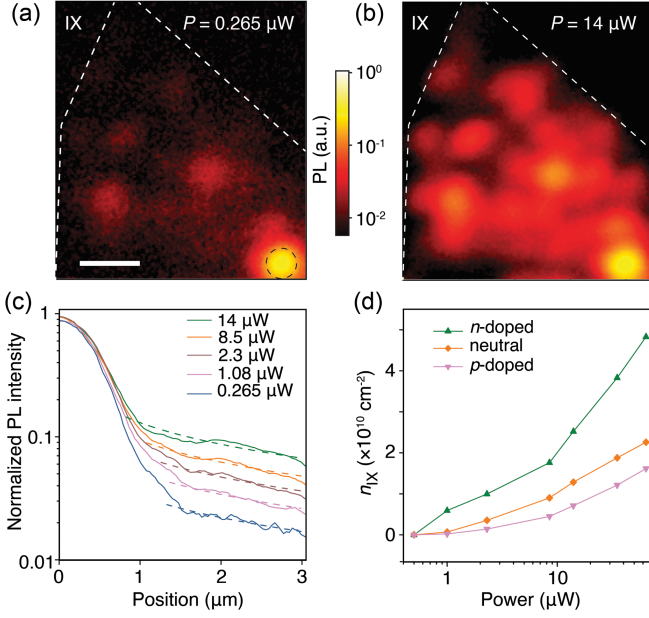


FIG. 3. Spatial diffusion and trapping of IX. (a),(b) Spatial map of IX emission under different excitation powers under an electric field of -0.2 V/nm, with fixed laser location (black dashed circle). Scale bar: 2 μm . (c) Radially averaged IX PL intensity as a function of the distance from laser center r under varying excitation powers. Dashed lines: fitted curves. (d) Estimated IXs density in a natural trap as a function of laser power.

the Gaussian beam profile and asymptotically approaches $n_{IX} \propto e^{-r/L_D} / \sqrt{r/L_D}$ further away (see Discussion IV [27]). Fitting the density profile away from the laser [dashed lines in Fig. 3(c)], we extract a diffusion length $L_D = 17 \pm 6$ μm for the neutral IX, which does not vary significantly with excitation power. As we move closer to the laser and increase the laser power, the interactions-driven current becomes increasingly prominent, surpassing the pure diffusion current driven by the density gradient (Fig. S11 and Discussion IV [27]). It is important to mention that we have ignored other nonlinear exciton decays such as exciton-exciton annihilation [46] and exciton-phonon interactions [47], since we focus on regions away from the laser excitation. However, these nonlinear processes, along with the drift and diffusion of IX, can contribute to the measured sublinear power dependence of exciton densities (Fig. S7e [27]).

The bright spots away from the laser in the diffusion maps can act as a natural trap for IX, which increases the local exciton density and the condensate temperature. Figure S12 show the PL of neutral and doped IXs collected from a local bright spot ~ 2.9 μm away from the laser, with a sharp linewidth of ~ 4 – 5 meV similar to Fig. 1(b). A blueshift of ~ 1 meV, along with linewidth broadening of ~ 1 meV, is observed under the maximum pump power (Figs. S12c and S12d [27]). We estimate the locally trapped exciton density to be $\sim 10^{10}$ cm^{-2} , only a few times less than that under direct laser excitation [Fig. 3(d)].

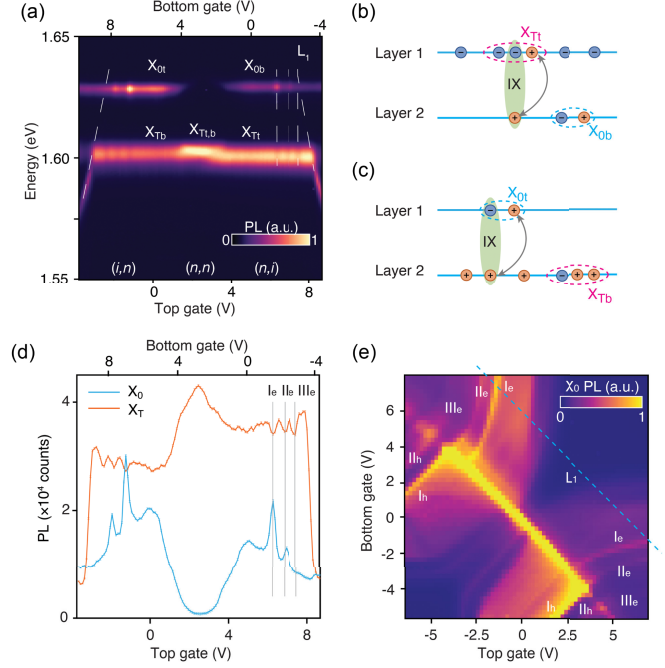


FIG. 4. Coupling between intra- and interlayer excitons. (a) PL spectra of a $\text{MoSe}_2/\text{hBN}/\text{MoSe}_2$ device as a function of electric field with a fixed electron doping. (b),(c) Hole tunneling facilitates (b) IX- X_T coupling under electron doping and (c) IX- X_0 under hole doping. (d) X_0 , and X_T intensities as a function of electric field. I_e , II_e , and III_e denote three anomalies, corresponding to the vertical dashed lines in (a). (e) A 2D map of X_0 . The dashed cyan line depicts the voltage conditions where (a) is collected.

Lastly, we present the intriguing observation of the periodic modulations of X_0 and X_T PL intensities in response to varying electric fields under fixed doping [Fig. 4(a)]. Under positive fields, electrons become layer-polarized, resulting in predominantly emission from the top layer's n -doped trion, X_{Tt} , and the bottom layer's neutral exciton, X_{0b} . IX emerges when its energy drops below X_{Tt} , different from the intrinsic and p -doped cases, where IX appears when it becomes degenerate with X_0 (Figs. 1 and S13 [27]). This difference stems from the more efficient hole tunneling than electrons in TMD heterostructures [6,42]: hole tunneling leads to IX- X_{Tt} hybridization in the n -doped region [Fig. 4(b)], as opposed to IX- X_{0b} coupling in the p -doped and intrinsic cases [Fig. 4(c)].

Increasing electric fields typically induce a continuous change in carrier density in each layer and a monotonic increase (decrease) in X_{Tt} (X_{0b}) intensity. However, at three distinct electric fields, we observe reduced X_{Tt} and enhanced X_{0b} emissions [Figs. 4(d) and S13b [27]]. These anomalies, marked as I_e , II_e , and III_e , recur periodically at ~ 21 mV/nm intervals. Feature III_e appears at the electric field where IX becomes degenerate with neutral exciton X_{0b} . This energy degeneracy can lead to a resonantly enhanced IX- X_{0b} coupling, introducing an additional decay

pathway for the long-lived IX into X_{0b} , which enhances X_{0b} and reduces X_{Ti} emission (Fig. S13 [27]). Similarly, features I_e and II_e may arise when possible dark interlayer excitons with lower energy than IX reach degeneracy with X_{0b} . Figure 4(e) shows a map of integrated X_0 intensity as we vary top and bottom gates, where we observe similar anomalous features in the intrinsic and p -doped regimes. Across all doping conditions, the energy difference between bright and dark excitons is ~ 17 meV. The dark excitons may emerge due to misaligned MoSe₂ layers creating local atomic registry variations. This moiré superlattice could give rise to IX species with different optical selection rules and oscillator strengths [25,48]. Alternatively, interlayer electron-phonon coupling might generate phonon replicas of IXs, a hypothesis supported by the similar energy scales to phonon energies in hBN and MoSe₂ [49–52]. Indeed, in a device with a larger twist angle ($\sim 3^\circ$), no IX emission is observed but the modulation of X_0 and X_T is still present, likely due to their coupling with momentum-indirect dark IXs. Detailed optical and transport investigations will be crucial to clarify the dynamics between dark and bright IXs.

The electrically tunable IX with sharp linewidth forms a promising platform for exploring many-body excitonic physics such as condensate and superfluidity. Using the experimentally extracted n_{IX} in the intrinsic regime, we estimate the quantum degeneracy temperature, $T_q = (2\pi\hbar^2 n_{IX} / m^* k_B)$, of ~ 3.3 K and a Berezinskii-Kosterlitz-Thouless (BKT) transition temperature T_{BKT} of ~ 0.7 K (Discussion V [27]), under a direct laser excitation of 16 μ W. Since nonresonant excitation may raise their temperature above that of the lattice, IXs trapped in the bright spots allow for more efficient IX cooling and offer a more viable pathway for achieving an exciton condensate. Our experiments suggest IXs confined in such traps have quantum degeneracy and superfluid temperatures of ~ 1.0 and ~ 0.2 K, respectively, already accessible in an optical dilution refrigerator.

Nevertheless, to enhance the critical temperatures, it is desirable to further increase the IX densities. The upper limit of n_{IX} imposed by the Mott transition is well above our experimental values, given their large binding energy (~ 81 meV). We estimate maximum quantum degeneracy T_q^{\max} and superfluid temperatures T_{BKT}^{\max} to be ~ 94 and ~ 19 K, near the Mott transition (see Discussion V and Fig. S14 [27]). Experimentally realizing such high densities necessitates further device optimization, including reducing gate current through resonant excitation and increasing the hBN gate thickness (Fig. S7f [27], sample D2). Another intriguing approach is to electrically inject IX, which may reduce heating in the bilayer system [7,53,54].

Crucially, disorder may disrupt the macroscopic coherence of the superfluid when its strength Δ exceeds the thermal energy at the critical temperature, $\Delta > k_B T_{BKT}$ [8]. Using the measured PL linewidth (~ 3.7 meV) as a proxy

for the maximum disorder strength Δ , we find Δ already significantly lower than the thermal energies at T_q^{\max} and comparable to that at T_{BKT}^{\max} . Another important consideration is the flavors of excitons, such as valley degeneracy and dark excitons. Although valley degeneracy in IXs would halve the quantum degeneracy temperature, leveraging the optical polarization of IXs shown here, possibly enhanced through resonant excitation, can substantially raise the condensate temperature. Likewise, dark IXs, having higher energies than bright ones in the intrinsic regime, might have a limited impact on the exciton condensate. In addition to quantum manipulation of bosonic particles, the electrical control and transport of robust interlayer excitons could form a basis for novel optoelectronics and valleytronics, such as excitonic transistors [14,55] and manipulation of spin currents.

This research is primarily supported by the U.S. Department of Energy, Office of Science, Office of Basic Energy Sciences Early Career Research Program under Award No. DE-SC-0022885. The fabrication of samples is supported by the National Science Foundation CAREER Award under Award No. DMR-2145712. This research used Quantum Material Press (QPress) of the Center for Functional Nanomaterials (CFN), which is a U.S. Department of Energy Office of Science User Facility, at Brookhaven National Laboratory under Contract No. DE-SC0012704. K. W. and T. T. acknowledge support from the JSPS KAKENHI (Grants No. 20H00354, No. 21H05233, and No. 23H02052) and World Premier International Research Center Initiative (WPI), MEXT, Japan for hBN synthesis.

*These authors contributed equally to this work.

†To whom all correspondence should be addressed: youzhou@umd.edu

- [1] L. V. Butov, A. L. Ivanov, A. Imamoglu, P. B. Littlewood, A. A. Shashkin, V. T. Dolgoplov, K. L. Campman, and A. C. Gossard, Stimulated scattering of indirect excitons in coupled quantum wells: Signature of a degenerate Bose-gas of excitons, *Phys. Rev. Lett.* **86**, 5608 (2001).
- [2] A. A. High, J. R. Leonard, A. T. Hammack, M. M. Fogler, L. V. Butov, A. V. Kavokin, K. L. Campman, and A. C. Gossard, Spontaneous coherence in a cold exciton gas, *Nature (London)* **483**, 584 (2012).
- [3] M. Combescot, R. Combescot, and F. Dubin, Bose-Einstein condensation and indirect excitons: A review, *Rep. Prog. Phys.* **80**, 066501 (2017).
- [4] M. Fogler, L. Butov, and K. Novoselov, High-temperature superfluidity with indirect excitons in van der Waals heterostructures, *Nat. Commun.* **5**, 4555 (2014).
- [5] F. Chiaruttini, T. Guillet, C. Brimont, B. Jouault, P. Lefebvre, J. Vives, S. Chenot, Y. Cordier, B. Damilano, and M. Vladimirova, Trapping dipolar exciton fluids in GaN/(AlGa)N nanostructures, *Nano Lett.* **19**, 4911 (2019).
- [6] Z. Wang, D. A. Rhodes, K. Watanabe, T. Taniguchi, J. C. Hone, J. Shan, and K. F. Mak, Evidence of high-temperature

- exciton condensation in two-dimensional atomic double layers, *Nature (London)* **574**, 76 (2019).
- [7] M. Xie and A. H. MacDonald, Electrical reservoirs for bilayer excitons, *Phys. Rev. Lett.* **121**, 067702 (2018).
- [8] F.-C. Wu, F. Xue, and A. MacDonald, Theory of two-dimensional spatially indirect equilibrium exciton condensates, *Phys. Rev. B* **92**, 165121 (2015).
- [9] O. L. Berman and R. Y. Kezerashvili, Superfluidity of dipolar excitons in a transition metal dichalcogenide double layer, *Phys. Rev. B* **96**, 094502 (2017).
- [10] P. Rivera, H. Yu, K. L. Seyler, N. P. Wilson, W. Yao, and X. Xu, Interlayer valley excitons in heterobilayers of transition metal dichalcogenides, *Nat. Nanotechnol.* **13**, 1004 (2018).
- [11] P. Rivera, K. L. Seyler, H. Yu, J. R. Schaibley, J. Yan, D. G. Mandrus, W. Yao, and X. Xu, Valley-polarized exciton dynamics in a 2D semiconductor heterostructure, *Science* **351**, 688 (2016).
- [12] Z. Sun, A. Ciarrocchi, F. Tagarelli, J. F. Gonzalez Marin, K. Watanabe, T. Taniguchi, and A. Kis, Excitonic transport driven by repulsive dipolar interaction in a van der Waals heterostructure, *Nat. Photonics* **16**, 79 (2022).
- [13] L. Yu, K. Pistunova, J. Hu, K. Watanabe, T. Taniguchi, and T. F. Heinz, Observation of quadrupolar and dipolar excitons in a semiconductor heterotrilayer, *Nat. Mater.* **22**, 1485 (2023).
- [14] D. Unuchek, A. Ciarrocchi, A. Avsar, K. Watanabe, T. Taniguchi, and A. Kis, Room-temperature electrical control of exciton flux in a van der Waals heterostructure, *Nature (London)* **560**, 340 (2018).
- [15] L. A. Jauregui *et al.*, Electrical control of interlayer exciton dynamics in atomically thin heterostructures, *Science* **366**, 870 (2019).
- [16] F. Tagarelli *et al.*, Electrical control of hybrid exciton transport in a van der Waals heterostructure, *Nat. Photonics* **17**, 615 (2023).
- [17] J. Choi *et al.*, Moiré potential impedes interlayer exciton diffusion in van der Waals heterostructures, *Sci. Adv.* **6**, eaba8866 (2020).
- [18] L. Yuan, B. Zheng, J. Kunstmann, T. Brumme, A. Beata Kuc, C. Ma, S. Deng, Daria Blach, Anlian Pan, and Libai Huang, Twist-angle-dependent interlayer exciton diffusion in $\text{WS}_2 - \text{WSe}_2$ heterobilayers, *Nat. Mater.* **19**, 617 (2020).
- [19] A. Weston *et al.*, Atomic reconstruction in twisted bilayers of transition metal dichalcogenides, *Nat. Nanotechnol.* **15**, 592 (2020).
- [20] S. Zhao *et al.*, Excitons in mesoscopically reconstructed moiré heterostructures, *Nat. Nanotechnol.* **18**, 572 (2023).
- [21] J. Sung *et al.*, Broken mirror symmetry in excitonic response of reconstructed domains in twisted $\text{MoSe}_2/\text{MoSe}_2$ bilayers, *Nat. Nanotechnol.* **15**, 750 (2020).
- [22] G. Scuri, T. I. Andersen, Y. Zhou, D. S. Wild, J. Sung, R. J. Gelly, D. Bérubé, H. Heo, L. Shao, A. Y. Joe, A. M. Mier Valdivia, T. Taniguchi, K. Watanabe, M. Lončar, P. Kim, M. D. Lukin, and H. Park, Electrically tunable valley dynamics in twisted $\text{WSe}_2/\text{WSe}_2$ bilayers, *Phys. Rev. Lett.* **124**, 217403 (2020).
- [23] T. I. Andersen *et al.*, Excitons in a reconstructed moiré potential in twisted $\text{WSe}_2/\text{WSe}_2$ homobilayers, *Nat. Mater.* **20**, 480 (2021).
- [24] D. S. Kim *et al.*, Electrostatic moiré potential from twisted hexagonal boron nitride layers, *Nat. Mater.* **23**, 65 (2024).
- [25] Y. Shimazaki, I. Schwartz, K. Watanabe, T. Taniguchi, M. Kroner, and A. Imamoğlu, Strongly correlated electrons and hybrid excitons in a moiré heterostructure, *Nature (London)* **580**, 472 (2020).
- [26] I. Schwartz, Y. Shimazaki, C. Kuhlenkamp, K. Watanabe, T. Taniguchi, M. Kroner, and A. Imamoğlu, Electrically tunable feshbach resonances in twisted bilayer semiconductors, *Science* **374**, 336 (2021).
- [27] See Supplemental Material at <http://link.aps.org/supplemental/10.1103/PhysRevLett.132.216903>, which includes Refs. [28–32], for additional information about experimental methods, discussions, and other figures.
- [28] L. Keldysh, Coulomb interaction in thin semiconductor, and semimetal films, *Sov. J. Exp. Theor. Phys. Lett.* **29**, 658 (1979).
- [29] D. Erckensten, S. Brem, R. Perea-Causín, and E. Malic, Microscopic origin of anomalous interlayer exciton transport in van der Waals heterostructures, *Phys. Rev. Mater.* **6**, 094006 (2022).
- [30] A. Laturia, M. L. Van de Put, and W. G. Vandenberghe, Dielectric properties of hexagonal boron nitride and transition metal dichalcogenides: From monolayer to bulk, *npj 2D Mater. Appl.* **2**, 6 (2018).
- [31] C. Schindler and R. Zimmermann, Analysis of the exciton-exciton interaction in semiconductor quantum wells, *Phys. Rev. B* **78**, 045313 (2008).
- [32] S. De Palo, F. Rapisarda, and G. Senatore, Excitonic condensation in a symmetric electron-hole bilayer, *Phys. Rev. Lett.* **88**, 206401 (2002).
- [33] A. Chernikov, T. C. Berkelbach, H. M. Hill, A. Rigosi, Y. Li, B. Aslan, D. R. Reichman, M. S. Hybertsen, and T. F. Heinz, Exciton binding energy and nonhydrogenic Rydberg series in monolayer WS_2 , *Phys. Rev. Lett.* **113**, 076802 (2014).
- [34] Y. Zhou, G. Scuri, J. Sung, R. Gelly, D. S. Wild, K. De Greve, A. Y. Joe, T. Taniguchi, K. Watanabe, P. Kim, M. D. Lukin, and H. Park, Controlling excitons in an atomically thin membrane with a mirror, *Phys. Rev. Lett.* **124**, 027401 (2020).
- [35] M. Van der Donck and F. Peeters, Interlayer excitons in transition metal dichalcogenide heterostructures, *Phys. Rev. B* **98**, 115104 (2018).
- [36] S. Larentis, H. C. P. Movva, B. Fallahazad, K. Kim, A. Behroozi, T. Taniguchi, K. Watanabe, S. K. Banerjee, and E. Tutuc, Large effective mass and interaction-enhanced Zeeman splitting of K -valley electrons in MoSe_2 , *Phys. Rev. B* **97**, 201407(R) (2018).
- [37] Y. Zhang *et al.*, Direct observation of the transition from indirect to direct bandgap in atomically thin epitaxial MoSe_2 , *Nat. Nanotechnol.* **9**, 111 (2014).
- [38] M. M. Glazov, T. Amand, X. Marie, D. Lagarde, L. Bouet, and B. Urbaszek, Exciton fine structure and spin decoherence in monolayers of transition metal dichalcogenides, *Phys. Rev. B* **89**, 201302(R) (2014).
- [39] T. Yu and M. Wu, Valley depolarization due to intervalley and intravalley electron-hole exchange interactions in monolayer MoS_2 , *Phys. Rev. B* **89**, 205303 (2014).

- [40] F. Wu, T. Lovorn, and A. MacDonald, Theory of optical absorption by interlayer excitons in transition metal dichalcogenide heterobilayers, *Phys. Rev. B* **97**, 035306 (2018).
- [41] J. R. Schaibley *et al.*, Valleytronics in 2D materials, *Nat. Rev. Mater.* **1**, 1 (2016).
- [42] A. Sushko *et al.*, Asymmetric photoelectric effect: Auger-assisted hot hole photocurrents in transition metal dichalcogenides, *Nanophotonics* **10**, 105 (2020).
- [43] Z. Wang, Y.-H. Chiu, K. Honz, K. F. Mak, and J. Shan, Electrical tuning of interlayer exciton gases in WSe₂ bilayers, *Nano Lett.* **18**, 137 (2018).
- [44] D. Sun, Y. Rao, G. A. Reider, G. Chen, Y. You, L. Br  zin, A. R. Harutyunyan, and T. F. Heinz, Observation of rapid exciton-exciton annihilation in monolayer molybdenum disulfide, *Nano Lett.* **14**, 5625 (2014).
- [45] S. Andreev, Spin-orbit-coupled depairing of a dipolar biexciton superfluid, *Phys. Rev. B* **103**, 184503 (2021).
- [46] M. Kulig, J. Zipfel, P. Nagler, S. Blanter, C. Sch  ller, T. Korn, N. Paradiso, M. M. Glazov, and A. Chernikov, Exciton diffusion and halo effects in monolayer semiconductors, *Phys. Rev. Lett.* **120**, 207401 (2018).
- [47] M. Glazov, Phonon wind, and drag of excitons in monolayer semiconductors, *Phys. Rev. B* **100**, 045426 (2019).
- [48] H. Yu, G.-B. Liu, J. Tang, X. Xu, and W. Yao, Moir   excitons: From programmable quantum emitter arrays to spin-orbit-coupled artificial lattices, *Sci. Adv.* **3**, e1701696 (2017).
- [49] C. Jin *et al.*, Interlayer electron-phonon coupling in WSe₂/hBN heterostructures, *Nat. Phys.* **13**, 127 (2017).
- [50] J. Serrano, A. Bosak, R. Arenal, M. Krisch, K. Watanabe, T. Taniguchi, H. Kanda, A. Rubio, and L. Wirtz, Vibrational properties of hexagonal boron nitride: Inelastic x-ray scattering and *ab initio* calculations, *Phys. Rev. Lett.* **98**, 095503 (2007).
- [51] P. Soubelet, A. E. Bruchhausen, A. Fainstein, K. Nogajewski, and C. Faugeras, Resonance effects in the Raman scattering of monolayer and few-layer MoSe₂, *Phys. Rev. B* **93**, 155407 (2016).
- [52] C. M. Chow, H. Yu, A. M. Jones, J. R. Schaibley, M. Koehler, D. G. Mandrus, R. Merlin, W. Yao, and X. Xu, Phonon-assisted oscillatory exciton dynamics in monolayer MoSe₂, *npj 2D Mater. Appl.* **1**, 33 (2017).
- [53] R. Qi *et al.*, Perfect Coulomb drag and exciton transport in an excitonic insulator, [arXiv:2309.15357](https://arxiv.org/abs/2309.15357).
- [54] P. X. Nguyen *et al.*, Perfect Coulomb drag in a dipolar excitonic insulator, [arXiv:2309.14940](https://arxiv.org/abs/2309.14940).
- [55] A. A. High, E. E. Novitskaya, L. V. Butov, M. Hanson, and A. C. Gossard, Control of exciton fluxes in an excitonic integrated circuit, *Science* **321**, 229 (2008).