

Quasi-1D $S = 1/2$ Antiferromagnet Cs_2CuCl_4 in a Magnetic Field

R. Coldea,¹ D. A. Tennant,^{1,*} R. A. Cowley,¹ D. F. McMorrow,² B. Dorner,³ and Z. Tylczynski⁴

¹*Oxford Physics, Clarendon Laboratory, Parks Road, Oxford OX1 3PU, United Kingdom*

²*Department of Solid State Physics, Risø National Laboratory, DK-4000 Roskilde, Denmark*

³*Institut Laue-Langevin, B.P. 156, F-38042 Grenoble Cédex 9, France*

⁴*Institute of Physics, Umultowska 85, 61-614 Poznań, Poland*

(Received 4 February 1997)

Magnetic excitations of the quasi-1D $S = 1/2$ Heisenberg antiferromagnet (HAF) Cs_2CuCl_4 have been measured as a function of magnetic field using neutron scattering. For $T < 0.62$ K and $B = 0$ T the weak interchain coupling produces 3D incommensurate ordering. Fields greater than $B_C = 1.66$ T, but less than the field (≈ 8 T) required to fully align the spins, are observed to decouple the chains, and the system enters a disordered intermediate-field phase (IFP). The IFP excitations are in agreement with the predictions of Müller *et al.* for the 1D $S = 1/2$ HAF, and Talstra and Haldane for the related $1/r^2$ chain (the Haldane-Shastry model). This behavior is inconsistent with linear spin-wave theory. [S0031-9007(97)03471-6]

PACS numbers: 75.10.Jm, 75.10.Hk, 75.30.Ds

In recent years there has been a general realization that widely used semiclassical and mean-field theories of magnetism, such as linear spin-wave theory, are often inadequate in describing the properties of low-dimensional quantum magnets [1]. Research on 1D systems has benefited from a strong interaction between theory and experiment, with novel concepts such as fractional excitations and topological energy gaps being introduced and developed. New magnetic materials continue to be found and the body of experimental and theoretical work is increasing. In this Letter we describe a further contribution to this progress by presenting experiments which show the novel features which occur when a magnetic field is applied to a quasi-1D antiferromagnet.

The canonical 1D quantum mechanical system is the $S = 1/2$ Heisenberg antiferromagnetic chain (HAF). The low-temperature ground state is a nonmagnetic spin singlet [2], and the excitations are spin- $\frac{1}{2}$ particles known as spinons, as shown by the solution of the $1/r^2$ Haldane-Shastry model (HSM) [3]. In a neutron scattering process the spin of the system changes by 1 or 0, and so the neutron-scattering measures a spinon pair continuum. Observations of this continuum for quasi-1D HAF's have been made and confirm the spinon picture [4]. The application of a magnetic field aligns a number of the spins along the field by creating an approximately regular array of condensed spinons. The triplet excitation continuum in zero field is then split into separate continua [5,6] as illustrated in Fig. 1. The positions of the continua alter as the applied field increases until at high fields $B \geq B_0$ the spins are aligned parallel along the field and the excitations have a well-defined magnon dispersion [5].

The $S = 1/2$ HAF has also been treated by mapping the spin chain into a system of interacting fermions [7]. In zero field the fermion band is half full and the excitation energies can be obtained using the Hartree-Fock approximation. The transverse excitations are well defined

and have dispersion relations similar to the lower boundaries (heavy lines) of Fig. 1(a). The application of a field changes the chemical potential and the Fermi wave vector, such that the transverse excitations have incommensurate dispersion relations similar to the heavy lines in Fig. 1(b).

Although there are a number of excellent realizations of the $S = 1/2$ HAF available, Cs_2CuCl_4 is one of the few quasi-one-dimensional systems with a *sufficiently low exchange interaction* that studies of an applied field *throughout* the intermediate-field phase (IFP) can be made. The IFP is the region of the phase diagram which occurs at low temperatures ($T \ll J/k_B$), for fields below the ferromagnetic transition field B_0 , and when the chains behave independently. For a quasi- as opposed to pure-1D antiferromagnet this is above a critical field B_C , the field necessary to decouple the chains, and the IFP region occurs for $B_C < B < B_0$.

Measurement of magnetic excitations in the IFP is technically challenging as it requires intense beams of cold neutrons, high magnetic fields, low temperatures,

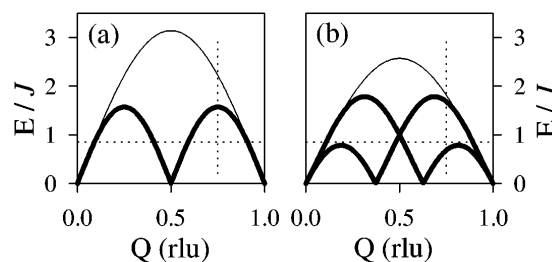


FIG. 1. Spectrum of longitudinal excitations in the 1D $S = 1/2$ HAF in (a) zero and (b) an applied field $B = J/g\mu_B$ [5]. The heavy and light lines are the boundaries of the scattering continua with the heavy lines indicating where strong scattering is expected. The dotted vertical and horizontal lines show the directions of constant- Q and constant- E scans in Figs. 3 and 4, respectively. The transverse modes also show similar effects, but have been omitted for the sake of clarity [5,6].

and large single crystals of a quasi-1D material with a low exchange. Because of this, previous experiments on quasi-1D $S = 1/2$ HAFCs have been exclusively in the province of applied fields which are low with respect to the exchange, and the difficulty of these experiments has precluded a comparison with theory [8]. In this Letter we report neutron-scattering measurements which, for the first time, span a large region of the IFP. Although Cs_2CuCl_4 has a large interchain coupling ($\sim 17\%$ of the intrachain value), we argue that the field decouples the chains and good agreement is found with the theories of Müller *et al.* [5] and Talstra and Haldane [6].

Cs_2CuCl_4 has an orthorhombic crystal structure [9]. The $S = 1/2$ Cu^{2+} spins are coupled into chains running parallel to the b axis, with four such chains passing through each unit cell. The magnetic susceptibility [10] is consistent with a quasi-1D $S = 1/2$ HAFC with an interaction $J = 0.34 \pm 0.02$ meV, where the exchange Hamiltonian for the 1D chains is $\mathcal{H}_{1D} = J \sum_i \mathbf{S}_i \cdot \mathbf{S}_{i+1}$. The chains are coupled in the c direction by a small exchange $J' = 0.175J$ as depicted in Fig. 2(a) (all other interchain exchanges are negligible) [11]. Below $T_N = 0.62$ K the spins order into a cycloid along the chain direction with an incommensurate wave vector $\mathbf{q} = (0, 0.472, 0)$; the incommensurate ordering is

due to the frustration caused by the staggering of chains with respect to their neighbors; see Fig. 2(a). A small anisotropy confines the spins to rotate within a plane containing the b direction and making a small angle with the (b, c) plane.

The single crystal of Cs_2CuCl_4 [11] was mounted with the (a, b) scattering plane horizontal, and a magnetic field was applied vertically. The sample was cooled using either a dilution refrigerator or a ^3He cryostat which provided base temperatures of 0.06 or 0.32 K, respectively. The inelastic neutron-scattering experiments were performed on the three-axis crystal spectrometer IN14 at Institut Laue-Langevin, Grenoble, France, while the elastic scattering measurements were made with the three-axis crystal spectrometer TAS7 at Risø National Laboratory, Denmark. Full details of the experiments will be given elsewhere [12].

Strong magnetic reflections were observed at $B = 0$ T and $T = 0.32$ K in the (a, b) plane at positions corresponding to the cycloidal ordering wave vector $\mathbf{q} = (0, 0.472, 0)$. When a field was applied along the crystallographic c axis the intensity of the magnetic Bragg peaks decreased with increasing B and finally disappeared at the critical field $B_C = 1.66$ T ($T = 0.32$ K); for all fields and temperatures the incommensurate ordering wave vector remained constant. The observed transition field is much smaller than the field B_0 necessary for full ferromagnetic alignment which was found to be $B_0 \approx 8$ T from susceptibility measurements [12]. Figure 2(b) shows a summary of the magnetic phase diagram for Cs_2CuCl_4 . No antiferromagnetic or incommensurate Bragg peaks were detected in the IFP, suggesting a decoupling of the chains.

Figure 2(c) shows the dispersion curves measured at $T = 0.1$ K in zero applied field. The asymmetry in the dispersion relation arises from the interchain coupling and is well accounted for by a calculation of the spin waves with a Heisenberg exchange J for the interactions along the chain and J' for the coupling between chains [13]. The solid line in Fig. 2(c) represents a fit of the dispersion relation with $J = 0.64 \pm 0.02$ meV and $J'/J = 0.17 \pm 0.02$. The latter ratio of exchange interactions is in good agreement with the value $J'/J = 0.175$ which gives a stable incommensurate structure [11]. The magnitude of J is larger than the value 0.34 meV deduced from the susceptibility measurements [10] by using a theory which includes quantum fluctuations. The quantum correction to the classical spin-wave result for an ideal $S = 1/2$ HAF chain is a multiplication of the energy scale by a factor of $\frac{\pi}{2}$ [14], and a value of $\tilde{J} = \frac{2}{\pi} 0.64 = 0.41$ meV is similar to the value deduced from susceptibility measurements.

The magnetic excitations were studied as a function of field by measuring the inelastic scattering at low temperatures ($T = 0.06$ K). Figure 3 summarizes the results of constant- Q scans for $Q = (0, 0.75, 0)$. The zero-field scan shows a well-defined, almost

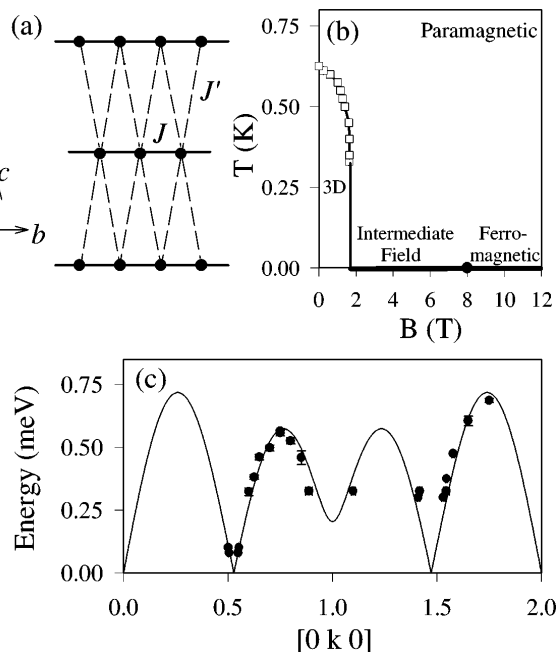


FIG. 2. (a) Magnetic chains and exchange paths in Cs_2CuCl_4 . (b) Magnetic phase diagram in a field applied along c . The squares represent the measured boundary of the 3D cycloidal phase. The intermediate field and ferromagnetic labels strictly refer to the $T = 0$ K line, but are effectively good descriptions of the ground state at very low temperatures $T \ll J/k_B$. (c) Dispersion of the magnetic excitations along the chain direction at $B = 0$ T. The solid line is a fit to the linear spin-wave dispersion.

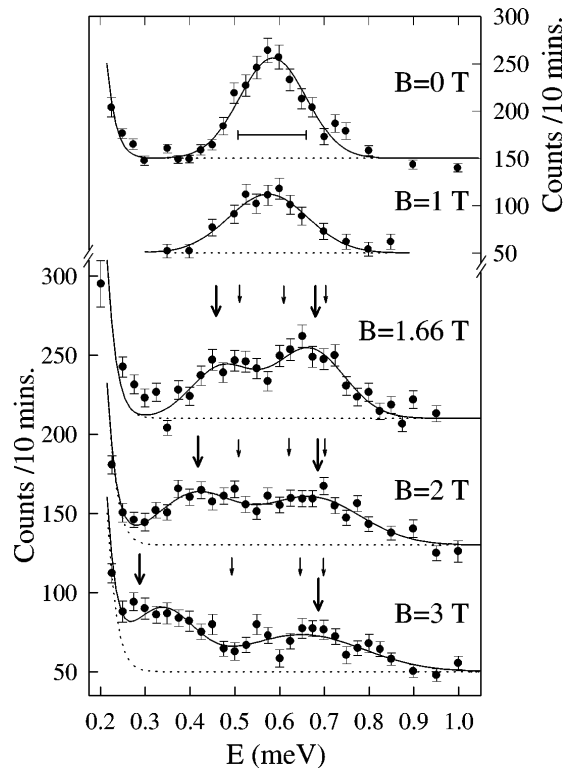


FIG. 3. The intensity observed at $Q = (0, 0.75, 0)$ as a function of energy and field. Two different scales are used and scans are shifted upwards by 100 (0 T) (right axis), 160 (1.66 T), and 80 (2 T) (left axis). Solid lines are fits as described in the text, and dotted lines represent the nonmagnetic background. The energies at which the intensity is expected to be large for quantum chains [5] are shown by long vertical arrows above the scans, while the short vertical arrows indicate the spin-wave energies for a cone structure. The horizontal bar in the zero-field scan represents the energy resolution (FWHM).

resolution-limited peak centered at $E = 0.58 \pm 0.01$ meV. The solid line is a fit to a Gaussian peak and the tail at low energies comes from the incoherent scattering. The intensity of the magnetic excitation decreases on increasing the field and the line shape changes above the IFP transition at $B_C = 1.66$ T. A good but not unique fit to the line shape is obtained by two independent peaks, as shown by the solid line in the figure. The low-energy peak decreases in energy on increasing the field and has an almost constant width and intensity for $B_C < B < 3$ T. In the same field range, the high-energy peak is at $E = 0.66 \pm 0.02$ meV, slightly increased in energy compared to the peak position in the 3D cycloidal phase. It becomes broader on increasing the field, but its total integrated intensity is almost constant.

The inelastic scattering in fields up to 6 T was also measured at $Q = (-0.25, 2, 0)$, which is equivalent to the zone center for a quasi-1D magnetic system with chains along b^* . The results show an inelastic peak for $B > 3$ T which increases in energy and becomes more intense on increasing the field. This inelastic peak measures the

Zeeman energy gap $E_Z = g_c \mu_B B$, where g_c is the g value along the c axis. A fit to the peak positions gives $g_c = 2.36 \pm 0.02$, which is in good agreement with the value $g_c = 2.30 \pm 0.01$ determined by previous room temperature EPR measurements [15].

The results of scanning Q across the zone with $E = 0.35$ meV are presented in Fig. 4. The zero-field scan has inelastic peaks occurring at positions corresponding to the intersection of the scan direction with the dispersion relation, Fig. 2(c). The magnetic inelastic scattering decreases in intensity and becomes broader on increasing field. The double-peak structure at the zone boundary $k = 1.5$ transforms into a broad feature, and the peak on the low- Q side is displaced towards the zone boundary and cannot be distinguished from the other peak for $B > 4$ T.

Mean-field ordering and linear spin-wave theory predict that in the case of a field applied in the plane of spin rotation the IFP is either a spin-flop (SF) or a cone structure. Both of these have long-range antiferromagnetic-like order which was not observed. If the anisotropy confining the spins in the (b, c) plane is relatively large, the structure is a SF phase with antiferromagnetic ordering along b , and the transition field cycloidal \rightarrow SF phase is

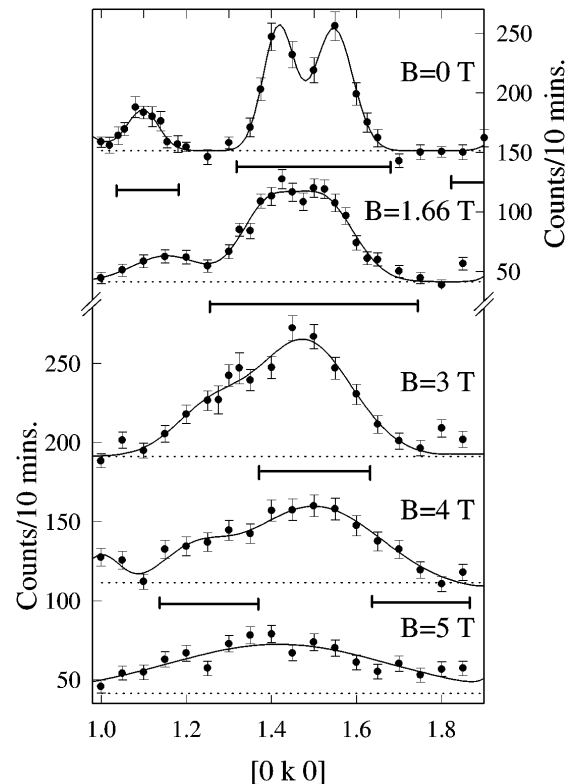


FIG. 4. The intensity observed for $E = 0.35$ meV as a function of wave vector and field. Two different scales are used and scans are shifted upwards by 110 (0 T) (right axis), 150 (3 T), and 70 (4 T) (left axis). Solid lines are guides to the eye and dotted lines represent the nonmagnetic background. Horizontal bars above the scans show where high intensity is predicted for quantum chains [5].

calculated to be $B_C = 1.425$ T [16]. The excitation energy at $Q = (0, 0.75, 0)$ for isolated 1D chains is field independent and equal to 0.64 meV [5]. This is clearly inconsistent with the observed splitting of the inelastic scattering as a function of field; see Fig. 3. Interchain coupling causes some broadening of the scattering, but cannot account for the results.

In the same mean-field approach, for smaller anisotropies the magnetic field produces a cone phase in which the spins cant towards the field direction to gain energy through the Zeeman interaction and the transverse spin components rotate in the (a, b) plane with the same wave vector \mathbf{q} as the zero-field structure in order to minimize the exchange interactions [16]. The spin waves in the cone phase have been calculated [17] and the results for the excitation energies at $Q = (0, 0.75, 0)$ are presented in Fig. 3 by the group of three vertical short arrows above the scans. The excitations of the cone structure also cannot explain the inelastic scattering observed at low energies with increasing field.

In the case of quantum chains the field produces some spins aligned parallel to the field direction and approximately regularly distributed along the chain. If there is no correlation between the positions of the aligned spins in neighboring chains, no long-range order will be formed even in the presence of a small interchain coupling. The IFP thus has incommensurate-like short-range order and the excitations form a spinon-magnon continuum according to calculations of Talstra and Haldane for the $1/r^2$ model, and Müller *et al.* for the nearest-neighbor model as shown schematically in Fig. 1(b). Measurements on Cs_2CuCl_4 for $B > 1.66$ T are consistent with the absence of long-range antiferromagnetic or incommensurate ordering of the IFP phase. The energies for which the inelastic neutron scattering is expected to be large for 1D chains with an exchange interaction \tilde{J} , according to calculations of Müller *et al.* [5], are shown in Fig. 3 by the long vertical arrows above the scans. The observed splitting of the inelastic scattering and its behavior in a field are well reproduced by the calculation. The strong field dependence of the low-energy scattering results from the field dependence of the short-range ordering wave vector as it varies across the zone with increasing field. The experiments are consistent with the total scattering being constant for $B_C < B < 3$ T, in agreement with numerical simulations on finite quantum chains using the Müller ansatz [5]. The regions where high intensity is expected in a constant- E scan are represented by horizontal bars in Fig. 4 and the measurements at the magnetic zone center $Q = (-0.25, 2, 0)$ are also consistent with the calculated behavior.

In conclusion, we have measured the magnetic ground state and the excitations in the quasi-1D $S = 1/2$

HAF Cs_2CuCl_4 as a function of applied field. In the intermediate-field region there is no long-range antiferromagnetic or incommensurate ordering and the excitations are in agreement with predictions of Müller *et al.* for the 1D $S = 1/2$ HAF and Talstra and Haldane for the related $1/r^2$ chain. Mean-field ordering and linear spin-wave theory cannot account for the observed behavior. Full details of these and related experiments on Cs_2CuCl_4 will be reported elsewhere [12].

We acknowledge the financial support for the experiments from the EPSRC at the Institut Laue-Langevin and Oxford, and the EU TMR programme at Risø National Laboratory. The technical support offered by Frederic Thomas, Jean-Louis Ragazzoni, Serge Pugol, Alan Brochier, and Moritz Lund is gratefully acknowledged. We would like to thank Dr. Kim Lefmann for useful discussions, and extend thanks to Dr. U. Wildgruber and Dr. J. Axe for help in lining up the crystal at BNL. R. C. is very grateful to the University of Oxford for support.

*Present address: Solid State Division, Oak Ridge National Laboratory, Oak Ridge, TN 37831-6393.

- [1] For a review see I. Affleck, *J. Phys. Condens. Matter* **1**, 3047 (1989).
- [2] H. A. Bethe, *Z. Phys.* **71**, 205 (1931).
- [3] F. D. M. Haldane and M. R. Zirnbauer, *Phys. Rev. Lett.* **71**, 4055 (1993).
- [4] D. A. Tennant, R. A. Cowley, S. E. Nagler, and A. M. Tsvelik, *Phys. Rev. B* **52**, 13 368 (1995).
- [5] G. Müller, H. Thomas, H. Beck, and J. C. Bonner, *Phys. Rev. B* **24**, 1429 (1981).
- [6] J. C. Talstra and F. D. M. Haldane, *Phys. Rev. B* **50**, 6889 (1994).
- [7] E. Pytte, *Phys. Rev. B* **10**, 4637 (1974).
- [8] I. U. Heilmann, G. Shirane, Y. Endoh, R. J. Birgeneau, and S. L. Holt, *Phys. Rev. B* **18**, 3530 (1978).
- [9] S. Bailleul, D. Svoronos, P. Porcher, and A. Tomas, *C. R. Acad. Sci. (Paris), Sér. II* **313**, 1149 (1991).
- [10] R. L. Carlin, R. Burriel, F. Palacio, R. A. Carlin, S. F. Keij, and D. W. Carnegie, Jr., *J. Appl. Phys.* **57**, 3351 (1985).
- [11] R. Coldea, D. A. Tennant, R. A. Cowley, D. F. McMorrow, B. Dorner, and Z. Tylczynski, *J. Phys. Condens. Matter* **8**, 7473 (1996).
- [12] R. Coldea, D. A. Tennant, R. A. Cowley, D. F. McMorrow, B. Dorner, and Z. Tylczynski (to be published).
- [13] A. Yoshimori, *J. Phys. Soc. Jpn.* **14**, 807 (1959).
- [14] J. des Cloizeaux and J. J. Pearson, *Phys. Rev.* **128**, 2131 (1962).
- [15] S. Bailleul, J. Hölsä, and P. Porcher, *Eur. J. Solid State Inorg. Chem.* **31**, 431 (1994).
- [16] T. Nagamiya, K. Nagata, and Y. Kitano, *Prog. Theor. Phys.* **27**, 1253 (1962).
- [17] T. Nagamiya, *Solid State Phys.* **20**, 348 (1967).