

Butterfly Hysteresis Loop at Nonzero Bias Field in Antiferromagnetic Molecular Rings: Cooling by Adiabatic Magnetization

O. Waldmann,^{1,*} R. Koch,¹ S. Schromm,¹ P. Müller,¹ I. Bernt,² and R.W. Saalfrank²

¹Physikalisches Institut III, Universität Erlangen-Nürnberg, D-91058 Erlangen, Germany

²Institut für Organische Chemie, Universität Erlangen-Nürnberg, D-91054 Erlangen, Germany

(Received 28 January 2002; published 21 November 2002)

At low temperatures, the magnetization of the molecular ferric wheel NaFe₆ exhibits a step at a critical field B_c due to a field-induced level crossing. By means of high-field torque magnetometry we observed a hysteretic behavior at the level crossing with a characteristic butterfly shape which is analyzed in terms of a dissipative two-level model. Several unusual features were found. The nonzero bias field of the level crossing suggests the possibility of cooling by adiabatic magnetization.

DOI: 10.1103/PhysRevLett.89.246401

PACS numbers: 71.70.-d, 33.15.Kr, 75.10.Jm

One of the most exciting recent discoveries in magnetism is that of magnetic hysteresis of purely molecular origin in metal complexes such as Mn₁₂ or Fe₈ [1–6]. In these large-spin molecules spin reversal is blocked at low temperatures due to an energy barrier. Recently, a different type of molecular hysteresis has been observed in the molecule called V₁₅ [7]. Here, the spin system is dynamically driven out of equilibrium leading to hysteresis loops with a characteristic butterfly shape. The relevant time scale is on the order of seconds because of the phonon bottleneck effect. All in all, V₁₅ is an experimental realization of a two-level system with dissipation [7].

In this work, we investigated the molecular ferric wheel [NaFe₆L₆]Cl · 6CHCl₃ with $L = N(CH_2CH_2O)_3$, or NaFe₆ in short [8]. Ferric wheels attracted much interest because of the possibility of coherent quantum tunneling [9,10]. In NaFe₆, the six iron(III) ions form a ring of spin-5/2 centers with dominant antiferromagnetic nearest-neighbor Heisenberg interactions [11]. At zero field the ground state is nonmagnetic ($S = 0$), but application of a magnetic field leads to a level crossing at a critical field B_c where the ground state changes abruptly to the first excited $S = 1, M = -1$ level [inset of Fig. 1(a)] [12,13]. Thus, from a general point of view, NaFe₆ represents a two-level system for fields close to B_c . We show that, for appropriate conditions, NaFe₆ exhibits a butterfly hysteresis similar to that observed in V₁₅. This allows for important conclusions concerning fundamental physical aspects of ferric wheels. Furthermore, we found several striking features of the spin reversal process, demonstrating that the dissipative two-level system realized in NaFe₆ is actually a very distinctive one.

The magnetic properties of single crystals of NaFe₆ were investigated by high-field torque magnetometry. The single crystals were prepared as reported [8]. They crystallize in the space group $R\bar{3}$. The cation [NaFe₆L₆]⁺ exhibits S_6 molecular symmetry with the S_6 symmetry axis oriented perpendicular to the plane of the cluster. The complex shows strict uniaxial magnetic behavior [11,13]. The uniaxial axis coincides

with the molecular S_6 symmetry axis. The torque was detected with homemade cantilever devices micromachined from crystalline silicon [13]. Resolution was typically 10^{-11} N m. For measurement, a single crystal selected

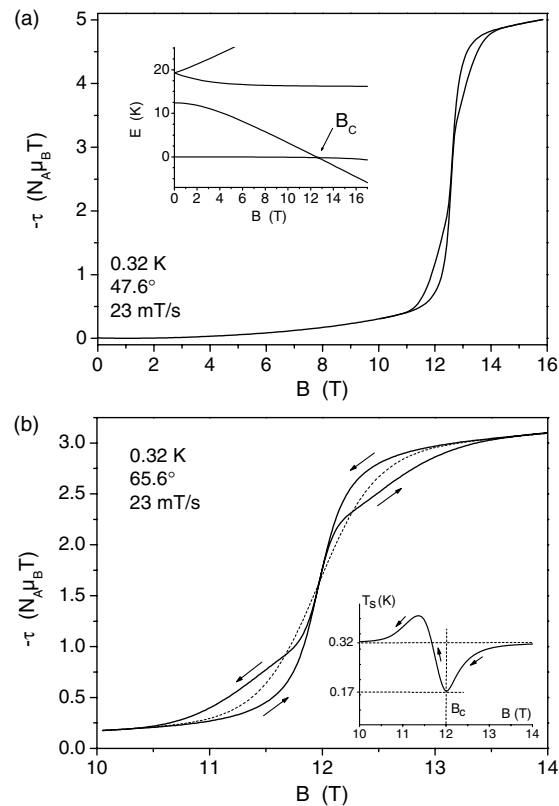


FIG. 1. Field dependence of the torque of a NaFe₆ single crystal demonstrating the butterfly hysteresis loop as it typically appears for field sweep rates in the saturation regime (see text). The inset in panel (a) schematically shows the field dependence of the low-lying energy states and the level crossing at $B = B_c$ leading to the pronounced torque step. In panel (b), the dashed curve represents the measured equilibrium curve; the inset sketches the behavior of the spin temperature T_s when the field is swept from $B > B_c$.

by light microscopy in the mother liquor was directly put from the solution into Apiezon grease and mounted on the cantilever. The weight of the crystals investigated was typically 20 μg ; nonlinearity was less than 1%. The torque meter was inserted into a 17 T cryomagnet with a vacuum loading ^3He insert. The angle between the crystal's uniaxial axis and magnetic field could be aligned *in situ* with an accuracy of 0.3° . Calibration of the torque signal is accurate to $\pm 15\%$. Temperature was measured with a RuO_2 thick film resistor to within ± 30 mK.

A typical result for the field dependence of the torque at $T = 0.32$ K is shown in Fig. 1. The negative sign of the torque manifests the hard axis anisotropy of NaFe_6 [11]. The torque signal exhibits a steplike field dependence at B_c due to the abrupt switch of the ground state from the zero-field $S = 0$ ground state to the first excited $S = 1$ state [inset of Fig. 1(a)]. This phenomenon is well known for ferric wheels [11–13], but for the first time we also observed a pronounced hysteresis of the torque signal for fields close to B_c , as shown in more detail in Fig. 1(b). The dependence of the butterfly curves on the sweep rate of the field and on temperature is presented in Fig. 2. The field position of the curves, i.e., the value of B_c , showed the expected angular dependence [11], but otherwise we did not observe an effect of the angle.

The underlying physics is quickly identified. Measurements performed with torque sensor and crystal

immersed in ^3He exchange gas resulted in perfectly reversible torque curves. In this work, however, we used a vacuum loading ^3He insert and thermal contact between crystal and bath was established via the silicon cantilever. In this configuration, thermal coupling should be weaker than with exchange gas. Obviously, the hysteretic behavior shown in Fig. 1 reflects a nonequilibrium state due to limitations in heat flow indicating that phonons play an important role in the process of changing the spin state at the level crossing.

Similar butterfly hysteresis curves were observed recently for the molecular cluster V_{15} and were successfully described in terms of a phonon bottleneck scenario (PBS) [7,14]. The essence of the PBS is that energy exchange between spin system and bath occurs via phonons [15]. The phonon bottleneck arises because the number of spins is much larger than the number of available resonant phonon modes at low temperatures. That is, the heat capacity of the spins C_s is much larger than that of the phonons C_p ($b = C_s/C_p \gg 1$). Therefore, the phonon temperature T_p follows that of the spin system T_s very quickly (on times $t_1 \approx b^{-1}t_s$) while energy transfer from the phonons to the bath is drastically delayed (time scale $t_2 \approx bt_p$). Here, t_s and t_p denote the spin-phonon and phonon-bath relaxation times, respectively. For the time scales of the present experiments, the spins and phonons may be regarded as a single coupled system ($T_s = T_p$) which is weakly coupled to the bath ($T_s \neq T$).

The butterfly hysteresis curves reflect the behavior of the spin temperature in the PBS. Spin temperature and torque are monotonously related: for a given magnetic field, $|\tau|$ is the larger the smaller T_s if $B > B_c$, and vice versa if $B < B_c$. Approaching the level crossing from a starting field of, e.g., $B > B_c$, the spin temperature first decreases since the spin-phonon system cannot pick up heat quickly enough from the bath [inset of Fig. 1(b)]. Thus, for sufficiently fast sweeping rates, the spin-phonon system is virtually decoupled from the bath resulting in a (quasi) adiabatic demagnetization process. At $B \approx B_c$, the spin system reaches a minimal temperature $T_{s,\text{min}}$. With further decreasing field, the spin system heats up (reverse of adiabatic demagnetization) but overshoots the bath temperature since it now receives heat from the bath which started to flow to reestablish equilibrium but reaches the spin system delayed due to the finite relaxation time t_2 .

The phonon bottleneck effect is obviously the underlying physical mechanism for the observed hysteresis in NaFe_6 , and in this respect the situation is analogous to that of a conventional two-level system. However, there are some particular characteristics to be noted, some of which are quite striking.

(1) With our setup we observed “heat-flow” hysteresis effects only for NaFe_6 (and related ferric wheels). We have investigated quite a number of different molecular spin clusters, but for them the thermal coupling provided by our silicon sensors was sufficient to achieve reversible

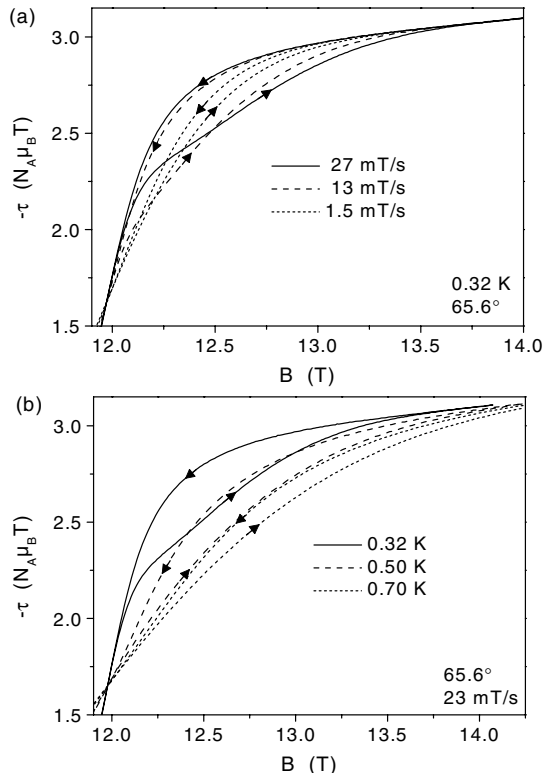


FIG. 2. Measured hysteresis loops for (a) three field sweep rates at $T = 0.32$ K and (b) three temperatures at a constant sweep rate of 23 mT/s. Only the branch with $B > B_c$ is plotted.

torque curves. In this respect, the observation of hysteresis in NaFe_6 is notable.

(2) A distinctive feature of the two-level system realized in NaFe_6 is that the two states involved belong to different spin and spatial quantum numbers. In NaFe_6 the strong exchange limit is realized and the total spin quantum number S is a good (though not exact) quantum number [11,13]. Additionally, the cyclic molecular symmetry implies a spin permutational symmetry [16] and states may be classified by the wave vector k [13,17]. The two states relevant in this work belong to $S \approx 0, k = \pi$ and $S \approx 1, k = 0$, respectively, so that phonon absorption/emission is constrained by $|\Delta S| \approx 1$ and $|\Delta k| = \pi$. To the best of our knowledge, the effects of these restrictions for the energy exchange between spins and bath have not been investigated so far. But conceivably the number of available phonons may be further reduced by these constraints. The Δk selection rule may be of particular relevance since it holds exactly as long as the molecular symmetry exhibits a C_2 symmetry axis.

(3) With a numerical analysis of the hysteresis curves based on the PBS, Chiorescu *et al.* evidenced a zero-field splitting for the molecule V_{15} [7]. In the case of ferric wheels, within a description in terms of a spin Hamiltonian consisting of terms related to the electronic spins only, the level crossing at $B = B_c$ is a true crossing by virtue of translational symmetry [13,17]. However, interactions with, e.g., the nuclear spins may lead to a splitting of the levels at the crossing point [18,19]. Their identification would be of considerable importance for the issue of quantum coherence in antiferromagnetic rings since they may act as sources of decoherence [19]. But so far, no clear evidence for a splitting of the level crossings, i.e., for anticrossings, has been reported.

We thus analyzed our data with the numerical procedure developed in Ref. [7] as adapted to torque measurements. Although we could generate curves which roughly resembled the experimental ones, we could not reproduce the data for different temperatures and sweeping rates satisfactorily. Values for, e.g., Δ_0 , the splitting of the level crossing at $B = B_c$ (inset of Fig. 3), showed unphysical scattering. This indicates that the PBS as outlined above is a too simple picture.

Therefore, we considered the dependence of the minimal spin temperature $T_{s,\min}$ as a function of the sweep rate of the magnetic field. In conjunction with a model Hamiltonian, $T_{s,\min}$ could be determined reliably from the slope of the torque curves at $B = B_c$ as the curves are essentially reversible in this field regime. In this way, $T_{s,\min}$ could be estimated with a reproducibility of 5 mK, but the values are subject to a systematic error of about ± 15 mK due to inaccuracies in the calibration of the torque signal. The results for two samples are shown in Fig. 3. For sample A, $T_{s,\min}$ first decreases linearly with increasing sweep rate and then saturates at about 0.17 K. It should be noted that the value of $T_{s,\min} = 0.325$ K extrapolated to a zero sweep rate agrees well with the bath

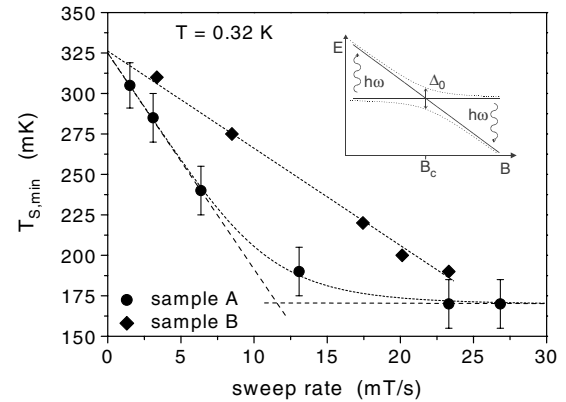


FIG. 3. Dependence of the minimal spin temperature $T_{s,\min}$ on the field sweep rate for two samples. Dashed lines are guides to the eye. The inset schematically presents the two states at the level crossing and indicates the splitting Δ_0 discussed in the text.

temperature as measured with the RuO_2 sensor. In the saturation regime, the spin system obviously behaves quasiadiabatically and it is thus very suggestive to identify the saturation temperature as a level splitting, i.e., $\Delta_0 = 0.17$ K.

We have also analyzed the broadening of the torque step as measured under reversible conditions for various temperatures down to 0.4 K. This method provides an alternative way to estimate Δ_0 [12,18]. However, even at the lowest temperatures the width of the step is in full accord with thermal broadening resulting in an upper limit of 0.05 K for Δ_0 .

We have no explanation for this serious discrepancy. It suggests that the minimal spin temperature in the limit of infinite sweep rates exceeds the thermodynamically determined splitting of the level crossing. The PBS in the present form obviously does not account for all the effects responsible for limiting $T_{s,\min}$ and/or broadening the torque step. It should be noted that the discrepancy cannot be explained by “extrinsic” effects as, e.g., crystal imperfections (twinning, mosaicity, etc.) [18].

Incidentally, Fig. 3 demonstrates the role of the thermal coupling between crystal and bath. In the case of sample B it is obviously better than for sample A as the crossover is shifted to larger sweep rates.

(4) As mentioned already, $T_{s,\min}$ as a function of the sweep rate exhibits a crossover from a linear regime to a saturation regime (Fig. 3). This is readily understood within the PBS. However, in the case of NaFe_6 the crossover is accompanied by a striking change of the hysteretic behavior. In the saturation regime the curves are symmetrical around B_c [Fig. 1(b)], but in the linear regime the hysteresis becomes clearly asymmetric. Two example curves are shown in Fig. 4. The asymmetry is more pronounced the slower the sweep rate or the higher the (bath) temperature and was always found to be such that the hysteresis is larger for $B > B_c$ than for $B < B_c$.

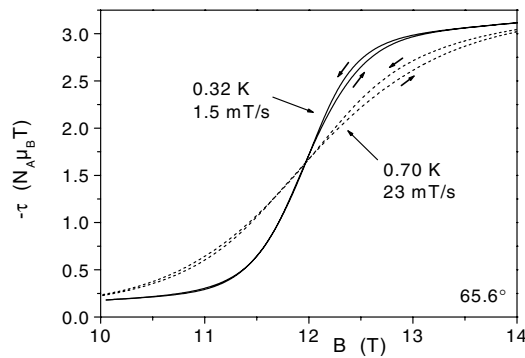


FIG. 4. Two example curves showing the asymmetry of the hysteresis loop around B_c discussed in the text.

It seems as if energy exchange between spin system and bath is different for $B < B_c$ and $B > B_c$. This is not easily explained. It is hardly conceivable that the thermal coupling between phonons and bath depends on magnetic field. But then one has to conclude that the asymmetry is related to peculiarities of the spin-phonon coupling in NaFe_6 . However, the arguments presented above and in Refs. [7,15] aim to show that spin-phonon coupling is so fast that in our experiments $T_s = T_p$ is always maintained so that any details of the spin-phonon coupling are indiscernible. As demonstrated by the symmetry of the curves for large sweep rates and under reversible conditions [Fig. 1(b)], an asymmetry of the energy levels is not an issue.

(5) The most obvious distinctive feature of the NaFe_6 two-level system is the nonzero bias field of the crossing, i.e., of $B_c > 0$. As shown in the above, the spin system cools down by approaching the critical field B_c as it is quasiadiabatically decoupled from the environment for large enough sweep rates. If one starts at $B > B_c$ and decreases field, the situation corresponds to cooling by adiabatic demagnetization. However, if one starts at $B < B_c$ (e.g., $B = 0$) and increases field, the reverse situation is realized, namely, that of cooling by adiabatic magnetization. Of course, in the present work no real adiabatic conditions were realized—but the effect is clearly evident from Fig. 1.

In summary, we observed a butterfly hysteresis loop of the torque at the first ground state level crossing in the molecular ferric wheel NaFe_6 . The results show that phonons are mostly responsible for transitions between the two states near the level crossing. This clarifies a recent proposal where it has been argued (as hysteresis was not yet observed) that dipole-dipole coupling between nuclear and electronic spins plays an important role [20]. The minimal spin temperature $T_{s,\min}$ achieved during the hysteresis loop was found to saturate for large sweep rates of the magnetic field—the first direct experimental evidence for interactions of the electronic spins with the environment in ferric wheels. A detailed analysis of the processes determining $T_{s,\min}$ should provide deep insight

into the conditions for quantum coherence in ferric wheels. The present work suggests a novel experimental route to measure them.

For slow sweep rates the hysteresis loop exhibited a striking asymmetry which is unexplainable within a standard phonon bottleneck scenario. One may only speculate about the role played by the unusual quantum numbers of the states involved in the level crossing. It also has been demonstrated that the NaFe_6 system allows for cooling by adiabatic magnetization, i.e., for the opposite of what is generally known. At the level crossing the ferric wheel NaFe_6 represents a dissipative two-level system—but with quite unusual properties shedding new light on a model one thought to know all about.

O.W. thanks I. Chiorescu for fruitful comments concerning the numerical simulation of the phonon bottleneck effect. This work was supported by the Deutsche Forschungsgemeinschaft, the Sonderforschungsbereich 583, and the Bayerisches Langzeitprogramm “Neue Werkstoffe.”

*Corresponding author.

Electronic address: waldmann@physik.uni-erlangen.de

- [1] R. Sessoli, D. Gatteschi, A. Caneschi, and M. A. Novak, *Nature (London)* **365**, 141 (1993).
- [2] D. Gatteschi, A. Caneschi, L. Pardi, and R. Sessoli, *Science* **265**, 1054 (1994).
- [3] L. Thomas *et al.*, *Nature (London)* **383**, 145 (1996).
- [4] J. R. Friedman, M. P. Sarachik, J. Tejada, and R. Ziolo, *Phys. Rev. Lett.* **76**, 3830 (1996).
- [5] C. Sangregorio *et al.*, *Phys. Rev. Lett.* **78**, 4645 (1997).
- [6] D. Gatteschi, R. Sessoli, and A. Cornia, *Chem. Commun. (Cambridge)* No. 9, 725 (2000).
- [7] I. Chiorescu *et al.*, *Phys. Rev. Lett.* **84**, 3454 (2000).
- [8] R.W. Saalfrank, I. Bernt, E. Uller, and F. Hampel, *Angew. Chem.* **109**, 2596 (1997).
- [9] K. L. Taft *et al.*, *J. Am. Chem. Soc.* **116**, 823 (1994).
- [10] A. Chiolero and D. Loss, *Phys. Rev. Lett.* **80**, 169 (1998).
- [11] O. Waldmann *et al.*, *Inorg. Chem.* **38**, 5879 (1999).
- [12] A. Cornia, A. G. M. Jansen, and M. Affronte, *Phys. Rev. B* **60**, 12177 (1999).
- [13] O. Waldmann *et al.*, *Inorg. Chem.* **40**, 2986 (2001).
- [14] Please note that in Ref. [7] magnetization was measured while we used torque. However, for NaFe_6 , the gap between the two lowest levels depends on field and angle approximately as $\Delta(B, \phi) = \Delta[B - B_c(\phi)]$ for fields close to B_c . In this approximation, torque is directly proportional to magnetization.
- [15] A. Abragam and B. Bleaney, *Electronic Paramagnetic Resonance of Transition Ions* (Clarendon Press, Oxford, 1970), Chap. 10.
- [16] O. Waldmann, *Phys. Rev. B* **61**, 6138 (2000).
- [17] O. Waldmann, *Phys. Rev. B* **65**, 024424 (2002).
- [18] B. Normand *et al.*, *Phys. Rev. B* **63**, 184409 (2001).
- [19] F. Meier and D. Loss, *Phys. Rev. Lett.* **86**, 5373 (2001).
- [20] A. Cornia *et al.*, *Europhys. Lett.* **50**, 88 (2000).